

This is the accepted manuscript made available via CHORUS. The article has been published as:

Spectroscopic Investigation of Yb-Doped Silica Glass for Solid-State Optical Refrigeration

Esmail Mobini, Mostafa Peysokhan, Behnam Abaie, Markus P. Hehlen, and Arash Mafi

Phys. Rev. Applied **11**, 014066 — Published 31 January 2019

DOI: [10.1103/PhysRevApplied.11.014066](https://doi.org/10.1103/PhysRevApplied.11.014066)

Spectroscopic Investigation of Yb-doped Silica Glass for Solid-State Optical Refrigeration

Esmaeil Mobini,^{1,2} Mostafa Peysokhan,^{1,2} Behnam Abaie,^{1,2} Markus P. Hehlen,^{1,3} and Arash Mafi^{1,2,*}

¹*Department of Physics & Astronomy, University of New Mexico, Albuquerque, NM 87131, USA*

²*Center for High Technology Materials, University of New Mexico, Albuquerque, NM 87106, USA*

³*Space & Remote Sensing (ISR-2), Los Alamos National Laboratory, Los Alamos, NM 87545, USA*

(Dated: January 18, 2019)

We argue that a high-purity Yb-doped silica glass can potentially be cooled via anti-Stokes fluorescence optical refrigeration. In order to achieve net solid-state optical refrigeration, it is necessary for the cooling efficiency to be positive. This requires the pump wavelength to be greater than the mean fluorescence wavelength, and the internal quantum efficiency as well as the absorption efficiency to be near unity. Our conclusion is reached by showing, using reasonable assumptions for the host material properties, that the non-radiative decay rate of Yb ions can be made substantially smaller than the radiative decay rate. Therefore, an internal quantum efficiency of near unity can be obtained. Moreover, the background absorption coefficient in high-quality silica glass lies in an acceptable range to guarantee a near unity absorption efficiency at room temperature. Using spectral measurements of the fluorescence from a Yb-doped silica optical fiber at different temperatures, we estimate the minimum achievable temperature in Yb-doped silica glass for different values of the internal quantum efficiency.

I. INTRODUCTION

In solid-state optical refrigeration, anti-Stokes fluorescence removes thermal energy from the material, resulting in net cooling. Solid-state optical cooling was first proposed by Pringsheim in 1929 [1] and was put on a solid thermodynamic foundation by Landau in 1946 [2]. Solid-state optical cooling was first experimentally observed in 1995 by Epstein's group at Los Alamos National Laboratory in Yb-doped ZBLANP glass [3]. Much attention has since been devoted to solid-state optical refrigeration in different materials and geometries due to its interesting basic science properties and potential applications [4]. The quest for solid-state optical cooling in new configurations and materials is on-going [5].

In particular, solid-state optical refrigeration of Yb-doped silica glass, which is extensively used in high-power fiber lasers, is highly desirable. New generations of high power fiber amplifiers and lasers now operate at few kilowatt levels [6]. However, the significant heat-load in high-power operation has hindered the efforts to further scale up the power in fiber lasers and amplifiers [6–9]. Different methods have been developed to manage the heat-load in high-power fiber lasers or amplifiers; in particular, solid-state optical refrigeration via anti-Stokes fluorescence has been suggested as a viable path for heat mitigation [10–12]. So far, there is no report of solid-state optical refrigeration in Yb-doped silica; this manuscript is intended to highlight its possibility.

In this context, Radiation-Balanced Lasers (RBL) were first introduced by Bowman in 1999 [10]. In radiation balancing, the heat that originates from the quantum defect of the laser as well as parasitic absorption can be

removed by anti-Stokes fluorescence under a very subtle balance condition between different parameters of a laser (or an amplifier) [10, 11, 13]. In other words, the anti-Stokes fluorescence removes the excess heat generated in the medium. Therefore, heat mitigation by radiation-balancing via anti-Stokes fluorescence is highly desirable and will have great practical implications if it can be achieved in Yb-doped silica glass, which is the material of choice for most high-power fiber lasers and amplifiers [6, 14, 15].

Although the first solid-state optical refrigeration was observed in a Yb-doped ZBLAN glass, it soon became apparent that rare-earth-doped crystals can be cooled more efficiently because i) the absorption lines of the Yb ions in crystals have a smaller inhomogeneous broadening, and ii) crystals can accept higher concentrations of rare-earth ions [4, 5]. As such, rare-earth-doped crystals have become the material of choice for solid-state optical refrigeration [16]. Only recently has there been a renewed interest in glasses, mainly because of their potential in RBL fiber lasers and amplifiers [12].

The investigation of solid-state optical refrigeration can be done either directly or indirectly. In a direct investigation, the material is exposed to a laser in a thermally isolated setup, often in a sophisticated vacuum environment [16], and its temperature is measured directly by a thermal camera or similar methods. In an indirect method, the spectroscopic properties of materials at different temperatures are measured to evaluate the possibility of solid-state optical refrigeration [3, 16–18]. In this manuscript, we use the indirect method to argue for the potential of high-quality Yb-doped silica glass for solid-state optical refrigeration and radiation-balancing in lasers and amplifiers.

In order to characterize the cooling potential of Yb-doped silica glass, we use the cooling efficiency η_c defined

* mafi@unm.edu

as [16, 18]

$$\eta_c(\lambda_p, T) = \eta_q \eta_{abs}(\lambda_p, T) \frac{\lambda_p}{\lambda_f(T)} - 1. \quad (1)$$

In Eq. 1, λ_f is the mean fluorescence wavelength and λ_p is the pump wavelength. η_q is the internal quantum efficiency and η_{abs} is the absorption efficiency; they are defined as

$$\eta_q = \frac{W_r}{W_{tot}}, \quad W_{tot} = W_r + W_{nr}, \quad (2)$$

$$\eta_{abs}(\lambda_p, T) = \frac{\alpha_r(\lambda_p, T)}{\alpha_r(\lambda_p, T) + \alpha_b}, \quad (3)$$

where W_r , W_{nr} , and W_{tot} are radiative, non-radiative, and total decay rates of the excited state, respectively. α_b is the background absorption coefficient, and α_r is the resonant absorption coefficient. Note that α_b does not contain the attenuation due to scattering as this process does not lead to heating of the material. We have assumed that due to the small cross sectional area of optical fibers, the fluorescence escape efficiency to be unity [3, 19]. The mean fluorescence wavelength is defined by

$$\lambda_f(T) = \frac{\int_{\Delta} \lambda S(\lambda, T) d\lambda}{\int_{\Delta} S(\lambda, T) d\lambda}, \quad (4)$$

where $S(\lambda, T)$ is the fluorescence power spectral density, which is a function of the glass temperature T , and Δ is the spectral domain encompassing the relevant emission spectral range [16, 18].

In order to achieve net solid-state optical refrigeration, it is necessary for the cooling efficiency to be positive. Therefore, we must show that $\eta_c > 0$ is attainable over a range of λ_p and T values. It can be seen from Eq. 1 that because λ_p and λ_f are often very close to each other in solid-state optical refrigeration schemes ($\lambda_p \gtrsim \lambda_f$), the internal quantum efficiency η_q has to be close to unity ($\eta_q \approx 1$) [3, 16]. There are two main processes that lower the internal quantum efficiency: the multi-phonon non-radiative relaxation and the concentration quenching effect [20–27]. We will argue that the multi-phonon non-radiative relaxation is negligible in Yb-doped silica glass and the concentration quenching process can be prevented if the Yb ion density is kept lower than the characteristic Yb ion quenching concentration.

In order to evaluate the absorption efficiency η_{abs} , we need to know the background absorption (α_b) and resonant absorption (α_r) coefficients. For the background absorption coefficient in Yb-doped silica glass, we will use typical values reported in the literature [28–30]. By measuring the power spectral density of a Yb-doped silica optical fiber from its side at different temperatures, $S(\lambda, T)$, we can also obtain the resonant absorption coefficient (α_r) as well as the mean fluorescence wavelength (λ_f). Therefore, we will have all the necessary parameters in Eq. 1; using this information we will estimate the cooling efficiency and show that solid-state optical refrigeration is feasible in Yb-doped silica glass.

II. INTERNAL QUANTUM EFFICIENCY

The internal quantum efficiency is the fraction of the radiative decay versus the total decay of an excited state in a medium; therefore, the presence of non-radiative decay channels characterized by the non-radiative decay rate W_{nr} in Eq. 2 are responsible for decreasing η_q below unity. The non-radiative decay channels in a typical Yb-doped silica glass can be broken down according to the following equation:

$$W_{nr} = W_{mp} + W_{OH^-} + W_{Yb} + \sum_{TM} W_{TM} + \sum_{RE} W_{RE}. \quad (5)$$

The partial non-radiative decay channels are as follows: W_{mp} represents the multi-phonon decay of the Yb excited state, W_{OH^-} accounts for non-radiative decay of the Yb excited state via the high-energy vibrational modes of OH^- impurities, W_{Yb} accounts for non-radiative decay in Yb ion clusters, and W_{TM} and W_{RE} represent non-radiative decay due to interactions of the excited state with various transition-metal and rare-earth ion impurities, respectively.

In the following, we will discuss the various non-radiative decay channels in Eq. 5 and show that they can be made sufficiently small to allow for a near-unity internal quantum efficiency value ($\eta_q \approx 1$). We first begin with the multi-phonon relaxation that originates from the coupling of the excited state with the vibrational wavefunctions of the ground state. Using the energy-gap law [20, 22, 24, 31], we can calculate the decay rate from

$$W_{mp} = W_0 e^{-\alpha_h(E_g - 2E_p)}, \quad (6)$$

where E_p is the maximum phonon energy of the host material, and E_g is the energy gap of the dopant ion (Yb). W_0 and α_h are phenomenological parameters, whose values strongly depend on the host-material [20, 22, 24, 31]. Figure 1 shows the multi-phonon non-radiative decay rates of silica and ZBLAN glasses versus the energy gaps of the doped ions at $T = 300$ K, using the parameters shown in Table I.

TABLE I. Parameters related to Eq. 6 and Fig. 1 for silica and ZBLAN glasses [20, 22, 31].

Host	W_0 (s ⁻¹)	α_h (cm)	E_p (cm ⁻¹)
Silica	7.8×10^7	4.7×10^{-3}	1.10×10^3
ZBLAN	1.7×10^4	2.1×10^{-3}	0.58×10^3

The vertical solid line in Fig. 1 marks the energy gap of a Yb³⁺ ion. It is evident that for Yb-doped silica glass, the non-radiative decay rate is around $W_{mp}^{silica} \approx 10^{-8} s^{-1}$, which is much smaller than the Yb-doped ZBLAN glass multi-phonon decay rate $W_{mp}^{ZBLAN} \approx$

10^{-4} s^{-1} . This comparison suggests that with respect to Yb multi-phonon relaxation, silica glass is a more suitable choice for solid-state optical refrigeration than ZBLAN glass.

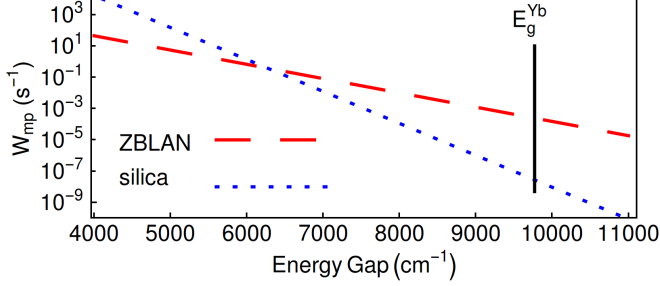


FIG. 1. Multi-phonon non-radiative decay rate (W_{mp}) of Yb-doped ZBLAN and silica glasses versus energy gap (E_g) calculated from Eq. 6 and the parameters listed in Table I.

Considering the advances in materials synthesis of fiber preforms, the term W_{OH-} in Eq. 5 can be made very small (see e.g. dry fiber technology [32]); therefore, it can be neglected [23]. It has also been shown by Auzel et al. [25] that the total effect of the last three terms in Eq. 5, $W_{Yb} + \Sigma W_{TM} + \Sigma W_{RE}$, can be described by a phenomenological equation based on a limited diffusion process, modeled as a non-radiative dipole-dipole interaction between the ions and impurities [25, 26]. This concentration quenching process can be prevented if the Yb ion density is lower than the critical quenching concentration of the Yb-doped silica glass, which exists because there are impurities. Therefore, the critical quenching concentration is generally a sample specific quantity. That is, it would be higher for lower impurity concentrations. For a Yb ion density smaller than the critical quenching concentration, the internal quantum efficiency can approach $\eta_q \approx 1$ [25–27]. It must be noted that an internal quantum efficiency of $\eta_q = 0.95$ is reported in [33] for Yb-doped silica, which is consistent with our claim that W_{nr} can be made quite small in Yb-doped silica.

III. ABSORPTION EFFICIENCY AND MEAN FLUORESCENCE WAVELENGTH

In order to calculate the cooling efficiency, we still need to obtain the resonant absorption coefficient and the mean fluorescence wavelength, both of which can be obtained from a spectroscopic investigation. The resonant absorption coefficient is used in conjunction with Eq. 3 to determine the absorption efficiency. The setup implemented in our experiment is shown in Fig. 2 and consists of a single-mode Yb-doped silica fiber (DF-1100, from Newport Corporation) that is pumped by a Ti:Sapphire laser at $\lambda = 900 \text{ nm}$. The fiber is mounted on a plate whose temperature is changed from nearly 180 K up to 360 K. The fluorescence of the Yb-doped silica fiber is captured by a multimode fiber from the side of the Yb-

doped silica fiber and is sent to an Optical Spectrum Analyzer (Yokogawa-AQ6319). Figure 3 shows the measured

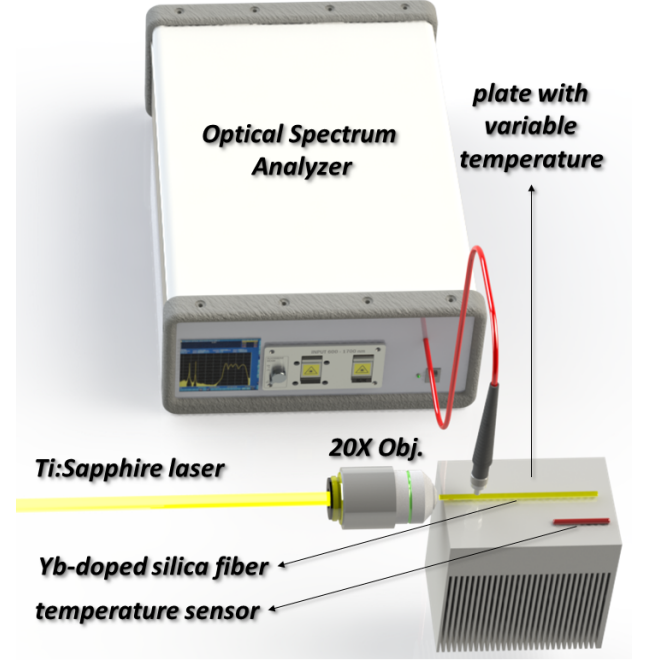


FIG. 2. The experimental setup is shown. A Ti:Sapphire laser at $\lambda = 900 \text{ nm}$ is used to pump a single-mode Yb-doped silica fiber using a 20X objective lens. The fiber is mounted on a plate whose temperature is changed from nearly 180 K up to 360 K. The temperature of the plate is monitored by a temperature sensor. The fluorescence of the Yb-doped silica fiber is captured by a multimode fiber from the side of the Yb-doped silica fiber and is sent to an Optical Spectrum Analyzer.

fluorescence spectra (power spectral density $S(\lambda, T)$), normalized to their peak values at $\lambda_{\text{peak}} \approx 976 \text{ nm}$, at different temperatures.

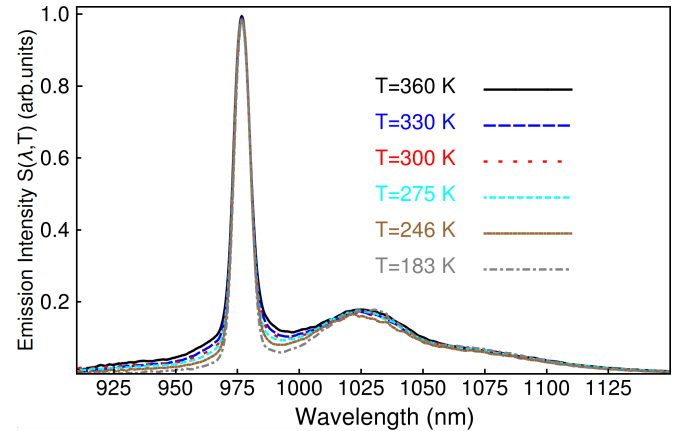


FIG. 3. Measured peak normalized emission spectra (fluorescence power spectral density) of DF-1100 Yb-doped silica fiber at different temperatures.

By inserting the measured fluorescence spectra into

Eq. 4 and considering $\Delta \in \{905\text{nm}, 1150\text{nm}\}$, the dependence of the mean fluorescence wavelength on temperature is obtained. The mean fluorescence wavelength follows approximately the following function:

$$\lambda_f(T) \approx 999 \text{ (nm)} + b \times T^{-1}, \quad b = 2735 \pm 31 \text{ nm/K.} \quad (7)$$

This behavior at temperatures above 245 K to 360 K is nearly linear, which is similar to that reported in other host materials, such as ZBLAN [17, 20].

In order to calculate the resonant absorption coefficient α_r , we first calculate the emission cross section σ_e , and then use the McCumber relation to obtain the absorption cross section σ_a and then the resonant absorption coefficient α_r [34–36]. The emission cross section is obtained from the measured fluorescence power spectral density $S(\lambda, T)$ via the F  chtbauer-Ladenburg equation [36, 37]:

$$\sigma_e(\lambda, T) = \frac{\lambda^5}{8\pi n^2 c \tau_r(T)} \times \frac{S(\lambda, T)}{\int_{\Delta} \lambda S(\lambda, T) d\lambda}, \quad (8)$$

where n is the refractive index of the fiber core, c is the speed of light in vacuum, and $\tau_r = W_r^{-1}$ is the radiative lifetime.

In order to apply Eq. 8, the radiative lifetime at each temperature needs to be measured. In high-quality samples for which the non-radiative decay rates are negligible compared to the radiative decay rates, the fluorescence lifetimes are comparable to the radiative lifetimes ($\tau_f \approx \tau_r$); therefore, we measured the fluorescence lifetimes at different temperatures from the side of the fiber [38]. Using this assumption, the emission cross sections at different temperatures are calculated and are shown in Fig. 4. The absorption cross sections can be readily obtained using the McCumber relation:

$$\sigma_a(\lambda, T) = \sigma_e(\lambda, T) \times \mathcal{Z}(\lambda, T), \quad (9)$$

$$\mathcal{Z}(\lambda, T) = \exp \left[\frac{hc}{k_b T} \left(\frac{1}{\lambda} - \frac{1}{\lambda_0} \right) \right],$$

where k_b is the Boltzmann constant, h is the Planck constant and $\lambda_0 = 976 \text{ nm}$ is the wavelength corresponding to the zero-line phonon energy [14, 18, 35]. The resonant absorption coefficient can be calculated from $\sigma_a(\lambda, T)$ in Eq. 9 (and Fig. 4) using

$$\alpha_r(\lambda, T) = \sigma_a(\lambda, T) \times N. \quad (10)$$

Here, we will assume a typical Yb ion density of $N = 5 \times 10^{25} \text{ m}^{-3}$. We now have all the necessary ingredients to calculate the cooling efficiency η_c in Eq. 1. We only need to provide a value for the background absorption coefficient in Eq. 3 to determine the absorption efficiency η_{abs} . Here, we assume a background absorption coefficient of $\alpha_b = 10 \text{ dB/km} \approx 2.3 \times 10^{-3} / \text{m}$, which is a typical value for commercial grade Yb-doped silica fibers. Using this information, we present a contour plot of the

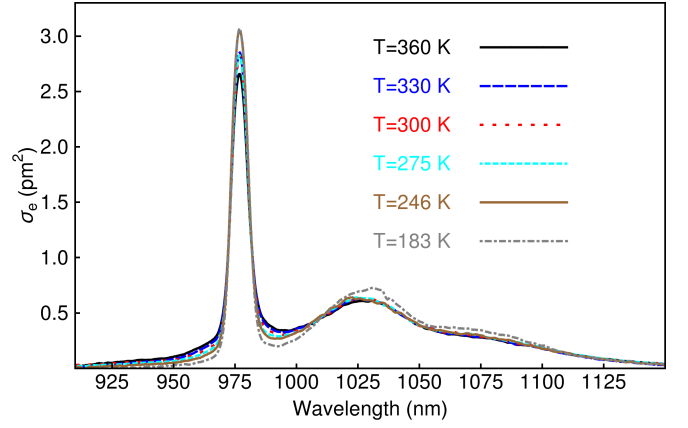


FIG. 4. Emission cross section versus wavelength for DF-1000 Yb-doped silica fiber at different temperatures. The spectra are calculated from Eq. 8 using the emission spectra shown in Fig. 3 and the measured radiative lifetimes from Ref. [38].

cooling efficiency η_c in Fig. 5 as a function of the pump wavelength and temperature, assuming that $\eta_q = 1$. Note that we only know the values of $\alpha_r(\lambda, T)$ at discrete values of temperature T for which our measurements were performed in Fig. 3; the density plot in Fig. 5 is an interpolation of the measured values. It is seen in Fig. 5 that the cooling efficiency decreases with decreasing temperature; this behavior is due to the red-shift of the mean fluorescence wavelength and the decrease in the resonant absorption coefficient with decreasing temperature [16, 20].

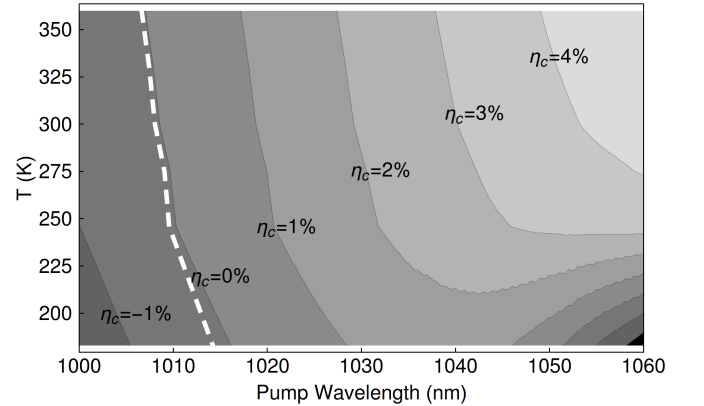


FIG. 5. Cooling efficiency versus temperature and pump wavelength with $\eta_q = 1$ and $\alpha_b = 10 \text{ dB/km}$ for DF-1100 Yb-doped silica fiber calculated from Eq. 1. The dashed line connects the experimental measurements of the mean fluorescence wavelength versus the temperature.

In practice, it is impossible to achieve an internal quantum efficiency of unity; therefore, in Fig. 6 we investigate the effect of a non-ideal internal quantum efficiency on the cooling efficiency, for $\lambda_p = 1030 \text{ nm}$, as a function of the temperature. The discrete points in Fig. 6 signify the values of η_c obtained for the assumed η_q at the particular

measured temperatures reported in Fig. 3. The apparent difference between the cooling efficiency obtained for $\eta_q = 1$ versus $\eta_q = 0.98$ highlights the importance of having a high-quality glass for radiative cooling. While the discrete points in Fig. 6 reveal the main expected behavior of η_c versus the temperature, it is helpful to estimate the minimum achievable temperature for solid-state optical refrigeration in Yb-doped silica glass, subject to the assumptions made about η_q , N , and α_b . In order to do so, we next present an analytical fitting to the discrete points in Fig. 6 that can be used to estimate the minimum achievable temperature. The analytical fitting, which is described in the next paragraph, is used in conjunction with Eq. 1 to plot the colored lines for each value of η_q in Fig. 6 and is in reasonable agreement with the experimentally measured discrete data. From the discussions

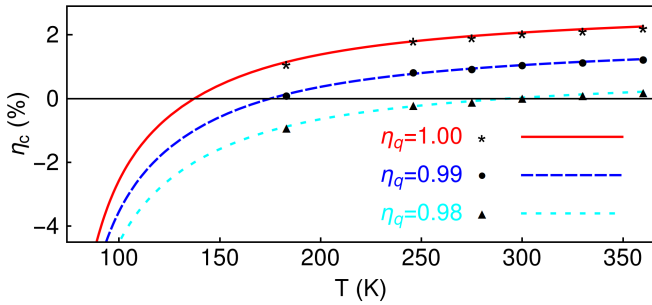


FIG. 6. Cooling efficiency versus temperature with $\alpha_b = 10$ dB/km for DF-1100 Yb-doped silica fiber calculated from Eq. 1 for different internal quantum efficiencies, η_q . The colored lines are plotted using Eq. 1 and the fitting presented in Eq. 14.

above and Eqs. 8, 9, and 10, we note that $\alpha_r(\lambda_p, T)$ (at the pump wavelength) can be expressed as:

$$\alpha_r(\lambda_p, T) \propto \frac{1}{c} \frac{\lambda_p^5}{\tau_r(T)} \times \frac{S(\lambda_p, T)}{\int_{\Delta} \lambda S(\lambda, T) d\lambda} \times \mathcal{Z}(\lambda_p, T). \quad (11)$$

In Ref. [38], we performed fluorescence lifetime measurements in Yb-silica. Here, we present a fitting of $\tau_r(T)$ to an analytical form that is based on a two-level excited state:

$$\tau_r(T) = \frac{1 + \exp(-\delta E/k_b T)}{\tau_1^{-1} + \tau_2^{-1} \exp(-\delta E/k_b T)}. \quad (12)$$

$\tau_1 = 798 \pm 2 \mu\text{s}$, and $\tau_2 = 576 \pm 27 \mu\text{s}$ are the lifetimes of the first and second energy levels of the excited state, respectively, and $\delta E = 506 \pm 56 \text{ cm}^{-1}$ is the energy difference between these two levels [36, 39]. We also present the following approximation:

$$\frac{\lambda_p^2 S(\lambda_p, T)}{\int_{\Delta} \lambda S(\lambda, T) d\lambda} \approx 7.4 + \left(\frac{d}{T}\right)^5, \quad d = 205.9 \pm 2.4 \text{ K}. \quad (13)$$

Using Eqs. 12 and 13, we can approximate $\alpha_r(\lambda_p, T)$ [Eq. 11] with the following mathematical form:

$$\alpha_r(\lambda_p, T) \approx \frac{\alpha_{r,0}}{c \tau_r(T)} \times \left(7.4 + (d/T)^5\right) \times \mathcal{Z}(\lambda_p, T). \quad (14)$$

Fitting the analytical in Eq. 14 to the discrete points in Fig. 6, we find the dimensionless coefficient $\alpha_{r,0} = (0.95 \pm 0.01) \times 10^6$. The fitted lines in Fig. 6 show that the minimum achievable temperature can reach down to $T_{\min} = 138 \text{ K}$ for $\eta_q = 1$, $T_{\min} = 175 \text{ K}$ for $\eta_q = 0.99$, and $T_{\min} = 290 \text{ K}$ for $\eta_q = 0.98$. Figure 6 also shows that the maximum cooling efficiency for Yb-silica glass is around $\eta_c^{\max} \approx 2\%$ at room temperature for $\lambda_p = 1030 \text{ nm}$. Setting the background absorption to zero ($\alpha_b = 0$) increases this value to $\eta_c^{\max} \approx 2.2\%$. In order to increase the cooling efficiency, the background absorption must be minimized, the internal quantum efficiency has to be close to unity, and the ion dopant density N must be increased to enhance the resonant absorption coefficient. We note that these requirements are not necessarily compatible with each other; e.g. increasing N can potentially decrease η_q due to quenching. Therefore, a compromise determined by careful measurements must be obtained.

IV. DISCUSSION AND CONCLUSION

It must be noted that by taking $N = 5 \times 10^{25} \text{ m}^{-3}$ in this manuscript, we have implicitly assumed that the silica glass host is co-doped with some modifiers like Al_2O_3 , in order to shift the quenching concentration to higher values to reduce clustering and ensure an adequate cooling efficiency [40, 41]. For pure silica, applying the model developed by Auzel et al. [25] to the experimental data from Ref. [23], it can be shown that $N = 0.7 \times 10^{25} \text{ m}^{-3}$ can guarantee a near unity internal quantum efficiency [40, 41]. Using $N = 0.7 \times 10^{25} \text{ m}^{-3}$ in pure silica, we have calculated the minimum achievable temperature to be $T_{\min} = 216 \text{ K}$ for $\eta_q = 1$, and $T_{\min} = 262 \text{ K}$ for $\eta_q = 0.99$. For $\eta_q = 0.98$, T_{\min} is higher than the room temperature. As expected, a decrease in ion density results in a lower cooling efficiency.

In conclusion, we have argued that a high-purity Yb-doped silica glass can potentially be cooled via anti-Stokes fluorescence. In order to achieve net solid-state optical refrigeration, it is necessary for the cooling efficiency to be positive. This requires the pump wavelength to be greater than the mean fluorescence wavelength, and the internal quantum efficiency as well as the absorption efficiency to be near unity. For the internal quantum efficiency we have shown that, in principle, the non-radiative decay rate W_{nr} can be made substantially smaller than the radiative decay rate W_r . Therefore, an internal quantum efficiency of near unity can be obtained, making Yb-doped silica glass suitable for solid-state optical refrigeration. Our assessment is based on reasonable assumptions for material properties, e.g. we have assumed a typical

background absorption coefficient of $\alpha_b = 10$ dB/km and an internal quantum efficiency of larger than $\eta_q = 0.98$. We have made spectral measurements of the fluorescence from a Yb-doped silica optical fiber at different temperatures. Using these measurements, we have reported the temperature dependence of the mean fluorescence wavelength, and have estimated the minimum achievable temperature in Yb-doped silica glass.

Our analysis highlights the potential for Yb-doped silica glass to be used as the gain medium for radiation-balanced high-power fiber lasers and amplifiers. In order to observe the solid-state optical refrigeration of silica, high-quality samples with adequate Yb doping concen-

trations are required. It is preferable to co-dope silica with modifiers such as Al_2O_3 to increase the solubility of Yb ions and consequently increase the cooling efficiency. Of course, proper thermal isolation in solid-state optical refrigeration is essential. Such experiments are quite delicate [16] and Yb-doped silica will be no exception.

ACKNOWLEDGMENT

This material is based upon work supported by the Air Force Office of Scientific Research under award number FA9550-16-1-0362 titled Multidisciplinary Approaches to Radiation Balanced Lasers (MARBLE).

-
- [1] P. Pringsheim, "Zwei Bemerkungen über den Unterschied von Lumineszenz- und Temperaturstrahlung," *Zeitschrift für Physik* **57**, 739–746 (1929).
 - [2] L. Landau, "On the thermodynamics of photoluminescence," *J. Phys. (Moscow)* **10** (1946).
 - [3] R. I. Epstein, M. I. Buchwald, B. C. Edwards, T. R. Gonnell, and C. E. Mungan, "Observation of laser-induced fluorescent cooling of a solid," *Nature* **377**, 500 (1995).
 - [4] R. I. Epstein and M. Sheik-Bahae, *Optical refrigeration: science and applications of laser cooling of solids* (John Wiley & Sons, 2010).
 - [5] D. V. Seletskiy, R. Epstein, and M. Sheik-Bahae, "Laser cooling in solids: advances and prospects," *Reports on Progress in Physics* **79**, 096401 (2016).
 - [6] D. J. Richardson, J. Nilsson, and W. A. Clarkson, "High power fiber lasers: current status and future perspectives," *J. Opt. Soc. Am. B* **27**, B63–B92 (2010).
 - [7] A. V. Smith and J. J. Smith, "Mode instability in high power fiber amplifiers," *Opt. Express* **19**, 10180–10192 (2011).
 - [8] J. W. Dawson, M. J. Messerly, R. J. Beach, M. Y. Shverdin, E. A. Stappaerts, A. K. Sridharan, P. H. Pax, J. E. Heebner, C. W. Siders, and C. Barty, "Analysis of the scalability of diffraction-limited fiber lasers and amplifiers to high average power," *Opt. Express* **16**, 13240–13266 (2008).
 - [9] C. Jauregui, T. Eidam, H.-J. Otto, F. Stutzki, F. Jansen, J. Limpert, and A. Tünnermann, "Physical origin of mode instabilities in high-power fiber laser systems," *Opt. Express* **20**, 12912–12925 (2012).
 - [10] S. R. Bowman, "Lasers without internal heat generation," *IEEE journal of quantum electronics* **35**, 115–122 (1999).
 - [11] S. R. Bowman, S. P. O'Connor, S. Biswal, N. J. Condon, and A. Rosenberg, "Minimizing heat generation in solid-state lasers," *IEEE Journal of Quantum Electronics* **46**, 1076–1085 (2010).
 - [12] E. Mobini, M. Peysokhan, B. Abaie, and A. Mafi, "Thermal modeling, heat mitigation, and radiative cooling for double-clad fiber amplifiers," *JOSA B Early Posting*, 0000–0000 (2018).
 - [13] G. Nemova and R. Kashyap, "Athermal continuous-wave fiber amplifier," *Optics Communications* **282**, 2571–2575 (2009).
 - [14] H. Pask, R. J. Carman, D. C. Hanna, A. C. Tropper, C. J. Mackechnie, P. R. Barber, and J. M. Dawes, "Ytterbium-doped silica fiber lasers: versatile sources for the 1–1.2 μm region," *IEEE Journal of Selected Topics in Quantum Electronics* **1**, 2–13 (1995).
 - [15] R. Paschotta, J. Nilsson, A. C. Tropper, and D. C. Hanna, "Ytterbium-doped fiber amplifiers," *IEEE Journal of quantum electronics* **33**, 1049–1056 (1997).
 - [16] D. V. Seletskiy, S. D. Melgaard, S. Bigotta, A. Di Lieto, M. Tonelli, and M. Sheik-Bahae, "Laser cooling of solids to cryogenic temperatures," *Nature Photonics* **4**, 161 (2010).
 - [17] G. Lei, J. E. Anderson, M. I. Buchwald, B. C. Edwards, R. I. Epstein, M. T. Murtagh, and G. Sigel, "Spectroscopic evaluation of Yb^{3+} -doped glasses for optical refrigeration," *IEEE journal of quantum electronics* **34**, 1839–1845 (1998).
 - [18] S. Melgaard, D. Seletskiy, M. Sheik-Bahae, S. Bigotta, A. Di Lieto, M. Tonelli, and R. Epstein, "Spectroscopy of Yb-doped YLF crystals for laser cooling," in *Laser Refrigeration of Solids III*, , vol. 7614 (International Society for Optics and Photonics, 2010), p. 761407.
 - [19] X. Ruan and M. Kaviani, "Enhanced laser cooling of rare-earth-ion-doped nanocrystalline powders," *Physical Review B* **73**, 155422 (2006).
 - [20] M. P. Hehlen, R. I. Epstein, and H. Inoue, "Model of laser cooling in the Yb^{3+} -doped fluorozirconate glass ZBLAN," *Physical Review B* **75**, 144302 (2007).
 - [21] M. J. Dignonnet, *Rare-earth-doped fiber lasers and amplifiers, revised and expanded* (CRC press, 2001).
 - [22] C. Hoyt, M. Hasselbeck, M. Sheik-Bahae, R. Epstein, S. Greenfield, J. Thiede, J. Distel, and J. Valencia, "Advances in laser cooling of Thulium-doped glass," *JOSA B* **20**, 1066–1074 (2003).
 - [23] P. Barua, E. Sekiya, K. Saito, and A. Ikushima, "Influences of Yb^{3+} ion concentration on the spectroscopic properties of silica glass," *Journal of Non-Crystalline Solids* **354**, 4760–4764 (2008).
 - [24] J. Van Dijk and M. Schuurmans, "On the nonradiative and radiative decay rates and a modified exponential energy gap law for 4 f–4 f transitions in rare-earth ions," *The Journal of Chemical Physics* **78**, 5317–5323 (1983).
 - [25] F. Auzel, G. Baldacchini, L. Laversenne, and G. Boulon, "Radiation trapping and self-quenching analysis in Yb^{3+} ,

- Er³⁺, and Ho³⁺ doped Y₂O₃,” *Optical Materials* **24**, 103–109 (2003).
- [26] G. Boulon, “Why so deep research on Yb³⁺-doped optical inorganic materials?” *Journal of Alloys and Compounds* **451**, 1–11 (2008).
- [27] D. T. Nguyen, J. Zong, D. Rhonehouse, A. Miller, Z. Yao, G. Hardesty, N. Kwong, R. Binder, and A. Chavez-Pirson, “All fiber approach to solid-state laser cooling,” in *Laser Refrigeration of Solids V*, , vol. 8275 (International Society for Optics and Photonics, 2012), p. 827506.
- [28] S. Jetschke, S. Unger, A. Schwuchow, M. Leich, and J. Kirchhof, “Efficient Yb laser fibers with low photodarkening by optimization of the core composition,” *Optics Express* **16**, 15540–15545 (2008).
- [29] M. Leich, F. Just, A. Langner, M. Such, G. Schötz, T. Eschrich, and S. Grimm, “Highly efficient Yb-doped silica fibers prepared by powder sinter technology,” *Optics letters* **36**, 1557–1559 (2011).
- [30] R. Sidharthan, S. H. Lim, K. J. Lim, D. Ho, C. H. Tse, J. Ji, H. Li, Y. M. Seng, S. L. Chua, and S. Yoo, “Fabrication of low loss low-NA highly Yb-doped Aluminophosphosilicate fiber for high power fiber lasers,” in *Conference on Lasers and Electro-Optics*, (Optical Society of America, 2018), p. JTh2A.129.
- [31] B. Faure, W. Blanc, B. Dussardier, and G. Monnom, “Improvement of the Tm³⁺: ³H₄ level lifetime in silica optical fibers by lowering the local phonon energy,” *Journal of Non-Crystalline Solids* **353**, 2767–2773 (2007).
- [32] G. A. Thomas, B. I. Shraiman, P. F. Glodis, and M. J. Stephen, “Towards the clarity limit in optical fibre,” *Nature* **404**, 262 (2000).
- [33] Y. Jeong, J. K. Sahu, D. N. Payne, and J. Nilsson, “Ytterbium-doped large-core fiber laser with 1.36 kw continuous-wave output power,” *Opt. Express* **12**, 6088–6092 (2004).
- [34] T. Fan and M. Kokta, “End-pumped Nd:LaF₃ and Nd:LaMgAl₁₁O₁₉ lasers,” *IEEE journal of quantum electronics* **25**, 1845–1849 (1989).
- [35] D. E. McCumber, “Theory of phonon-terminated optical masers,” *Physical review* **134**, A299 (1964).
- [36] T. Newell, P. Peterson, A. Gavrielides, and M. Sharma, “Temperature effects on the emission properties of Yb-doped optical fibers,” *Optics communications* **273**, 256–259 (2007).
- [37] B. Aull and H. Jenssen, “Vibronic interactions in Nd:YAG resulting in nonreciprocity of absorption and stimulated emission cross sections,” *IEEE Journal of Quantum Electronics* **18**, 925–930 (1982).
- [38] E. Mobini, M. Peysokhan, B. Abaie, and A. Mafi, “Investigation of solid state laser cooling in ytterbium-doped silica fibers,” in *Conference on Lasers and Electro-Optics*, (Optical Society of America, 2018), p. FF3E.4.
- [39] Z. Zhang, K. Grattan, and A. Palmer, *Journal of applied physics* **73**, 3493 (1993).
- [40] K. Arai, H. Namikawa, K. Kumata, T. Honda, Y. Ishii, and T. Handa, “Aluminum or phosphorus co-doping effects on the fluorescence and structural properties of neodymium-doped silica glass,” *Journal of Applied Physics* **59**, 3430–3436 (1986).
- [41] J. Lægsgaard, “Dissolution of rare-earth clusters in SiO₂ by Al codoping: a microscopic model,” *Physical Review B* **65**, 174114 (2002).