

This is the accepted manuscript made available via CHORUS. The article has been published as:

Dirac polaron dynamics in the correlated semimetal of
perovskite $\text{Mn}_3\text{Ti}_2\text{O}_{10}$

$\text{Mn}_3\text{Ti}_2\text{O}_{10}$

J. Fujioka, R. Yamada, T. Okawa, and Y. Tokura

Phys. Rev. B **103**, L041109 — Published 19 January 2021

DOI: [10.1103/PhysRevB.103.L041109](https://doi.org/10.1103/PhysRevB.103.L041109)

Dirac polaron dynamics in the correlated semimetal of perovskite CaIrO_3

J. Fujioka¹, R. Yamada², T. Okawa² and Y. Tokura^{2,3,4}

¹ *Faculty of Material Science,
University of Tsukuba,
1-1-1 Tennodai, Tsukuba,
Ibaraki 305-8573, Japan*

² *Department of Applied Physics,
University of Tokyo, Hongo,
Tokyo 113-8656, Japan*

³ *RIKEN Center for Emergent Matter Science (CEMS),
Wako 351-0198, Japan*

⁴ *Tokyo College, University of Tokyo,
Hongo, Tokyo 113-8656, Japan*

(Dated: January 6, 2021)

Abstract

We have investigated the charge dynamics of the correlated Dirac semimetallic perovskite CaIrO_3 by infrared spectroscopy. The optical conductivity spectra show the ω -linear-type interband transition and a tiny Drude response at low temperatures, suggesting that the Dirac node is pinned nearby the Fermi energy due to the Mott criticality. Moreover, a large polaron absorption appears at around 0.04 eV, when thermally excited carriers diminish and the plasma frequency decreases below the optical phonon energy. The electron correlation and resultant reduced plasma frequency are likely to enhance the electron-phonon interaction via the insufficient electronic screening, realizing the Dirac polaron.

The quantum phenomena in topological (Dirac/Weyl) semimetals are subjects of great interest in the condensed matter science. One of the remarkable features of topological semimetal is that highly mobile Dirac/Weyl electrons give rise to unconventional quantum phenomena as exemplified by the giant-magnetoresistance and anomalous/spin Hall effect [1]. Thus far, many studies have focused on the phenomena described by the single-particle physics, but there is a growing interest in the effect of strong electron correlation as a unique pathway to explore emergent quantum phenomena. In general, the electron correlation not only renormalizes an effective mass or Fermi velocity of electron, but also promotes several electronic interactions including the magnetic exchange interaction and electron-phonon interaction, which are important to realize unconventional topological phases. In particular, recent studies argue that the axionic charge density wave or excitonic insulator can be induced, given that the electron correlation or electron-phonon interaction is sufficiently strong [2–6].

In this context, the topological semimetal coupled to the Mott criticality may offer a fertile ground to study unconventional topological phases of correlated Dirac/Weyl electrons [7–10]. The perovskite AIrO_3 ($\text{A}=\text{Ca}, \text{Sr}, \text{Ba}$) [see Fig. 1 (a)] is a candidate of the Dirac semimetal nearby the Mott transition, which is characterized by the strong electron correlation and relativistic spin-orbital coupling due to the Ir $5d$ -electron [11–13]. In particular, the electronic state nearby the Fermi level (E_F) is dominated by a nearly half-filled Ir $5d$ -state with $J_{\text{eff}} = 1/2$ pseudo-spin [10, 14], resulting in the compensated semimetal with electron pockets with Dirac nodal line nearby the U-point and a massive hole pocket nearby the Γ -point [see Fig. 1 (b)–(d)]. In a series of AIrO_3 , the effective one-electron bandwidth can be varied by tuning the Ir-O-Ir bond angle (ϕ) depending on the ionic radius of the A -site ion [Fig. 1(a)] [15]; the largest GdFeO_3 -type lattice distortion results in the largest effective electron correlation in the CaIrO_3 .

The recent experiments have uncovered that the line node is nearly pinned to E_F (about 10 meV below E_F) due to the Mott criticality, leading to the Dirac electrons with the dilute carrier density about $2 \times 10^{17} \text{ cm}^{-3}$ and mobility exceeding $60,000 \text{ cm}^2/\text{Vs}$ at low temperatures [16–18]. In particular, when the system reaches the quantum limit, wherein the electrons are quasi-one dimensionally confined by the magnetic field, the resistivity steeply increases, yielding the longitudinal magnetoresistance with a ratio of 5,500%. On the contrary, a more conventional metallic state with higher carrier density is realized in

SrIrO₃ and BaIrO₃ [13] with the smaller GdFeO₃-type lattice distortion and effective electron correlation. The effective electron correlation and/or electron-phonon interaction likely play crucial roles for the transport of Dirac electron in these materials, yet the electronic interaction has been poorly understood. In this study, we have investigated the charge dynamics of CaIrO₃ by means of optical spectroscopy and found that the Dirac electron exhibits the polaronic excitation around 0.04 eV at low temperatures. It is likely that the electron correlation significantly reduces the electronic screening via the renormalized plasma frequency, promoting the Frohlich (long-range) electron-phonon interaction and formation of highly-mobile polaronic Dirac electrons (Dirac polarons).

The samples of CaIrO₃ were grown at 1300°C under 1 GPa by using the cubic anvil-type high-pressure facility. The obtained crystal is the densely-packed assembly of the single crystalline grain with typical size of about 0.2–0.4 mm. We polished the exposed surface of unoriented grain and measured the reflectivity spectra with unpolarized light [19]. Since the Fermi surface and crystal structure are not significantly anisotropic [16], it is reasonable to consider that the intra/interband optical transition does not show remarkable polarization or crystal-orientation dependence in the low-energy region. The spectra in the region 0.02–0.7 eV (0.5–5 eV) are measured by using a Fourier transform (grating) type spectrometer equipped with microscope, while those in the region 0.004–0.1 eV are also measured for a lump of grains with using macro-optics. The results obtained by using the microscope are similar to those obtained by using macro-optics, indicating that the effect from the grain boundary is not remarkable [19]. The spectra in the region 3–40 eV are measured at room temperature in the UV-SOR. We derived the optical conductivity ($\sigma(\omega)$) spectra by the Kramers-Kronig analysis with appropriate extrapolations [19][see Figs. S3].

The resistivity of single crystalline CaIrO₃ [see Fig. 1(e)] exhibits a metallic temperature dependence above 150 K, but a prominent peak is observed around 20 K [16]. As shown in the inset to Fig. 1 (e), the carrier density monotonically decreases with decreasing temperature and reaches about $\sim 1 \times 10^{17} \text{ cm}^{-3}$ below 20 K. We note that the resistivity peak can be explained in term of the temperature dependence of electron density and electron mobility; the former (latter) decreases (increases) as temperature decreases, the balance of which causes the resistivity peak. This behavior is in contrast with the case of SrIrO₃, wherein the resistivity shows a metallic behavior in all temperature region and the carrier density is as high as $6 \times 10^{19} \text{ cm}^{-3}$ even at 10 K.

In both CaIrO_3 and SrIrO_3 , the $\sigma(\omega)$ at 10 K [see Fig 1(f)] shows two broad peaks (α - and β -band), which are assigned to the optical transition from occupied $j_{\text{eff}} = 1/2$ -state to unoccupied $j_{\text{eff}} = 1/2$ -state, and that from occupied $j_{\text{eff}} = 3/2$ -state to unoccupied $j_{\text{eff}} = 1/2$ -state, respectively [see Fig. 1(d)] [14, 20]. The spectral intensity of α -band, which is defined by the effective number of electron (N_{eff}) below 0.5 eV [19], is smaller by about 10 % in CaIrO_3 than in SrIrO_3 . This is consistent with the smaller one-electron bandwidth in CaIrO_3 than in SrIrO_3 , since the spectral intensity of α -band is scaled to the one-electron bandwidth of $j_{\text{eff}} = 1/2$ -state [14]. On the other hand, the charge dynamics below 0.1 eV is qualitatively different between these two systems [see the inset to the Fig. 1 (f)]. The tail of Drude response is observed in SrIrO_3 , but is likely to be located below 0.004 eV in the CaIrO_3 [19][see also Figs. S3]. Furthermore, the CaIrO_3 shows an absorption peak around 0.04 eV (peak-A), the shape of which is different from other sharp peaks of optical phonons.

Figures 2 (a) and (b) display the $\sigma(\omega)$ spectra above 150 K and those below 120 K, respectively. The $\sigma(\omega)$ spectra above 150 K show the Drude response accompanied by a very broad hump-like structure around 0.03 eV due perhaps to the thermally induced incoherent charge dynamics. With decreasing temperature, both structures gradually diminish; in particular, the hump-like structure is no longer discernible below 150 K. On the contrary, it is clear that the peak-A appears below 120 K. To quantify the temperature dependence of Drude response and peak-A, we fitted the spectra with using the following formula,

$$\sigma(\omega) = \frac{\sigma_D}{1 + \omega^2 \tau_D^2} + \frac{S_0 \gamma_0 \omega_0^2 \omega^2}{(\omega^2 - \omega_0^2)^2 + \gamma_0^2 \omega^2} + A\omega^\alpha + \sum_{i=1}^9 S_i \omega \left[1 - \frac{(q_i + (\omega - \omega_i)/\gamma_i)^2}{1 + (\omega - \omega_i)^2/\gamma_i^2} \right]. \quad (1)$$

The first term represents the Drude response with the dc-conductivity (σ_D) and relaxation time (τ_D), respectively. The second term represents the peak-A with the oscillator strength (S_0), damping constant (γ_0) and peak energy (ω_0), respectively. We modeled the interband transition as the third term with the parameters A and α . The phonons are modeled by the forth terms with oscillator strength (S_i), damping constant (γ_i), asymmetric parameter (q_i) and peak energy (ω_i), considering the asymmetric shape due to the electron-phonon interaction [19].

As shown in Figs. 2 (c) and (d), the fitting nearly reproduces the experimental results. Specifically, below 70 K, the fitting yields $\alpha \sim 1$, suggesting that the interband transition

spectrum is of ω -linear type as the case of Dirac semimetals with a point-node [21, 22]. The theoretical study proposes that the nodal line semimetal shows the ω -linear type interband transitions, when the radius of nodal line is sufficiently small [23]. This is consistent with the previous report that the size of nodal line is as small as 1/60 of the reciprocal lattice unit [16]. By assuming that the present band structure can be regarded as the nearly degenerate two Dirac cones [see Fig. 1(b)], the v_F is estimated to be $(5.6 \pm 0.1) \times 10^4$ m/s from the slope of interband transition [24].

We also calculated the spectral weight for the peak-A and Drude response by using the effective number of electrons N_{eff} , *i.e.* the energy-integration of $\sigma(\omega)$ [19]. As shown in Fig. 3 (a) [see also the Fig. S4], the Drude weight monotonically decreases with decreasing temperature. In Dirac semimetals with finite carrier density, generally, the Drude weight is temperature independent at low temperatures, but increases as a function of temperature when the thermal excitation of carriers becomes remarkable. Specifically, at high temperatures of $k_B T > E_F$, it is predicted that the Drude weight for Dirac semimetals with a point node is described by $\pi e^2 (k_B T)^2 / (18 \hbar^3 v_F)$ [25, 26]. By regarding the present band structure as the nearly degenerate two Dirac cones [see Fig. 1(b) and (d)], the experimental result agrees with the model calculation with $v_F = (5.6 \pm 0.3) \times 10^4$ m/s [see Fig. 3(a)]. This is consistent with the results of transport measurements [16], suggesting that the Drude response originates from the Dirac electrons.

On the contrary, the spectral weight of peak-A rises below 120 K and appears to maximize around 30 K. To clarify the origin of the peak-A, we explored the plasmon resonance and longitudinal optical (LO) phonon with use of the loss function spectra $\text{Im}[-1/\epsilon(\omega)]$. As shown in Fig. 3 (d), at 210 K, the $\text{Im}[-1/\epsilon(\omega)]$ spectra exhibit a broad peak of plasmon resonance with fine dips and peaks due to optical phonons. With decreasing temperature, the plasmon peak shifts toward lower energy and cannot be traced below 40 K. Moreover, the three LO-phonons in the energy range 0.24 - 0.35 eV become clear below 120 K, wherein the plasma frequency is lower than their energies. In other words, the three LO-phonons and the plasmon resonance form an amalgamated band at high temperatures, suggesting that the formers are strongly coupled to the latter, *i.e.* the Drude response. Figure 3 (b) shows the energy of peak-A, energy range of the three LO-phonons and the plasma frequency derived from the $\text{Im}[-1/\epsilon(\omega)]$ spectra [19]. The energy of peak-A is slightly higher than the energy range of the three LO-phonons [see also Fig. 3 (d)]. Moreover, it is likely that the

peak-A rises when the energy of plasmon resonance decreases across the three LO-phonons around 0.24 - 0.35 eV with decreasing temperature.

Then, we discuss the origin of peak-A. Considering that the spectral intensity steeply increases below 120 K and the peak width is more than 0.01 eV, which is one order larger than those of other optical phonons [19], the peak-A may not be the conventional infrared active phonon. Indeed, the corresponding absorption is absent in the SrIrO₃, which has a similar crystal structure to CaIrO₃ [see inset to the Fig. 1(f)]. Another possibility would be the interband excitation of the Dirac band or other bands [27, 28]. It is argued that the excitonic charge excitation may show a peak around the energy of $2E_F$ [29]. In the present system, however, $2E_F$ would be at most 0.02 eV [16], which may not be consistent with the observed peak energy. Although the interband transition around the Γ -point appears to be possible in terms of the energy scale [see Fig. 1(d)], this is also unlikely, since the corresponding absorption is absent in SrIrO₃, which has a similar electronic state around the Γ -point [14].

Considering the strong coupling to the LO-phonons, the most plausible origin of peak-A is the polaron excitation. In case of large polaron (Fröhlich-polaron), the polaron excitation is usually observed as a broad absorption band emerging at higher energy side of LO-phonon(s), when ω_p^* is lower than the energy of LO-phonon, or equivalently, when the LO-phonons are not sufficiently screened by charge carriers [30–32]. In the present case, given that the three LO-phonons around 0.24 - 0.35 eV [Fig. 3 (d)] are relevant for the polaron formation, it is reasonable that the reduction of ω_p^* induces the polaron band below 120 K [see Fig. 3(a) and (b)]. Following the Frohlich polaron model, the mass enhancement factor $v_F^b/v_F^*(=1+\lambda)$ is defined as the ratio of Drude weight to the summation of Drude weight and polaron band (Here, v_F^b and v_F^* are the bare and renormalized Fermi velocity, respectively.). As shown in Fig. 3 (c), the $1+\lambda$ increases with decreasing temperature and reaches about 2.7 at 50 K, which corresponds to the coupling constant of Frohlich interaction $\alpha = 4.3$ [33]. We note that this scenario can naturally explain the absence of polaron band in the SrIrO₃; as shown in Fig. 3 (e), the plasmon peak lies as high as 0.032 eV even at 10 K due to the larger carrier density and less renormalized v_F^* , which results in the reduction of Frohlich interaction through the enhanced electronic screening. In other words, in CaIrO₃, it is likely that the strong electron correlation nearby the Mott transition results in the lowness of ω_p^* at low temperatures and consequently promotes the Fröhlich interaction to form the polaronic

Dirac electron state.

The enhancement of polaronic state is often seen in correlated electron oxides nearby the Mott transition. In general, the electron correlation rather promotes the short-range electron-phonon interaction and formation of small polaron [34]. Although the present results appear to be different from the conventional case, we cannot exclude the possibility of mixture of the small polaron character from the above results alone. A remarkable feature of small polaron is the effect of quenched disorder; the disorder promotes the self-trapping of small polaron [35], which could be observed as the change in the polaron band.

To address this issue, we explored the doping variation of polaron band for $\text{CaIr}_{1-x}\text{Rh}_x\text{O}_3$, wherein the doped-Rh mainly acts as the quenched disorder. As shown in Fig. 4 (a), the resistivity of the doped system shows a similar temperature dependence with that of $x = 0$, but the electron mobility significantly decreases with increasing x [see the inset to Fig. 4(a)], suggesting the enhancement of electron scattering. Figures 4 (b)-(d) show the $\sigma(\omega)$ spectra measured at 50 K. Both the Drude response and polaron band are observed even in the doped system. As shown in Fig. 4 (e), the spectral weight of polaron band decreases with increasing x , but the Drude weight increases in accord with the modest enhancement of carrier density [19], leading to the reduction of $1 + \lambda$. The result can be straightforwardly understood by the Fröhlich polaron model and the signature of self-trapping of small polaron is not discernible. A possible reason may be that electrons with a tiny Fermi surface in the present system is less amenable to the deformation potential due to the acoustic phonons with large momentum, which is a typical source of short-range electron-phonon interaction [36].

In summary, we have explored the charge dynamics of the correlated Dirac semimetallic CaIrO_3 by means of optical spectroscopy. The optical conductivity exhibits the ω -linear-type interband transition and the Drude weight monotonically decreases with lowering temperatures, which is consistent with the experimentally observed fact that the Fermi energy is nearly pinned to the line node due to the strong electron correlation nearby the Mott transition. We found that the absorption band of large polaron with intermediate coupling strength appears at around 0.04 eV in the low temperature regime, where the plasma frequency is lower than the energy of relevant longitudinal phonons. These results suggest that the correlated Dirac electron forms the large polaron nearby the Mott criticality as the Fröhlich-type electron-phonon interaction becomes appreciable via the insufficient screening

of optical phonons due to the dilute carrier density and reduced Fermi velocity. Although the electron-phonon interaction is not likely strong enough to change the topology of line node at the present state, it could be a unique knob to induce other topological phases, when the Dirac electron is quasi-one-dimensionally confined in the quantum limit.

We thank M. Kawamura, S. Sakai, M. Hirayama, R. Arita, M. Hoshino, and D. Hashizume for useful discussions. This work was partly supported by Grant-In-Aid for Science Research (Nos. 16H00981, 18H01171, 18H04214, 16H06345) from the MEXT, and by PRESTO(No. JPMJPR15R5) and CREST(No. JPMJCR16F1), JST, Japan.

-
- [1] N. P. Armitage, E. J. Mele and A. Vishwanath, *Rev. Mod. Phys.* **90**, 015001 (2018).
 - [2] H. Wei, S-P. Chao and V. Aji, *Phys. Rev. Lett.* **109**, 196403(R) (2012).
 - [3] Z. Wang and S. C. Zhang *Phys. Rev. B* **87**, 161107(R) (2013).
 - [4] B. Roy and J. D. Sau, *Phys. Rev. B* **92**, 125141 (2015).
 - [5] Z. Song, Z. Fang and X. Dai, *Phys. Rev. B* **96**, 235104 (2017).
 - [6] J. Gooth *et al.*, *Nature*, **575**, 315 (2019).
 - [7] X. Wan, A. M. Turner, A. Vishwanath and S. Y. Savrasov, *Phys. Rev. B* **83**, 205101 (2011).
 - [8] W. Witczak-Krempa and Y. B. Kim, *Phys. Rev. B* **85**, 045124 (2012).
 - [9] R. Schaffer, E. Kin-Ho Lee, B.-J. Yang, and Y. B. Kim, *Rep. Prog. Phys.* **79**, 094504 (2016).
 - [10] J.-M. Carter, V. V. Shankar, M. A. Zeb, and H.-Y. Kee, *Phys. Rev. B* **85**, 115105 (2012).
 - [11] C. L. McDaniel and S. J. Schneider, *J. Solid State Chem.* **4**, 275 (1972).
 - [12] J. M. Longo, J. A. Kafalas and R. J. Arnett, *J. Solid State Chem.* **3**, 174 (1971).
 - [13] J.-G. Cheng, T. Ishii, H. Kojitani, K. Matsubayashi, A. Matsuo, X. Li, Y. Shirako, J.-S. Zhou, J. B. Goodenough, C. Q. Jin, M. Akaogi and Y. Uwatoko *Phys. Rev. B* **88**, 205114 (2013).
 - [14] H. Zhang, K. Haule and D. Vanderbilt *Phys. Rev. Lett.* **111**, 246402 (2013).
 - [15] M. Imada, A. Fujimori, and Y. Tokura, *Rev. Mod. Phys.* **70**, 1039 (1998).
 - [16] J. Fujioka, R. Yamada, M. Kawamura, S. Sakai, M. Hirayama, R. Arita, T. Okawa, D. Hashizume, M. Hoshino and Y. Tokura, *Nature Commun.* **10**, 362 (2019).
 - [17] M. Masuko, J. Fujioka, M. Nakamura, M. Kawasaki, and Y. Tokura, *APL Mater.* **7**, 081115 (2019).
 - [18] R. Yamada, J. Fujioka, M. Kawamura, S. Sakai, M. Hirayama, R. Arita, T. Okawa, D.

- Hashizume, M. Hoshino and Y. Tokura, *Phys. Rev. Lett.* **123**, 216601 (2019).
- [19] See Supplemental Material for additional information on reflectivity measurements, calculation of spectral intensity and fitting analysis.
- [20] S. J. Moon, H. Jin, K. W. Kim, W. S. Choi, Y. S. Lee, J. Yu, G. Cao, A. Sumi, H. Funakubo, C. Bernhard and T. W. Noh *Phys. Rev. Lett.* **101**, 226402 (2008).
- [21] B. Xu *et al.*, *Phys. Rev. B* **93**, 121110(R) (2016).
- [22] A. Akrap *et al.*, *Phys. Rev. Lett.* **117**, 136401 (2016).
- [23] S. P. Mukherjee and J. P. Carbotte *Phys. Rev. B* **95**, 214203 (2017).
- [24] P. Hosur, S. A. Parameswaran and A. Vishwanath *Phys. Rev. Lett.* **108**, 046602 (2012).
- [25] R. E. Throckmorton, J. Hofmann, E. Barnes and S. Das Sarma, *Phys. Rev. B* **92**, 115101 (2015).
- [26] C. J. Tabert, J. P. Carbotte and E. J. Nicol *Phys. Rev. B* **93**, 085426 (2016).
- [27] S. I. Kimura, H. Yokoyama, H. Watanabe, J. Sichelschmidt, V. Suss, M. Schmidt and C. Felser *Phys. Rev. B* **96**, 075119 (2017).
- [28] D. Neubauer, J. P. Carbotte, A. A. Nateprov, A. Lohle, M. Dressel, and A. V. Pronin, *Phys. Rev. B* **93**, 121202(R) (2016).
- [29] N. M. R. Peres, R. M. Ribeiro and A. H. Castro Neto, *Phys. Rev. Lett.* **105**, 055501 (2010).
- [30] J. T. Devreese and A. S. Alexandrov, *Rep. Prog. Phys.* **72** (2009) 066501 (52pp)
- [31] A. S. Mishchenko, N. Nagaosa, N.V. Prokofev, A. Sakamoto and B.V. Svistunov, *Phys. Rev. Lett.* **91**, 236401 (2003).
- [32] C. Verdi, F. Caruso and F. Giustino, *Nature Commun.* **8**, 15769 (2017).
- [33] A. S. Mishchenko, N. V. Prokofev, A. Sakamoto and B. V. Svistunov, *Phys. Rev. B* **62**, 6317 (2000).
- [34] E. Dagotto, T. Hotta, and A. Moreo, *Phys. Rep.* **344**, 1 (2001).
- [35] Y. Shinozuka and Y. Toyozawa, *J. Phys. Soc. Jpn.* **46**, 505 (1979).
- [36] F. M. Peeters and J. T. Devreese, *Phys. Rev. B* **32**, 3515 (1985).

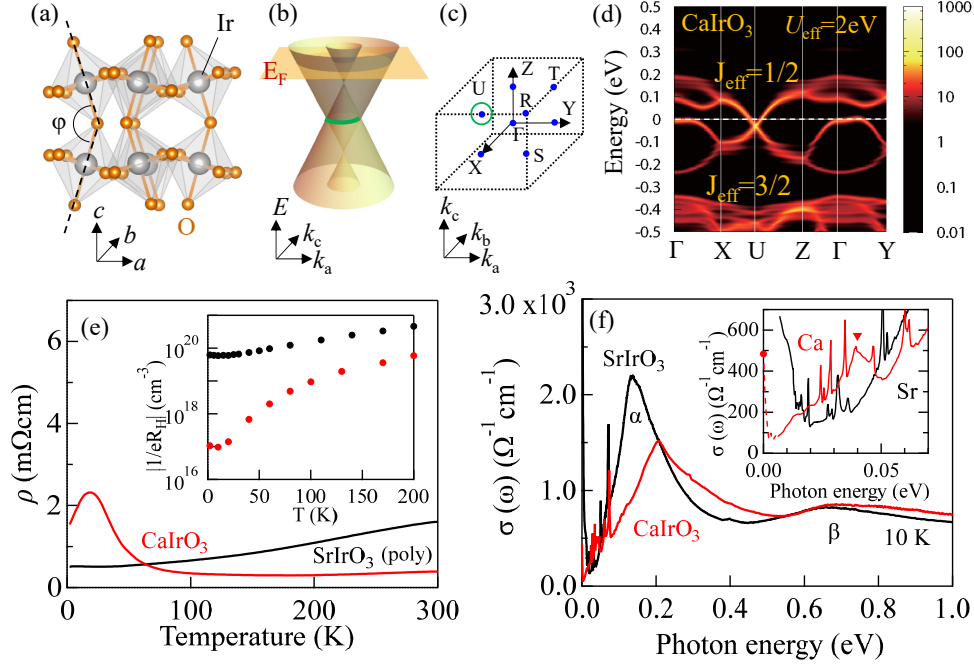


FIG. 1: (a) The crystal structure of CaIrO_3 . Illustration of (b) Dirac band dispersion and (c) location of line node (green line) in the momentum space. The line node is on $k_b=\pi$ -plane. (d) The band structure derived by the theoretical calculation employing the dynamical mean field theory (Ref. [16]). The color code (dahed line) represents the spectral intensity (E_F). (e) Resistivity for single crystalline CaIrO_3 and polycrystalline SrIrO_3 . The inset shows the inverse of Hall coefficient. (f) $\sigma(\omega)$ spectra at 10 K. Inset shows the magnified view of low energy region. The triangle indicates the peak-A. The circle and dashed line denote the DC conctivity and the expected spectra from the Hagen-Rubens extrapolation, respectively.

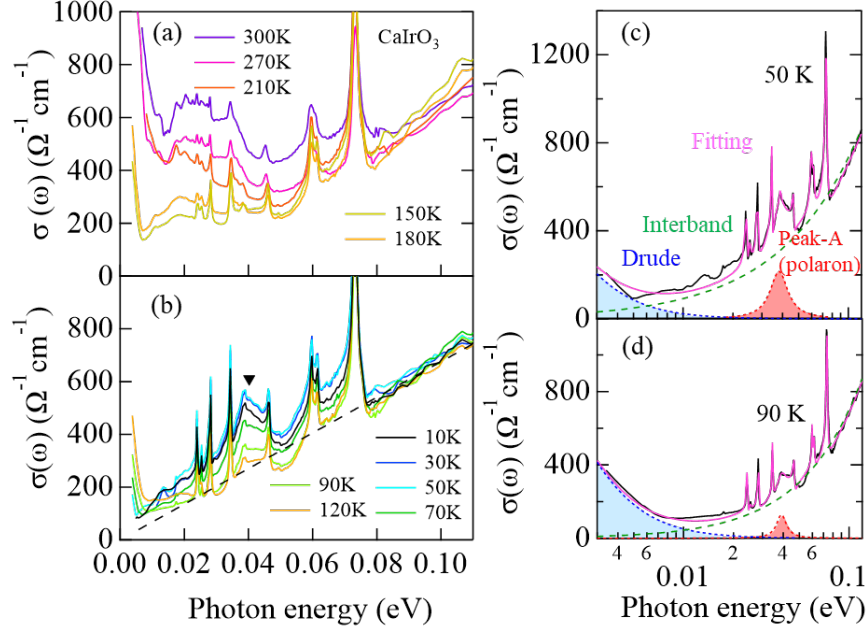


FIG. 2: The optical conductivity spectra (a) above 150 K and (b) below 120 K. The triangle indicates the peak-A. The dashed line denotes the fitting results for interband transition at 10 K (see also the text). The fitting results (c) at 50 K and (d) at 90 K, respectively (magenta lines). The Drude response, interband transition and peak-A (polaron band) are shown by blue, green and red dotted lines.

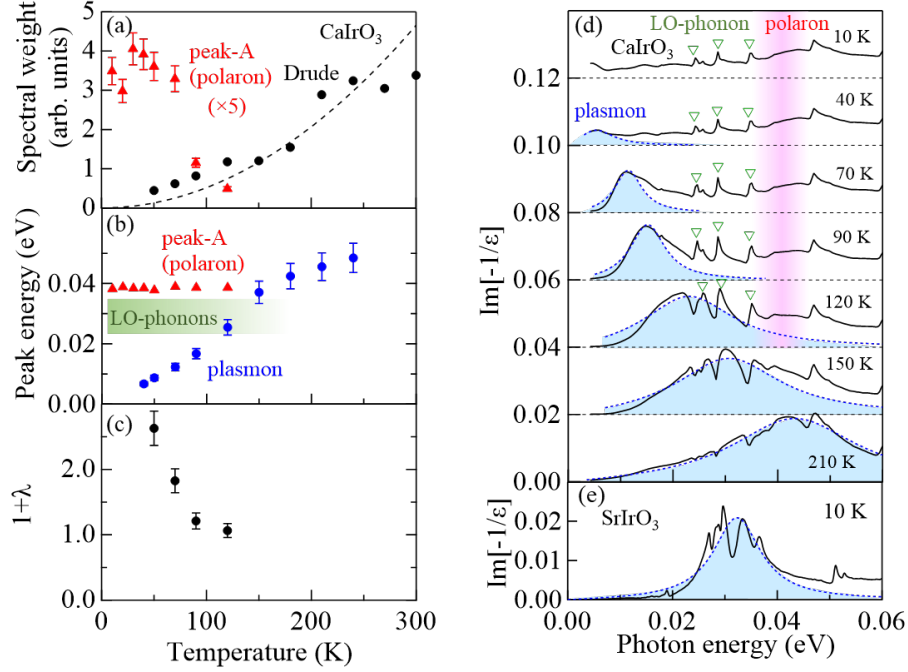


FIG. 3: (a) The spectral weight of peak-A (polaron band) and Drude weight. The dashed line is the fitting result by the model (see text). (b) The temperature dependence of renormalized plasma frequency (ω_p^*) and energy of peak-A (polaron band) (ω_0). The hatched region denotes the energy range of the three LO-phonons [triangles in Fig. 3 (d)]. (c) The mass enhancement factor $1 + \lambda$. (d) The loss function spectra ($\text{Im}[-1/\epsilon(\omega)]$) of CaIrO₃. The spectra are offset for clarity. The dotted lines (open triangles) indicate the plasmon resonance (the LO-phonons). The hatched region denotes the energy range of peak-A (polaron band). (e) $\text{Im}[-1/\epsilon(\omega)]$ spectrum of SrIrO₃ at 10 K.

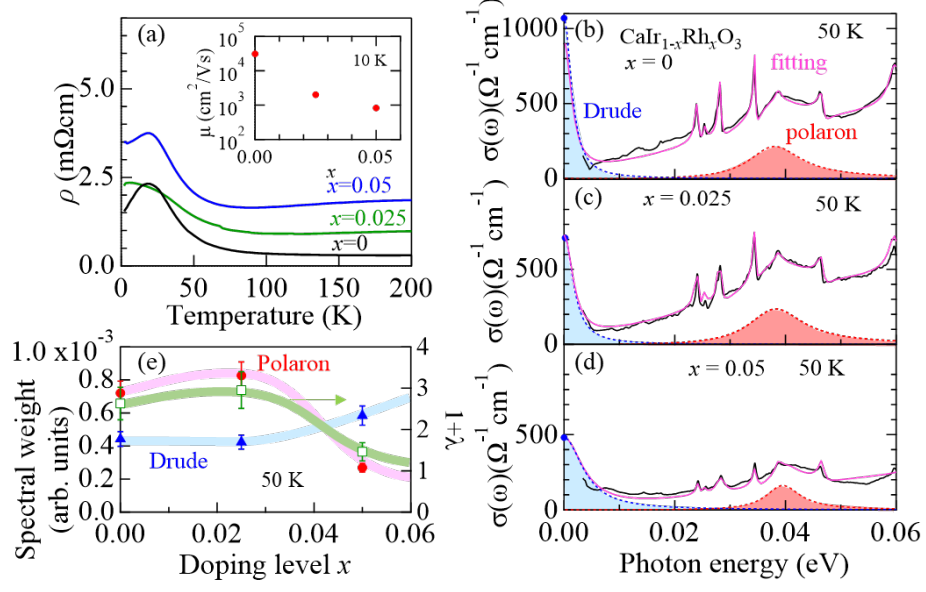


FIG. 4: (a) Temperature dependence of resistivity in $\text{CaIr}_{1-x}\text{Rh}_x\text{O}_3$. The inset shows the electron mobility at 10 K. The $\sigma(\omega)$ -spectra at 50 K for (b) $x=0$ (c) 0.025 and (d) 0.05, respectively. The magenta line denotes the fitting curve with the Drude response (blue dotted line) and polaron band (red dotted line). The closed circle at $\omega = 0$ denotes the dc-conductivity. (e) The Drude weight (blue), spectral weight of polaron band (red) and the mass enhancement factor $1 + \lambda$ (green), all derived at 50 K.