

This is the accepted manuscript made available via CHORUS. The article has been published as:

Lattice-driven chiral charge density wave state in TaS_2

Manoj Singh, Boning Yu, James Huber, Bishnu Sharma, Ghilles Ainouche, Ling Fu, Jasper van Wezel, and Michael C. Boyer

Phys. Rev. B **106**, L081407 — Published 19 August 2022

DOI: [10.1103/PhysRevB.106.L081407](https://doi.org/10.1103/PhysRevB.106.L081407)

Lattice-Driven Chiral Charge Density Wave State in 1T-TaS₂

Manoj Singh,¹ Boning Yu,¹ James Huber,¹ Bishnu Sharma,¹ Ghilles Ainouche,¹ Ling Fu,¹ Jasper van Wezel,² and Michael C. Boyer^{1,*}

¹*Department of Physics, Clark University, Worcester, Massachusetts 01610, USA*

²*Institute for Theoretical Physics Amsterdam, University of Amsterdam, Science Park 904, 1098 XH Amsterdam, The Netherlands*

(Dated: August 4, 2022)

We use scanning tunneling microscopy to study the domain structure of the nearly-commensurate charge density wave (NC-CDW) state of 1T-TaS₂. In our sub-angstrom characterization of the state, we find a continual evolution of the CDW lattice from domain wall to domain center, instead of a fixed CDW arrangement within a domain. Further, we uncover an intradomain chirality characterizing the NC-CDW state. Unlike the orbital-driven chirality previously observed in related transition-metal dichalcogenides, the chiral nature of the NC-CDW state in 1T-TaS₂ appears driven by a strong coupling of the NC-CDW state to the lattice.

The complexity of the physics driven by electron-electron and electron-phonon interactions makes the transition-metal dichalcogenides (TMDs) a fertile playground to study complex orders as well as their coexistence with and evolution to other quantum orders. 1T-TaS₂ has been cited as a "prototypical" TMD compound [1, 2] in which to explore such interplay, though it also hosts some unique physics among the TMDs resulting in intense interest in this particular compound. Initially, the correlated metallic TMD received attention for its four distinct charge density wave (CDW) phases.[3–5] 1T-TaS₂ has also garnered extensive interest for a potential low-temperature Mott insulating state, not found in the other TMDs, coexisting with the low-temperature CDW state [6–10] drawing comparisons to high-temperature superconducting and heavy fermion systems [11].

The proximity of multiple quantum orders in 1T-TaS₂ has led to an interest in tuning these electron-electron and electron-phonon interactions to alter and control the materials electronic and structural properties. Elemental doping has led to the emergence of superconductivity [12, 13] and to the reported evolution of the Mott insulating state to a metallic state [14]. Perturbations induced by electromagnetic fields and strain have led to new stable electronic states.[8, 15–18] The application of pressure has led to the emergence of superconductivity and coexistence of the superconducting state with a CDW state.[19, 20] Altering the thickness of 1T-TaS₂ crystals provides another mechanism by which to control the 1T-TaS₂ phase diagram.[21, 22] The diverse ways in which 1T-TaS₂ can be tuned leads to rich phase diagrams reminiscent of those seen for high-temperature superconducting and heavy fermion systems [23]. Emerging from these studies is a better understanding not only of the fundamental physics hosted by the 1T-TaS₂ but also of the mechanisms by which to appropriately tailor the ma-

terials properties for possible future applications in electronics and data storage. Very recently, the previously-reported achiral 1T-TaS₂ has induced-chiral CDW domains with Ti doping [24], opening additional paths for electronic applications through the possibility of chiral domain switching [25].

Here we focus on our scanning tunneling microscopy (STM) studies of the nearly-commensurate CDW (NC-CDW) state of 1T-TaS₂. Figure 1a shows the crystal structure for the undistorted material. At a temperature of ~ 543 K, the Ta ions in the S-Ta-S layers distort and 1T-TaS₂ transitions from a metallic to an incommensurate CDW (I-CDW) state.[5] At temperatures below ~ 180 K, 1T-TaS₂ enters a commensurate CDW (C-CDW) state. In this CDW state, 12 Ta ions distort toward a central Ta ion in a David star-like pattern.[26] These stars then create a $\sqrt{13}a_0 \times \sqrt{13}a_0$ commensurate pattern across the layer.

Between the I-CDW and C-CDW phases resides the NC-CDW state. The transition from the IC-CDW to the NC-CDW state occurs at ~ 350 K.[29] The NC-CDW state is commonly characterized as having hexagonally ordered C-CDW domains separated by an IC-CDW domain-wall network or by discommensurations.[8, 22, 30, 31] However, as has previously been noted [5], this description may be a simplification of the true NC-CDW domain structure. Lacking is a characterization of the NC-CDW state which details with sub-angstrom resolution the evolution of the CDW state from the domain wall to the domain center. Given that distortions of Ta ions within 1T-TaS₂ are fundamental to driving the observed CDW states and electronic properties of the material, there is an essential need to better-characterize and understand the nanoscale modulations of the NC-CDW state. Further, as we characterize the NC state in 1T-TaS₂, we uncover a previously unreported intradomain CDW chirality.

Figure 1b shows an STM topographic image of the NC-CDW state we acquired at room temperature. The acquired-image shows a roughly hexagonally-ordered do-

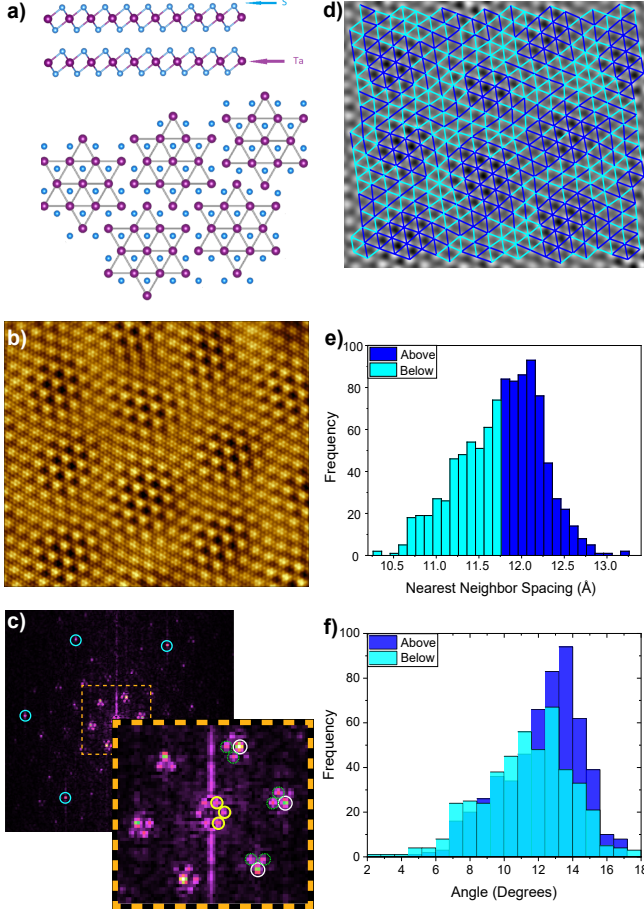


FIG. 1. a) Top: Layered crystal structure for 1T-TaS₂. Bottom: Top view showing Ta-formed David stars. Surface S ions, directly imaged by STM, are superimposed for reference. Crystal structure created using Vesta.[27] b) 230 Å x 200 Å STM topography ($I = 450$ pA and $V_{Bias} = 150$ mV). Image was Fourier filtered to include signals identified in (c). Zoom of single domain in supplemental material.[28] c) Fourier transform of 230 Å x 200 Å topographic image at left. Atomic signals are circled in blue. Large orange dotted square is zoom of central FFT region. Within this central region are low wavevector peaks (yellow) and average CDW peaks (white) around which there are satellite peaks (dotted green). d) Connections between NN CDW maxima superimposed on Fourier filtered topographic image (now grayscale). Filtered image shows only locations of CDW maxima. Average NN distance is 11.76 Å. Blue (cyan) connections show NN separations above (below) 11.76 Å threshold. e) Histogram of NN distances with 0.1 Å bin size, reflecting image resolution. f) Angles of NN connectors relative to atomic lattice. Blue (cyan) show angular distributions for connectors above (below) 11.76 Å threshold.

main pattern characteristic of the NC state. The fast Fourier transform (FFT) of the image (Figure 1c) evinces essential peaks from which we extract average quantities characterizing the NC-CDW state. We find the CDW superlattice to have an average periodicity of 11.76 Å

at an average angle of 11.8° relative to the atomic lattice, in agreement with previous STM, x-ray, and electron diffraction measurements.[3, 5, 26] Using the position of satellite peaks relative to the CDW peaks allows us to determine the average domain periodicity of 73 Å, also in agreement.[5, 32]

To fully understand the NC-CDW state requires going beyond average quantities. To do this, we focus only on the CDW superlattice and Fourier filter our topographic image such that only the central CDW and surrounding satellite peaks are included (Figure 1d). We next calculate nearest neighbor (NN) distances between CDW maxima so as to understand the distribution of distances. We find a large range of NN distances spanning 10.26 Å to 13.22 Å. Superimposed on the image in Figure 1d are line segments connecting the CDW maxima which are color coded according to the 11.76 Å threshold with segments colored dark blue (cyan) being greater (smaller) than the threshold. Generally, the CDW maxima have a greater spacing within the domain than in the domain walls.

In the NC-CDW state, the CDW lattice is rotated relative to the atomic lattice. This is seen in Figure 1c where the CDW peaks are rotated by 11.8° relative to the atomic peaks in the FFT, in agreement with angles as measured by electron-diffraction [20] and STM measurements [3] acquired at this temperature. Using the NN distance threshold of 11.76 Å, we create histograms for the local CDW lattice rotation relative to the atomic lattice for NNs above and below the threshold as seen in Figures 1e and 1f. While the average relative angle for NN above the distance threshold (those generally within a domain) of 12.1° is greater than the average for those below (those generally within the domain wall) of 11.3°, there is a wide range of angles within each grouping.

To obtain a better idea of the evolution of the CDW spacing and angles from domain wall to domain center, we employ a local masking technique. For a given domain, we identify all CDW maxima with an intensity which is within 95% of the maximum CDW intensity as the domain center. We then calculate the NN distances among each of these CDW peaks thereby quantifying NN distances at the center of the domain (Figure 2a blue). We next include the NN CDW peaks to the domain center CDW peaks and recalculate NN distances omitting the NN domain center values (Figure 2a red). We then include the next nearest neighbor (NNN) peaks (Figure 2a green). Finally, we include all remaining CDW peaks (Figure 2a cyan) allowing us to determine the evolution of the NN distances progressing from domain walls to domain centers (Figure 2b). Obvious from the histograms are: 1) an increase in NN spacing and 2) a narrowing of the distribution width as one moves from the domain walls toward the domain center. These two apparent progressions are confirmed with the evolution of the mean and standard deviation of 11.54±0.52 Å (cyan) to 11.75±0.49 Å (green) to 12.06±0.27 Å (red)

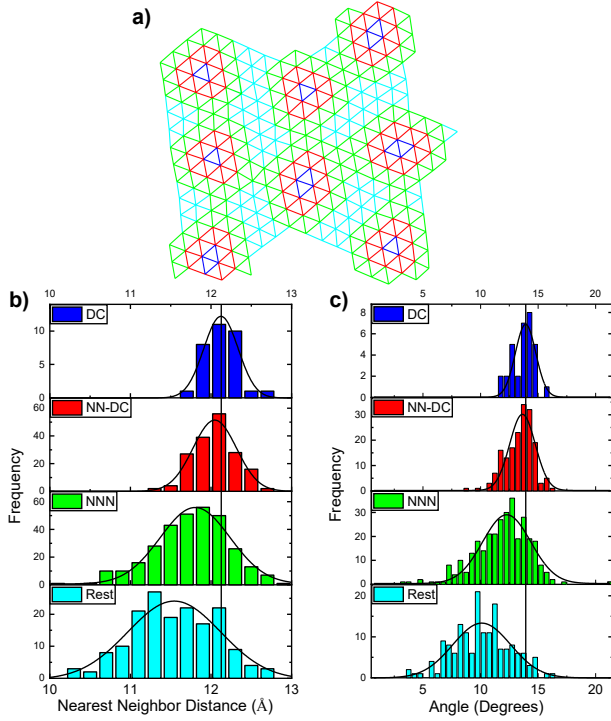


FIG. 2. a) Domain center (blue) found using local intensity thresholding. NN-DC (red) nearest neighbor CDW connectors towards domain center (excludes blue connectors). NNN (green) next nearest neighbor connectors towards domain center (excludes blue and red). Rest (cyan) remaining connectors (excludes blue, red, green). Domains with centers near the edge of the topography are ignored. b) Histograms of NN distances for each connector grouping with $0.2 \text{ \AA}$ bin size. c) Histograms of CDW angles relative to atomic lattice for each connector grouping. Gaussian fits and vertical line at DC peak are superimposed in b) and c) to illustrate evolution of peak location and width.

to $12.14 \pm 0.20 \text{ \AA}$ (blue). We note that the NN spacing in our measurements directly at the domain center is slightly larger than the fixed NN CDW spacing of the low-temperature C-CDW state. Using the same groupings, we determine the local CDW lattice angle relative to the atomic lattice. There is a similar evolution in the mean and distribution width of the CDW angle toward the low-temperature commensurate value of 13.9° as one progresses from the domain walls to the domain centers (Figure 2c): $10.1^\circ \pm 2.5^\circ$ (cyan) to $11.9^\circ \pm 2.4^\circ$ (green) to $13.4^\circ \pm 1.2^\circ$ (red) to $13.7^\circ \pm 0.9^\circ$ (blue).

Underlying crystal disorder and defects within a sample can obscure fundamental/overarching characteristics within a material. To obtain a clearer progression of the NN distances from the domain walls to the domain center, we used the wavevectors extracted from the FFT (Figure 1c) to simulate our topographic image (Figure 3a). Our simulated topography well-matches our topographic image in Figure 1b. Using intensity thresholding we calculate NN distances and angles starting at the

domain centers and progressing toward the domain walls (Figure 3b). The histograms appearing in Figures 3c and 3d illustrate the range of values and confirm the progression found in the data: the average NN CDW spacing and angle continually increase from domain wall to domain center, and the width of the distributions narrows only approaching values found for the low-temperature C-CDW state near the center of a domain.

Having elucidated the spacing and local angle of the CDW evolution from domain wall to domain center, we study the connection satellite peaks (Figure 1c) have to the domain structure observed in topographic images. Fourier filtering of the STM-acquired topographic image (Figure 1b) where only the central CDW peaks in the

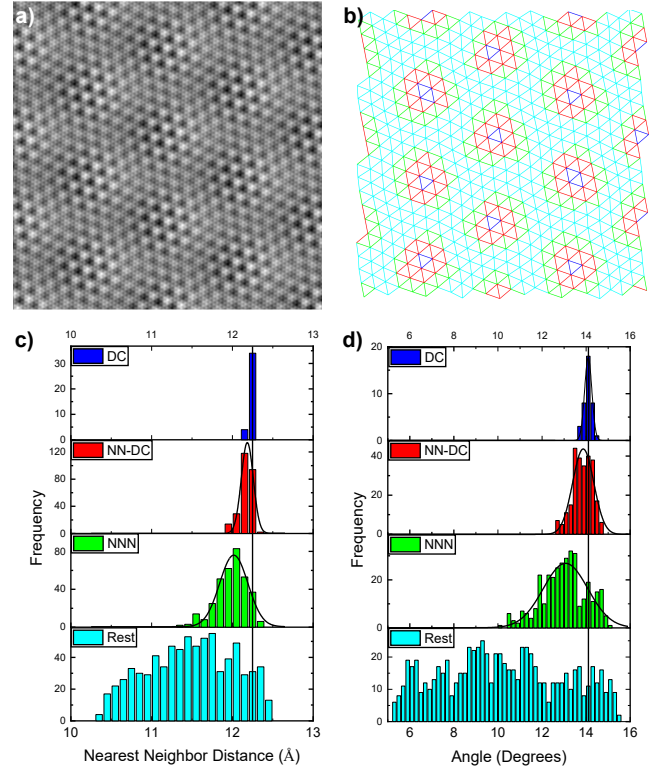


FIG. 3. a) $253 \text{ \AA} \times 253 \text{ \AA}$ computer-simulated STM topography. Average intensity and wavevectors for atomic, CDW, satellite, and low-wavevector peaks from Figure 1c were used to create image (supplemental materials [33]). b) From intensity thresholding: Domain center (blue). NN-DC (red) nearest neighbor CDW connectors towards domain center (excludes blue connectors). NNN (green) next nearest neighbor connectors towards domain center (excludes blue and red). Rest (cyan) remaining connectors (excludes blue, red, green). c) Histograms of NN distances for each connector grouping. Statistics: $11.48 \pm 0.53 \text{ \AA}$ (cyan) to $11.98 \pm 0.19 \text{ \AA}$ (green) to $12.16 \pm 0.08 \text{ \AA}$ (red) to $12.23 \pm 0.03 \text{ \AA}$ (blue) d) Histograms of CDW angles relative to atomic lattice for each connector grouping. Statistics: $10.2^\circ \pm 2.7^\circ$ (cyan) to $13.0^\circ \pm 1.0^\circ$ (green) to $13.8^\circ \pm 0.5^\circ$ (red) to $14.1^\circ \pm 0.2^\circ$ (blue). Gaussian fits and vertical line at DC peak are superimposed in c) and d) to illustrate evolution of peak location and width.

FFT are included (white circles in Figure 1c) produces a topography with a regular hexagonal CDW lattice with NN CDW spacing (and angle relative to the lattice) equal to the average CDW periodicity (and angle) for the material, and which is purely incommensurate with the atomic lattice. We will call this lattice CDW_{ave} . Including the satellite peaks (in addition to the central CDW peak when Fourier filtering the STM-acquired image) leads to the full NC-CDW lattice with domain structure as seen in Figure 1d. We will call this lattice CDW_{ltc} . We now compare the two images. Figure 4a shows the locations for CDW maxima for 1) CDW_{ave} (black dots) and 2) CDW_{ltc} (blue dots). Arrows superimposed on this image point from CDW_{ave} maxima to the nearest CDW_{ltc} maxima locations, with the length of the arrow proportional to the shift distance.

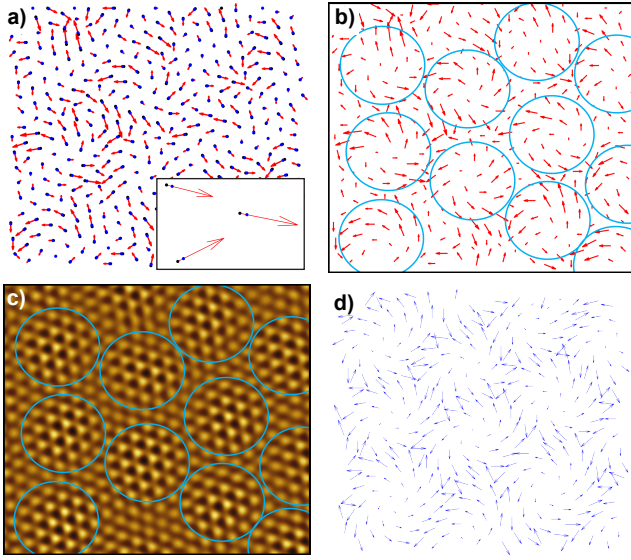


FIG. 4. a) Arrows point from CDW_{ave} maxima to nearest CDW_{ltc} maxima. Arrow length is proportional to displacement. Inset shows zoom and illustrates arrows pointing from CDW_{ave} maximum (black) to CDW_{ltc} maximum (blue). b) Blue circles are superimposed on arrows from a) as a guide to the eye to show the vortex-like chiral displacement patterns. c) The same blue circles are superimposed on CDW_{ltc} topography and match domain locations. d) Arrows are drawn from the CDW_{ave} maximum location to the nearest imaged sulfur ion. An identical, though translated, pattern is produced if arrows are drawn from CDW_{ave} maxima locations to the nearest Ta ions (supplemental material [34]). We chose the sulfur ion for this figure since we image those ions directly and obtain the same information. Note, while the Lawler-Fujita algorithm has proven useful in extracting picometer-scale drift and lattice strain fields,[35, 36] it is not suitable for use in extracting the local displacement fields shown in this figure (supplemental material [37]).

The shift of the CDW_{ltc} maxima locations relative to the CDW_{ave} locations varies spatially in a way that mimics the domain pattern of the NC-CDW state. Further,

the shift arrows can be used to easily identify the locations and extent of individual domains. Within a domain, each shift arrow has a continual evolution in direction (counterclockwise rotation) and size (the shift is smallest at the domain center and largest at the domain edge). In short, we uncover a previously unreported intradomain chirality to the NC-CDW state. At the domain wall, there is a sudden shift in this evolution with shift arrows from neighboring domains sometimes pointing in direct opposition to one another. This shift is indicative of the CDW discommensuration between domains. Using the shift arrows as reference, we overlay blue circles as a general guide to the eye to illustrate the domain locations, rough size, and arrangement (Figure 4b). The same circles are superimposed on the CDW_{ltc} filtered image (Figure 4c) verifying the ability to use the shift arrows to appropriately identify domain locations. Quantifying the CDW_{ltc} shift from the CDW_{ave} , we find an average displacement of 0.72 Å with a maximum displacement of 1.70 Å. This maximum displacement is significant and represents a displacement of $\sim 14\%$ of the CDW_{ave} lattice spacing. Simulating CDW_{ave} and CDW_{ltc} confirms and provides even clearer evidence of this chirality (supplemental material [38]).

The observed shifts highlight an intrinsic chirality to the NC-CDW state: there is a counter-clockwise vortex-like displacement of the CDW_{ltc} maxima relative to the CDW_{ave} locations. The signature of this intradomain chirality is embedded in the satellite peaks in the FFT of the topographic image (supplemental material [39]). While Figure 1c show multiple satellite peaks around several of the CDW peaks in the FFT, each CDW peak (white circles) has two associated high-intensity satellite peaks (green dotted circles). These two intense satellite peaks rotate clockwise around the CDW peaks as one progresses clockwise around the FFT center. FFTs of our topographic images of the NC-CDW state indeed commonly show two intense satellite peaks which rotate around an average CDW peak and is also commonly seen in other published STM studies of the NC-CDW state of 1T-TaS₂. [5, 17]

Finally, we explore the origin of the chiral nature of the CDW state. A chiral CDW state has been observed in 1T-TiSe₂ [40] and recently in the low-temperature state of Ti-doped 1T-TaS₂ [24]. The chiral nature these states originates from the orbital structure.[24, 41–43] The chirality is detected in FFTs of STM topographies through CDW peak intensities which increase/decrease clockwise or anticlockwise.[24, 40] We detect no such intensity progression in the CDW peak intensities in our studies of the NC-CDW state of 1T-TaS₂. Rather, in our FFTs we find a clockwise rotation of two intense satellite peaks around the central CDW peaks, connected to the domain formation and chiral CDW lattice distortions from the average CDW lattice. Figure 4d shows arrows pointing from CDW_{ave} maxima to the nearest imaged atom

evincing a very similar chiral pattern to Figure 4a. In each, shifts are in the counterclockwise direction leading to clear domain formation. In short, Figure 4d shows the CDW displacements in the limit of a perfectly incommensurate CDW lattice which has very strong homogenous coupling to the atomic lattice with no energy cost for CDW deformations. This strongly suggests that the chiral domains formed in the NC-CDW state of 1T-TaS₂ are driven through a strong coupling of the CDW state to the atomic lattice, not through orbital ordering which is believed to drive chiral CDW orders in related TMDs. We can understand the origin of the strong coupling of the CDW to the lattice in the NC-CDW state of 1T-TaS₂ in the following way. Within a David star, there are 13 5d-electrons, one from each Ta ion, 12 of which are bonded leaving a single extra electron per star.[44] The strong coupling of the CDW state to the lattice likely originates from the Coulomb interaction of these extra electrons with the Ta lattice; these extra electrons preferentially locate near Ta ions.

Previous chiral CDW orders found in the TMDs have been attributed to orbital ordering. In the NC-CDW state of the TMD 1T-TaS₂ we find, instead, a CDW state with chiral domains which appears to originate from a strong coupling of an incommensurate CDW to the lattice. Further, our work suggests a competition between lattice coupling, producing the chiral domains within the NC-CDW state, and the energy gained from the electronic structure, in which a particular Q-vector is favored leading to the commensurate C-CDW state at low temperatures. A natural way to theoretically model and explore this interplay would be to explicitly include CDW-lattice coupling in existing McMillian-type Landau free energy frameworks.[3, 45–47] Such domain chirality may be a more-general phenomena which can be explored in systems hosting incommensurate CDW states, including in TMDs.

Methods

STM measurements were conducted at room temperature and ultra-high vacuum ($\sim 10^{-9}$ Torr) using an RHK PanScan STM. The chemically-etched tungsten tip was annealed and then sharpened using electron bombardment in-situ. High-quality single crystals of 1T-TaS₂ studied in this were purchased from HQ Graphene. Samples were cleaved in UHV.

Acknowledgements

This work was supported by the National Science Foundation under Grant No. DMR-1904918.

* To whom correspondence should be addressed. mboyer@clarku.edu

- [1] D. Kuhn, M. Muller, F. Sorgenfrei, E. Giangrisostomi, R. M. Jay, R. Ovsyannikov, N. Martensson, D. Sanchez-Portal, and A. Fohlich, Directional sub-femtosecond charge transfer dynamics and the dimensionality of 1T-TaS₂, *Scientific Reports* **9**, 488 (2019).
- [2] T. Ritschel, H. Berger, and J. Geck, Stacking-driven gap formation in layered 1T-TaS₂, *Phys. Rev. B* **98**, 195134 (2018).
- [3] K. Nakanishi, H. Takatera, Y. Yamada, and H. Shiba, The nearly commensurate phase and effect of harmonics on the successive phase transition in 1T-TaS₂, *Journal of the Physical Society of Japan* **43**, 1509 (1977).
- [4] S. Tanda, T. Sambongi, T. Tani, and S. Tanaka, X-ray study of charge density wave structure in 1T-TaS₂, *Journal of the Physical Society of Japan* **53**, 476 (1984).
- [5] R. E. Thomson, B. Burk, A. Zettl, and J. Clarke, Scanning tunneling microscopy of the charge-density-wave structure in 1T-TaS₂, *Physical Review B* **49**, 16899 (1994).
- [6] K. T. Law and P. A. Lee, 1T-TaS₂ as a quantum spin liquid, *Proceedings of the National Academy of Sciences* **114**, 6996 (2017).
- [7] D. Cho, S. Cheon, K.-S. Kim, S.-H. Lee, Y.-H. Cho, S.-W. Cheong, and H. W. Yeom, Nanoscale manipulation of the Mott insulating state coupled to charge order in 1T-TaS₂, *Nature Communications* **7**, 10453 (2016).
- [8] L. Ma, C. Ye, Y. Yu, X. F. Lu, X. Niu, S. Kim, D. Feng, D. Tomnek, Y.-W. Son, X. H. Chen, and Y. Zhang, A metallic mosaic phase and the origin of Mott-insulating state in 1T-TaS₂, *Nature Communications* **7**, 10956 (2016).
- [9] L. Perfetti, P. A. Loukakos, M. Lisowski, U. Bovensiepen, H. Berger, S. Biermann, P. S. Cornaglia, A. Georges, and M. Wolf, Time evolution of the electronic structure of 1T-TaS₂ through the insulator-metal transition, *Physical Review Letters* **97**, 067402 (2006).
- [10] C. J. Butler, M. Yoshida, T. Hanaguri, and Y. Iwasa, Mottness versus unit-cell doubling as the driver of the insulating state in 1T-TaS₂, *Nature Communications* **11**, 2477 (2020).
- [11] T.-R. T. Han, F. Zhou, C. D. Malliakas, P. M. Duxbury, S. D. Mahanti, M. G. Kanatzidis, and C.-Y. Ruan, Exploration of metastability and hidden phases in correlated electron crystals visualized by femtosecond optical doping and electron crystallography, *Science Advances* **1**, e1400173 (2015).
- [12] Y. Liu, R. Ang, W. J. Lu, W. H. Song, L. J. Li, and Y. P. Sun, Superconductivity induced by Se-doping in layered charge-density-wave system 1T-TaS_{2-x}Se_x, *Applied Physics Letters* **102**, 192602 (2013).
- [13] L. J. Li, W. J. Lu, X. D. Zhu, L. S. Ling, Z. Qu, and Y. P. Sun, Fe-doping-induced superconductivity in the charge-density-wave system 1T-TaS₂, *EPL (Europhysics Letters)* **97**, 67005 (2012).
- [14] S. Qiao, X. Li, N. Wang, W. Ruan, C. Ye, P. Cai, Z. Hao, H. Yao, X. Chen, J. Wu, Y. Wang, and Z. Liu, Mottness collapse in 1T-TaS_{2-x}Se_x transition-

- metal dichalcogenide: An interplay between localized and itinerant orbitals, *Physical Review X* **7**, 041054 (2017).
- [15] L. Stojchevska, I. Vaskivskiy, T. Mertelj, P. Kusar, D. Svetin, S. Brazovskii, and D. Mihailovic, Ultrafast switching to a stable hidden quantum state in an electronic crystal, *Science* **344**, 177 (2014).
 - [16] I. Vaskivskiy, J. Gospodaric, S. Brazovskii, D. Svetin, P. Sutar, E. Goreshnik, I. A. Mihailovic, T. Mertelj, and D. Mihailovic, Controlling the metal-to-insulator relaxation of the metastable hidden quantum state in 1T-TaS₂, *Science Advances* **1**, e1500168 (2015).
 - [17] Y. A. Gerasimenko, P. Karpov, I. Vaskivskiy, S. Brazovskii, and D. Mihailovic, Intertwined chiral charge orders and topological stabilization of the light-induced state of a prototypical transition metal dichalcogenide, *npj Quantum Materials* **4**, 32 (2019).
 - [18] K. Bu, W. Zhang, Y. Fei, Z. Wu, Y. Zheng, J. Gao, X. Luo, Y.-P. Sun, and Y. Yin, Possible strain induced mott gap collapse in 1T-TaS₂, *Communications Physics* **2**, 146 (2019).
 - [19] T. Ritschel, J. Trinckauf, G. Garbarino, M. Hanfland, M. v. Zimmermann, H. Berger, B. Buchner, and J. Geck, Pressure dependence of the charge density wave in 1T-TaS₂ and its relation to superconductivity, *Physical Review B* **87**, 125135 (2013).
 - [20] B. Sipos, A. F. Kusmartseva, A. Akrap, H. Berger, L. Forr, and E. Tutis, From mott state to superconductivity in 1T-TaS₂, *Nature Materials* **7**, 960 (2008).
 - [21] M. Yoshida, Y. Zhang, J. Ye, R. Suzuki, Y. Imai, S. Kimura, A. Fujiwara, and Y. Iwasa, Controlling charge-density-wave states in nano-thick crystals of 1T-TaS₂, *Scientific Reports* **4**, 7302 (2014).
 - [22] M. Yoshida, R. Suzuki, Y. Zhang, M. Nakano, and Y. Iwasa, Memristive phase switching in two-dimensional 1T-TaS₂ crystals, *Science Advances* **1**, e1500606 (2015).
 - [23] M. R. Norman, The challenge of unconventional superconductivity, *Science* **332**, 196 (2011).
 - [24] J. J. Gao, W. H. Zhang, J. G. Si, X. Luo, J. Yan, Z. Z. Jiang, W. Wang, H. Y. Lv, P. Tong, W. H. Song, X. B. Zhu, W. J. Lu, Y. Yin, and Y. P. Sun, Chiral charge density waves induced by Ti-doping in 1T-TaS₂, *Applied Physics Letters* **118**, 213105 (2021).
 - [25] X. Song, L. Liu, Y. Chen, H. Yang, Z. Huang, B. Hou, Y. Hou, X. Han, H. Yang, Q. Zhang, T. Zhang, J. Zhou, Y. Huang, Y. Zhang, H.-J. Gao, and Y. Wang, Atomic-scale visualization of chiral charge density wave superlattices and their reversible switching, *Nature Communications* **13**, 1843 (2022).
 - [26] T. Ishiguro and H. Sato, Electron microscopy of phase transformations in 1T-TaS₂, *Physical Review B* **44**, 2046 (1991).
 - [27] K. Momma and F. Izumi, Vesta.3 for three-dimensional visualization of crystal, volumetric and morphology data, *Journal of Applied Crystallography* **44**, 1272 (2011).
 - [28] See Supplemental Material at URL for a topographic image of a single domain.
 - [29] C. B. Scruby, P. M. Williams, and G. S. Parry, The role of charge density waves in structural transformations of 1T TaS₂, *The Philosophical Magazine: A Journal of Theoretical Experimental and Applied Physics* **31**, 255 (1975).
 - [30] D. F. Shao, R. C. Xiao, W. J. Lu, H. Y. Lv, J. Y. Li, X. B. Zhu, and Y. P. Sun, Manipulating charge density waves in 1T-TaS₂ by charge-carrier doping: A first-principles investigation, *Physical Review B* **94**, 125126 (2016).
 - [31] W. Wang, D. Dietzel, and A. Schirmeisen, Lattice discontinuities of 1T-TaS₂ across first order charge density wave phase transitions, *Scientific Reports* **9**, 7066 (2019).
 - [32] A. W. Tsen, R. Hovden, D. Wang, Y. D. Kim, J. Okamoto, K. A. Spoth, Y. Liu, W. Lu, Y. Sun, J. C. Hone, L. F. Kourkoutis, P. Kim, and A. N. Pasupathy, Structure and control of charge density waves in two-dimensional 1T-TaS₂, *Proceedings of the National Academy of Sciences* **112**, 15054 (2015).
 - [33] See Supplemental Material at URL for details on simulating the NC-CDW 1T-TaS₂ topography.
 - [34] See Supplemental Material at URL for figures showing arrows drawn from CDW_{ave} to nearest Ta ions.
 - [35] M. Lawler, K. Fujita, J. Lee, A. Schmidt, Y. Kohsaka, C. K. Kim, H. Eisaki, S. Uchida, J. Davis, J. Sethna, *et al.*, Intra-unit-cell electronic nematicity of the high-*tc* copper-oxide pseudogap states, *Nature* **466**, 347 (2010).
 - [36] S. Gao, F. Flicker, R. Sankar, H. Zhao, Z. Ren, B. Rachmilowitz, S. Balachandrar, F. Chou, K. S. Burch, Z. Wang, J. van Wezel, and I. Zeljkovic, Atomic-scale strain manipulation of a charge density wave, *Proceedings of the National Academy of Sciences* **115**, 6986 (2018).
 - [37] See Supplemental Material at URL for further discussion on extracting the displacement field.
 - [38] See Supplemental Material at URL for analysis of the simulated topography evincing the same intradomain chiral nature of the NC-CDW state found from the data.
 - [39] See Supplemental Material at URL for additional details on the link between satellite peaks and domain chirality.
 - [40] J. Ishioka, Y. H. Liu, K. Shimatake, T. Kurosawa, K. Ichimura, Y. Toda, M. Oda, and S. Tanda, Chiral charge-density waves, *Physical Review Letters* **105**, 176401 (2010).
 - [41] A. Klosinski, A. M. Oles, C. Efthimia Agrapdis, J. van Wezel, and K. Wohlfeld, Chalcogenic orbital density waves in the weak- and strong-coupling limit, *Physical Review B* **103**, 235123 (2021).
 - [42] J. van Wezel, Chirality and orbital order in charge density waves, *EPL (Europhysics Letters)* **96**, 67011 (2011).
 - [43] Y. Peng, X. Guo, Q. Xiao, Q. Li, J. Stremper, Y. Choi, D. Yan, H. Luo, Y. Huang, S. Jia, O. Janson, P. Abbamonte, M. van den Brink, and J. van Wezel, Observation of orbital order in the van der waals material 1T-TiSe₂, arXiv:2105.13195 (2021).
 - [44] M. Kratochvilova, A. D. Hillier, A. R. Wildes, L. Wang, S.-W. Cheong, and J.-G. Park, The low-temperature highly correlated quantum phase in the charge-density-wave 1T-TaS₂ compound, *npj Quantum Materials* **2**, 42 (2017).
 - [45] W. L. McMillan, Landau theory of charge-density waves in transition-metal dichalcogenides, *Phys. Rev. B* **12**, 1187 (1975).
 - [46] W. L. McMillan, Theory of discommensurations and the commensurate-incommensurate charge-density-wave phase transition, *Phys. Rev. B* **14**, 1496 (1976).
 - [47] K. Nakanishi and H. Shiba, Domain-like incommensurate charge-density-wave states and the first-order incommensurate-commensurate transitions in layered tantalum dichalcogenides. I. 1T-polytype, *Journal of the Physical Society of Japan* **43**, 1839 (1977).