



This is the accepted manuscript made available via CHORUS. The article has been published as:

Insulating vortex cores in disordered superconductors

Anushree Datta, Anurag Banerjee, Nandini Trivedi, and Amit Ghosal

Phys. Rev. B **107**, L140502 — Published 11 April 2023

DOI: [10.1103/PhysRevB.107.L140502](https://doi.org/10.1103/PhysRevB.107.L140502)

Insulating vortex cores of disordered superconductors

Anushree Datta*,¹ Anurag Banerjee†,¹ Nandini Trivedi,² and Amit Ghosal¹

¹Indian Institute of Science Education and Research Kolkata, Mohanpur, India-741246

²Department of Physics, The Ohio State University, Columbus, Ohio 43210, USA

We show that while orbital magnetic field and disorder, acting individually weaken superconductivity, acting together they produce an intriguing evolution of a two-dimensional type-II s-wave superconductor. For weak disorder, the critical field H_c at which the superfluid density collapses is coincident with the field at which the superconducting energy gap gets suppressed. However, with increasing disorder these two fields diverge from each other creating a pseudogap region with insulating vortex cores. Our results naturally explain two outstanding puzzles: the gigantic magnetoresistance peak observed as a function of magnetic field in thin disordered superconducting films and the disappearance of the celebrated zero-bias Caroli-de Gennes-Matricon peak in the local density of states at the vortex core of disordered superconductors.

Introduction: – The response of an s-wave superconductor (sSC) individually to disorder and orbital magnetic field has by now been well established [1–4]. In a pristine Bardeen-Cooper-Schrieffer (BCS) superconductor, the two energy scales, the single particle energy gap, E_g measurable by scanning tunneling spectroscopy [5], and the superfluid stiffness, D_s , related to the diamagnetic susceptibility [6], both vanish simultaneously at the critical temperature T_c .

Upon including disorder, extensive research in the last few decades has established that the pairing amplitude of a disordered superconductor (SC) becomes inhomogeneous forming SC-islands on the scale of the coherence length, ξ , separated by an insulating sea [7–10]. Ultimately, the superconductor is driven into an insulating state, not by the collapse of the single particle energy gap [11–14], but rather by the vanishing of the superfluid phase stiffness (See Fig. 1(a)) due to enhanced quantum phase fluctuations [15–17]. Since E_g remains finite while D_s vanishes as a function of disorder, it is argued that the universal properties near the superconductor-insulator transition (SIT) is well described by an effective “bosonic” Hamiltonian [18–20].

Turning next to the effect of an applied magnetic field, H , on a clean BCS superconductor, it is well known that the magnetic field penetrates the SC by generating a periodic array of Abrikosov vortices [21] with a normal metallic core of size ξ with circulating currents around the vortex on the scale of the penetration depth λ . With increasing H , the density of vortices increases and overlap at a critical field strength H_c [22], and beyond that the superconductor transitions into a metal.

How does the superconductor evolve in the combined presence of disorder V and magnetic field H ? Our findings for s-wave superconductors suggest that the paradigm of Abrikosov vortices with metallic cores, which successfully described the behavior of conventional superconductors for more than half a century, must be modified in the presence of disorder, (see

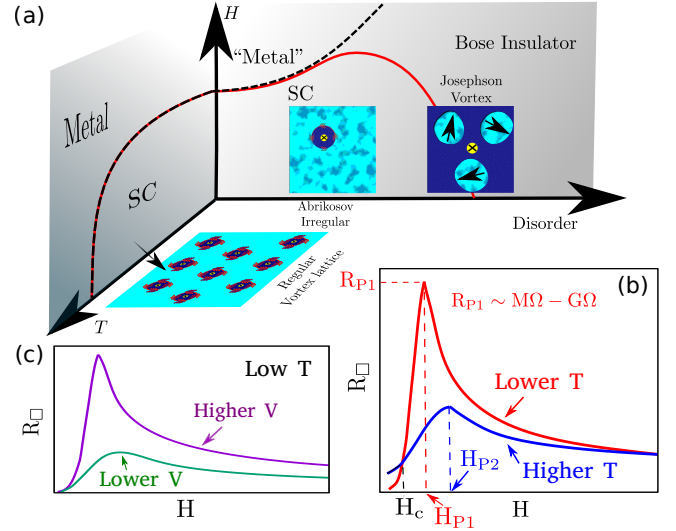


FIG. 1: (a) **Schematic Phase diagram** of a type II superconductor along the magnetic field (H), temperature (T), and disorder (V) axes reveals 3 phases: SC with single particle gap $E_g \neq 0$ and superfluid stiffness $D_s \neq 0$; fermionic metal $E_g = 0$ and $D_s = 0$; and Bose insulator $E_g \neq 0$ and $D_s = 0$. The vortices change character from Abrikosov-type with metallic cores to Josephson-type with insulating cores as V is increases. (b,c) illustrates the experimental puzzles in the magnetoresistance (MR) which rises sharply beyond the SIT at H_c by orders of magnitude [23–31], whose explanations emerge naturally from our phase-diagram.

Fig. 1 and discussions below).

We are also motivated by experimental puzzles [23–28] that show the sheet resistance shooting up by more than 8 orders of magnitude beyond a field-driven SIT. Furthermore, the line-shape of magneto-resistance (MR) $\rho(H)$ is asymmetric [23, 25] with a sharp rise to a peak at H_P followed by a gradual decrease to the normal state resistance [25, 29, 32, 33]. Interestingly, the MR-peak becomes sharper and stronger with increasing disorder in the films [24, 25, 30, 31] (see Fig. 1).

Several theoretical attempts have been made to explain this behavior ranging from Coulomb blockade on the SC-islands [34], to boson-localization [35–37], ‘superinsulator’ and charge-vortex duality [28, 38]. Suggestions have also been made that the high field phase is a finite-temperature in-

*Present Address: Université Paris cité, Laboratoire Matériaux et Phénomènes Quantiques, CNRS, F-75013, Paris, France, Université Paris-Saclay, CNRS, Laboratoire de Physique des Solides, 91405, Orsay, France.

†Present Address: Department of Physics, Ben-Gurion University of the Negev, Beer-Sheva 84105, Israel.

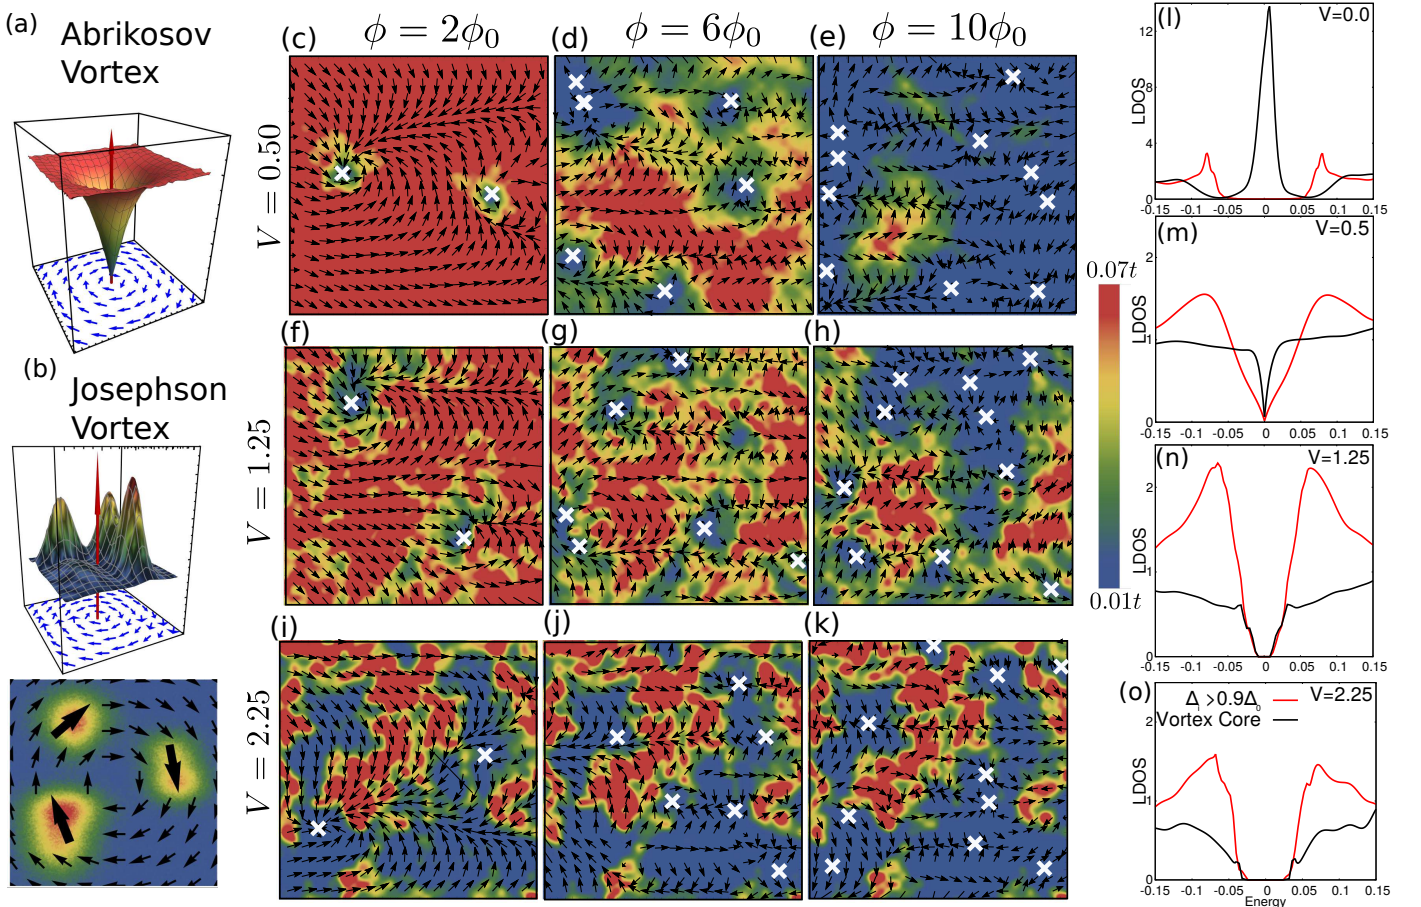


FIG. 2: **Crossover from Abrikosov to Josephson vortices with increasing disorder:** Panel (a): Schematic plot of an Abrikosov vortex showing the suppression of the pairing amplitude and the curling of the phase around the vortex core. Panel (b): Schematic plot of a Josephson vortex centered in the non-SC region surrounded by 3 SC-islands with finite pairing amplitude Δ . Magnetic field shown by red vertical arrows in (a) and (b). The spatial color-density map of the superconducting pairing amplitude (in one unit cell; see SM) with H increasing from left to right along each row for weak $V = 0.5$ (panels (c-e) in the top row), moderate $V = 1.25$ (panels (f-h) in the middle row) and strong $V = 2.25$ (panels (i-k) in the bottom row) disorder strengths. The phase of order parameter is superimposed on the amplitude map by tiny arrows. Panels (l-o): LDOS [47] at vortex core (black) and away from core (red) for weak H , with increasing disorder.

ulator – akin to a many-body localized state [39].

Model and methods: – We consider the disordered attractive Hubbard Hamiltonian in a magnetic field:

$$\mathcal{H} = - \sum_{\langle ij \rangle, \sigma} (t e^{i\phi_{ij}} \hat{c}_{i\sigma}^\dagger \hat{c}_{j\sigma} + \text{h.c.}) - |U| \sum_i \hat{n}_{i\uparrow} \hat{n}_{i\downarrow} + \sum_{i\sigma} (V_i - \mu) \hat{n}_{i\sigma} \quad (1)$$

This model has been used previously to study the BCS-BEC crossover in the clean system [40], the finite temperature pseudogapped state in strong coupling [41, 42], and the disorder-driven SIT [1]. In the study here we include the effects of a magnetic field in addition to disorder. Here, t and $U < 0$ denote the hopping amplitude and on-site Hubbard attraction respectively, $c_{i\sigma}^\dagger$ ($c_{i\sigma}$) creates (annihilates) an electron on site i with spin σ on a 2D square lattice, and $\hat{n}_{i\sigma}$ is the spin-resolved number operator. The magnetic field $\mathbf{H} = \nabla \times \mathbf{A}$ and the vector potential $\mathbf{A}$ is incorporated through the Peierls factor: $\phi_{ij} = \frac{\pi}{\phi_0} \int_i^j \mathbf{A} \cdot d\mathbf{l}$, where $\phi_0 = h/2e$ is the superconducting flux quantum; V is the disorder strength for uni-

formly distributed site energies $V_i \in [-V, V]$. We obtain the distribution of the inhomogeneous complex pairing amplitude $\Delta_i = -|U| \langle c_{i,\downarrow} c_{i,\uparrow} \rangle$ and the local density $n_i = \sum_\sigma \langle \hat{n}_{i\sigma} \rangle$ for a given disorder realization and field using the self-consistent Bogoliubov de-Gennes (BdG) method. From the longitudinal and transverse current-current correlation function we obtain the frequency-dependent conductivity $\sigma(\omega)$ and the superfluid stiffness D_s respectively. Results for disordered cases are averaged over 15-25 disorder configurations (see Supplementary material (SM) [43]).

Evolution from Abrikosov to Josephson vortices: The field induced spatial inhomogeneities in the pairing amplitude and the nature of vortex cores for different disorder strengths in Fig. 2 give insights into (a) the underlying mechanism of the field driven transition of a type-II disordered SC, and (b) the nature of the resulting non-SC state.

We observe the evolution of Abrikosov vortices with a metallic core for low disorder to “core-less” Josephson vor-

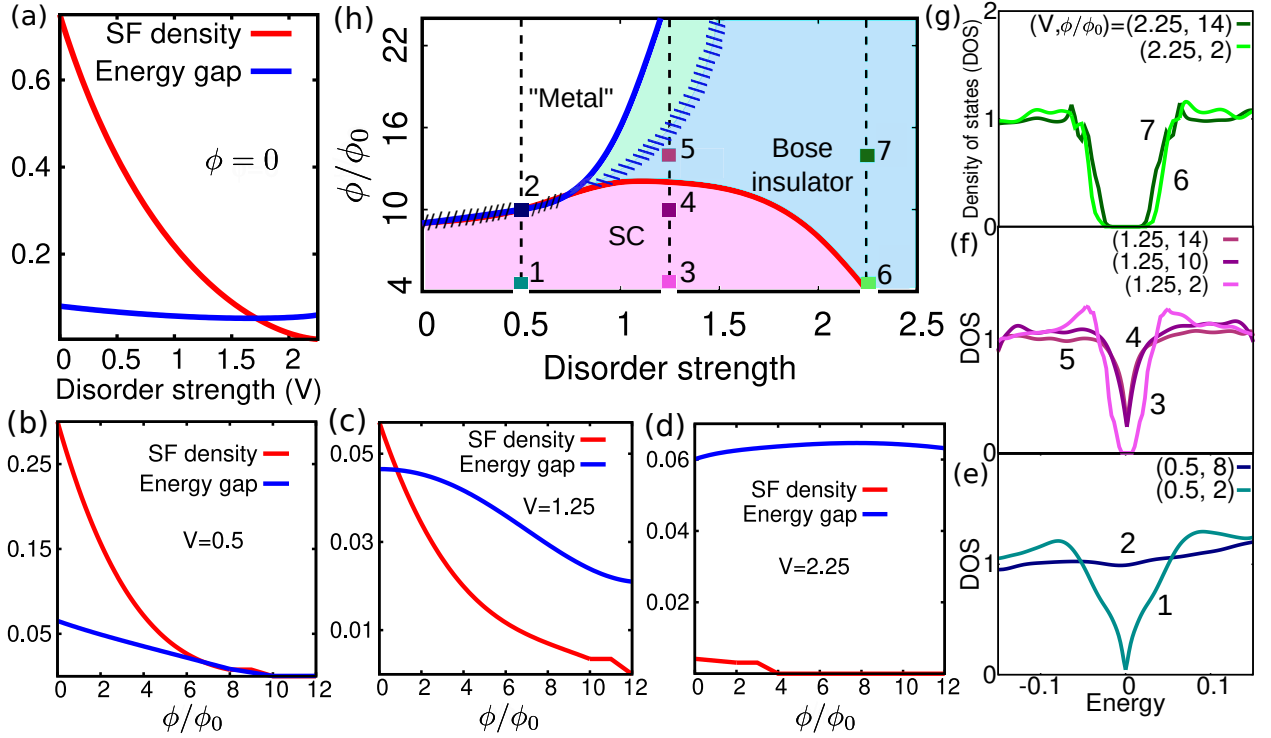


FIG. 3: **Phase diagram of the 2D superconductor in the disorder V - magnetic field H plane.** Panels (a-d): evolution of superfluid stiffness D_s , including harmonic quantum phase fluctuations [53–55] (See SM) and single-particle spectral gap E_g for $H = 0$ vs. disorder V [weak ($V = 0.5$), moderate ($V = 1.25$) and strong ($V = 2.25$)]. Panels (e-g): average DOS, $N(\omega)$ for different H and V . The magnetic field H is in units of ϕ , the number of SC flux quanta penetrating a 36×36 magnetic unit cell. Panel (h): Phase boundaries in the $V - H$ plane – critical fields obtained from vanishing of D_s (red trace) and vanishing of E_g (blue trace). The phase diagram features three distinct regions: (I) SC ($E_g \neq 0$ and $D_s \neq 0$); (II) fermi metal or gapless fermionic Anderson insulator 56) ($E_g = 0$ and $D_s = 0$); and (III) Bose insulator ($D_s = 0$, $E_g \neq 0$). The region III is further divided by a hashed line where the ‘two-particle’ gap in $\sigma(\omega)$ disappears.

tices at higher disorder [48, 49]. With increasing disorder, Fig. 2(f-k) the pairing amplitude $\Delta(\mathbf{r})$ becomes strongly inhomogeneous even in the absence of H and form SC puddles separated from insulating regions. It is now energetically favorable for flux-lines to penetrate the system in regions where Δ is already small, typically coinciding with high disorder regions. These Josephson vortices (Fig. 2(b)) cause the SC phase on the adjacent grains to wind around.

Local Density of states (LDOS): – The clean SC with an Abrikosov vortex shows a peak in the LDOS near zero bias [50], called Caroli-de Gennes-Matignon (CdGM) peak, originating from the low lying quasiparticle bound states formed at the metallic core, see Fig. 2(l) (also in SM [51]). With increasing disorder, the peak in the vortex core is replaced by a suppression of density of states (evolving from a V-shape to a deeper U-shape to a hard gap) with increasing disorder (Figs. 2(m-o)). While for weak disorder the LDOS fills up and evolves into a metallic DOS with increasing H , it remains a hard gap in the Bose insulator.

Energy scales and Phase Diagram: The contrasting behavior of the superfluid stiffness D_s and the spatially-averaged single-particle energy gap-scale E_g as a function of the strength of disorder V is shown in Fig. 3(a). In the absence of

the magnetic field, the superconductor transitions into an insulating state as signaled by the collapse of D_s , though E_g remains finite beyond the SIT [7, 9, 10]. Here we focus on their H -dependence (Figs. 3(b-d)) in different disorder regimes.

For weak disorder ($D_s \gg E_g$), both D_s and E_g decrease with increasing H and vanish linearly at the critical H_c [57], consistent with the expectations from Abrikosov theory for a clean sSC and with experimental observations [58]. For moderate disorder ($D_s \sim E_g$), E_g decreases more gradually with H compared to D_s and the two curves cross at a finite ϕ . For high disorder ($D_s \ll E_g$), E_g barely changes with increasing H , while D_s declines precipitously. The energy gaps are extracted from the average density of states (DOS) $N(\omega)$ (Fig. 3(e-g)) shown for different combinations of V and H (see SM [59]). We notice that the standard BCS-type ‘hard’ gap in $N(\omega)$ for a clean and disordered sSC [7, 9] turns into a soft pseudogap in a finite field H , particularly at weaker V .

In the resulting phase diagram in Fig. 3(h) we identify three phases: the superconductor in which both D_s and E_g are finite, the “metal” [56] in which both of these energy scales vanish, and the Bose insulator in which D_s is zero but E_g remains finite. The familiar Abrikosov scenario: a direct transition from a superconductor to a metal observed in a clean SC [21] with increasing magnetic field, is not found for larger

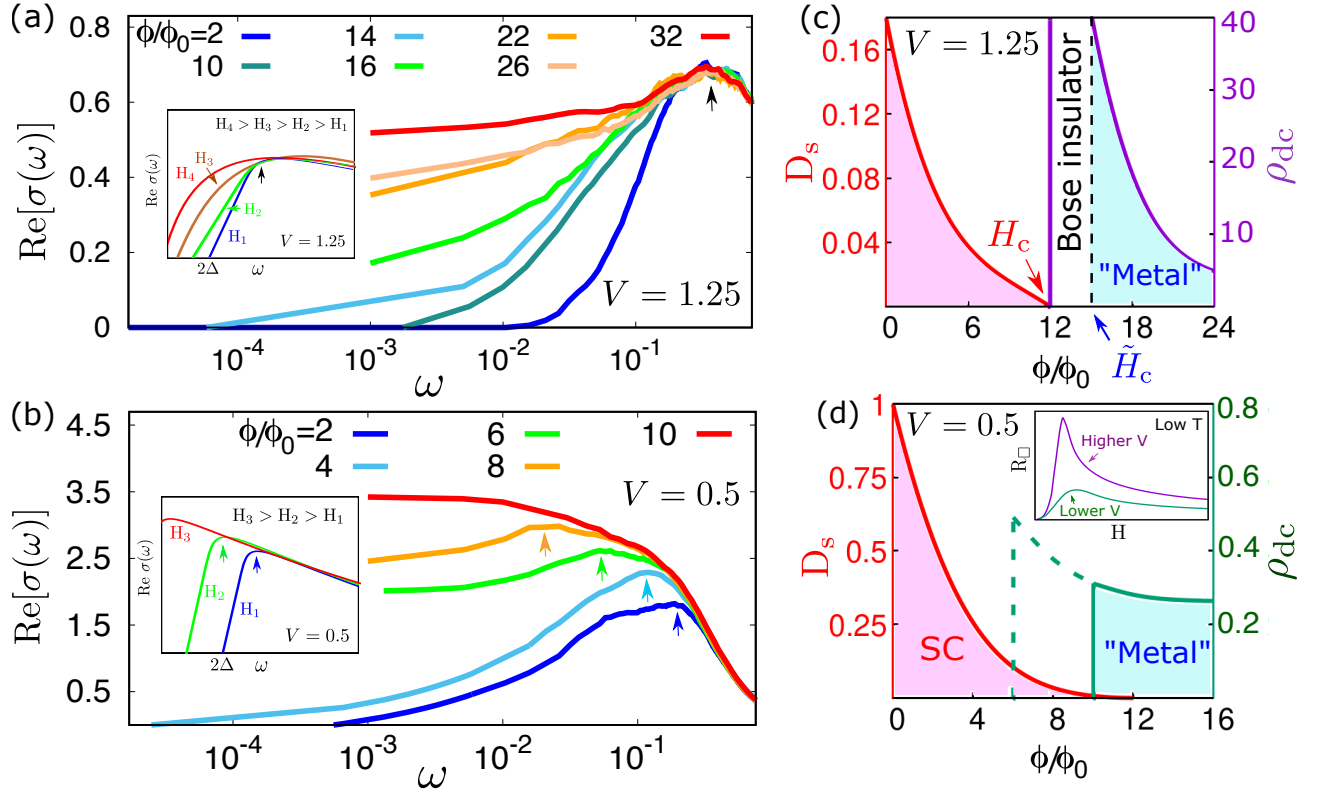


FIG. 4: **Field and disorder-dependence of dynamical conductivity:** $\sigma(\omega)$ for weak (a) and moderate (b) disorder. The contrast in the mechanism of gap filling is highlighted in the insets on a linear scale. Panels (c,d): D_s (red) and sheet resistance ρ_{dc} (blue) for moderate $V = 1.25$ and weak $V = 0.5$ as a function of H . The pseudogapped Bose insulator is absent for weak disorder and results in a finite ρ_{dc} hump in the magnetoresistance. For moderate disorder, superfluidity is depleted beyond $\phi_c \approx 12\phi_0$, and the resistivity ρ_{dc} diverges. The “Metal” region indicates a localized insulating region of electrons with $\sigma_{dc} = 0$ at $T = 0$. At any finite temperature, there will be finite conduction by the variable range hopping mechanism as schematically depicted by the purple curve. The inset of panel (d) represents the schematic experimental observations (Fig. 1(c)) maintaining the same color coding of ρ_{dc} presented in main panels (b,d). Note the tantalizing similarity of our results with experiments.

disorder strengths. Instead an insulating state of Cooper pairs intervenes in which the resistance diverges as the temperature approaches zero. We thus provide a new paradigm for the fate of superconductivity as a function of magnetic field for films with stronger disorder.

Origin of gigantic magnetoresistance: In a clean sSC at $T = 0$ as expected there is no absorption of electromagnetic radiation for $H = 0$ for $\omega \leq 2\Delta_0$, where Δ_0 is the single particle gap, if one ignores the weak absorption by collective modes. Disorder generates states within the gap. For weak disorder, the peak in $\sigma(\omega)$ [61] shifts to lower frequencies with increasing disorder, whereas for larger V there is no such downshift, leading to a qualitatively different gap-filling for weak and strong disorder.

Based on D_s and $\sigma_{dc} = \sigma(\omega \rightarrow 0)$ we identify two qualitatively different transport behavior: For moderate disorder (Fig. 4(a)), D_s decreases with increasing field and vanishes at H_c . However, the gap in $\sigma(\omega)$ closes only for $H > \tilde{H}_c$ where $\tilde{H}_c > H_c$. In the region $\tilde{H}_c < H < H_c$, between these two critical fields the system remains a Bose insulator with $D_s = 0$ and $\sigma_{dc} = 0$.

On the other hand, for weaker disorder (Fig. 4(b)) we find

that D_s remains finite at $\phi \approx 6\phi_0$, whereas σ_{dc} jumps up to a finite value from zero. The dissipative response is thus short-circuited by a finite D_s , ensuring dissipationless (superfluid) transport in the system. Resistive transport with finite σ_{dc} sets in for $H \geq H_c$ only after the collapse of D_s (E_g also vanishes at the same H_c) and leads to only a weak hump in MR.

Our analysis explains the existence of the sharp peak in the MR $\rho_{dc}(H) = 1/\sigma_{dc}(H)$ (Figs. 4(c,d)), its asymmetric shape, and its disorder-dependence, in agreement with experiments [23–25, 30]. In a recent experiment [29] it is claimed that the MR peak position $H_P \rightarrow H_c$ as $T \rightarrow 0$, an observation consistent with our ρ_{dc} in panel Fig. 4(c). Consistent with this picture, we see in Fig. 4(d) that for weakly disordered samples, the energy gap to transport collapses at the same critical field where D_s vanishes.

Conclusion: Upon increasing the magnetic field in a clean superconductor, the metallic cores of Abrikosov vortices overlap and drive the system into a normal fermionic metal. We present a new paradigm for moderately disordered superconductors in which Josephson vortices with insulating cores drive the system into a Bose insulator with a two-particle gap E_σ that is smaller than the one-particle gap E_g . With fur-

ther increase in field we find a “Bose metal”-type phase with zero superfluid stiffness, a vanishing two particle gap $E_\sigma = 0$ but a finite E_g (hashed line in Fig. 3(h)) [62]. Open questions remain about the nature and mechanism of transport by pairs or collective modes in the pseudogap phase. These questions, together with the role of Coulomb repulsion in the observed anomalous metallic region in a gate-tuned transition in a 2D semiconductor-superconductor heterostructures [33, 63], as well as the subtleties of the Bose-metal phase [64–68] will continue to be discussed in future investigations.

Acknowledgment: We thank Pratap Raychaudhuri for valuable discussions. A.D. acknowledges support from her fellowship from University Grants Commission (UGC), India. A.D. and A.G acknowledges support from SPARC grant #460. N.T. acknowledges support from DOE-BES grant DE-FG02-07ER46423 and NSF-DMR grant 2138905. We acknowledge the DIRAC computing facility at IISER Kolkata.

-
- [1] V. Dobrosavljevic, N. Trivedi, and J. M. Valles Jr., *Conductor-Insulator Quantum Phase Transitions* (Oxford University Press, 2012).
 - [2] N. Kopnin, *Vortices in Type-II Superconductors: Structure and Dynamics* (Oxford University Press, 2001).
 - [3] A. A. Abrikosov, Nobel Lecture: Type-II superconductors and the vortex lattice, *Rev. Mod. Phys.* **76**, 975 (2004).
 - [4] D. Sherman, U. S. Pracht, B. Gorshunov, S. Poran, J. Jesudasan, M. Chand, P. Raychaudhuri, M. Swanson, N. Trivedi, A. Auerbach, M. Scheffler, A. Frydman, and M. Dressel, The Higgs mode in disordered superconductors close to a quantum phase transition, *Nat. Phys.* **11**, 188 (2015).
 - [5] O. Fischer, M. Kugler, I. Maggio-Aprile, C. Berthod, and C. Renner, Scanning tunneling spectroscopy of high-temperature superconductors, *Rev. Mod. Phys.* **79**, 353 (2007).
 - [6] M. Tinkham, *Introduction to Superconductivity*, Dover Books on Physics Series (Dover Publications, 2004).
 - [7] A. Ghosal, M. Randeria, and N. Trivedi, Role of Spatial Amplitude Fluctuations in Highly Disordered *s*-Wave Superconductors, *Phys. Rev. Lett.* **81**, 3940 (1998).
 - [8] B. Sacépé, M. Feigel'man, and T. M. Klapwijk, Quantum breakdown of superconductivity in low-dimensional materials, *Nat. Phys.* **16**, 734 (2020).
 - [9] A. Ghosal, M. Randeria, and N. Trivedi, Inhomogeneous pairing in highly disordered *s*-wave superconductors, *Phys. Rev. B* **65**, 014501 (2001).
 - [10] K. Bouadim, Y. L. Loh, M. Randeria, and N. Trivedi, Single- and two-particle energy gaps across the disorder-driven superconductor-insulator transition, *Nature Physics* **7**, 884 (2011).
 - [11] M. D. Stewart, A. Yin, J. M. Xu, and J. M. Valles, Superconducting Pair Correlations in an Amorphous Insulating Nanohoneycomb Film, *Science* **318**, 1273 (2007).
 - [12] R. Crane, N. P. Armitage, A. Johansson, G. Sambandamurthy, D. Shahar, and G. Grüner, Survival of superconducting correlations across the two-dimensional superconductor-insulator transition: A finite-frequency study, *Phys. Rev. B* **75**, 184530 (2007).
 - [13] B. Sacépé, T. Dubouchet, C. Chapelier, M. Sanquer, M. Ovadia, D. Shahar, M. Feigel'man, and L. Ioffe, Localization of pre-formed Cooper pairs in disordered superconductors, *Nat. Phys.* **7**, 239 (2011).
 - [14] D. Sherman, G. Kopnov, D. Shahar, and A. Frydman, Measurement of a Superconducting Energy Gap in a Homogeneously Amorphous Insulator, *Phys. Rev. Lett.* **108**, 177006 (2012).
 - [15] G. Alvarez, M. Mayr, A. Moreo, and E. Dagotto, Areas of superconductivity and giant proximity effects in underdoped cuprates, *Phys. Rev. B* **71**, 014514 (2005).
 - [16] Y. Dubi, Y. Meir, and Y. Avishai, Nature of the superconductor-insulator transition in disordered superconductors, *Nature* **449**, 876 (2007).
 - [17] M. Mondal, A. Kamlapure, M. Chand, G. Saraswat, S. Kumar, J. Jesudasan, L. Benfatto, V. Tripathi, and P. Raychaudhuri, Phase Fluctuations in a Strongly Disordered *s*-Wave NbN Superconductor Close to the Metal-Insulator Transition, *Phys. Rev. Lett.* **106**, 047001 (2011).
 - [18] M. P. A. Fisher, G. Grinstein, and S. M. Girvin, Presence of quantum diffusion in two dimensions: Universal resistance at the superconductor-insulator transition, *Phys. Rev. Lett.* **64**, 587 (1990).
 - [19] M.-C. Cha, M. P. A. Fisher, S. M. Girvin, M. Wallin, and A. P. Young, Universal conductivity of two-dimensional films at the superconductor-insulator transition, *Phys. Rev. B* **44**, 6883 (1991).
 - [20] M. Swanson, Y. L. Loh, M. Randeria, and N. Trivedi, Dynamical Conductivity across the Disorder-Tuned Superconductor-Insulator Transition, *Phys. Rev. X* **4**, 021007 (2014).
 - [21] A. Abrikosov, The magnetic properties of superconducting alloys, *J. Phys. Chem. Solids* **2**, 199 (1957).
 - [22] In our study we consider a strongly type-II superconductor so first critical field for the insertion of a single vortex $H_{c1} \rightarrow 0$. For notational simplicity H_c refers to H_{c2} in standard literature.
 - [23] G. Sambandamurthy, L. W. Engel, A. Johansson, and D. Shahar, Superconductivity-Related Insulating Behavior, *Phys. Rev. Lett.* **92**, 107005 (2004).
 - [24] M. Steiner and A. Kapitulnik, Superconductivity in the insulating phase above the field-tuned superconductor-insulator transition in disordered indium oxide films, *Physica C: Superconductivity* **422**, 16 (2005).
 - [25] T. I. Baturina, C. Strunk, M. R. Baklanov, and A. Satta, Quantum Metallicity on the High-Field Side of the Superconductor-Insulator Transition, *Phys. Rev. Lett.* **98**, 127003 (2007).
 - [26] B. Sacépé, C. Chapelier, T. I. Baturina, V. M. Vinokur, M. R. Baklanov, and M. Sanquer, Disorder-Induced Inhomogeneities of the Superconducting State Close to the Superconductor-Insulator Transition, *Phys. Rev. Lett.* **101**, 157006 (2008).
 - [27] M. D. Stewart, A. Yin, J. M. Xu, and J. M. Valles, Magnetic-field-tuned superconductor-to-insulator transitions in amorphous Bi films with nanoscale hexagonal arrays of holes, *Phys. Rev. B* **77**, 140501 (2008).
 - [28] M. Ovadia, D. Kalok, B. Sacépé, and D. Shahar, Duality symmetry and its breakdown in the vicinity of the superconductor-insulator transition, *Nat. Phys.* **9**, 415 (2013).
 - [29] A. Doron, I. Tamir, T. Levinson, F. Gorniaczyk, and D. Shahar, Temperature dependence of the magnetoresistance peak in highly disordered superconductors, *Phys. Rev. B* **98**, 184515 (2018).
 - [30] T. I. Baturina, A. Y. Mironov, V. M. Vinokur, M. R. Baklanov, and C. Strunk, Localized Superconductivity in the Quantum-Critical Region of the Disorder-Driven Superconductor-Insulator Transition in TiN Thin Films, *Phys. Rev. Lett.* **99**, 257003 (2007).
 - [31] B. Sacépé, J. Seidemann, M. Ovadia, I. Tamir, D. Shahar, C. Chapelier, C. Strunk, and B. A. Piot, High-field termination

- of a Cooper-pair insulator, Phys. Rev. B **91**, 220508 (2015).
- [32] I. S. Burmistrov, I. V. Gornyi, and A. D. Mirlin, Superconductor-insulator transitions: Phase diagram and magnetoresistance, Phys. Rev. B **92**, 014506 (2015).
- [33] B. Hen, X. Zhang, V. Shelukhin, A. Kapitulnik, and A. Palevski, Superconductor–insulator transition in two-dimensional indium–indium-oxide composite, PNAS **118**, e2015970118 (2021).
- [34] Y. Dubi, Y. Meir, and Y. Avishai, Theory of the magnetoresistance of disordered superconducting films, Phys. Rev. B **73**, 054509 (2006).
- [35] A. Gangopadhyay, V. Galitski, and M. Müller, Magnetoresistance of an Anderson Insulator of Boson, Phys. Rev. Lett. **111**, 026801 (2013).
- [36] M. Müller, Magnetoresistance and localization in bosonic insulators, EPL (Europhysics Letters) **102**, 67008 (2013).
- [37] M. A. Steiner, N. P. Breznay, and A. Kapitulnik, Approach to a superconductor-to-Bose-insulator transition in disordered films, Phys. Rev. B **77**, 212501 (2008).
- [38] V. M. Vinokur, T. I. Baturina, M. V. Fistul, A. Y. Mironov, M. R. Baklanov, and C. Strunk, Superinsulator and quantum synchronization, Nature **452**, 613 (2008).
- [39] D. Basko, I. Aleiner, and B. Altshuler, Metal-insulator transition in a weakly interacting many-electron system with localized single-particle states, Ann. Phys. **321**, 1126 (2006).
- [40] M. Randeria and E. Taylor, Crossover from Bardeen-Cooper-Schrieffer to Bose-Einstein Condensation and the Unitary Fermi Gas, Annual Review of Condensed Matter Physics **5**, 209 (2014).
- [41] M. R. Randeria, N. Trivedi, A. Moreo, R. T. Scalettar, Pairing and spin gap in the normal state of short coherence length superconductors, Phys. Rev. Lett. **69**, 2001 (2001).
- [42] V. J. Emery and S. A. Kivelson, Importance of phase fluctuations in superconductors with small superfluid density, Nature **374**, 434 (1995).
- [43] See supplementary material for the relation between V and ρ_{dc} , and other details related to BdG calculation and frequency dependent conductivity, also including Refs. [44–46].
- [44] H. Smith, and H. H. Jensen *Transport phenomena* (Oxford University Press, 1989).
- [45] A. Ghosal, C. Kallin, and A. J. Berlinsky, Competition of superconductivity and antiferromagnetism in a d-wave vortex lattice, Phys. Rev. B **66**, 214502 (2002).
- [46] D. D. Johnson Modified Broyden’s method for accelerating convergence in self-consistent calculations, Phys. Rev. B **38**, 12807 (1988).
- [47] In our calculation, the LDOS in the core region is defined by averaging it over 9 sites of the square lattice – the site at the vortex center, its 4 nearest neighbors, and the 4 next-nearest neighbors of the vortex center. Such coarse-graining is necessary for producing an acceptable resolution from BdG numerics on finite size systems.
- [48] S.-Y. Hsu and J. M. Valles, Tunneling studies of vortices in high-sheet-resistance granular superconducting films, Phys. Rev. B **49**, 6416 (1994).
- [49] H. A. Radovan, T. P. Murphy, E. C. Palm, S. W. Tozer, J. C. Cooley, I. Mihut, and A. C. C., Abrikosov-to-Josephson vortex lattice crossover in heavy fermion CeCoIn₅, Philosophical Magazine **86**, 3569 (2006).
- [50] C. Caroli, P. D. Gennes, and J. Matricon, Bound Fermion states on a vortex line in a type II superconductor, Phys. Lett. **9**, 307 (1964).
- [51] See supplementary material for magnetic field dependence of Abrikosov vortices in a clean superconductor, also including Ref. [52].
- [52] S. Dutta, I. Roy, J. Jesudasan, S. Sachdev, and P. Raychaudhuri, Evidence of zero-point fluctuation of vortices in a very weakly pinned *a*-MoGe thin film, Phys. Rev. B. **103**, 214512 (2021).
- [53] D. M. Wood and D. Stroud, Charging effects and the phase-ordering transition in granular superconductors, Phys. Rev. B **25**, 1600 (1982).
- [54] E. Simánek and P. Simanek, *Inhomogeneous Superconductors: Granular and Quantum Effects* (Oxford University Press, 1994).
- [55] T. V. Ramakrishnan, Superconductivity in disordered thin films, Phys. Scr. **T27**, 24 (1989).
- [56] Within our numerics, we cannot distinguish with confidence the “metallic” phase from an Anderson insulator. Our identification of a “metallic” phase relies on the fact that the localization length, particularly for small disorder, remains larger than our system size.
- [57] While we introduced in text the two critical fields $H_c^{D_s}$ and $H_c^{E_g}$ for clarity, in true sense the ‘critical field’ is identified by $H_c^{D_s}$ that marks the destruction of type-II superconductivity. For all our discussions, the simplified notation H_c always represents $H_c^{D_s}$.
- [58] B. Sączépé, J. Seidemann, F. Gay, K. Davenport, A. Rogachev, M. Ovadia, K. Michaeli, and M. V. Feigel’man, Low-temperature anomaly in disordered superconductors near BC_2 as a vortex-glass property, Nat. Phys. **15**, 48 (2019).
- [59] See supplementary material for details on the extraction of the gap-scale E_g from the average density of states for different combinations of V and H , also included Ref. [60].
- [60] I. Guillamón, H. Suderow, S. Vieira, L. Cario, P. Diener, and P. Rodière Superconducting Density of States and Vortex Cores of 2H-NbS₂, Phys. Rev. Lett. **101**, 166407 (2008).
- [61] D. J. Scalapino, S. R. White, and S. Zhang, Insulator, metal, or superconductor: The criteria, Phys. Rev. B **47**, 7995 (1993).
- [62] B. Cheng, L. Wu, N. J. Laurita, H. Singh, M. Chand, P. Raychaudhuri, and N. P. Armitage, Anomalous gap-edge dissipation in disordered superconductors on the brink of localization, Phys. Rev. B **93**, 180511 (2016).
- [63] C. G. L. Bøttcher, F. Nichele, M. Kjaergaard, H. J. Suominen, J. Shabani, C. J. Palmstrøm, and C. M. Marcus, Superconducting, insulating and anomalous metallic regimes in a gated two-dimensional semiconductor–superconductor array, Nat. Phys. **14**, 1138 (2018).
- [64] A. Kapitulnik and S.A. Kivelson, and B Spivak, Colloquium: Anomalous metals: Failed superconductors, Rev. Mod. Phys. **91**, 011002 (2019).
- [65] P. Phillips and D. Dalidovich, The Elusive Bose Metal, Science **302**, 243 (2003).
- [66] A. W. Tsen, B. Hunt, Y. D. Kim, Z. J. Yuan, S. Jia, R. J. Cava, J. Hone, P. Kim, C. R. Dean, A. N. Pasupathy, Nature of the quantum metal in a two-dimensional crystalline superconductor, journal Nat. Phys. **12**, 208 (2016).
- [67] S. Ichinokura, Y. Nakata, K. Sugawara, Y. Endo, A. Takayama, T. Takahashi, and S. Hasegawa, Vortex-induced quantum metallicity in the mono-unit-layer superconductor NbSe₂, Phys. Rev. B **99**, 220501 (2019).
- [68] D. Das and S. Doniach, Existence of a Bose metal at $T = 0$, Phys. Rev. B **60**, 1261 (1999).