



This is the accepted manuscript made available via CHORUS. The article has been published as:

Indirect-to-direct band gap transition induced by μ - d coupling between cations in rare-earth chalcogenide perovskites

Han Zhang, Yichun Pan, Zexin Liu, Biao Zeng, Xiaowei Wu, Chen Ming, Guoqing Xin, Weihang Zhou, Hao Zeng, Shengbai Zhang, and Yi-Yang Sun

Phys. Rev. B **110**, L041201 — Published 25 July 2024

DOI: [10.1103/PhysRevB.110.L041201](https://doi.org/10.1103/PhysRevB.110.L041201)

Indirect-to-direct band gap transition induced by d - d coupling between cations in rare-earth chalcogenide perovskites

Han Zhang,^{1,2} Yichun Pan,³ Zexin Liu,³ Biao Zeng,^{1,2} Xiaowei Wu,^{1,2} Chen Ming,^{1,2}
Guoqing Xin,³ Weihang Zhou,³ Hao Zeng,⁴ Shengbai Zhang,⁵ and Yi-Yang Sun^{1,2,*}

¹*State Key Laboratory of High Performance Ceramics and Superfine Microstructure,
Shanghai Institute of Ceramics, Chinese Academy of Sciences, Shanghai 201899, China*

²*Center of Materials Science and Optoelectronics Engineering,
University of Chinese Academy of Sciences, Beijing 100049, China*

³*Wuhan National High Magnetic Field Center and School of Physics,
Huazhong University of Science and Technology, Wuhan, Hubei 430074, China*

⁴*Department of Physics, University at Buffalo, The State University of New York, Buffalo, New York 14260, USA*

⁵*Department of Physics, Applied Physics and Astronomy,
Rensselaer Polytechnic Institute, Troy, New York 12180, USA*

(Dated: July 8, 2024)

Chalcogenide perovskite materials have been shown to exhibit excellent properties for optoelectronics and photovoltaics. The research, however, has been focused on the II-IV-S₃ series of compounds. Here, by theoretical calculation, we predict that in the III-III-S₃ perovskites, there could exist a transition between the indirect and direct band gaps induced by the coupling strength of the d orbitals between the A-site and B-site cations. We validated this prediction by synthesizing LaScS₃ through solid state reaction from three elemental materials. Micro-Raman analysis combined with Raman tensor calculations are used to identify the perovskite phase of micrometer-size grains, from which photoluminescence can be observed. The emitted light peaks at about 519 nm (or 2.39 eV), which corresponds the largest band gap among the sulfide perovskites. The discovery of light-emitting LaScS₃ enriches the family of chalcogenide perovskites for optoelectronic applications.

Semiconductor light-emitting devices have revolutionized various aspects of modern life. White light-emitting diodes (LEDs) [1–3] are rapidly replacing traditional devices like incandescent lamps, making significant strides in the lighting market. From mobile devices to theater-size screens, display technology is also increasingly adopting LEDs [4]. Semiconductor lasers [5], with their compact design, have facilitated a wide range of applications, including laboratory light sources, fiber optic communication [6], and autonomous driving [7]. However, despite these successful applications, there are still unresolved issues in the field of LEDs that necessitate the development of new optoelectronic materials and devices. For instance, the next-generation display technology, micro-LED, experiences efficiency deterioration in the red-color range when the device size shrinks below 20 μm [8]. Green-color LEDs often suffer from low quantum efficiency, creating what is commonly known as the “green gap” problem [9] when compared to blue-color and red-color LEDs. Furthermore, the long-term stability of recently developed halide perovskite LEDs, particularly the blue-color ones, remains a challenge due to the segregation of Cl and Br anions under working conditions [10–12].

Sulfide perovskites, a new family of optoelectronic materials, were initially proposed for photovoltaic applications [13], but they also display appealing luminescent properties. In a recent study by Kota *et al.*, SrHfS₃ was investigated and found to hold great potential as

a green-color luminescent material [14]. In comparison to halide perovskites, sulfide perovskites possess inherent advantages such as thermal and environmental stability [15–18], as well as being free from toxic elements like lead [13]. However, research on sulfide perovskites has predominantly focused on the II-IV-S₃ series, composed of group-II elements (Ca, Sr, and Ba) and group-IV elements (Zr and Hf) [14–36]. The experimentally measured and theoretically calculated band gaps of these materials fall below 2.32 eV [13]. In our recent theoretical study, we predicted that the III-III-S₃ perovskite YScS₃ could possess a band gap approaching 3 eV. Unfortunately, its indirect nature renders it unsuitable for optoelectronic applications [37].

In this paper, we draw inspiration from the wide band gap of YScS₃ and the recent discovery of LaScSe₃ [38], a predicted direct-gap selenide perovskite, to investigate the III-III-S₃ perovskite LaScS₃. Our objective is to discover novel optoelectronic materials. Through first-principles calculations, we find that the bottom of the conduction band in III-III-S₃ perovskites is primarily influenced by the d - d coupling between the A-site cation and B-site cation. In YScS₃, the strong coupling between the $4d$ orbitals of Y and $3d$ orbitals of Sc significantly lowers the band at the S point in the Brillouin zone, resulting in an indirect band gap. However, in LaScS₃, the coupling between the $5d$ orbitals of La and $3d$ orbitals of Sc is weaker than the $4d$ - $3d$ coupling in YScS₃. As a result, the band at the S point is lifted, leading to a direct band gap in LaScS₃. To validate this theoretical prediction, we synthesize LaScS₃ by solid-state reaction. Photoluminescence measurements, assisted by micro-Raman

* Email: yysun@mail.sic.ac.cn

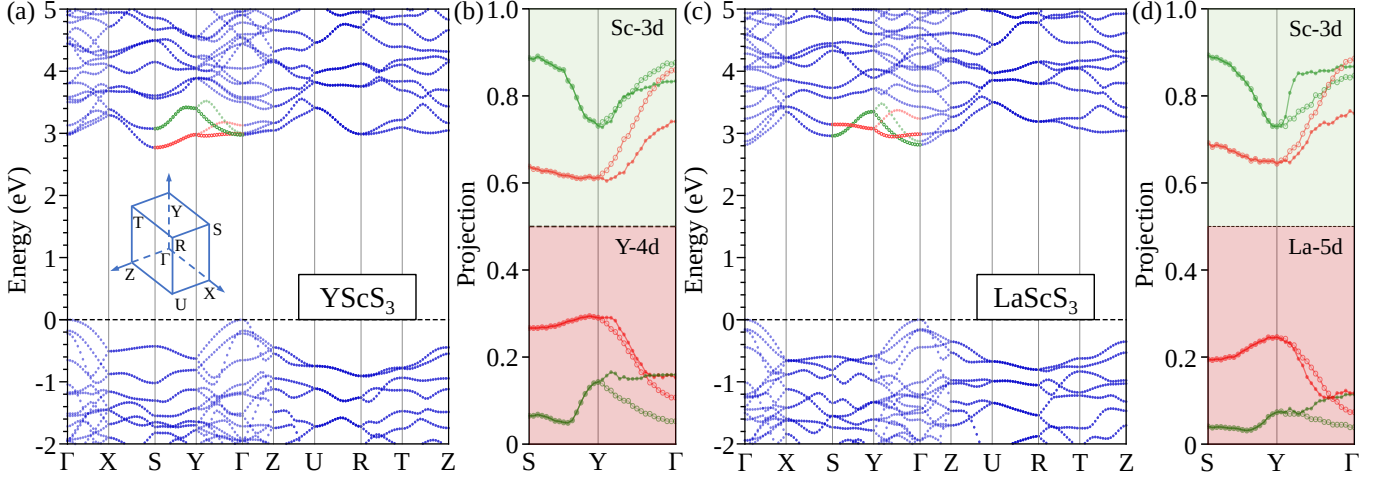


FIG. 1. (a) and (c) show the band structures of YScS_3 and LaScS_3 based on HSE06 functional calculations. The inset shows the irreducible Brillouin zone. (b) and (d) show the projection of bottom four conduction bands, as highlighted in (a) and (c), on the d orbitals of A-site and B-site cations along the S-Y- Γ path for YScS_3 and LaScS_3 , respectively.

measurements and DFT calculations on Raman tensors, confirm our prediction that LaScS_3 exhibits a direct band gap. Our work thus expands the family of chalcogenide perovskites to the III-III-S₃ series for optoelectronic applications.

First-principles calculations in this work were based on density functional theory (DFT), as implemented in the VASP program [39]. Projector augmented wave (PAW) potentials [40] were used to describe the interaction between ion cores and valence electrons. The wavefunctions were expanded by plane-wave basis sets. Hierarchical exchange-correlation functionals were used in our calculations for different purposes: (1) PBEsol functional [41] was used in calculation of dielectric tensors; (2) strongly constrained and appropriately normed (SCAN) functional [42] was used in all structure relaxations and frequency calculations; (3) hybrid HSE06 functional [43] was used in band structure calculations, where the screening parameter for range separation was set to $0.2 \text{ \AA}^{-1}$ and the mixing parameter for Hartree-Fock exchange was set to 0.25. Raman tensors (α_{ij}^k) were calculated by the partial difference of dielectric tensor (ϵ_{ij}) with respect to the phonon modes (q^k) at the Brillouin zone center according to $\alpha_{ij}^k = \frac{\partial \epsilon_{ij}}{\partial q^k}$ [44]. The dielectric tensors were calculated using density functional perturbation theory [45]. More calculation details about Raman intensity, convergence criteria and k -point sampling in different parts of calculations are listed in calculation method part and Tables S1 and S2 in the Supplementary Information (SI).

Crystal structures of the synthesized samples were evaluated using X-ray diffraction (XRD, Bruker D8 Advance) with Cu K α radiation, a tube current of 40 mA, and a tube voltage of 40 kV. The surface morphology and chemical composition were examined by scanning electron microscopy (SEM, Hitachi S-4800) and energy-

dispersive spectroscopy (EDS, Hitachi S-4800). The photoluminescence and Raman measurements were conducted using three wavelengths for the excitation light. The system excited by the 360-nm laser is equipped with a Horiba iHR-550 spectrometer, while the system excited by the 473-nm and 532-nm lasers is equipped with a Renishaw inVia confocal Raman microscope.

Figure 1 shows the band structures of YScS_3 and LaScS_3 computed using the hybrid HSE06 functional. For comparison, FIG. S1 in the SI also shows the band structures calculated with the SCAN and PBEsol functionals. The atomic structures, including lattice constants and internal parameters, were optimized using the SCAN functional (see Table S3 in the SI). The band structures calculated with the three functionals exhibit similar features around the band edges, with YScS_3 exhibiting indirect bandgaps and LaScS_3 exhibiting direct bandgaps. We also examined the effect of spin-orbit coupling (SOC) on the band structure. The results from calculations using HSE06 functional with SOC are shown in FIG. S2 in the SI. We found that in LaScS_3 , bands located approximately 1.5 eV above the conduction band minimum exhibit splitting, while the band structure of YScS_3 remains largely unchanged. Based on the results above, we conclude that the direct or indirect nature of LaScS_3 and YScS_3 is not affected by the exchange-correlation functional and the SOC effect.

To analyze the origin of the difference between the two materials, we focus on the bottom four bands along the S-Y- Γ direction, which are highlighted by red and green colors in FIGs. 1a and 1c. Note that from S to Y points, the bands are doubly degenerate. However, the point group symmetry cannot afford double degeneracy. As the 20-atom $Pnma$ unit cell is derived from four 5-atom $Pm\bar{3}m$ unit cells by octahedron rotation, this process could result in legacy degeneracy from the high-symmetry cubic

cell.

In FIGs. 1b and 1d, we plot the projections of each state on the d orbitals of A-site and B-site cations. It is seen that the green bands are dominated by Sc $3d$ orbitals. In contrast, the red bands contain more contributions from the Y $4d$ and La $5d$ orbitals, especially along the S-Y direction. For YScS₃, the projections of Y $4d$ orbitals on the red bands are 0.31 at the S point and 0.14 and 0.19 at the Γ point, respectively. For LaScS₃, the corresponding projections of La $5d$ orbitals are 0.24 at the S point and 0.09 and 0.14 at the Γ point, respectively. We also examined the effect of using different functionals on the projection values of the d -orbitals for the corresponding four bands. As shown in FIG. S3 in the SI, taking the S point as an example, the projection values of the d -orbitals for the corresponding four bands obtained using the HSE06, SCAN, and PBEsol functionals exhibit the same trend. Besides the smaller projections of La $5d$ orbitals, it is also expected that the coupling strength between the $5d$ and $3d$ orbitals is weaker than that between the $4d$ and $3d$ orbitals because of the larger energy level difference. The weaker $5d$ - $3d$ coupling in LaScS₃ render the red bands along the S-Y direction lifted up so that the band gap becomes direct at the Γ point. According to the HSE06 calculation, the direct band gap of LaScS₃ is 2.81 eV.

Note that the effect of d - d coupling discussed above is entangled with the effect of atomic structure difference between the two materials, e.g., the octahedral tilting. In the case of cubic LaScS₃ without any octahedral tilting, its band gap is indirect and the band gap value is also significantly smaller (see FIG. S4 in the SI). Table S3 in the SI compares the atomic structures of LaScS₃ and YScS₃, including the octahedral tilting angles. It is found that YScS₃ exhibits larger tilting angles than LaScS₃, which also influence the band structures. Figure S5 in the SI compares the band structures of LaScS₃ with the octahedra in the native tilting angles and in the angles of YScS₃. It is seen that the tilting angles have a similar effect of shifting the red bands near the bottom conduction bands. Thus, from the atomic structure point of view, the octahedral tilting contributes to the indirect-to-direct transition, while from the electronic structure point of view, the d - d coupling plays an important role in this transition.

To validate the prediction above, we synthesized LaScS₃ by solid-state reaction. Up to date, only two papers reported the synthesis of LaScS₃ [46, 47], where the binary sulfides were first synthesized and used as the reactants to obtain the ternary compound. Here, we used elemental La (purity 99.9% from Alfa), Sc (purity 99.9% from Alfa), and S (purity 99.998% from Aldrich) as reactants to obtain LaScS₃. The elemental reactants were weighed, put in an Al₂O₃ crucible, and then sealed in a quartz tube within an Ar-filled glovebox. The mixture was heated in a muffle furnace at 1100 °C for 72 hours. The resulting product was grounded, pressed into a pellet, and resealed in a quartz tube within the glovebox.

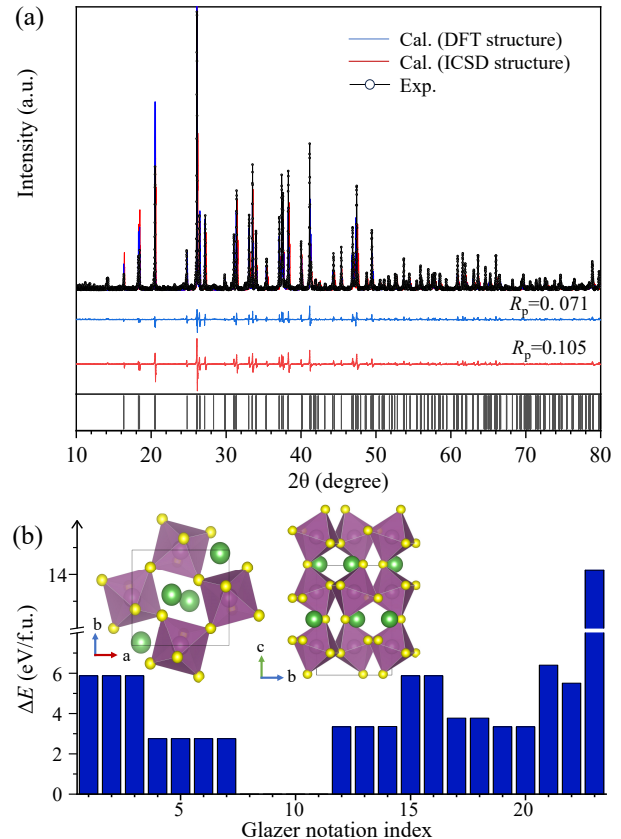


FIG. 2. (a) XRD pattern of powder LaScS₃ sample compared with calculated patterns using the atomic structures obtained from the SCAN functional calculation and the ICSD database. The red and blue lines below the patterns show the differences between the experimental and calculated patterns. Corresponding reliability factors (R_p) are also shown together with the lines. The black short lines at the bottom display the XRD peak positions calculated using the atomic structure obtained from the SCAN functional. (b) Calculated total energy of LaScS₃ with 23 different octahedron rotation patterns following the Glazer notation based on the SCAN functional, where the lowest energy patterns are taken as the energy reference. The inset shows the structure with the lowest total energy, which possesses the $Pnma$ space-group symmetry (No. 62).

Then, the pellet was heated again at 1100 °C for 72 hours.

Figure 2a displays the XRD pattern of the obtained LaScS₃ powder. We compared the experimental pattern with that calculated based on the structure optimized using the SCAN functional. The good agreement between the two patterns indicates the successful synthesis of a pure phase of LaScS₃, up to the detection limit of our XRD equipment. Moreover, this comparison highlights the high accuracy of the computationally optimized structure using the SCAN functional. In FIG. 2a, we also compared the XRD patterns of our experiment and that from the structure listed in the ICSD, which is linked to a previous reference [47]. The obtained reliability factor R_p (0.105) using the ICSD structure is slightly worse

than the R_p (0.071) obtained using our optimized structure. The formula for evaluating R_p [48, 49] is provided in the SI.

The space group symmetry of LaScS_3 has been labeled as $Pna21$ (No. 33) in the ICSD with the Sc atoms displaced away from the octahedron centers. However, our DFT calculations using the SCAN functional yielded a higher symmetry with space group $Pnma$ (No. 62). Additionally, as shown in FIG. S6 in the SI, the phonon spectrum of LaScS_3 calculated using the SCAN functional did not exhibit any imaginary frequencies, indicating that the $Pnma$ structure is stable. As seen in FIG. 2a, our high-symmetry structure also yielded smaller R_p factor, suggesting that the actual structure of LaScS_3 has the $Pnma$ symmetry. Similar symmetry issue also occurred for CeScS_3 , which was reported to have a lower symmetry and then redetermined to be the $Pnma$ symmetry [50, 51]. In addition, we measured the ferroelectric properties of LaScS_3 by fabricating a ceramic plate using spark plasma sintering. The result is presented in FIG. S7 in the SI and suggests that the material lacks ferroelectricity. Based on the results above, we conclude that LaScS_3 has the $Pnma$ perovskite structure.

We also carried out a systematic determination of the particular octahedron rotation pattern in the perovskite structure by employing the Glazer notation [52], which classified the octahedron rotations into 23 possibilities. The information on the space groups of the 23 possible structures and their corresponding rotation modes is displayed in Table S4 in the SI. In these calculations, we employed a supercell containing 8 octahedra (i.e., a $2 \times 2 \times 2$ supercell based on the non-distorted cubic perovskite unit cell) to accommodate the alternating octahedron rotations between nearest neighbors. SCAN functional [42] and a $4 \times 4 \times 4$ k -mesh were employed in these calculations to ensure computational accuracy. Figure 2b shows the calculated total energies with respect to the most stable rotation pattern. After relaxation, the patterns from 8 to 11, namely, $a^+b^-c^-$, $a^+a^-c^-$, $a^+b^-b^-$, and $a^+a^-a^-$, all ended up with the $Pnma$ symmetry, which is the lowest-energy structure. The energy difference among the four patterns is less than 2 meV per formula of LaScS_3 . Additionally, a $6 \times 6 \times 6$ k -mesh was used to check the convergence of the energy, and the results are presented in Table S5 in the SI. For comparison, we also performed the above calculations using the PBEsol functional [41], as shown in FIG. S8 in the SI. The calculated results are consistent with the trends based on the SCAN functional, where the energy of patterns from 8 to 11 is the lowest, exhibiting the symmetry of $Pnma$.

Scanning electron microscope (SEM) characterization was conducted on the as-synthesized LaScS_3 powder samples. At a magnification of $500\times$, displayed in FIG. 3a, grains of various sizes can be observed. At a magnification of $5,000\times$, displayed in FIG. 3b, detailed structure of a single grain can be observed to be polycrystalline with the grain boundaries clearly seen. By performing selected area electron diffraction (SAED) on the grains

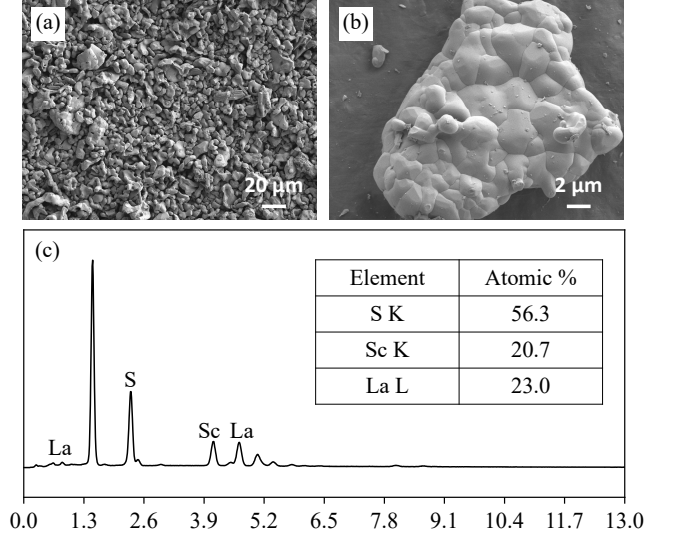


FIG. 3. SEM images of the synthesized LaScS_3 sample magnified by 500 (a) and 5000 times (b) and EDS spectrum (c) acquired from the sample in (b). The table of the inset lists the atomic ratio of the La, Sc, and S elements determined from the EDS measurement.

and calibrating the diffraction patterns, it can be demonstrated that the grains within the grain boundaries are single crystals. The characterization results are shown in FIG. S9 in the SI. Energy-dispersive X-ray spectroscopy (EDS) was used to measure the chemical composition. An elemental ratio of approximately 1:1:3 was obtained for La:Sc:S, as shown in FIG. 3c. The results of the EDS mapping are presented in FIG. S10 in the SI, indicating uniform elemental distribution in the prepared material. Additionally, a very small amount of black impurity grains were observed in the SEM analysis. According to the EDS results, the elemental composition of these impurity grains is approximately $\text{Sc:Si:O} = 2:2:7$. The results of the EDS analysis are presented in FIG. S11 in the SI.

We performed micro-Raman spectroscopy on individual polycrystalline grains. Continuous-wave lasers of 473 nm and 532 nm were used as the light source. As shown in FIG. 4a, we obtained consistent Raman spectra, with Raman signals detected even below 110 cm^{-1} for the 532 nm excitation. To analyze the Raman spectra, we calculated the Raman tensors of LaScS_3 using the SCAN functional, from which the theoretical peak intensity can be estimated. As shown in FIG. 4a, the calculated and the experimental spectra are in good agreement considering possible errors of about 10 cm^{-1} in the calculated peak positions, and symmetry labels were assigned to all Raman active peaks, as labelled in red. The calculation results of all Raman active modes are provided in the Table S6 in the SI.

The micro-Raman spectroscopy using the 473 nm laser allows us to measure the Raman and photoluminescence (PL) spectra on the same grain so that we can exclude the

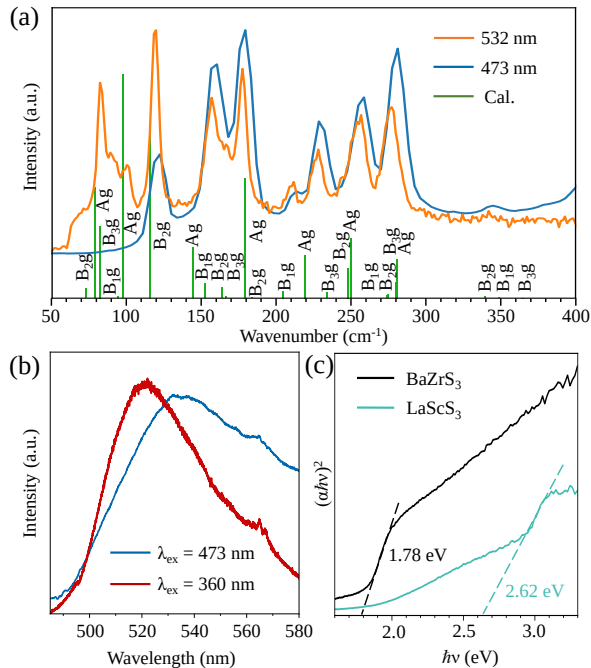


FIG. 4. (a) Raman spectra of LaScS_3 obtained using laser wavelengths of 532 nm and 473 nm. The calculated Raman peak positions and intensities, as well as the symmetry labels, are shown for comparison. (b) PL spectra of LaScS_3 using excitation laser wavelengths of 473 nm and 360 nm. (c) Optical absorption spectra of LaScS_3 and BaZrS_3 from diffuse reflectance spectroscopy.

possibility that the PL signal is from an impurity grain. As shown in FIG. 4b, a PL peak at 530 nm was observed. PL spectra of LaScS_3 were also measured using a 360 nm laser and a peak at 519 nm was observed, which corresponds to a band gap of 2.39 eV. We also performed diffuse reflectance spectroscopy (DRS) measurements. By the Tauc plot of the spectrum, as shown in FIG. 4c, the direct band gap is approximately determined to be 2.62 eV. We compared with BaZrS_3 , for which the direct band gap is found to be 1.78 eV, consistent with most reported values in the literature [22, 32]. The discrepancy on the band gap values from our HSE06 calculation, PL and DRS measurements could be originated from the excitonic effect excluded from our DFT calculation and the

inaccurate treatment of the localized La 4*f* and Sc 3*d* orbitals in the conduction band. The quality of powder sample may also contribute the discrepancy, which calls for further study to investigate.

It is worth noting that the powder samples used in micro-Raman measurement were dispersed in alcohol using 100 Hz ultrasonic treatment for 10 minutes, transferred to glass slides, and then dried before the measurements. The Raman spectra obtained from alcohol-dispersed samples and those obtained without alcohol dispersion showed good consistency, as shown in FIG. S12 in the SI. All measurements were performed under ambient conditions, demonstrating the good stability of the LaScS_3 perovskite.

In summary, by density functional theory calculation we predicted a light-emitting III-III-S₃ perovskite material, LaScS_3 . The direct band gap can be attributed to the relatively weak coupling between the La 5*d* orbitals and Sc 3*d* orbitals. We synthesized LaScS_3 through solid-state reaction from the three elemental materials. Combining micro-Raman and PL spectrum measurements, we verified the theoretical prediction by observing PL spectrum peaking at 519 nm, which is in reasonable agreement with the theoretical value and indicates the largest band gap among the chalcogenide perovskites. As the first light-emitting III-III-S₃ perovskite, LaScS_3 expands the choices of chalcogenide perovskites and, indeed, the entire perovskite family, for optoelectronic applications.

ACKNOWLEDGMENTS

The authors thank Zhen Liu, Xiangchao Kong and Biao He for their help on ferroelectric property measurements. This work is supported by the National Key Research and Development Program of China under Grant No. 2021YFB3500501. Y.-Y.S. acknowledges the support from the National Natural Science Foundation of China under Grant No. 91963208. C.M. acknowledges the support from the Natural Science Foundation of Shanghai under Grant No. 23ZR1472500. H.Z. acknowledges the support from NSF under Grant No. DMR-2042085. S.Z. acknowledges the support from NSF under Grant No. DMR-2042126.

- [1] S. Nakamura, T. Mukai, and M. Senoh, Candela-class high-brightness InGaN/AlGaN double-heterostructure blue-light-emitting diodes, *Appl. Phys. Lett.* **64**, 1687 (1994).
- [2] S. Nakamura, M. Senoh, N. Iwasa, S.-i. Nagahama, T. Yamada, and T. Mukai, Superbright Green InGaN Single-Quantum-Well-Structure Light-Emitting Diodes, *Jpn. J. Appl. Phys.* **34**, L1332 (1995).
- [3] G. Blasse and A. Bril, A NEW PHOSPHOR FOR

FLYING-SPOT CATHODE-RAY TUBES FOR COLOR TELEVISION: YELLOW-EMITTING $\text{Y}_3\text{Al}_5\text{O}_{12}-\text{Ce}^{3+}$, *Appl. Phys. Lett.* **11**, 53 (1967).

- [4] X. Lv, K. H. Loo, Y. M. Lai, and C. K. Tse, Energy-Saving Driver Design for Full-Color Large-Area LED Display Panel Systems, *IEEE Trans. Ind. Electron.* **61**, 4665 (2014).
- [5] D. Welch, A brief history of high-power semiconductor lasers, *IEEE J. Select. Topics Quantum Electron.* **6**, 1470

- (2000).
- [6] H. Kressel, M. Ettenberg, J. P. Wittke, and I. Ladany, Laser diodes and LEDs for fiber optical communication, in *Semiconductor Devices for Optical Communication*, Topics in Applied Physics, edited by H. Kressel (Springer, Berlin, Heidelberg, 1982) pp. 9–62.
 - [7] J. Y. Cho, K.-B. Kim, W. S. Hwang, C. H. Yang, J. H. Ahn, S. D. Hong, D. H. Jeon, G. J. Song, C. H. Ryu, S. B. Woo, J. Kim, T. H. Lee, J. Y. Choi, H. Cheong, and T. H. Sung, A multifunctional road-compatible piezoelectric energy harvester for autonomous driver-assist LED indicators with a self-monitoring system, *Appl. Energy* **242**, 294 (2019).
 - [8] Z. Chen, S. Yan, and C. Danesh, MicroLED technologies and applications: Characteristics, fabrication, progress, and challenges, *J. Phys. D: Appl. Phys.* **54**, 123001 (2021).
 - [9] M. Auf der Maur, A. Pecchia, G. Penazzi, W. Rodrigues, and A. Di Carlo, Efficiency Drop in Green InGaN/GaN Light Emitting Diodes: The Role of Random Alloy Fluctuations, *Phys. Rev. Lett.* **116**, 027401 (2016).
 - [10] Z. Ren, K. Wang, X. W. Sun, and W. C. H. Choy, Strategies Toward Efficient Blue Perovskite Light-Emitting Diodes, *Adv. Funct. Mater.* **31**, 2100516 (2021).
 - [11] L. Zhao, K. Roh, S. Kacmoli, K. Al Kurdi, S. Jhulki, S. Barlow, S. R. Marder, C. Gmachl, and B. P. Rand, Thermal Management Enables Bright and Stable Perovskite Light-Emitting Diodes, *Adv. Mater.* **32**, 2000752 (2020).
 - [12] Y. Zou, T. Wu, F. Fu, S. Bai, L. Cai, Z. Yuan, Y. Li, R. Li, W. Xu, T. Song, Y. Yang, X. Gao, F. Gao, and B. Sun, Thermal-induced interface degradation in perovskite light-emitting diodes, *J. Mater. Chem. C* **8**, 15079 (2020).
 - [13] K. V. Sopiha, C. Comparotto, J. A. Márquez, and J. J. S. Scragg, Chalcogenide Perovskites: Tantalizing Prospects, Challenging Materials, *Adv. Opt. Mater.* **10**, 2101704 (2022).
 - [14] K. Hanzawa, S. Iimura, H. Hiramatsu, and H. Hosono, Material Design of Green-Light-Emitting Semiconductors: Perovskite-Type Sulfide SrHfS₃, *J. Am. Chem. Soc.* **141**, 5343 (2019).
 - [15] N. Gross, Y.-Y. Sun, S. Perera, H. Hui, X. Wei, S. Zhang, H. Zeng, and B. A. Weinstein, Stability and Band-Gap Tuning of the Chalcogenide Perovskite BaZrS₃ in Raman and Optical Investigations at High Pressures, *Phys. Rev. Appl.* **8**, 044014 (2017).
 - [16] T. Gupta, D. Ghoshal, A. Yoshimura, S. Basu, P. K. Chow, A. S. Lakhnot, J. Pandey, J. M. Warrender, H. Efsthadiadis, A. Soni, E. Osei-Agyemang, G. Balasubramanian, S. Zhang, S.-F. Shi, T.-M. Lu, V. Meunier, and N. Koratkar, An Environmentally Stable and Lead-Free Chalcogenide Perovskite, *Adv. Funct. Mater.* **30**, 2001387 (2020).
 - [17] S. Niu, J. Milam-Guerrero, Y. Zhou, K. Ye, B. Zhao, B. C. Melot, and J. Ravichandran, Thermal stability study of transition metal perovskite sulfides, *J. Mater. Res.* **33**, 4135 (2018).
 - [18] Y. Wang, N. Sato, and T. Fujino, Synthesis of BaZrS₃ by short time reaction at lower temperatures, *J. Alloys Compd.* **327**, 104 (2001).
 - [19] C. Comparotto, A. Davydova, T. Ericson, L. Riekehr, M. V. Moro, T. Kubart, and J. Scragg, Chalcogenide Perovskite BaZrS₃ : Thin Film Growth by Sputtering and Rapid Thermal Processing, *ACS Appl. Energy Mater.* **3**, 2762 (2020).
 - [20] J. A. Márquez, M. Rusu, H. Hempel, I. Y. Ahmet, M. Kölbach, I. Simsek, L. Choubrac, G. Gurieva, R. Gunder, S. Schorr, and T. Unold, BaZrS₃ Chalcogenide Perovskite Thin Films by H₂S Sulfurization of Oxide Precursors, *J. Phys. Chem. Lett.* **12**, 2148 (2021).
 - [21] W. Meng, B. Saparov, F. Hong, J. Wang, D. B. Mitzi, and Y. Yan, Alloying and Defect Control within Chalcogenide Perovskites for Optimized Photovoltaic Application, *Chem. Mater.* **28**, 821 (2016).
 - [22] Y. Nishigaki, T. Nagai, M. Nishiwaki, T. Aizawa, M. Kozawa, K. Hanzawa, Y. Kato, H. Sai, H. Hiramatsu, H. Hosono, and H. Fujiwara, Extraordinary Strong Band-Edge Absorption in Distorted Chalcogenide Perovskites, *Sol. RRL* **4**, 1900555 (2020).
 - [23] S. Niu, H. Huyan, Y. Liu, M. Yeung, K. Ye, L. Blanke-meier, T. Orvis, D. Sarkar, D. J. Singh, R. Kapadia, and J. Ravichandran, Bandgap Control via Structural and Chemical Tuning of Transition Metal Perovskite Chalcogenides, *Adv. Mater.* **29**, 1604733 (2017).
 - [24] S. Perera, H. Hui, C. Zhao, H. Xue, F. Sun, C. Deng, N. Gross, C. Milleville, X. Xu, D. F. Watson, B. Weinstein, Y.-Y. Sun, S. Zhang, and H. Zeng, Chalcogenide perovskites – an emerging class of ionic semiconductors, *Nano Energy* **22**, 129 (2016).
 - [25] A. A. Pradhan, M. C. Uible, S. Agarwal, J. W. Turnley, S. Khandelwal, J. M. Peterson, D. D. Blach, R. N. Swope, L. Huang, S. C. Bart, and R. Agrawal, Synthesis of BaZrS₃ and BaHfS₃ Chalcogenide Perovskite Films Using Single-Phase Molecular Precursors at Moderate Temperatures, *Angew. Chem. Int. Ed.* **62**, e202301049 (2023).
 - [26] V. K. Ravi, S. H. Yu, P. K. Rajput, C. Nayak, D. Bhattacharyya, D. S. Chung, and A. Nag, Colloidal BaZrS₃ chalcogenide perovskite nanocrystals for thin film device fabrication, *Nanoscale* **13**, 1616 (2021).
 - [27] I. Sadeghi, K. Ye, M. Xu, Y. Li, J. M. LeBeau, and R. Jaramillo, Making BaZrS₃ Chalcogenide Perovskite Thin Films by Molecular Beam Epitaxy, *Adv. Funct. Mater.* **31**, 2105563 (2021).
 - [28] Y.-Y. Sun, M. L. Agiorgousis, P. Zhang, and S. Zhang, Chalcogenide Perovskites for Photovoltaics, *Nano Lett.* **15**, 581 (2015).
 - [29] M. Surendran, H. Chen, B. Zhao, A. S. Thind, S. Singh, T. Orvis, H. Zhao, J.-K. Han, H. Htoon, M. Kawasaki, R. Mishra, and J. Ravichandran, Epitaxial Thin Films of a Chalcogenide Perovskite, *Chem. Mater.* **33**, 7457 (2021).
 - [30] N. Thakur, P. Kumar, R. Neffati, and P. Sharma, Design and simulation of chalcogenide perovskite BaZr(S,Se)₃ compositions for photovoltaic applications, *Phys. Scr.* **98**, 065921 (2023).
 - [31] J. W. Turnley, K. C. Vincent, A. A. Pradhan, I. Panicker, R. Swope, M. C. Uible, S. C. Bart, and R. Agrawal, Solution Deposition for Chalcogenide Perovskites: A Low-Temperature Route to BaMS₃ Materials (M = Ti, Zr, Hf), *J. Am. Chem. Soc.* **144**, 18234 (2022).
 - [32] X. Wei, H. Hui, C. Zhao, C. Deng, M. Han, Z. Yu, A. Sheng, P. Roy, A. Chen, J. Lin, D. F. Watson, Y.-Y. Sun, T. Thomay, S. Yang, Q. Jia, S. Zhang, and H. Zeng, Realization of BaZrS₃ chalcogenide perovskite thin films for optoelectronics, *Nano Energy* **68**, 104317 (2020).
 - [33] X. Wei, H. Hui, S. Perera, A. Sheng, D. F. Watson, Y.-

- Y. Sun, Q. Jia, S. Zhang, and H. Zeng, Ti-Alloying of BaZrS₃ Chalcogenide Perovskite for Photovoltaics, *ACS Omega* **5**, 18579 (2020).
- [34] X. Wu, W. Gao, J. Chai, C. Ming, M. Chen, H. Zeng, P. Zhang, S. Zhang, and Y.-Y. Sun, Defect tolerance in chalcogenide perovskite photovoltaic material BaZrS₃, *Sci. China Mater.* **64**, 2976 (2021).
- [35] R. Yang, A. D. Jess, C. Fai, and C. J. Hages, Low-Temperature, Solution-Based Synthesis of Luminescent Chalcogenide Perovskite BaZrS₃ Nanoparticles, *J. Am. Chem. Soc.* **144**, 15928 (2022).
- [36] Z. Yu, X. Wei, Y. Zheng, H. Hui, M. Bian, S. Dhole, J.-H. Seo, Y.-Y. Sun, Q. Jia, S. Zhang, S. Yang, and H. Zeng, Chalcogenide perovskite BaZrS₃ thin-film electronic and optoelectronic devices by low temperature processing, *Nano Energy* **85**, 105959 (2021).
- [37] H. Zhang, C. Ming, K. Yang, H. Zeng, S. Zhang, and Y.-Y. Sun, Chalcogenide Perovskite YScS₃ as a Potential p-Type Transparent Conducting Material, *Chin. Phys. Lett.* **37**, 97201 (2020).
- [38] H. Zhang, X. Wu, K. Ding, L. Xie, K. Yang, C. Ming, S. Bai, H. Zeng, S. Zhang, and Y.-Y. Sun, Prediction and Synthesis of a Selenide Perovskite for Optoelectronics, *Chem. Mater.* **35**, 4128 (2023).
- [39] G. Kresse and J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Comput. Mater. Sci.* **6**, 15 (1996).
- [40] G. Kresse and D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Phys. Rev. B* **59**, 1758 (1999).
- [41] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, Restoring the Density-Gradient Expansion for Exchange in Solids and Surfaces, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [42] J. Sun, A. Ruzsinszky, and J. P. Perdew, Strongly Constrained and Appropriately Normed Semilocal Density Functional, *Phys. Rev. Lett.* **115**, 036402 (2015).
- [43] J. Heyd, G. E. Scuseria, and M. Ernzerhof, Hybrid functionals based on a screened Coulomb potential, *J. Chem. Phys.* **118**, 8207 (2003), **124**, 219906 (2006).
- [44] R. Caracas, Raman spectra and lattice dynamics of cubic gauche nitrogen, *J. Chem. Phys.* **127**, 144510 (2007).
- [45] M. Gajdoš, K. Hummer, G. Kresse, J. Furthmüller, and F. Bechstedt, Linear optical properties in the projector-augmented wave methodology, *Phys. Rev. B* **73**, 045112 (2006).
- [46] O. V. Andreev, O. Yu. Mitroshin, and I. A. Razumkova, Phase diagrams of the systems Sc₂S₃-Ln₂S₃ for Ln = La, Nd, or Gd, *Russ. J. Inorg. Chem.* **52**, 1161 (2007).
- [47] R. Noel, L. Pierre, and F. Jean, Sur une nouvelle serie de combinaisons des sesquisulfures de terres rares et d'yttrium avec le sesquisulfure de scandium, *C. R. Acad. Sc. Paris* **269**, 1391 (1969).
- [48] D. L. Bish and J. E. Post, *Modern Powder Diffraction* (Walter de Gruyter GmbH & Co KG, 2018).
- [49] L. B. McCusker, R. B. Von Dreele, D. E. Cox, D. Louër, and P. Scardi, Rietveld refinement guidelines, *J. Appl. Crystallogr.* **32**, 36 (1999).
- [50] K. J. Range, A. Gietl, and U. Klement, Crystal structure of cerium scandium trisulfide, CeScS₃, *Z. Kristallogr. Cryst. Mater.* **207**, 147 (1993).
- [51] D. J. W. IJdo, Cerium scandium sulphide: Structure refinement by powder neutron diffraction, *Acta Cryst. B* **36**, 2403 (1980).
- [52] A. M. Glazer, The classification of tilted octahedra in perovskites, *Acta Cryst. B* **28**, 3384 (1972).