

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Enhanced valence force field model for the lattice properties of gallium arsenide

Sebastian Steiger, Mehdi Salmani-Jelodar, Denis Areshkin, Abhijeet Paul, Tillmann Kubis, Michael Povolotskyi, Hong-Hyun Park, and Gerhard Klimeck

Phys. Rev. B **84**, 155204 — Published 17 October 2011

DOI: [10.1103/PhysRevB.84.155204](https://doi.org/10.1103/PhysRevB.84.155204)

# Enhanced valence force field model for the lattice properties of gallium arsenide

Sebastian Steiger,\* Mehdi Salmani, Denis Areshkin, Abhijeet Paul, Tillmann

Kubis, Michael Povolotskyi, Hong-Hyun Park, and Gerhard Klimeck

Network for Computational Nanotechnology, Purdue University, West Lafayette IN 47907, USA<sup>†</sup>

(Dated: September 26, 2011)

An enhanced valence force field model for zincblende crystals is developed to provide a unified description of the isothermal static and dynamical lattice properties of gallium arsenide. The expression for the lattice energy includes a second-nearest-neighbor coplanar interaction term, the Coulomb interaction between partially charged ions, and anharmonicity corrections. General relations are derived between the microscopic force constants and the macroscopic elastic constants in zincblende crystals. Applying the model to gallium arsenide, parameter sets are presented that yield quantitative agreement with experimental results for the phonon dispersion, elastic constants, sound velocities, and Grüneisen mode parameters.

PACS numbers: 73.21.-b, 63.22.-m, 73.21.Hb, 73.21.La

Keywords: valence force field, phonons, elastic constants, zincblende crystal, genetic algorithm fitting

## I. INTRODUCTION

The calculation of static and dynamic properties of crystal lattices from atomic configurations has a century-long history.<sup>1</sup> Interest in these quantities is currently revived because of the increasing importance of thermal effects in nanodevices. CPU power consumption, combined with increased resource scarcity, poses serious technological challenges for which the quantitative understanding of nano-scale lattice properties is critical.

A vast variety of models strain and phonon exist in literature, some of which agree very well with experimentally reported values.<sup>2,3</sup> The empirical valence force field (VFF) approach<sup>4</sup> offers an attractive alternative to more accurate *ab initio* models<sup>3</sup> due to its reduced computational cost and feasibility when it comes to the treatment of systems where thousands, if not millions, of atoms need to be explicitly considered. Yet, many devices are now heavily influenced by interfaces, alloy disorder and defects, such that an atomic-level understanding becomes preferable over less computationally expensive continuum models.

The simplest and most widely used flavor of the VFF model due to Keating,<sup>5</sup> together with anharmonic corrections,<sup>6</sup> has been shown to provide reasonable agreement with experiment when it comes to the modeling of electronic states in strained nanostructures.<sup>7</sup> Yet it is well-known that it fails to reproduce basic bulk properties of zincblende crystals. It can be easily shown that the two parameters entering the Keating model provide an insufficient amount of free parameters to match the three elastic constants. Furthermore, the disregard of the partially ionic nature of the bonds in III-V materials leads to large discrepancies especially in dynamical properties like optical phonon modes.

Several extensions of the Keating model exist. The original valence force field model for diamond<sup>4</sup> was shown to possess seven independent parameters in general, three of which are related to interactions between second-nearest neighbors. These results were extended to zincblende

structures by Martin<sup>8</sup> via inclusion of the Coulomb interaction between partially charged atoms within a rigid point-ion approximation. However, the second-nearest neighbor short-range interaction terms were neglected in Ref. 8 as well as various other works.<sup>9–11</sup> It was shown earlier for diamond<sup>12</sup> that especially the interaction associated with three connected coplanar bonds plays a significant role. In Ref. 13 the experimentally observed flattening of the TA mode near the zone boundary was explained in terms of the coplanar interaction. The importance of this interaction was advocated further in Ref. 14. Zunger *et al.* have included the stretch-bend interaction<sup>15,16</sup> and, on one occasion,<sup>9</sup> also the cross-stretch interaction in successful descriptions of GaP quantum dots,<sup>9</sup> InAs quantum dots,<sup>15</sup> InGaAs alloys<sup>16</sup> and InAs/GaAs superlattices.<sup>16</sup>

It is known that the quasi-harmonic VFF approach fails to provide even qualitative agreement with properties associated with volume expansion of the crystal.<sup>6,13</sup> This deficiency can be lifted by an inclusion of anharmonic corrections to the force constants. The additional parameters enable a fitting of the Grüneisen mode parameters<sup>17</sup> which describe the crystal behavior under hydrostatic strain.

This work aims to unify the VFF descriptions for zincblende crystals by including all nearest-neighbor as well as the coplanar second-nearest neighbor interactions, incorporating the Coulomb interaction within the rigid-ion approximation<sup>8</sup> and anharmonicity corrections. An in-depth analysis of the resulting VFF model is presented in an attempt to increase its applicability in zincblende structures.

Two central results are derived within the scope of this work: 1. an analytic relation between the model's parameters and the second-order elastic constants, and 2. the application of the enhanced model to GaAs. The resulting model will be shown to provide, for the first time, a unified description of isothermal static and dynamic lattice properties of a zincblende crystal using a VFF approach. It agrees with reported experimental values to

a satisfying degree.

After a detailed description of the model in Sec. II, analytical expressions for the elastic constants and the internal strain parameter as a function of the force constants are derived in Sec. III. These expressions extend the work in Refs. 13 and 18 by including the Coulomb interaction. In Sec. IV, parameter sets for gallium arsenide are presented which yield good agreement between computed quantities and experimental measurements for phonon spectra, elastic constants, sound velocities and Grüneisen coefficients. A few aspects of the model are revisited and a remark on its predictiveness is made. The paper concludes in Sec. V.

## II. MODEL

This section presents the expression for the lattice energy, which constitutes the core of the model, and outlines how a number of lattice properties are obtained from it. The potential energy of the lattice is expressed in terms of atomic locations as follows:<sup>4,13,14</sup>

$$\begin{aligned}
 U = & \frac{3}{16} \sum_{i,j \in NN(i)} \left[ \alpha_{ij} (\delta r_{ij})^2 \right. \\
 & + \sum_{k \in NN(i)}^{k \neq j} \left( \beta_{jik} (\delta \theta_{jik})^2 + \gamma_{jik} \delta r_{ij} \delta \theta_{jik} + \delta_{jik} \delta r_{ij} \delta r_{ik} \right. \\
 & \left. \left. + \sum_{l \in NN(k)}^{COP(j-i-k-l)} \nu_{jilk} (\delta \theta_{jik}) (\delta \theta_{ikl}) \right) \right] \\
 & + \frac{1}{8\pi\epsilon_0} \sum_{i,j \neq i} \frac{Z_i Z_j}{|\mathbf{r}_i - \mathbf{r}_j|}, \quad (1)
 \end{aligned}$$

with

$$\delta r_{ij} \equiv \frac{(r_{ij}^2 - d_{ij}^2)}{d_{ij}}, \quad (2a)$$

$$\delta \theta_{jik} \equiv \frac{(\mathbf{r}_{ij} \cdot \mathbf{r}_{ik} - \cos \theta_0 d_{ij} d_{ik})}{\sqrt{d_{ij} d_{ik}}}. \quad (2b)$$

Here  $\mathbf{r}_{ij} \equiv \mathbf{r}_j - \mathbf{r}_i$  is the bond vector pointing from atom  $i$  to atom  $j$ ,  $d_{ij}$  is a model parameter which in the absence of Coulomb interaction represents the equilibrium length  $r_0$  of the bond  $i-j$  (see Subsection III A),  $\theta_0$  is the ideal tetrahedral bond angle,  $\alpha, \beta, \gamma, \delta, \nu$  are the force constants for bond stretching, bond bending, stretch-bend interactions, cross-stretch interactions and coplanar bend-bend interactions, respectively, and  $Z_i$  is an effective point charge sitting at atom  $i$ . The summation of  $i$  extends over all explicitly considered atoms (two for a bulk primitive zincblende unit cell).  $NN(i)$  denotes all nearest neighbors of atom  $i$  and  $COP(j-i-k-l)$  denotes the condition that the bonds  $j-i$ ,  $i-k$  and  $k-l$  need to be coplanar.

Any background dielectric screening of the Coulomb interaction is incorporated into the effective charges  $Z_i$ ,

which correspond to the Born transverse charge  $e_T^* e$  in Ref. 22 with  $\epsilon_\infty = 1$ . For bulk zincblende crystals they can be determined from the experimental LO-TO phonon splitting at  $\Gamma$  using the relationship<sup>23</sup>

$$Z^2 = V_{prim} M_r \epsilon_0 (\omega_{LO}^2 - \omega_{TO}^2). \quad (3)$$

Here  $V_{prim} = \frac{a^3}{4}$  is the volume of the primitive unit cell and  $M_r \equiv \frac{M_C M_A}{M_C + M_A}$  is the reduced cation-anion mass. Thus there is a charge  $+Z$  sitting at cation sites and an opposite charge  $-Z$  sitting at anion sites, as opposed to bond-charge models<sup>2,24,25</sup> where additional point charges are fixed at<sup>24</sup> or adiabatically moving around<sup>2,25</sup> the middle of bonds. In bulk crystals the Coulomb interaction is computed using Ewald summation<sup>26,27</sup> (see Appendix A).

For zincblende structures the force constants  $\beta, \gamma$  and  $\delta$  may differ depending on whether an anion (A) or a cation (C) sits at the apex of the bond angle. However, it will be shown that the lattice energy of bulk systems depends only on the arithmetic average of the two values. It is therefore convenient to define

$$\beta \equiv \frac{\beta_{ACA} + \beta_{CAC}}{2}, \quad (4)$$

and similarly for  $\gamma$  and  $\delta$ .

*Comparison to other models:* The present model is similar to the one of Kane<sup>14</sup> but includes stretch-bend and third-order-stretching nearest-neighbor terms instead of a second-nearest-neighbor stretch term. Also, the parameter sets in Refs. 13 and 14 were exclusively fitted against selected phonon frequencies whereas this work includes the elastic constants and the sound velocities in the fitting procedure. Lastly, anharmonic parameter corrections are introduced here to obtain agreement with experimental Grüneisen parameters.

The Coulomb interaction is treated under the assumption that as the ions oscillate, a constant fractional amount of point-like charges moves along rigidly, generating merely a monopole field.<sup>19</sup> Kane's model<sup>14</sup> is more refined in that it incorporates a multipole-expanded Coulomb interaction. The deformation-dipole-model (DDM) of Kunc *et al.*<sup>20</sup> allows for an additional deformation of the electronic charge with the lattice vibration and an electronic polarizability due to microscopic fields. It was shown in Ref. 21 that an 11-parameter rigid-ion model, which is obtained from the 15-parameter DDM by neglecting polarizabilities, can match the accuracy of the DDM along high-symmetry lines of the Brillouin zone, but the two models differ in the phonon density of states which is a signature of the entire phonon dispersion. This work assumes the rigid-ion approximation to be sufficient, and no attempts were made to fit the phonon density of states.

### A. Anharmonic modifications of the force constants

The force constants are assumed to have a parametric dependence on the atomic positions:<sup>13</sup>

$$\alpha = \alpha_0 (1 + A_\alpha \Delta_r^{ij}), \quad (5a)$$

$$\beta = \beta_0 (1 + A_\beta \Delta_r^{jik}), \quad (5b)$$

$$\gamma = \gamma_0 (1 + A_\gamma \Delta_r^{jik}), \quad (5c)$$

$$\delta = \delta_0 (1 + A_\delta \Delta_r^{jik}), \quad (5d)$$

$$\nu = \nu_0 \left( 1 + A_\nu \frac{\Delta_r^{jik} + \Delta_r^{ikl}}{2} \right). \quad (5e)$$

Here the definitions

$$\Delta_r^{ij} \equiv \frac{r_{ij}^2 - r_{0,ij}^2}{2r_{0,ij}^2}, \quad (6a)$$

$$\Delta_r^{jik} \equiv \frac{r_{ij}r_{ik} - r_{0,ij}r_{0,ik}}{2r_{0,ij}r_{0,ik}} \quad (6b)$$

were made.

The dependencies in Eqn. 5 are parametric in the sense that no spatial derivatives are taken during the computation of the dynamical matrix (see Eqn. 9). The anharmonic corrections thus influence the mode Grüneisen parameters and third-order elastic constants but not the second-order elastic constants or unstrained phonon dispersions, for the terms involving  $\Delta_r$  in Eqn. 5 vanish in these cases.

*Comparison to other models:* The functional dependence in Eqn. 5 is a simplified version of Sui *et al.*<sup>13</sup> but differs from Refs. 6, 28 and also from the modified VFF model in Ref. 29. In Refs. 6 and 13 additional anharmonic parameters related to bond angles are taken into account which were derived from the shear deformation parameter. However, the authors of Ref. 30, the original source of this type of correction, argue that when using a generalized model like the present one such additional corrections are small. We also refrain from a further proliferation of parameters by introducing atom-type-dependent anharmonicity parameters.

Lastly it is noted that some angle dependence is indeed included in all but the first terms of Eqn. 1, and it will be shown that five independent parameters which are exclusively related to anharmonicity provide sufficient degrees of freedom to fit the corresponding Grüneisen parameters.

### B. Phonon spectra

Using the ansatz

$$\mathbf{u}_{n\mathbf{q}}(i)(t) = \mathbf{u}_{n\mathbf{q}}(i)e^{i(\mathbf{q} \cdot \mathbf{r}_i - \omega_n(\mathbf{q})t)} \quad (7)$$

for an oscillating displacement  $\mathbf{u}_{n\mathbf{q}}(i)(t)$  with amplitude  $\mathbf{u}_{n\mathbf{q}}(i) = (u_{n\mathbf{q},i}^x, u_{n\mathbf{q},i}^y, u_{n\mathbf{q},i}^z)^T$  at an atomic site  $i$ , the

Newton equation of motion for the atoms becomes the eigenvalue equation<sup>23</sup>

$$\mathbf{D}(\mathbf{q})\mathbf{u}_{n\mathbf{q}} = \omega_n^2(\mathbf{q})\mathbf{u}_{n\mathbf{q}}, \quad (8)$$

where  $\omega_n(\mathbf{q})$  is the phonon frequency of branch  $n$  and wavevector  $\mathbf{q}$ . The dynamical matrix  $\mathbf{D}$  is related to the second derivatives of the potential energy by<sup>9,26</sup>

$$D_{i\mu,j\nu}(\mathbf{q}) = \frac{1}{\sqrt{M_i M_j}} \sum_l \frac{\partial^2 U}{\partial r_i^\mu \partial (r_j^\nu + \mathbf{R}_l^\nu)} e^{-i\mathbf{q} \cdot \mathbf{R}_l}. \quad (9)$$

Here  $i$  and  $j$  denote atomic indices in the primary unit cell,  $M_i$  and  $M_j$  are the respective masses,  $\mu, \nu \in \{x, y, z\}$  and  $l$  runs over all lattice vectors  $\mathbf{R}_l$ .

### C. Elastic constants and internal strain parameter

In the presence of homogeneous strain, the Bravais vectors  $\mathbf{a}_i$  of the crystal experience a distortion

$$\mathbf{a}'_i = (\mathbf{1} + \boldsymbol{\epsilon})\mathbf{a}_i, \quad (10)$$

where  $\boldsymbol{\epsilon}$  is the (infinitesimal) strain tensor. In addition, the two-atom zincblende primitive unit cell composed of a cation at  $\mathbf{r}_C = 0$  and an anion at  $\mathbf{r}_A = \frac{a}{4}(1, 1, 1)$  can be distorted internally by an additional displacement of one atom with respect to the other:<sup>13,23</sup>

$$\mathbf{r}'_A = (\mathbf{1} + \boldsymbol{\epsilon})\mathbf{r}_A - \xi \frac{a}{2} \begin{pmatrix} \epsilon_{yz} \\ \epsilon_{xz} \\ \epsilon_{xy} \end{pmatrix}. \quad (11)$$

Here  $\xi$  denotes Kleinman's internal strain parameter. A relationship between  $\xi$  and the force constants can be found by a condition of minimal energy:<sup>13</sup>

$$\left. \frac{\partial U}{\partial \xi} \right|_{\xi=\xi_0} = 0. \quad (12)$$

### D. Sound velocities and Grüneisen mode parameters

The sound velocities of acoustic branches

$$c_s^n \equiv \frac{\partial \omega_n(0)}{\partial q} \quad (13)$$

and the Grüneisen mode parameters<sup>17</sup>

$$\gamma_n(\mathbf{q}) \equiv \frac{V_{prim}}{\omega_n(\mathbf{q})} \frac{\partial \omega_n(\mathbf{q})}{\partial V_{prim}} \quad (14)$$

can be determined numerically from the computed phonon spectra (see also comment in Appendix A). The authors observed that the small-strain limit for the Grüneisen parameters is only reached for bond length distortions below 0.01%. However, the results in Sec. IV are

computed using a hydrostatic strain of 0.03, corresponding to a bond elongation of 1%. This yields values for the Grüneisen coefficients which can differ by as much as 10% from the converged small-strain values. This choice was made in anticipation of nonvanishing strain in nanostructures. It is also noted that  $\gamma_{LO}(\Gamma)$  and  $\gamma_{TO}(\Gamma)$  have the same value in the limit of vanishingly small strain, but the reported experimental values (see Table II) exhibit a split.

### III. ANALYTICAL RESULTS

This section presents analytical results following from the model in Sec. II. First, it is shown that the model parameter  $d$  cannot simply be chosen as the equilibrium bond length in a polar crystal if the consistency of the model is to be preserved. Second, material properties such as the elastic constants are expressed in terms of the model input parameters.

#### A. Coulomb-induced modification of the model parameter $d$

Using Eqns. 1 to 6, the crystal energy of a bulk zincblende primitive unit cell in equilibrium can be found by inserting the atomic positions and exploiting periodicity. It evaluates to

$$U_{\text{bulk}}^{\text{unstrained}} = \left( F + G \frac{r_0^2 - d^2}{2d^2} \right) \frac{(r_0^2 - d^2)^2}{2d^2} + \alpha_M \frac{S}{r_0}, \quad (15)$$

where

$$S \equiv \frac{Z^2}{4\pi\epsilon_0} \quad (16)$$

is the strength of the Coulomb interaction,  $r_0$  is the bond length, and the definitions

$$F \equiv 3\alpha_0 + \beta_0 - 3\gamma_0 + 9\delta_0 + \nu_0, \quad (17a)$$

$$G \equiv 6\alpha_0 r_0 A_\alpha + \beta_0 A_\beta - 3\gamma_0 A_\gamma + 9\delta_0 A_\delta + \nu_0 A_\nu \quad (17b)$$

were made.  $\alpha_M$  is the Madelung constant for zincblende:

$$\alpha_M \equiv -1.638055053388790. \quad (18)$$

The constant was computed to this accuracy by equating  $\alpha_M \frac{S}{r_0}$  with the numerically evaluated Ewald sum (see Appendix A).

As pointed out in Ref. 31, the energy of an unstrained bulk crystal should be minimal at the experimental bond length  $r_{0,\text{exp}}$  in order for the model to be consistent. The

attractive Coulomb energy shifts the minimum to smaller bond lengths and hence  $d$  must be modified to counterbalance this effect. Applying the condition

$$\left. \frac{\partial U_{\text{bulk}}^{\text{unstrained}}}{\partial r_0} \right|_{r_0=r_{0,\text{exp}}} = 0 \quad (19)$$

to Eqn. 15 yields a relation between  $d$  and the experimental bond length. In the absence of anharmonic corrections the relation reads

$$d^2 = r_{0,\text{exp}}^2 \frac{1}{1 + S_1}, \quad (20)$$

where

$$S_1 \equiv S \frac{\alpha_M}{2F r_{0,\text{exp}}^3}. \quad (21)$$

When anharmonic corrections are included the relation becomes

$$d^2 = r_{0,\text{exp}}^2 \frac{2 + \frac{G}{2F}}{1 + S_1 + \frac{G}{2F} + \sqrt{(1 + S_1)^2 + \frac{G}{F} S_1}}. \quad (22)$$

The experimental bond length  $r_{0,\text{exp}}$  will henceforth be called  $r_0$ . We find that the analytical expressions in the following section become intractable when using Eqn. 22. Hence Eqn. 20 is used for all subsequent results, including the parameter fitting, causing a minor inconsistency of the model. Using this approach, the force constants as well as the parameter  $d$  are not influenced by the anharmonicity constants in an unstrained crystal. Thus the unstrained phonon spectra remain unchanged with respect to the choice of the anharmonic coefficients. The influence of the choice of  $d$  is revisited in Subsection IV C.

#### B. Elastic constants, internal strain parameter and sound velocities

Using the program *Mathematica*, Eqns. 10 and 11 can be inserted into Eqn. 1 for the primitive zincblende unit cell, using Eqn. A1 for the Coulomb term. A Taylor expansion to second order in  $\epsilon_{ij}$  can then be compared to the total energy per primitive unit cell in terms of the elastic constants:<sup>13</sup>

$$\begin{aligned} \frac{U(\epsilon)}{V_{\text{prim}}} &= \frac{U(0)}{V_{\text{prim}}} + \frac{C_{11}}{2}(\epsilon_{xx}^2 + \epsilon_{yy}^2 + \epsilon_{zz}^2) \\ &\quad + C_{12}(\epsilon_{xx}\epsilon_{yy} + \epsilon_{xx}\epsilon_{zz} + \epsilon_{yy}\epsilon_{zz}) \\ &\quad + 2C_{44}(\epsilon_{xy}^2 + \epsilon_{xz}^2 + \epsilon_{yz}^2). \end{aligned} \quad (23)$$

The result reads

$$C_{11} = \frac{\sqrt{3}}{4r_0} \left( (\alpha_0 + 3\beta_0 - \gamma_0 + 3\delta_0 + 3\nu_0) + (5\alpha_0 + 7\beta_0 - 5\gamma_0 + 15\delta_0 + 7\nu_0) \frac{S_1}{2} \right) + \mathcal{B} \frac{S}{r_0^4}, \quad (24a)$$

$$C_{12} = \frac{\sqrt{3}}{4r_0} (\alpha_0 - \beta_0 - \gamma_0 + 3\delta_0 - \nu_0) (1 + S_1) + \mathcal{C} \frac{S}{r_0^4}, \quad (24b)$$

$$C_{44} = \frac{\sqrt{3}}{4r_0} \left[ ((1 - \xi)^2 \alpha_0 + (1 + \xi)^2 \beta_0 - (1 - \xi^2) \gamma_0 - (1 - \xi)^2 \delta_0 + (1 + \xi)^2 \nu_0) \right. \\ \left. + (7\alpha_0 + 5\beta_0 - 7\gamma_0 + 5\delta_0 + 5\nu_0 + 8(-\alpha_0 + \beta_0 + \delta_0 + \nu_0)\xi + 2(5\alpha_0 - \beta_0 + 5\gamma_0 + 7\delta_0 - \nu_0)\xi^2) \frac{S_1}{4} \right] \\ + (\mathcal{D} + \mathcal{E}\xi - \frac{3\pi}{64}\xi^2) \frac{S}{r_0^4}, \quad (24c)$$

$$\xi = \frac{(\alpha_0 - \beta_0 - \delta_0 - \nu_0)(1 + S_1) - \frac{2\mathcal{E}S}{\sqrt{3}r_0^3}}{(\alpha_0 + \beta_0 + \gamma_0 - \delta_0 + \nu_0) + (5\alpha_0 - \beta_0 + 5\gamma_0 + 7\delta_0 - \nu_0) \frac{S_1}{2} - \frac{\sqrt{3}\pi S}{16r_0^3}}. \quad (24d)$$

Here the numerical constants  $\mathcal{B}, \mathcal{C}, \mathcal{D}, \mathcal{E}$  are

$$\mathcal{B} \equiv +0.034811170691607, \quad (25a)$$

$$\mathcal{C} \equiv -0.194730246474826, \quad (25b)$$

$$\mathcal{D} \equiv -0.106067915910315, \quad (25c)$$

$$\mathcal{E} \equiv +0.707179791600111. \quad (25d)$$

The constants  $\beta_0, \gamma_0$  and  $\delta_0$  in Eqns. (24a-d) represent the averages between anion and cation values, as defined in Eqn. 4. This averaging is not an approximation but an outcome of the calculation that is related to the symmetry properties of the crystal.

From Eqn. 15 and Eqns. (24a-d) it can be seen that a) the contributions of the harmonic parameters to the crystal energy have the same order of magnitude and b) there is an intricate interplay between the parameters when it comes to crystal distortions. It is therefore nontrivial to make any judgment on the signs that the parameters should have. Indeed, any combination of positive and negative parameters will increase the crystal energy in the presence of distortions as long as the resulting elastic constants are positive. This situation is further complicated by the fact that the elastic constants are invariant with respect to sign inversion of the cation and anion values of  $\beta, \gamma$  and  $\delta$ .

*Comparison to other models and validation:* It is important to put Eqns. (24a-d) in context with earlier work. The equations are consistent with Ref. 13 in the limit of nonionic crystals, apart from the prefactor in front of  $\delta_0$  in the expression for  $C_{44}$ . The numerical constant  $\mathcal{B}$  is very close to equivalent expressions found in Refs. 1 and 32, the results of which are used in other work related to the Coulomb interaction in zincblende crystals.<sup>33,34</sup> However, the cited calculations assume two-body cen-

tral forces for the repulsive interaction while Eqn. 1 violates this assumption. Although the purely Coulombic terms are not influenced by this disparity, a deviation from the total expressions for the elastic constants obtained in Refs. 1 and 32 can be expected. Furthermore, a comparison of the Coulomb energies for an unstrained crystal and a crystal with small hydrostatic strain yields the relation

$$\mathcal{C} = \frac{3\sqrt{3}\alpha_M}{16} - \frac{\mathcal{B}}{2}, \quad (26)$$

which is fulfilled by the values in Eqns. 25a and 25b. Another validation of Eqns. (24a-d) is given by comparison to sound velocities evaluated from Eqn. 13. The following relations hold for cubic crystals:<sup>23</sup>

$$c_s^{TA}[100] = \sqrt{C_{44}/\rho}, \quad (27a)$$

$$c_s^{LA}[100] = \sqrt{C_{11}/\rho}, \quad (27b)$$

$$c_s^{TA1}[110] = \sqrt{(C_{11} - C_{12})/(2\rho)}, \quad (27c)$$

$$c_s^{TA2}[110] = \sqrt{C_{44}/\rho} = c_s^{TA}[100], \quad (27d)$$

$$c_s^{LA}[110] = \sqrt{(C_{11} + 2C_{12} + 4C_{44})/(2\rho)}, \quad (27e)$$

$$c_s^{TA}[111] = \sqrt{(C_{11} - C_{12} + C_{44})/(3\rho)}, \quad (27f)$$

$$c_s^{LA}[111] = \sqrt{(C_{11} + 2C_{12} + 4C_{44})/(3\rho)}, \quad (27g)$$

where  $\rho = 4(M_C + M_A)/a^3$  is the mass density. These simple relations are indeed satisfied by the results in Section IV. Using Eqns. 24 and 27, the elastic constants and sound velocities can be predicted analytically from the VFF parameters without the need for numerical phonon energy computations.



Constant	P8	P5	P8/C	P5/C	P8/el	P5/el
$\alpha_0$ [N/m]	38.8356	39.3883	45.0000	38.9425	43.2347	43.8470
$\beta_{0,ACA}$ [N/m]	1.9074	2.8660	13.0980	4.0663	-2.6178	3.1854
$\beta_{0,CAC}$ [N/m]	12.8298	2.8660	-5.1908	4.0663	11.3187	3.1854
$\gamma_{0,ACA}$ [N/m]	81.6749	0.0	19.2399	0.0	48.0814	0.0
$\gamma_{0,CAC}$ [N/m]	-88.4692	0.0	-22.4448	0.0	-54.3912	0.0
$\delta_{0,ACA}$ [N/m]	45.6625	1.7962	5.1675	0.0	22.0988	4.5357
$\delta_{0,CAC}$ [N/m]	-43.7240	1.7962	-10.0261	0.0	-16.4250	4.5357
$\nu_0$ [N/m]	1.9238	6.5832	5.6298	5.8559	3.3087	3.9710
$Z$ [e]	0.658741	0.658741	0.0	0.0	0.658741	0.658741
$A_\alpha$ [nm <sup>-1</sup> ]	-13.1091	-12.1307	-11.5785	-12.9325	-13.0084	-12.1712
$A_\beta$	-2.7353	-11.3577	-4.8975	-3.5689	-10.3376	-15.0271
$A_\gamma$	-3.2391	—	-15.4117	—	-11.3817	—
$A_\delta$	-10.0070	1.1664	-11.0843	—	-7.2233	-3.0958
$A_\nu$	-23.1807	-5.8621	-5.4246	-3.7367	6.6924	-4.6313

TABLE I: Force constants (see Eqn. 1) and anharmonicity correction parameters (see Eqn. 5) for gallium arsenide. The columns correspond to the full model (P8), 5-parameter model (P5), 8-parameter model excluding Coulomb interaction (P8/C), 5-parameter model excluding Coulomb interaction (P5/C), 8-parameter model disregarding the elastic constants (P8/el) and 5-parameter model disregarding the elastic constants (P5/el).

#### IV. RESULTS FOR GALLIUM ARSENIDE

This section presents and discusses sets of force constants obtained by numerically fitting the model outcomes against experimental targets. It is anticipated that the importance of the different lattice properties varies with the application of the model, and that parameters can be specialized to model certain problems particularly well. For example, in thermal transport problems the elastic constants may be disregarded for the benefit of having a better fitted phonon dispersion. On the other hand, the influence of optical modes is expected to be negligible in lattice relaxation problems or low-gradient phonon transport. Neglecting the Coulomb interaction, which poses tremendous computational challenges in large systems, is thus desirable for such problems. Six different parameter sets are therefore presented in this work:

1. The full-fledged model presented in the preceding sections, termed P8, consists of 8 parameters for unstrained zincblende materials and an additional 5 parameters related to anharmonicity corrections. The parameters were fitted against targets for the phonon dispersion along three symmetry lines, sound velocities, elastic constants and (for the anharmonicity corrections) Grüneisen parameters.
2. A simpler fit termed P5 assumes the parameters  $\beta, \gamma$  and  $\delta$  to be the same for anions and cations, resulting in 5 free parameters for the unstrained case.

3. 4. Two fits against the acoustic phonon branches and elastic constants were performed under exclusion of the Coulomb interaction (P8/C, P5/C).
5. 6. Fits were performed against all phonon branches, disregarding the elastic constants (P8/el, P5/el).

The results of several other fits are not reported in detail here. It was empirically found that fits of the acoustic branches alone do not yield any significant improvement over the P8/C and P5/C fits. Fits of the acoustic branches and elastic constants which include the Coulomb interactions also do not improve the P8/C and P5/C fits, as can be expected. The authors also tried a six-parameter model where the stretch-bend interaction was neglected. This model yielded no significant improvement over the 5-parameter model.

As already mentioned in Section III B, an *a priori* determination of the correct signs of the model parameters  $\beta, \gamma$  and  $\delta$  is not straightforward. The authors' experience is that fits of similar quality can be achieved with combinations of different, sometimes opposite, signs, thus suggesting ambiguities in the model parameters. For the lack of better knowledge, the convention is made that the cation values of  $\gamma$  and  $\nu$  be positive and the anion values be negative in the P8/el and P8/C fits. Furthermore, all parameters are chosen to be nonnegative in the P5 fits. The numerical computation of all quantities was performed using *NEMO5*, a nanoelectronics modeling tool developed by the authors to obtain a diverse range of nanostructure characteristics. The details of *NEMO5* are presented elsewhere.<sup>35</sup> The implementation was validated against literature results.<sup>6,11,13,18,36</sup>

Quantity [unit]	Exp.	P8	dev.	P5	dev.	P8/C	dev.	P5/C	dev.	P8/el	dev.	P5/el	dev.
$C_{11}$ [GPa]	119.0	120.20	1%	120.35	1%	120.83	2%	121.54	2%	129.32	9%	131.29	10%
$C_{12}$	53.4	55.53	4%	54.63	2%	51.33	-4%	51.33	-4%	75.43	41%	80.77	51%
$C_{44}$	59.6	58.26	-2%	54.57	-8%	58.86	-1%	55.95	-6%	51.42	-14%	45.52	-24%
$c_s^{TA}[100]$ [km/s]	3.34	3.31	-1%	3.20	-4%	3.32	-1%	3.24	-3%	3.11	-7%	2.93	-12%
$c_s^{LA}[100]$	4.73	4.75	0%	4.76	1%	4.76	1%	4.78	1%	4.93	4%	4.97	5%
$c_s^{TA1}[110]$	2.47	2.47	0%	2.49	1%	2.55	3%	2.57	4%	2.25	-9%	2.18	-12%
$c_s^{TA2}[110]$	3.34	3.31	-1%	3.20	-4%	3.33	0%	3.24	-3%	3.11	-7%	2.93	-12%
$c_s^{LA}[110]$	5.24	5.24	0%	5.17	-1%	5.22	0%	5.17	-1%	5.38	3%	5.34	2%
$c_s^{TA}[111]$	2.78	2.78	0%	2.75	-1%	2.83	2%	2.81	1%	2.57	-8%	2.45	-12%
$c_s^{LA}[111]$	5.39	5.40	0%	5.30	-2%	5.36	-1%	5.30	-2%	5.52	2%	5.46	1%
$\xi$	ca. 0.55	0.575	5%	0.526	-4%	0.67	22%	0.59	7%	0.67	22%	0.634	15%
$\hbar\omega_{LO}(\Gamma)$ [meV]	36.35	36.07	-1%	37.16	2%	40.23	11%	37.58	3%	36.50	0%	36.98	2%
$\hbar\omega_{TO}(\Gamma)$	33.62	33.17	-1%	34.35	2%	40.23	20%	37.58	12%	33.63	0%	34.15	2%
$\hbar\omega_{LO}(X)$	29.78	28.90	-3%	27.73	-7%	29.27	-2%	28.15	-5%	29.30	-2%	29.14	-2%
$\hbar\omega_{TO}(X)$	31.80	32.42	2%	30.11	-5%	37.09	17%	33.55	6%	32.12	1%	31.00	-3%
$\hbar\omega_{LA}(X)$	27.91	27.20	-3%	26.76	-4%	27.76	-1%	27.15	-3%	27.57	-1%	28.11	1%
$\hbar\omega_{TA}(X)$	10.13	8.93	-12%	10.58	4%	10.06	-1%	10.83	7%	10.00	-1%	10.93	8%
$\hbar\omega_{LO}(L)$	29.98	30.45	2%	27.61	-8%	31.67	6%	29.34	-2%	30.97	3%	29.37	-2%
$\hbar\omega_{TO}(L)$	32.67	32.04	-2%	32.28	-1%	38.64	18%	35.62	9%	32.62	0%	32.60	0%
$\hbar\omega_{LA}(L)$	25.64	24.81	-3%	25.21	-2%	23.47	-8%	23.56	-8%	24.64	-4%	26.14	2%
$\hbar\omega_{TA}(L)$	7.86	8.83	12%	6.92	-12%	7.35	-6%	7.66	-3%	7.59	-3%	7.22	-8%
$\gamma_{LO}(\Gamma)$	1.23	1.34	9%	1.23	0%	1.23	0%	1.31	7%	1.16	-6%	1.23	0%
$\gamma_{TO}(\Gamma)$	1.39	1.50	8%	1.36	-2%	1.23	-12%	1.31	-6%	1.28	-8%	1.36	-2%
$\gamma_{LO}(X)$	1.01	0.79	-22%	1.11	10%	1.21	20%	1.16	15%	1.19	18%	1.12	11%
$\gamma_{TO}(X)$	1.73	1.51	-13%	1.73	0%	1.49	-14%	1.69	-2%	1.73	0%	1.74	1%
$\gamma_{LA}(X)$	1.22	1.44	18%	1.11	-9%	1.01	-17%	1.16	-5%	1.08	11%	1.12	-8%
$\gamma_{TA}(X)$	-1.62	-1.86	15%	-1.39	-14%	-1.75	8%	-1.57	-3%	-1.62	0%	-1.44	-11%
$\gamma_{LO}(L)$	1.62	1.38	-15%	1.59	-2%	1.52	-6%	1.71	6%	1.53	-6%	1.60	-1%
$\gamma_{TO}(L)$	1.5	1.59	6%	1.51	1%	1.34	-11%	1.47	-2%	1.51	1%	1.52	1%
$\gamma_{LA}(L)$	0.56	0.68	21%	0.64	14%	0.57	2%	0.55	-2%	0.74	32%	0.60	7%
$\gamma_{TA}(L)$	-1.7	-1.45	-15%	-1.92	13%	-1.75	3%	-1.76	4%	-1.70	0%	-1.87	10%

TABLE II: Comparison of literature values versus model results for the lattice properties of GaAs. The different models P8, P5, P8/C, P5/C, P8/el and P5/el are discussed in the text. The column to the right of P8 displays the deviation between calculated and experimental values.

### A. Model parameter sets and comparison to experimental values

The fitted parameter sets are displayed in Table I. The procedure for obtaining these sets via genetic algorithms is outlined in Appendix B and, to a more detailed extent, in Ref. 37. Table II compares the model outcomes and experimental targets. Experimental values for the targets are taken from Ref. 38 for the room temperature elastic constants  $C_{ij}$  and sound velocities  $c_s$ . The value of the internal strain parameter  $\xi$  has a large uncertainty<sup>39</sup> but seems to be roughly 0.55.<sup>40</sup> Data from Ref. 41 is used for the phonon spectra and frequencies at high-symmetry points. It is noted that even though the measurements in Ref. 41 were taken at  $T = 12\text{K}$ , the temperature dependence is expected to be relatively small<sup>42</sup> and the authors were unable to find comparable room-temperature data. Targets for the Grüneisen parameters are taken from experi-

mental data<sup>43</sup> for  $\gamma_{LO,TO}(\Gamma)$ ,  $\gamma_{TO,TA}(X)$  and  $\gamma_{TO,TA}(L)$  and from *ab initio* calculations<sup>44</sup> for  $\gamma_{LO,LA}(X)$  and  $\gamma_{TO,TA}(L)$ . The calculations use a lattice constant of  $a = 0.565324\text{nm}$  and atomic masses  $M_{Ga} = 69.723\text{amu}$  and  $M_{As} = 74.92160\text{amu}$ .

### B. Discussion of the fits

#### 1. Best overall fit

*Phonon spectra:* Figure 1 shows the result obtained by fitting the 8-parameter model against the sound velocities, the elastic constants, and the entire phonon dispersion (P8 parameter set). Also plotted for comparison is the Keating model with Martin's parameters<sup>8</sup> that were optimized for the elastic constants. The P8 fit slightly overestimates the coplanar interaction, as can be seen by the negative slope of the TA branch around X, and has



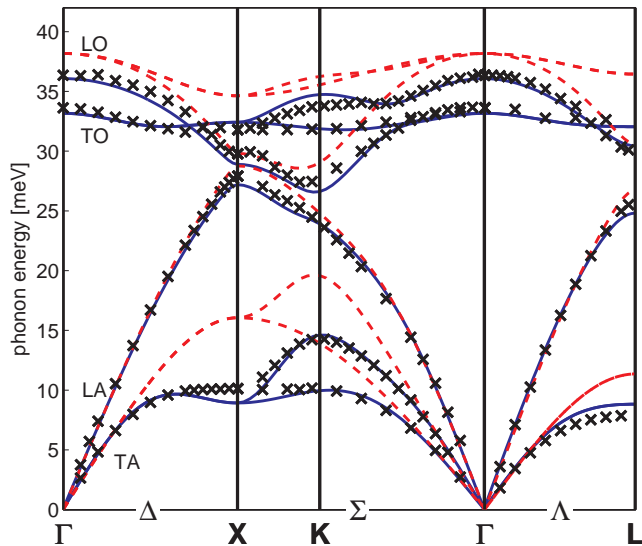


FIG. 1: Phonon dispersion of gallium arsenide. *Solid line*: P8 set of parameters (see Table I) fitted against the dispersion, the sound velocities and the elastic constants. *Dashed line* Keating model with  $\alpha = 41.19 \frac{N}{m}$ ,  $\beta = 8.94 \frac{N}{m}$ . *Crosses*: Experimental data.<sup>41</sup>

a large imbalance between anion and cation parameters. Also, the main quantitative deviations to experimental data occur at the zone boundary between  $X$  and  $K$  where the rigid ion model is most likely to break down.<sup>21</sup>

*Grüneisen parameters*: As mentioned in Subsec. II A, the Grüneisen parameter fits in Table II were obtained by comparing the phonon frequencies for a hydrostatic strain of 0.03 with the unstrained phonon frequencies. This may yield results which differ from the small-strain limit by as much as 10%. An accurate modeling of Grüneisen parameters has been problematic in the past. *Ab initio* calculations exhibit deviations from experiment of up to a factor of 2.<sup>3,45</sup> Ref. 17 used a rigid ion model to obtain results within 20% of experiment. In Ref. 46 a bond charge model calculation yielded agreement on the order of 10% or better when employing a finite hydrostatic strain of 0.01 for the finite-difference extraction. In Ref. 6 a different type of anharmonic correction was used to obtain the correct signs of all but one of the Grüneisen parameters within a Keating VFF description, however differences to experimental values of up to 90% remained. With these prior efforts in mind, and given some uncertainty about experimental methods, the maximum discrepancy of 22% in the fits of the Grüneisen parameters of the P8 model can be termed sufficiently accurate.

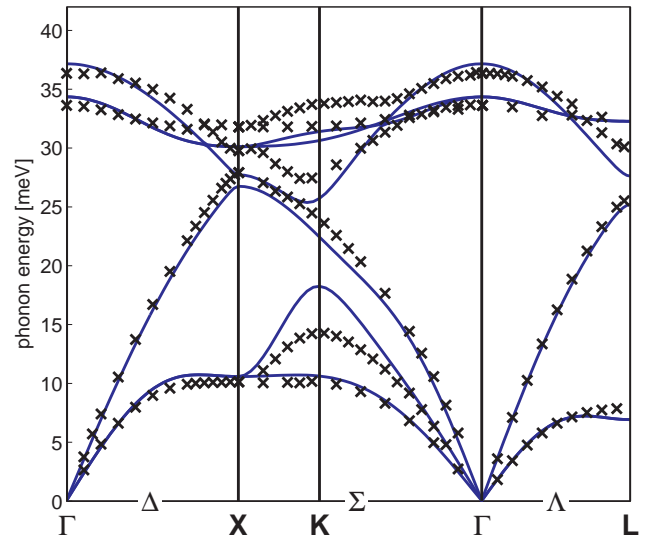


FIG. 2: Phonon dispersion of gallium arsenide obtained with the 5-parameter model (see Table I). *Solid line*: P5 parameter set. *Crosses*: Experimental data.<sup>41</sup>

## 2. 5-parameter fit

The 5-parameter fit is in qualitative disagreement with experiment for the optical branches along the  $\Sigma$ -line and overestimates the maximum of the upper TA mode around  $K$ . An accurate model for these parts of the phonon dispersion should employ 8 parameters. However, the 5-parameter model offers a good description of the low-frequency acoustic branches as well as the elastic constants. The maximum deviation from experiment for the lower TA mode occurs at  $L$  (12%). The Grüneisen parameters are fit better than for the P8 set, with a maximum discrepancy of 14%.

From Table I it is observed that the best 5-parameter fits employ no stretch-bend and only a small, if any, cross-stretch interaction. This stands in contrast to the coplanar interaction, which is essential in order to obtain flattened TA branches around  $X$  and  $L$ . Neglecting the coplanar interaction term results in either an overestimation of the zone-boundary phonon frequencies<sup>8</sup> or an underestimation of the frequencies around the zone-center and the speed of sound (such as with the  $n=1$  parameters in Ref. 14). In Ref. 14 the cross-stretch interaction was termed the least important out of all considered ones (the stretch-bend term was not included), which is consistent with the present findings. It was found in the scope of the present work, however, that a 6-parameter model which takes into account the different atom types but neglects the stretch-bend term, does not yield fits of the same quality as the 8-parameter model.

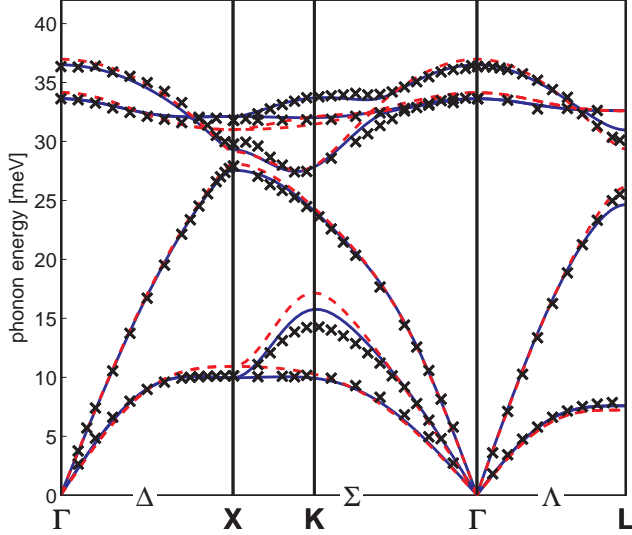


FIG. 3: Comparisons of results obtained using models fitted exclusively against the dispersion relation (see Table I). *Solid line*: P8/el parameter set. *Dashed line*: P5/el parameter set. *Crosses*: Experimental data.<sup>41</sup>

### 3. Fits neglecting the elastic constants

The requirement of matching the elastic constants is relaxed in the fits displayed in Fig. 3. The fitting process still incorporates the sound velocities to a small extent in order to retain physically meaningful values. The P8/el fit of the phonon dispersion seems less forced than the P8 fit and has parameters of smaller magnitude, but it allows for discrepancies versus experimental values of up to 40% in the elastic constants (see Table II). The discrepancy of the upper TA mode around  $K$  is larger than in the P8 set, suggesting that atom-type-dependent parameters which are large and of roughly opposite magnitude are required to fit it. The P5/el set models most of the phonon dispersion to a satisfactory degree but has both qualitative and quantitative deficiencies along the  $\Sigma$ -line near the zone boundary. The Grüneisen parameters are generally modeled well, with the exception of  $\gamma_{LA}(L)$  in the P8/el set. As with the P8 and P5 fits, the P5/el fit of the Grüneisen parameters has less deviations (max. 11%) than the P8/el fit (max. 32%).

### 4. Fits neglecting Coulomb interaction

For the modeling of large nanostructures consisting of thousands or millions of atoms, the long-range Coulomb interaction poses a serious challenge as it destroys the sparsity of the involved matrices. The P8/C and P5/C parameter sets were obtained by fitting the acoustic phonon branches as well as the elastic constants without Coulomb interaction. The obtained fits (Fig. 4)

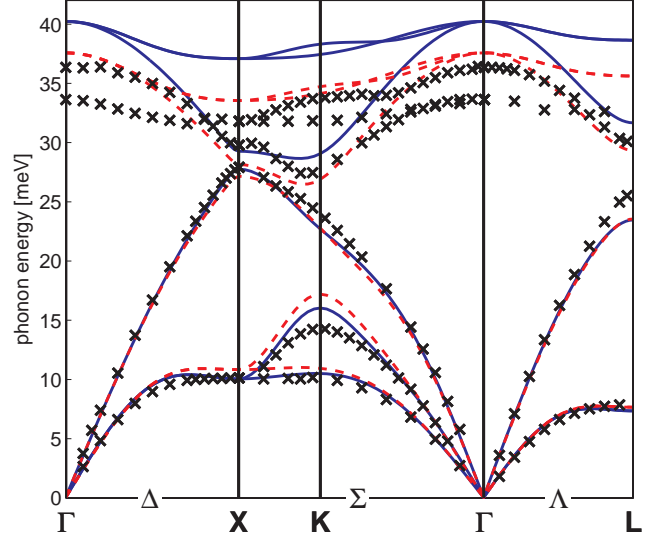


FIG. 4: Comparisons of results obtained using models without Coulomb interaction (see Table I). The parameter sets were obtained by fitting the acoustic branches and sound velocities, as well as the elastic constants. *Solid line*: P8/C parameter set. *Dashed line*: P5/C parameter set. *Crosses*: Experimental data.<sup>41</sup>

are sufficiently good as long as the optical modes are not of critical interest. The dispersion curves are lacking any LO-TO splitting and overestimate the optical phonon energies in general. Main deviations in the acoustic branches occur for the upper TA branch near  $K$  and the LA branch near  $L$ . The Grüneisen parameters for the acoustic modes are generally modeled well.

## C. Discussion of some model aspects

### 1. Influence of the correction of $d$

In Subsection III A it was argued that the model parameter  $d$  must deviate from the experimental bond length  $r_0$  in the presence of Coulomb interaction. Figure 5 displays the phonon dispersion obtained with the P8 parameter set for three different choices of  $d$ :  $d$  according to Eqn. 20 (same as Fig. 1),  $d = r_0$ , and  $d$  according to Eqn. 22. It is apparent that the choice of  $d$  has a large influence on the obtained results, and the parameter sets need to be consistent with this choice.  $d$  typically differs from  $r_0$  by 1.5-2%, but the simplification of using Eqn. 20 instead of Eqn. 22 only imposes minor changes on the order of  $10^{-4}r_0$  on the bond length and 0.1meV ( $<1\%$ ) on the dispersion. This provides an *a posteriori* justification of the simplification of using Eqn. 20 instead of Eqn. 22. The three cases reduce to one in the absence of Coulomb interaction.

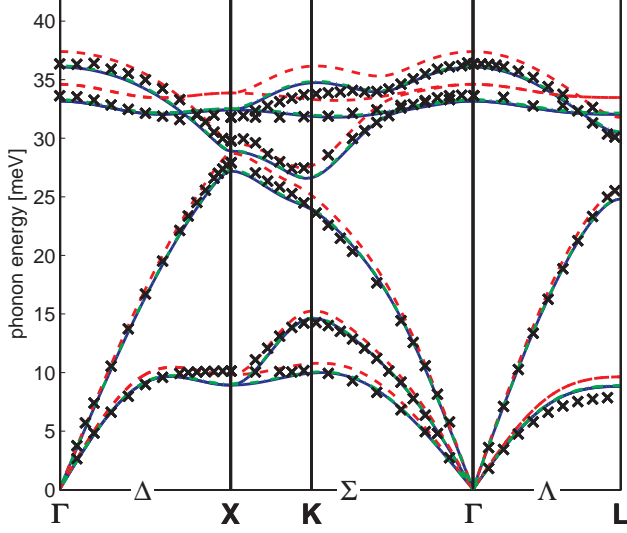


FIG. 5: Phonon dispersion of GaAs using the P8 parameter set in Table I and different choices of  $d$ . *Solid line*:  $d$  according to Eqn. 20. This was the choice for the fit. *Dashed line*:  $d = r_0$ . *Dash-dotted line*: (almost overlapping with the solid curve) Eqn. 22. *Crosses*: Experimental data.<sup>41</sup>

## 2. Anharmonicity and the elastic constants

Eqns. 24 for the second-order elastic constants are exact as long as the functional dependence of the VFF parameters on the bond lengths, given in Eqns. 5, is taken to be parametric, i.e. no spatial derivatives of the force constants are taken for the energy gradient and the dynamical matrix. Table III illustrates the difference to the case when the derivatives are included. A difference of up to 28% is observed when including Coulomb interactions, compared to less than 3% difference without it. The Coulomb interaction introduces a monotonically decaying long-range potential which is counterbalanced with the short-range VFF potential such that an energetic minimum energy at the equilibrium bond length is achieved. However, the short-range potential taken by itself has a non-vanishing first derivative  $\frac{\partial \delta r_{ij}}{\partial \epsilon}$  at this position, and anharmonicity thus yields contributions of the form  $\frac{\partial \alpha}{\partial \epsilon} \frac{\partial \delta r_{ij}}{\partial \epsilon}$ . The parametric dependence assumption therefore has a strong influence on the second-order elastic constants in systems with Coulomb interaction.

The authors have also derived equations for the six independent third-order elastic constants<sup>47,48</sup> under the assumption of a full (not parametric) anharmonic dependence of the VFF parameters. This can be achieved by expanding Eqns. 1 and 5 up to third order in the infinitesimal strain  $\epsilon_{ij}$  and transforming the results to the expansion in terms of the Lagrangian strain.<sup>47,48</sup> The third-order expansion of the energy depends heavily on the parametric dependence assumption. Alternatively, third-order constants can be extracted numerically from

Parameter set	P8	P5	P8/C	P5/C
$C_{11}$ ( <i>param.</i> ) [GPa]	120.2	120.4	120.8	121.5
$C_{11}$ ( <i>full</i> ) [GPa]	140.5	137.0	120.4	121.5
$C_{12}$ ( <i>param.</i> ) [GPa]	55.53	54.63	51.33	51.33
$C_{12}$ ( <i>full</i> ) [GPa]	75.70	71.20	52.59	51.33
$C_{44}$ ( <i>param.</i> ) [GPa]	58.26	54.57	58.86	55.95
$C_{44}$ ( <i>full</i> ) [GPa]	61.73	58.43	57.95	55.95

TABLE III: Influence of the anharmonicity model on the second-order elastic constants. *param.* denotes the values for a model where the dependence of the VFF parameters on the bond stretching (Eqns. 5) is taken to be parametric, i.e. no spatial derivatives are included in the dynamical matrix. The second-order elastic constants are then independent of the anharmonicity parameters (Eqns. 24). *full* denotes the values for a model where such derivatives are included.

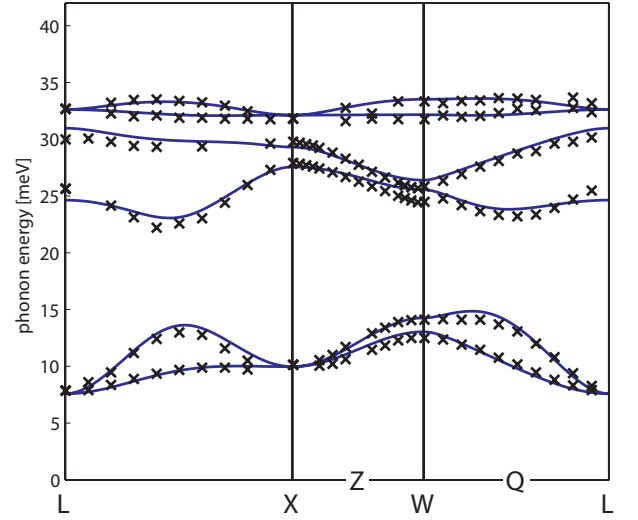


FIG. 6: Phonon dispersion of GaAs along the path  $L - X - W - L$ . *Solid line*: P8/el parameter set (see Table I). *Crosses*: Experimental data.<sup>41</sup>

the dependence of the sound velocities on hydrostatic and uniaxial pressure.<sup>49</sup> Incorporation of the third-order constants into the fitting process and understanding the relationship between third-order constants and anharmonic VFF parameters is the scope of future work.

## 3. Predictiveness of the model

The strength of any model is given by its ability to predict experimental data not included in the fitting process. While applications to nanostructures lie outside the scope of this work, a first indication of the model's predictive abilities is given by phonon frequencies which were not included in the fitting process. Fig. 6 compares the model versus experiment for the phonon dispersion path  $L - X - W - L$ . Good agreement is observed, suggesting a solid physical foundation of the chosen approach.

## V. CONCLUSION

This paper presents an extended valence force field model for the static and dynamic lattice properties of zincblende crystals, and applies it to gallium arsenide. The goal of the model is to provide a unified VFF description of isothermal elastic properties as well as phonon modes which agrees with experiment. Computational methods, in particular the software *Mathematica* for analytical transformations and *NEMO5*<sup>35</sup> for numerical phonon dispersion calculations, enable the following two main results: Eqn. 24, an expression for the elastic constants in zincblende materials as a function of the force constants and the fractional ionic charges, and Table I, parameter sets for gallium arsenide that are found by fitting against published experimental values. Good agreement between model and experiment was achieved for all considered quantities, surpassing prior VFF-based efforts.

The P8 parameter set represents the most consistent fit, but it is shown that for practical purposes good results can also be achieved using less parameters. The P5/C set, which excludes Coulomb interaction, may be employed for the static strain relaxation in nanostructures. The P5/el and P8/el models may be useful in the modeling of thermal transport or electron-phonon interactions.

## Acknowledgments

The authors would like to thank Profs. Roland Martin and Yann-Michel Niquet for discussions as well as Junzhe Geng, Yu He, Kai Miao and Parijat Sengupta for their help. This work was partially supported by grant EEC-0228390 of the National Science Foundation (NSF) that funds the Network for Computational Nanotechnology and by NSF PetaApps grant OCI-0749140. Support by the Semiconductor Research Corporation (SRC) and Intel Corporation is acknowledged.

## Appendix A: Ewald sum

An accurate computation of the long-range Coulomb interaction energy in a bulk crystal with point charges  $Z_i$  is achieved by adding and subtracting a charge distribution  $-Z_i G_\sigma(\mathbf{r})$  around every position  $\mathbf{r}_i$ , where  $G_\sigma$  is a normalized Gaussian distribution with standard deviation  $\sigma$ . The interaction then splits into a short-range part, which can be computed in real space by a finite sum over a few unit cells, and a long-range term that has a fast-decaying analytical expression in reciprocal space. The standard deviation  $\sigma$  of the Gaussian is a tunable parameter that allows for balancing short- and long-range contributions and reasonably small cut-offs in

both spaces. The Coulomb energy becomes<sup>26,27</sup>

$$\begin{aligned} U_{coul} &= U_S + U_L - U_{self} \\ &= \frac{1}{4\pi\epsilon_0} \frac{1}{2} \sum_{i=1}^N \sum_{\mathbf{n}} \sum_{j=1}^N, \frac{Z_i Z_j}{|\mathbf{r}_i - \mathbf{r}_j + \mathbf{R}_n|} \operatorname{erfc}\left(\frac{|\mathbf{r}_i - \mathbf{r}_j + \mathbf{R}_n|}{\sqrt{2}\sigma}\right) \\ &\quad + \frac{1}{2V_{prim}\epsilon_0} \sum_{\mathbf{G} \neq 0} \frac{\exp(-\sigma^2 G^2/2)}{G^2} |\mathcal{S}(\mathbf{G})|^2 \\ &\quad - \frac{1}{4\pi\epsilon_0} \frac{1}{\sqrt{2\pi}\sigma} \sum_{i=1}^N Z_i^2. \end{aligned} \quad (\text{A1})$$

Here  $\mathbf{R}_n = n_1 \mathbf{a}_1 + n_2 \mathbf{a}_2 + n_3 \mathbf{a}_3$  is a real-space lattice vector,  $\mathbf{G} = n_{k1} \mathbf{b}_1 + n_{k2} \mathbf{b}_2 + n_{k3} \mathbf{b}_3$  is a reciprocal lattice vector,  $\mathcal{S}(\mathbf{G}) \equiv \sum_i Z_i e^{i\mathbf{G}\cdot\mathbf{r}_i}$  is called structure factor and  $\operatorname{erfc}(x) \equiv 1 - \operatorname{erf}(x)$  is the complementary error function. We compute the sums using  $\sigma = 0.05 \text{ nm} \sim \frac{r_0}{5}$ , with a cutoff in reciprocal space of  $-5 \leq n_{ki} \leq 5$  and short-range interactions up to the second-nearest neighbor (cutoff range  $\sim 0.3 \text{ nm}$ ).

The computation of contributions to the dynamical matrix arising from Eqn. A1 is nontrivial due to non-analytical behavior at  $\mathbf{q} = 0$ .<sup>3,26</sup> The results obtained in Ref. 26 are replicated here for completeness. The contribution to the dynamical matrix element  $D_{i\mu,j\nu}(\mathbf{q})$  (where  $i, j$  are atom indices and  $\mu, \nu \in \{x, y, z\}$ , see Eqn. 9) arising from such Coulomb forces is

$$\begin{aligned} D_{i\mu,j\nu}^C(\mathbf{q}) &= -\frac{Z_i Z_j}{4\pi\epsilon_0 \sqrt{M_i M_j}} Q_{\mu\nu}(i, j|\mathbf{q}) \\ &\quad + \delta_{ij} \sum_{j'} \frac{Z_i Z_{j'}}{4\pi\epsilon_0 M_i} Q_{\mu\nu}(i, j'|\mathbf{0}). \end{aligned} \quad (\text{A2})$$

Here  $\delta_{ij}$  is the Kronecker symbol,  $V$  is the volume of the cell and the index  $j'$  runs over all the atoms of the considered cell.  $Q_{\mu\nu}(i, j|\mathbf{q})$  is defined as follows:

$$\begin{aligned} Q_{\mu\nu}(i, j|\mathbf{q}) &\equiv -\delta_{\mathbf{q} \neq 0} \frac{4\pi}{V} \frac{q_\mu q_\nu}{q^2} e^{-\sigma^2 q^2/2} e^{i\mathbf{q} \cdot (\mathbf{r}_i - \mathbf{r}_j)} \\ &\quad - \frac{4\pi}{V} \sum_{\mathbf{G} \neq 0} \frac{|\mathbf{G} + \mathbf{q}|_\mu |\mathbf{G} + \mathbf{q}|_\nu}{|\mathbf{G} + \mathbf{q}|^2} e^{-\sqrt{2}/4\sigma |\mathbf{G} + \mathbf{q}|^2} e^{i(\mathbf{G} + \mathbf{q}) \cdot (\mathbf{r}_i - \mathbf{r}_j)} \\ &\quad + \frac{1}{(\sqrt{2}\sigma)^3} \sum_{\mathbf{n}} H_{\mu\nu} \left( \frac{\mathbf{r}_i - \mathbf{r}_j + \mathbf{R}_n}{\sqrt{2}\sigma} \right) e^{-i\mathbf{q} \cdot (\mathbf{r}_i - \mathbf{r}_j + \mathbf{R}_n)}. \end{aligned} \quad (\text{A3})$$

The index  $\mathbf{n}$  includes the primary cell itself. The function  $H$  is defined as:

$$\begin{aligned} H_{\mu\nu}(\mathbf{x}) &\equiv \frac{x_\mu x_\nu}{x^2} \left( \frac{3}{x^3} \operatorname{erfc}(x) + \frac{2}{\sqrt{\pi}} \left( \frac{3}{x^2} + 2 \right) e^{-x^2} \right) \\ &\quad - \delta_{\mu\nu} \left( \frac{1}{x^3} \operatorname{erfc}(x) + \frac{2}{\sqrt{\pi}} \frac{1}{x^2} e^{-x^2} \right). \end{aligned} \quad (\text{A4})$$

The sound velocities in Table II were computed from finite differences in absence of the nonanalytic term on the first line of Eqn. A3. Inclusion of this term even for small  $\mathbf{q}$  results in erroneous values in particular for  $c_s^{TA2}[110]$  and  $c_s^{LA}[111]$ .

## Appendix B: Parameter fitting procedure

The parameter sets of Table I were found using a parallel genetic algorithm<sup>50</sup> (PGA) fitting method. This method is inspired and steered by biological processes. The fitting process starts with an initial population of random force constants which are coded as chromosomes. By applying selection, crossover and mutation processes to chromosomes, a better population is searched for. The measure of fitness is provided by a cost function which is taken as the sum of the weighted least-square residuals between the target values and model outputs. The GA process tries to minimize this cost function. The algorithm is stopped after a fixed number of iterations.

The fitting was divided into two phases: In a first phase, the 8 or 5 harmonic force constants  $\alpha_0, \beta_0, \gamma_0, \delta_0$  and  $\nu_0$  were fitted against some or all branches of the dispersion relation, the sound velocities, and possibly the elastic constants. Then, for fixed harmonic force constants, the anharmonic correction parameters  $A_\alpha, A_\beta, A_\gamma, A_\delta, A_\nu$  were fitted to the Grüneisen parameters.

Three issues needed to be considered in the process:

- A multi-objective cost function was used in order to obtain a variety of physical characteristics of the material. The process of assigning weights to the various targets is intricate and requires manual adjustment. Thus any fit reflects decisions on the relative importance of the targets which can be adjusted at will.
- Model inputs need to be constrained in order to retain their physical meaningfulness. This was achieved by adding a large penalty to the cost value when a parameter lies outside a certain range. The range consists of a maximum (soft-wall) boundary of 45 N/m for  $\alpha$  without which the GA for the acoustic mode fits would have pushed up the optical branches to unphysically high values. For the P8/el and P8/C sets the coefficients  $\beta, \gamma$  and  $\delta$  were restricted to have positive values for the cation and negative values for the anion, as ambiguities in the signs may exist in the model. The 5-parameter coefficients were restricted to be nonnegative.
- Errors in reported experimental values were initially accounted for by modifying the cost function to vanish within a certain range, typically 1%, of the target rather than just the target itself. However, this adjustment did not improve the fitting process, and the reported parameter sets do not include this feature.

An evolutionary algorithm was employed due to the complexity of the cost function and multi-objective nature of the problem. To speed up the solution process, the PGA was run on 8 cores simultaneously. Due to the randomness of the method, every optimization was performed 10

times and the best solution reported. More details about the process are given in Ref. 37.



\* Electronic address: [sebi.steiger@gmail.com](mailto:sebi.steiger@gmail.com)

† URL: <https://engineering.purdue.edu/gekcogrp/>

- <sup>1</sup> M. Born and E. Bormann, *Annalen der Physik* **367**, 218 (1920), ISSN 1521-3889.
- <sup>2</sup> K. Rustagi and W. Weber, *Solid State Communications* **18**, 673 (1976), ISSN 0038-1098.
- <sup>3</sup> P. Giannozzi, S. de Gironcoli, P. Pavone, and S. Baroni, *Phys. Rev. B* **43**, 7231 (1991).
- <sup>4</sup> M. Musgrave and J. Pople, *Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences* **268**, 474 (1962), ISSN 0080-4630.
- <sup>5</sup> P. Keating, *Physical Review* **145**, 637 (1966), ISSN 0031-899X.
- <sup>6</sup> O. Lazarenkova, P. Von Allmen, F. Oyafulo, S. Lee, and G. Klimeck, *Superlattices and Microstructures* **34**, 553 (2003), ISSN 0749-6036.
- <sup>7</sup> S. Lee, O. Lazarenkova, P. Von Allmen, F. Oyafulo, and G. Klimeck, *Physical Review B* **70**, 125307 (2004), ISSN 1550-235X.
- <sup>8</sup> R. Martin, *Physical Review B* **1**, 4005 (1970), ISSN 1550-235X.
- <sup>9</sup> H. Fu, V. Ozoliņš, and A. Zunger, *Physical Review B* **59**, 2881 (1999), ISSN 1550-235X.
- <sup>10</sup> K. Biswas, A. Franceschetti, and S. Lany, *Physical Review B* **78**, 85212 (2008), ISSN 1550-235X.
- <sup>11</sup> J. Zi, X. Wan, G. Wei, K. Zhang, and X. Xie, *Journal of Physics: Condensed Matter* **8**, 6323 (1996).
- <sup>12</sup> H. McMurtry, A. Solbrig Jr, and J. Boyter, *Journal of Physics and Chemistry of Solids* **28**, 2359 (1967), ISSN 0022-3697.
- <sup>13</sup> Z. Sui and I. Herman, *Physical Review B* **48**, 17938 (1993), ISSN 1550-235X.
- <sup>14</sup> E. Kane, *Physical Review B* **31**, 7865 (1985), ISSN 1550-235X.
- <sup>15</sup> A. Williamson, L. Wang, and A. Zunger, *Physical Review B* **62**, 12963 (2000).
- <sup>16</sup> K. Kim, P. Kent, A. Zunger, and C. Geller, *Physical Review B* **66**, 45208 (2002).
- <sup>17</sup> D. N. Talwar and M. Vandebyver, *Phys. Rev. B* **41**, 12129 (1990).
- <sup>18</sup> A. Paul, M. Luisier, and G. Klimeck, *Journal of Computational Electronics* **9**, 160 (2010), ISSN 1569-8025.
- <sup>19</sup> E. Kellermann, *Philosophical Transactions of the Royal Society of London. Series A, Mathematical and Physical Sciences* **238**, 513 (1940), ISSN 0080-4614.
- <sup>20</sup> K. Kunc, M. Balkanski, and M. A. Nusimovici, *Phys. Rev. B* **12**, 4346 (1975).
- <sup>21</sup> K. Kunc, M. Balkanski, and M. Nusimovici, *physica status solidi (b)* **72**, 229 (1975), ISSN 1521-3951.
- <sup>22</sup> W. Harrison, *Elementary Electronic Structure* (World Scientific, 2004).
- <sup>23</sup> P. Yu and M. Cardona, *Fundamentals of Semiconductors* (Springer, Berlin, 2005).
- <sup>24</sup> R. Martin, *Physical Review* **186**, 871 (1969), ISSN 0031-899X.
- <sup>25</sup> W. Weber, *Physical Review B* **15**, 4789 (1977), ISSN 1550-235X.
- <sup>26</sup> A. Maradudin, E. Montroll, G. Weiss, and I. Ipatova, *Theory of lattice dynamics in the harmonic approximation* (Academic press New York, 1963).
- <sup>27</sup> H. Lee and W. Cai, *Ewald summation for coulomb interactions in a periodic supercell*, [http://micro.stanford.edu/mediawiki/images/4/46/Ewald\\_notes.pdf](http://micro.stanford.edu/mediawiki/images/4/46/Ewald_notes.pdf) (Jan 2009), retrieved online Apr 21 2011.
- <sup>28</sup> H. Ruecker and M. Methfessel, *Physical Review B* **52**, 11059 (1995), ISSN 1550-235X.
- <sup>29</sup> D. Vanderbilt, S. Taole, and S. Narasimhan, *Physical Review B* **40**, 5657 (1989).
- <sup>30</sup> F. Cerdeira, C. Buchenauer, F. Pollak, and M. Cardona, *Physical Review B* **5**, 580 (1972).
- <sup>31</sup> F. Grosse and J. Neugebauer, *Physical Review B* **63**, 85207 (2001), ISSN 1550-235X.
- <sup>32</sup> M. Blackman, *Philosophical Magazine* **3**, 831 (1958), ISSN 1478-6435.
- <sup>33</sup> A. Rajagopal and R. Srinivasan, *Zeitschrift fuer Physik A Hadrons and Nuclei* **158**, 471 (1960), ISSN 0939-7922.
- <sup>34</sup> J. Vetelino and S. Mitra, *Solid State Communications* **7**, 1181 (1969), ISSN 0038-1098.
- <sup>35</sup> S. Steiger, M. Povolotskyi, T. Kubis, H.-H. Park, and G. Klimeck, *IEEE Transactions on Nanotechnology* (Manuscript accepted) (2011).
- <sup>36</sup> S. Yamakawa, R. Akis, N. Faralli, M. Saraniti, and S. Goodnick, *Journal of Physics: Condensed Matter* **21**, 174206 (2009).
- <sup>37</sup> M. Salmani-Jelodar, S. Steiger, A. Paul, and G. Klimeck, in *Proceedings of the 2011 IEEE Congress on Evolutionary Computation* (2011).
- <sup>38</sup> S. Adachi, *Properties of Group-IV, II-V and II-VI Semiconductors* (Wiley, New York, 2005).
- <sup>39</sup> O. Madelung, U. Rössler, and M. e. Schulz ([www.springermaterials.com](http://www.springermaterials.com)).
- <sup>40</sup> C. Cousins, L. Gerward, J. Olsen, B. Selsmark, B. Sheldon, and G. Webster, *Semiconductor Science and Technology* **4**, 333 (1989).
- <sup>41</sup> D. Strauch and B. Dorner, *Journal of Physics: Condensed Matter* **2**, 1457 (1990).
- <sup>42</sup> R. Cottam and G. Saunders, *Journal of Physics C: Solid State Physics* **6**, 2105 (1973).
- <sup>43</sup> B. Weinstein and R. Zallen, *Light Scattering in Solids IV (Eds. M. Cardona and G. Guntherodt)* (Springer, 1984).
- <sup>44</sup> A. Debernardi and M. Cardona, *Physical Review B* **54**, 11305 (1996).
- <sup>45</sup> K. Kunc and R. M. Martin, *Phys. Rev. B* **24**, 2311 (1981).
- <sup>46</sup> R. Eryigit and I. P. Herman, *Phys. Rev. B* **53**, 7775 (1996).
- <sup>47</sup> P. N. Keating, *Phys. Rev.* **149**, 674 (1966).
- <sup>48</sup> J. M. Skipp and D. J. Dunstan, *Phys. Rev. B* **69**, 054105 (2004).
- <sup>49</sup> R. N. Thurston and K. Brugger, *Phys. Rev.* **133**, A1604 (1964).
- <sup>50</sup> E. Cantú-Paz, *Calculateurs paralleles, reseaux et systems repartis* **10**, 141 (1998).