



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Density functional theory study on the electronic structure of n- and p-type doped SrTiO₃ at anodic solid oxide fuel cell conditions

Suwit Suthirakun, Salai Cheettu Ammal, Guoliang Xiao, Fanglin Chen, Hans-Conrad zur Loye, and Andreas Heyden

Phys. Rev. B **84**, 205102 — Published 4 November 2011

DOI: [10.1103/PhysRevB.84.205102](https://doi.org/10.1103/PhysRevB.84.205102)

Density Functional Theory Study on the Electronic Structure of n- and p-type Doped SrTiO₃ at Anodic Solid Oxide Fuel Cell Conditions

Suwit Suthirakun¹, Salai Cheettu Ammal¹, Guoliang Xiao², Fanglin Chen², Hans-Conrad zur Loye³, and Andreas Heyden*¹

¹*Department of Chemical Engineering, University of South Carolina, 301 S. Main St., Columbia, South Carolina 29208, USA*

²*Department of Mechanical Engineering, University of South Carolina, 300 S. Main St., Columbia, South Carolina 29208, USA*

³*Department of Chemistry and Biochemistry, University of South Carolina, 631 Sumter Street, Columbia, South Carolina 29208, USA*

*Corresponding author, Email: HEYDEN@cec.sc.edu

The electronic conductivity and thermodynamic stability of mixed n-type and p-type doped SrTiO₃ have been investigated at anodic solid oxide fuel cell (SOFC) conditions using density functional theory (DFT) calculations. In particular, constrained *ab initio* thermodynamic calculations have been performed to evaluate the phase stability and reducibility of various Nb- and Ga-doped SrTiO₃ at synthesized and anodic SOFC conditions. The density of states of these materials was analyzed to study the effects of n- and p-doping on the electronic conductivity. In agreement with experimental observations, we find that the transformation from 20% Nb-doped Sr-deficient SrTiO₃ to a non Sr-deficient phase occurs at high temperature and low oxygen partial pressure which leads to a significant improvement in electronic conductivity. A mixed ionic/electronic conductor is obtained when doping 20% Nb-doped SrTiO₃ with small amounts of Ga (10%) in a reducing environment and high temperature. Doping with higher concentrations of Ga, e.g., 20%, diminishes the electronic conductivity of the material. These findings suggest that independent of the specific dopant, mixed ionic/electronic conductivity can be obtained in perovskite oxides under reducing

conditions and high temperatures by doping the B-site with small amounts of both n-type and p-type dopants.


I. INTRODUCTION

Although Ni supported yttria stabilized zirconia (Ni/YSZ) cermet exhibits very good catalytic activity for fuel oxidation in solid oxide fuel cells (SOFCs), it is easily poisoned by small amounts of sulfur impurities in the fuel gas.¹ Moreover, it is prone to sintering²⁻⁴ and coking when exposed to hydrocarbon fuels.⁵ As a result, exploring alternative SOFC anode materials to replace Ni/YSZ has become a crucial subject for the development of SOFC technology. Of the novel anode catalysts, perovskite based materials have been shown to satisfy most intrinsic SOFC anode requirements such as high mixed ionic/electronic conductivity, good catalytic activity, and high thermodynamic stability at anodic conditions.⁶⁻¹² Furthermore, perovskite based materials possess high resistance to sulfur impurities¹³⁻¹⁵ and coke formation^{5, 6, 16, 17} since both sulfur and carbon species can easily be oxidized at the surface of the perovskite oxide.¹⁸

Among the numerous perovskite systems that have been explored, SrTiO₃ based perovskites have been widely used as alternative SOFC anode materials.^{8, 9, 14, 19} Indeed, several research groups have reported that SrTiO₃ based perovskites exhibit some advantages over Ni/YSZ anode catalysts, such as promising mixed ionic/electronic conductivity, adequate thermodynamic stability in a wide range of oxygen partial pressure, and tolerance to sulfur impurities as well as coke formation.^{9, 13-15} Moreover, it has been found that yttrium doped SrTiO₃ (SYT) possesses a thermal expansion coefficient compatible with that of YSZ and Lanthanum Strontium Gallium Magnesium Oxide (LSGM) based electrolytes.⁹

However, stoichiometric SrTiO₃ is a band insulator with a band gap of 3.2 eV.²⁰ Therefore, various dopants have been introduced to improve the electronic conductivity of this material. It is well known that doping the material with either n- or p-type dopants can enhance the degree of electronic conduction.²¹⁻²⁵ For example, the transformation from an insulating state to a metallic state has been observed when doping SrTiO₃ with n-type impurities such as La, Y, and Nb.^{14, 26-28} In addition, theoretical studies have suggested that substituting Ti with n-type dopants can shift the Fermi level into the conduction band making the system metallic.^{23, 29}


It is well known that the substitution of n-type dopants in the SrTiO₃ lattice generates a defect with an effective positive charge in the host lattice. Overall electroneutrality of the lattice can be achieved by two different mechanisms, namely, electronic compensation and cation-vacancy compensation.³⁰⁻³² At low oxygen chemical potential, the formal charges of n-type dopants are electronically compensated by creating conduction electrons that travel along the Ti–O–Ti bridge where Ti remains mixed-valent Ti³⁺/Ti⁴⁺.³³ This electron transferring process is considered to be the origin of the electronic conductivity of the material.³⁴ On the other hand, at higher oxygen chemical potential the excess positive charge can be compensated by generating Sr²⁺ cation vacancies.³⁵ This type of electron compensation provides no conduction electrons and there is no improvement in electronic conductivity. For example, Kolodiazhnyi and Petric²⁸ found that TiO₂ and niobium oxide second phases were formed when sintering the Sr_{1-x/2}Ti_{1-x}Nb_xO₃ (x = 0.17) at low oxygen partial pressure and high temperature. This transformation can be expressed with the following equation:



where $y < x \leq 0.2$.

Furthermore, they observed a very high electronic conductivity of $\text{Sr}_{0.9}\text{Ti}_{0.8}\text{Nb}_{0.2}\text{O}_3$ and $\text{Sr}_{0.88}\text{Y}_{0.08}\text{TiO}_3$ when these samples were sintered in forming gas.²⁸

In contrast to n-type doping, p-type dopants create an effective negative charge in the lattice. One way to neutralize the charge is introducing oxygen vacancies in the lattice. This mechanism of charge neutralization can take place at moderate oxygen chemical potentials and does generally not lead to improved electronic conductivity since there is no transfer of charges or electrons into the lattice. However, lowering the oxygen chemical potential can result in more oxygen vacancies, leading to an excess electron density in the lattice. The reduction reaction takes place at the surface of the material and delivers electrons to the lattice.³⁶



(2)

These conduction electrons can often be transferred to neighboring atoms such as Ti which can be mixed-valent $\text{Ti}^{3+}/\text{Ti}^{4+}$. As a result, the electrical conductivity of the material is again improved.

The addition of p-type impurities not only improves the electronic conductivity but also enhances the ionic conductivity by increasing the reducibility and number of oxygen vacancies in the material. Furthermore, the amount of available oxygen vacancies plays an essential role in the enhancement of the oxide ion diffusivity (D_{O_2}) in the lattice as evidenced by the following equation³⁷:

$$D_{V_O} = \beta [V_O] \alpha^2 \nu_0 e^{-\Delta H_m / RT}$$

(3)

where $[V_O]$ is the concentration of mobile vacancies, α is the cell parameter, ν_0 is a characteristic lattice frequency, ΔH_m is the enthalpy of vacancy migration, T is temperature, R is the ideal gas constant, and $\beta = \frac{z}{\xi} f e^{-\Delta S_m / R}$ is a function of the number of equivalent near-neighbor sites, z , the entropy of ion migration, ΔS_m , and a correction factor, f (≈ 1). It is noted that the mobile vacancy concentration is usually smaller than the stoichiometric concentration due to vacancy trapping or vacancy ordering.^{38, 39}

Recently, various research groups reported that the catalytic activity and mixed ionic/electronic conductivity of n-type doped SrTiO₃ can be modified by B-site doping with p-type impurities such as Sc, Mn and Ga.⁴⁰ For example, Li et al.^{41, 42} suggested that doping with Sc and Co at the B-site of La_{0.3}Sr_{0.7}TiO₃ can improve its ionic conductivity. Similarly, Xiao et al.⁴³ and Neagu and Irvine⁴⁴ proposed a similar doping strategy to improve the conductivity of n-type doped SrTiO₃ by enhancing bulk oxide ion mobility. In particular, they studied the effects of Ga dopants on the reducibility and conductivity of n-type doped SrTiO₃ systems by varying the concentration of Ga. They found that Ga doping promotes fast reduction and improves the phase stability of the material in an oxidizing environment. Impressive improvements in total conductivity were observed when doping with small amounts of Ga.

It is the objective of this theoretical study to further investigate the effect of concurrent n- and p-doping on the number of oxygen vacancies and the electronic conductivity of SrTiO₃ perovskites. In particular, we performed density functional theory (DFT) calculations of Nb- and Ga-doped SrTiO₃ and analyzed the electronic structure of

the resulting materials. To evaluate the thermodynamic stability of doped SrTiO₃ phases at synthesized and anodic SOFC conditions, we furthermore performed constrained *ab initio* thermodynamic simulations.

II. COMPUTATIONAL DETAILS

A. Crystallographic data of SrTiO₃

Stoichiometric SrTiO₃ develops an ideal cubic perovskite structure at room temperature with *Pm3m* space group. The structural phase transition from cubic to tetragonal and to orthorhombic occurs at 110 and 65 K, respectively.⁴⁵ The cubic unit cell includes one molecular unit of SrTiO₃. As shown in Fig. 1(a), the structure contains 12-coordinated strontium ions occupying corner positions of the cube whereas the titanium ion, at the center of the cubic cell, is surrounded by six oxygen ions forming a TiO₆ octahedral unit. The octahedral units are connected by a sharing Ti-O-Ti bridge, forming a three-dimensional framework.

B. Computational method

To investigate the bulk electronic properties of stoichiometric and doped SrTiO₃, we initially optimized the lattice parameter of the SrTiO₃ unit cell and created a 100 atom supercell containing twenty unit cells (5×2×2). To generate doped structures we replaced B-site cations (Ti) with various amounts of n-type (Nb) and p-type (Ga) dopants. Substitution of two Ti atoms with two dopants yields 10% B-site doped SrTiO₃, etc. In order to better understand the charge compensation mechanism in n- and p-type doped systems, both A-site deficient and reduced structures were created by generating

strontium vacancies and oxygen vacancies, respectively. In this study, we considered up to two strontium vacancies and three oxygen vacancies in each structure. For all doped structures, we employed the lattice parameter of 20% Nb-doped SrTiO₃ and tried close to all ion position possibilities to identify the lowest energy structures.

All calculations performed for this study are based on the plane wave density functional theory implementation of the Vienna Ab initio Simulation Package (VASP 4.6).^{46, 47} We used the projector-augmented wave (PAW) method to represent the inner core potentials⁴⁶ and treated the Sr *4s4p5s*, Ti *3d4s*, O *2s2p*, Nb *4p5s4d*, and Ga *4s4p* as valence electrons. The cutoff of the kinetic energy was set for all calculations to 400 eV. Exchange correlation is described within the generalized gradient approximation (GGA) with the Perdew-Burke-Ernzerhof (PBE) functional.⁴⁸ All calculations are spin-polarized and Brillouin zone integration was performed with a 2×5×5 Monkhorst-Pack k-point mesh.⁴⁹ For density of state (DOS) calculations we used a 4×10×10 k-mesh. In all structure optimizations, all atoms are fully relaxed until the Hellman-Feynman forces are less than 0.02 eV Å⁻¹.

Our calculated stoichiometric SrTiO₃ bulk unit cell has an optimized lattice constant of 3.948 Å which is in reasonable agreement to the experimental value of 3.90 Å.⁵⁰ The optimized supercell of 20% Nb-doped SrTiO₃ exhibits only a very small change in lattice parameters (3.949 Å) to that of stoichiometric SrTiO₃. Computations predict a Sr-O and Ti-O bond distance of 2.792 and 1.974 Å, respectively. As illustrated in Fig. 1(b), the density of states of stoichiometric SrTiO₃ exhibits insulating behavior with a band gap of 1.80 eV. It should be noted that while DFT within the GGA approximations is known to underestimate band gaps, several studies showed excellent agreement in the

predicted electronic behavior of doped oxides computed by DFT within the GGA approximation and experimental observation.⁵¹⁻⁵³

III. RESULTS AND DISCUSSION

In this work, we are most interested in the electronic properties of n- and p-type doped SrTiO₃. Kolodiazhnyi and Petric²⁸ observed experimentally that Sr_{0.9}Ti_{0.8}Nb_{0.2}O₃ exhibits a very high conductivity at low oxygen chemical potential and Xiao et al.⁴³ suggested that the reducibility of this material can be promoted by doping with a certain (small) amount of p-type dopant (Ga). Therefore, we performed three different sets of calculations based on the concentration of B-site dopants, i.e., 20% Nb-doped SrTiO₃, 10% Ga- and 20% Nb-doped SrTiO₃, and 20% Ga- and 20% Nb-doped SrTiO₃. In this way we can systematically study the effect of Ga (p-type) doping on Nb (n-type) doped SrTiO₃ on the reducibility/phase stability and electronic conductivity/density of states of the resulting materials.


For all structures we first performed constrained *ab initio* thermodynamic calculations to evaluate the relative thermodynamic stability of the systems. This *ab initio* thermodynamic approach allows us to calculate the free energy of different systems as a function of oxygen chemical potential, i.e., temperature and oxygen partial pressure, and construct phase diagrams. The reaction energies of the most dominant structures in the phase diagrams are summarized in Table 1. Next, the DOS related to the most dominant structures in the phase diagram were evaluated and analyzed with respect to the relative electronic conductivity. Figures of all structures found most stable at a specific oxygen

chemical potential and the stoichiometry and reaction energy of all structures considered can be found in the supporting information.⁵⁴

A. Electronic structure and phase diagram of 20% Nb-doped SrTiO₃

In this set of calculations we substituted four Ti atoms with four Nb atoms in the 5×2×2 supercell to obtain a model for 20% Nb-doped SrTiO₃ (Sr₂₀Ti₁₆Nb₄O₆₀ or SrTi_{0.8}Nb_{0.2}O₃). In addition, we generated structures with one or two Sr vacancies to create partial (5%) A-site deficient (Sr₁₉Ti₁₆Nb₄O₆₀ or Sr_{0.95}Ti_{0.8}Nb_{0.2}O₃) and full (10%) A-site deficient 20% Nb-doped SrTiO₃ (Sr₁₈Ti₁₆Nb₄O₆₀ or Sr_{0.9}Ti_{0.8}Nb_{0.2}O₃) model structures, respectively. From the configuration of the most stable structures, we observe that Nb impurities prefer to be as far apart as possible due to the repulsion of the extra electrons from the Nb⁵⁺ cations that can be transferred to neighboring Ti atoms that are mixed-valent Ti³⁺/Ti⁴⁺. In contrast when there are Sr vacancies in the structure, Nb prefers to stay close to the vacancies since the charges originating from the Nb atoms can be compensated by the absence of the Sr²⁺ cations. Moreover, it was found that the Sr-vacancy sites stay apart from each other in structures with more than one vacancy (see supporting information for the structures, Fig. S1).⁵⁴

Constrained *ab initio* thermodynamic calculations of 20% Nb-doped SrTiO₃ systems were performed to determine the phase stability of these structures at various temperatures and oxygen partial pressures. We employed two different types of calculations based on the main products that were generated when the phase transition occurred. First, we calculated the free energies of 20% Nb-doped SrTiO₃ with a SrO rich second phase experimentally obtained by cooling SrTi_{0.8}Nb_{0.2}O₃.



(4)

Where x represents the number of Sr-vacancy sites in the structure $(x - 1, 2)$ and free energies are given by

$$\Delta G = E_{\text{Sr-vacancy}} + xE_{\text{SrO}} - E_{\text{full}} - x[E_{\text{O}} + \Delta\mu_{\text{O}}(T, P)]$$

(5)

with $E_{\text{Sr-vacancy}}$ being the DFT-calculated electronic energy of the structure with Sr-vacancy, E_{full} is the DFT-calculated electronic energy of the structure without Sr-vacancy, E_{SrO} is the DFT-calculated electronic energy of the SrO lattice, and E_{O} is a half of the energy of an oxygen molecule, E_{O_2} , which is obtained from the H₂O splitting reaction using the experimental reaction energy and calculated DFT energies of H₂ and H₂O in the gas phase,^{55, 56}

$$E_{\text{O}_2} = 2[(E_{\text{H}_2\text{O}}^{\text{DFT}} + E_{\text{H}_2\text{O}}^{\text{ZPE}}) - (E_{\text{H}_2}^{\text{DFT}} + E_{\text{H}_2}^{\text{ZPE}}) - E_{\text{hof}}] - E_{\text{O}_2}^{\text{ZPE}},$$


(6)

where E^{ZPE} is the experimental zero point energy⁵⁷, E_{hof} is the experimental heat of formation of a gas-phase H₂O molecule⁵⁷, and E^{DFT} is the energy calculated with PBE functional. The chemical potential of O, which includes the temperature- and pressure-dependent free energy contributions of the O₂ molecule, is described by $\Delta\mu_{\text{O}}(T, P)$ and has been calculated from first principles and the rotational, translational, and vibrational partition functions of the O₂ molecule. We note that we neglect all zero point energies in equation 5 and assume that entropic contributions from the solids to the free energy difference are insignificant.⁵⁸⁻⁶⁰ Also, the pressure dependence of $\Delta\mu_{\text{O}}(T, P)$ is obtained assuming that the gas phase is ideal.⁵⁹

$$\Delta\mu_{\text{O}}(T, P) = \frac{1}{2} \left(\Delta\mu_{\text{O}_2}(T, P^0) + k_B T \ln \left(\frac{P}{P^0} \right) \right)$$

(7)


Next, we employed the same *ab initio* thermodynamic approach to investigate the thermodynamic stability of 20% Nb-doped SrTiO₃ with TiO₂ and niobium oxide rich second phases that can experimentally be obtained by heating Sr-deficient 20% Nb-doped SrTiO₃. Considering that Nb₂O₅ can be reduced to NbO₂ in a reducing environment at high temperature,⁶¹ we first performed *ab initio* thermodynamic calculations of the Nb₂O₅/NbO₂ system




(8)

and Fig. 2 illustrates that at low temperature Nb₂O₅ is the dominant phase whereas the NbO₂ phase predominates at higher temperatures.

In the following, we performed *ab initio* thermodynamic calculations of the Nb-doped SrTiO₃ system according to the dominant phase in the Nb₂O₅/NbO₂ phase diagram, i.e., whenever the Nb₂O₅ phase is preferred we calculate the free energies of the system according to eq. (9),



and whenever NbO₂ is preferred, we calculate the free energies of the system according to eq. (10),



(10) where x is the number of Sr vacancies with $x = 0, 1$. Figure 3 shows the calculated

phase diagrams of 20% Nb-doped SrTiO₃ with SrO rich second phase and TiO₂ and niobium oxide rich second phases. The phase transformation from 10% Sr-deficient (Sr_{0.9}Ti_{0.8}Nb_{0.2}O₃) to 5% Sr-deficient (Sr_{0.95}Ti_{0.8}Nb_{0.2}O₃) to non Sr-deficient structures (SrTi_{0.8}Nb_{0.2}O₃) occurs with increasing temperature and decreasing oxygen partial pressure. We note that an oxygen deficient structure is thermodynamically unstable in the considered temperature and oxygen partial pressure range.

The electronic conductivity of these materials can to a first approximation be analyzed from their electronic structures. As illustrated in Fig. 4(a), the DOS of a 10% Sr-deficient material (Sr_{0.9}Ti_{0.8}Nb_{0.2}O₃) exhibits insulating behavior with a band gap of 1.80 eV. The charges from the four Nb dopants are compensated by the presence of two Sr vacancies. The DOS of the 5% Sr-deficient structure (Sr_{0.95}Ti_{0.8}Nb_{0.2}O₃) shows a slight improvement in electronic conductivity (Fig. 4(b)). The Fermi energy shifts inside the conduction band with two conduction electrons per supercell below the Fermi level. An even greater improvement in the electronic conductivity occurs when the material is fully electronically compensated. As depicted in Fig. 4(c), the DOS of 20% Nb-doped SrTiO₃ with no Sr vacancies (SrTi_{0.8}Nb_{0.2}O₃) exhibits metallic character with four delocalized electrons at the Fermi level. Calculated band structures of this material shown in the supporting information (Fig. S5) confirm the metallic behavior of this material.⁵⁴

It is interesting to note that the simulation results are in agreement with experimental observations from Kolodiazny and Petric.²⁸ They reported that the transformation of cation vacancy compensated materials to electronically compensated materials (and corresponding change in electronic conductivity) occurred when the materials were equilibrated at high temperature and low oxygen partial pressure. This

condition corresponds to anodic SOFC conditions with temperatures between 1000 and 1200 K and oxygen partial pressures in the range of 10^{-20} bar.

B. Electronic structure and phase diagram of 10% Ga- and 20% Nb-doped SrTiO₃

Substitution of two Ti atoms with two Ga atoms in our 20% Nb-doped SrTiO₃ model leads to 10% Ga- and 20% Nb-doped SrTiO₃. The presence of Sr and oxygen vacancies in the structure was investigated in a similar manner as described above. It is found that Ga atoms prefer to be next to Nb atoms since the extra electron from the Nb dopant can be compensated by the electron hole generated from the Ga dopant (see also supporting information, Fig. S2).⁵⁴ At high temperatures and low oxygen partial pressures oxygen vacancies start to form. The first oxygen vacancy is created by removing an oxygen atom from the Ga-O-Ti bridge forming GaO₅ units whereas the second vacancy is positioned next to the same Ga atom generating a GaO₄ unit. Upon removal of the third oxygen atom another GaO₅ unit is formed in our unit cell. It is noteworthy that we find structures with neighboring Ga atoms to be significantly less stable.

Figures 5(a) and 5(b) illustrate the phase diagram for 10% Ga- and 20% Nb-doped SrTiO₃ as a function of temperature and partial pressure of oxygen corresponding to the formation of SrO and TiO₂/Ga₂O₃/niobium oxide rich second phases, respectively. In the presence of Ga, we find that the reduced structures (SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.95}, SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.90}, and SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.85}) are stable in the studied high temperature and low oxygen partial pressure range. The existence of a reduced structure indicates that Ga doping improves the reducibility of the materials as previously reported in Neagu and Irvine's work.⁴⁴ More interestingly, Ga and Nb dopants do not seem to

compensate each other with respect to electronic conductivity. Figure 6 illustrates the density of states of the most important structures. While $\text{Sr}_{0.95}\text{Ti}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_3$ exhibits insulating behavior with a band gap of 1.80 eV (the charges from the Nb dopants are compensated by the Sr vacancies and Ga dopants), $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_3$, $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.95}$, $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.90}$, and $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.85}$ exhibit metallic behavior with up to four conduction electrons at the Fermi level (the same number as in the absence of Ga). In $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_3$, the two Ga atoms in the supercell compensate for two of the Nb atoms, leaving the remaining two Nb atoms to contribute two conduction electrons at the Fermi level (Fig. 6b). In $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.95}$, one oxygen atom connected to a Ga atom is removed, compensating the hole doping effect of two Ga atoms. Thus, we see the effect of 20% Nb doping in this structure (Fig. 6c). In $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.9}$ and $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.85}$, the electrons generated by creating further oxygen vacancies are localized mainly on the Ga atoms and an extra peak is observed in the DOS (Fig. 6d and 6e) between the valence band and the conduction band. A partial density of states (PDOS) analysis and electron density integration for $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.9}$, as illustrated in Fig. 7(a), shows that there are two electrons in this peak which contains predominantly contributions from the oxygen PDOS. We see no reason for these two electrons to be delocalized and believe that these states do not contribute to the electronic conductivity of the material. We find a qualitatively similar picture for the four electrons in the extra peak in the band gap of $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.85}$. This observation is in agreement with previous computational and experimental results that the electrons from oxygen vacancies are often localized and have little contribution to the electronic conductivity of the materials.^{62, 63} Next, Fig. 7(b) shows the PDOS of

$\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.9}$ below the Fermi level and confirms that these states are primarily from mixed-valent $\text{Ti}^{3+}/\text{Ti}^{4+}$ that contribute to electronic conduction. A similar behavior is observed for all structures studied with states below the Fermi level.

To conclude, further doping of 20% Nb-doped SrTiO_3 with 10% Ga leads to a comparable degree of electronic conductivity to that of only 20% Nb-doped SrTiO_3 under anodic SOFC conditions. Further, Ga promotes ionic conductivity by enhancing the reducibility of the material. These results support the experimental observations reported by several groups^{43,44} that Ga doped titanates possess a high number of oxygen vacancies and good oxide ion conduction.

C. Electronic structure and phase diagram of 20% Ga- and 20% Nb-doped SrTiO_3

Replacing another two Ti atoms with Ga atoms in 10% Ga- and 20% Nb-doped SrTiO_3 we obtain a model for 20% Ga- and 20% Nb-doped SrTiO_3 . The most stable structures in this set of calculations have Ga atoms close to Nb atoms. Up to three oxygen vacancies were generated in this structure to study the effect of reducing conditions. It is preferable to create the first two oxygen vacancies at the Ga-O-Ti bridge where two vacancies share the same Ga atom forming a GaO_4 unit, whereas the third oxygen vacancy is again positioned at a Ga-O-Ti bridge forming a GaO_5 unit (see supporting information for the structures, Fig. S3).⁵⁴

Constrained *ab initio* thermodynamic calculations of this system were carried out to determine the phase stability at various temperatures and oxygen partial pressures. In some respects, the phase transition of this system is quite similar to that of the 10% Ga doped system. In particular, the presence of a reduced phase of both the 10% and 20% Ga

doped systems occurs at approximately the same temperature and oxygen partial pressure range, indicating that increasing the concentration of Ga does not significantly improve the reducibility of the material. However, the phase diagram of the 20% Ga doped system shown in Fig. 8 displays no Sr-deficient phase (i.e., there are no SrO or $\text{TiO}_2/\text{Ga}_2\text{O}_3$ /niobium oxide rich second phases). Furthermore, we observe from the DOS (Fig. 9) a reduction in the electronic conductivity with increase in Ga doping. As shown in Figs. 9(c) and 9(d), the DOS of $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.90}$ and $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.85}$ exhibit only two conduction electrons at the Fermi level. It seems that doping with 20% Ga (and 20% Nb) and removing the first oxygen atom in our supercell leads to a compensation of the hole doping effect of two Ga atoms and generation of two conduction electrons from two uncompensated Nb atoms at the Fermi level (Fig. 9b). In contrast, removing one or two more oxygen atoms from the supercell leads to localized electrons observed in an extra peak in the DOS between the valence and conduction band and no compensation of the hole doping effect of the remaining two Ga atoms, and thus, no increase in charge carrier density (Fig. 9c and 9d). Interestingly, creating a fourth oxygen vacancy under very reducing conditions (usually not encountered in SOFC operation and therefore not included in the phase diagram), leads again to a full compensation of the hole doping effect of all four Ga atoms and generation of four conduction electrons from the four Nb atoms at the Fermi level (see supporting information, Fig S4).⁵⁴ Thus, while doping with 20% Ga improves the ionic conductivity, the electronic conductivity of the material is likely diminished under realistic fuel cell operating conditions.

IV. CONCLUSIONS

We have investigated the electronic properties and thermodynamic stability of Nb (n-type) and Ga (p-type) doped SrTiO₃ perovskites using density functional theory and constrained *ab initio* thermodynamic simulations. We find that cation vacancy compensated 20% Nb-doped Sr-deficient SrTiO₃ (Sr_{0.9}Ti_{0.8}Nb_{0.2}O₃) transforms to an electronically compensated non Sr-deficient phase (SrTi_{0.8}Nb_{0.2}O₃) at high temperature and low oxygen partial pressure which leads to a significant improvement in electronic conductivity. This result is in excellent agreement with the defect chemistry model and experimental observations reported by Kolodiazhnyi and Petric.²⁸ Doping 20% Nb-doped SrTiO₃ with 10% Ga enhances the ionic conductivity of the material by creating oxygen vacancies. The electronic conductivity is not reduced by small amounts of Ga so that a mixed ionic/electronic conductor is formed. However, doping with 20% Ga decreases the electronic conductivity of the material. This result supports the experimental observations^{43, 44} that doping with a small amount of Ga improves the conductivity and promotes fast reduction of the material. From both experimental observations and our calculations, we propose that a mixed n-type and p-type doping strategy could be a general approach to obtaining mixed ionic/electronic conductivity in perovskite oxide materials.

ACKNOWLEDGEMENTS

Helpful discussions with Michele Pavone and Emily A. Carter at Princeton University are acknowledged. This work has been funded by the Heterogeneous Functional Materials Center (HeteroFoaM), an Energy Frontier Research Center funded by the U.S. Department of Energy, Office of Basic Energy Sciences under Award

Number DE-SC0001061. Computations were performed at the U.S. Department of Energy facilities located at EMSL, a national scientific user facility located at Pacific Northwest National Laboratory (Grant Proposal No. 34900), at the National Energy Research Scientific Computing Center (NERSC), and at Oak Ridge National Laboratory (CNMS2009-248). Furthermore, a portion of this research was performed at Teragrid resources provided by the National Center for Supercomputing Applications (NCSA), Purdue University, and Texas Advanced Computing Center (TACC) under grant number TG-CTS090100. Finally, computing resources from the USC NanoCenter, USC's High Performance Computing Group, and the Minnesota Supercomputing Institute for Advanced Computational Research are gratefully acknowledged.

- 1 M. Guillodo, P. Vernoux, and J. Fouletier, *Solid State Ionics* **127**, 99 (2000).
- 2 T. Iwata, *J. Electrochem. Soc.* **143**, 1521 (1996).
- 3 A. Tsoga, A. Naoumidis, and P. Nikolopoulos, *Acta Mater.* **44**, 3679 (1996).
- 4 D. Simwonis, F. Tietz, and D. Stover, *Solid State Ionics* **132**, 241 (2000).
- 5 Y. B. Lin, Z. L. Zhan, and S. A. Barnett, *J. Power Sources* **158**, 1313 (2006).
- 6 S. W. Tao and J. T. S. Irvine, *Nature Materials* **2**, 320 (2003).
- 7 Y. H. Huang, R. I. Dass, Z. L. Xing, and J. B. Goodenough, *Science* **312**, 254 (2006).
- 8 D. P. Fagg, V. V. Kharton, A. V. Kovalevsky, A. P. Viskup, E. N. Naumovich, and J. R. Frade, *J. Eur. Ceram. Soc.* **21**, 1831 (2001).
- 9 S. Q. Hui and A. Petric, *J. Eur. Ceram. Soc.* **22**, 1673 (2002).
- 10 T. Ishihara, H. Matsuda, and Y. Takita, *J. Am. Chem. Soc.* **116**, 3801 (1994).
- 11 M. Feng and J. B. Goodenough, *Eur. J. Solid State Inorg. Chem.* **31**, 663 (1994).
- 12 K. Q. Huang, M. Feng, J. B. Goodenough, and M. Schmerling, *J. Electrochem. Soc.* **143**, 3630 (1996).
- 13 J. Canales-Vazquez, S. W. Tao, and J. T. S. Irvine, *Solid State Ionics* **159**, 159 (2003).
- 14 O. A. Marina, N. L. Canfield, and J. W. Stevenson, *Solid State Ionics* **149**, 21 (2002).
- 15 J. Canales-Vazquez, J. C. Ruiz-Morales, J. T. S. Irvine, and W. Z. Zhou, *J. Electrochem. Soc.* **152**, A1458 (2005).
- 16 A. Sin, E. Kopnin, Y. Dubitsky, A. Zaopo, A. S. Arico, L. R. Gullo, D. La Rosa, and V. Antonucci, *J. Power Sources* **145**, 68 (2005).
- 17 P. Vernoux, E. Djurado, and M. Guillodo, *J. Am. Ceram. Soc.* **84**, 2289 (2001).

18 L. Aguilar, S. W. Zha, Z. Cheng, J. Winnick, and M. L. Liu, *J. Power Sources*
19 **135**, 17 (2004).
20 P. R. Slater, D. P. Fagg, and J. T. S. Irvine, *J. Mater. Chem.* **7**, 2495 (1997).
21 J. A. Noland, *Phys. Rev.* **94**, 724 (1954).
22 J. F. Schooley, W. R. Hosler, E. Ambler, J. H. Becker, M. L. Cohen, and C. S.
23 Koonce, *Phys. Rev. Lett.* **14**, 305 (1965).
24 Y. Aiura, H. Bando, I. Hase, S. Nishihara, Y. Haruyama, and H. Suzuki,
25 *Superlattices Microstruct.* **21**, 321 (1997).
26 N. Shanthi and D. D. Sarma, *Phys. Rev. B* **57**, 2153 (1998).
27 T. Yokoya, T. Sato, H. Fujisawa, T. Takahashi, A. Chainani, and M. Onoda, *Phys.*
28 *Rev. B* **59**, 1815 (1999).
29 T. Jarlborg, *Phys. Rev. B* **61**, 9887 (2000).
30 S. Lee, G. Kim, J. M. Vohs, and R. J. Gorte, *J. Electrochem. Soc.* **155**, B1179
31 (2008).
32 H. Kurokawa, L. M. Yang, C. P. Jacobson, L. C. De Jonghe, and S. J. Visco, *J.*
33 *Power Sources* **164**, 510 (2007).
34 T. Kolodiazhnyi and A. Petric, *J. Electroceram.* **15**, 5 (2005).
35 W. Luo, W. Duan, S. G. Louie, and M. L. Cohen, *Phys. Rev. B* **70**, 214109
36 (2004).
37 U. Balachandran and N. G. Eror, *J. Electrochem. Soc.* **129**, 1021 (1982).
38 A. M. J. Seuter, *Philips Res. Repts*, 1 (1974).
39 R. Moos and K. H. Hardtl, *J. Am. Ceram. Soc.* **80**, 2549 (1997).
40 J. B. Goodenough and Y. H. Huang, *J. Power Sources* **173**, 1 (2007).
41 R. Moos, A. Gnudi, and K. H. Härdtl, *J. Appl. Phys.* **78**, 5042 (1995).
42 R. Moos, T. Bischoff, W. Menesklou, and K. H. Hardtl, *J. Mater. Sci.* **32**, 4247
43 (1997).
44 M. J. Akhtar, Z. U. N. Akhtar, R. A. Jackson, and C. R. A. Catlow, *J. Am. Ceram.*
45 *Soc.* **78**, 421 (1995).
46 *Perovskite oxide for solid oxide fuel cells* (Springer, New York, 2009).
47 K. Vidyasagar, A. Reller, J. Gopalakrishnan, and C. N. R. Rao, *J. Chem. Soc.*
48 *Chem. Comm.*, 7 (1985).
49 J. A. Kilner, *Solid State Ionics* **129**, 13 (2000).
J. C. Ruiz-Morales, J. Canales-Vazquez, C. Savaniu, D. Marrero-Lopez, W. Z.
Zhou, and J. T. S. Irvine, *Nature* **439**, 568 (2006).
X. Li, H. L. Zhao, F. Gao, N. Chen, and N. S. Xu, *Electrochem. Commun.* **10**,
1567 (2008).
X. Li, H. L. Zhao, N. S. Xu, X. Zhou, C. J. Zhany, and N. Chen, *Int. J. Hydrogen*
Energy **34**, 6407 (2009).
X. Guoliang, X. Dong, K. Huang, and F. Chen, *Mater. Res. Bull.* **46**, 57 (2011).
D. Neagu and J. T. S. Irvine, *Chem. Mater.* **23**, 1607 (2011).
F. W. Lytle, *J. Appl. Phys.* **35**, 2212 (1964).
G. Kresse and J. Furthmuller, *Phys. Rev. B* **54**, 11169 (1996).
G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).

- 50 Y. A. Abramov, V. G. Tsirelson, V. E. Zavodnik, S. A. Ivanov, and B. I. D., *Acta*
Crystallogr. B **51**, 942 (1995).
- 51 K. van Benthem, C. Elsasser, and R. H. French, *J. Appl. Phys.* **90**, 6156 (2001).
- 52 J. Robertson, K. Xiong, and S. J. Clark, *Thin Solid Films* **496**, 1 (2006).
- 53 C. Zhang, C. L. Wang, J. C. Li, K. Yang, Y. F. Zhang, and Q. Z. Wu, *Mater.*
Chem. Phys. **107**, 215 (2008).
- 54 See Supplemental Material at [] for [most dominant structures of doped SrTiO₃
identified in constrained *ab initio* thermodynamic calculations, summary of all
reaction energies used in *ab initio* thermodynamic simulations, density of states of
SrTi_{0.6}Nb_{0.2}Ga_{0.2}O_{2.8}, and calculated electronic band structure of selected
materials].
- 55 S. C. Ammal and A. Heyden, *J. Chem. Phys.* **133**, 164703 (2010).
- 56 J. K. Norskov, J. Rossmeisl, A. Logadottir, L. Lindqvist, J. R. Kitchin, T.
Bligaard, and H. Jonsson, *J. Phys. Chem. B* **108**, 17886 (2004).
- 57 P. W. Atkins, *Physical Chemistry* (Oxford University Press, Oxford, 1998).
- 58 S. Laursen and S. Linic, *Phys. Chem. Chem. Phys.* **11**, 11006 (2009).
- 59 S. Laursen and S. Linic, *J. Phys. Chem. C* **113**, 6689 (2009).
- 60 J. Rogal, K. Reuter, and M. Scheffler, *Phys. Rev. B* **75**, 205433 (2007).
- 61 C. K. Gupta and A. K. Suri, *Extractive metallurgy of niobium* (CRC Press, Boca
Raton, 1994).
- 62 K. Kuroda, W. Sugimoto, M. Shirata, M. Takemoto, S. Hayami, and Y. Sugahara,
Solid State Ionics **108**, 315 (1998).
- 63 J. N. Yun, Z. Y. Zhang, J. F. Yan, and W. Zhao, *J. Appl. Phys.* **107** (2010).

TABLE I. Summary of reaction energies used in constrained *ab initio* thermodynamic calculations

Phase Diagram	Reaction	ΔE (eV)
Nb ₂ O ₅ /NbO ₂	Nb ₂ O ₅ --> 2NbO ₂ + 1/2O ₂	3.71
20% Nb-doped SrTiO ₃ with SrO rich phase	Sr ₂₀ Ti ₁₆ Nb ₄ O ₆₀ + 1/2O ₂ --> Sr ₁₉ Ti ₁₆ Nb ₄ O ₆₀ + SrO	-1.94
	Sr ₂₀ Ti ₁₆ Nb ₄ O ₆₀ + O ₂ --> Sr ₁₈ Ti ₁₆ Nb ₄ O ₆₀ + 2SrO	-3.49
20% Nb-doped SrTiO ₃ with TiO ₂ /niobium oxide rich phases	19Sr ₁₈ Ti ₁₆ Nb ₄ O ₆₀ --> 18Sr ₁₉ Ti ₁₆ Nb ₄ O ₆₀ + 16TiO ₂ + 2Nb ₂ O ₅ + 9O ₂	2.58
	10Sr ₁₈ Ti ₁₆ Nb ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₆ Nb ₄ O ₆₀ + 16TiO ₂ + 2Nb ₂ O ₅ + 9O ₂	5.24
	19Sr ₁₈ Ti ₁₆ Nb ₄ O ₆₀ --> 18Sr ₁₉ Ti ₁₆ Nb ₄ O ₆₀ + 16TiO ₂ + 4NbO ₂ + 10O ₂	2.97
	10Sr ₁₈ Ti ₁₆ Nb ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₆ Nb ₄ O ₆₀ + 16TiO ₂ + 4NbO ₂ + 10O ₂	5.98
10% Ga- and 20% Nb-doped SrTiO ₃ with SrO rich phase	Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ + 1/2O ₂ --> Sr ₁₉ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ + SrO	-1.74
	Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₉ + 1/2O ₂	4.54
	Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₈ + O ₂	9.01
	Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₇ + 3/2O ₂	14.16
10% Ga- and 20% Nb-doped SrTiO ₃ with TiO ₂ /Ga ₂ O ₃ /niobium oxide rich phases	19Sr ₁₈ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> 18Sr ₁₉ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ + 14TiO ₂ + 2Nb ₂ O ₅ + Ga ₂ O ₃ + 19/2O ₂	-1.29
	10Sr ₁₈ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> 9Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ + 14TiO ₂ + 2Nb ₂ O ₅ + Ga ₂ O ₃ + 19/2O ₂	1.28
	10Sr ₁₈ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> 9Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₉ + 14TiO ₂ + 2Nb ₂ O ₅ + Ga ₂ O ₃ + 14O ₂	5.37
	10Sr ₁₈ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> 9Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₈ + 14TiO ₂ + 2Nb ₂ O ₅ + Ga ₂ O ₃ + 37/2O ₂	9.39
	10Sr ₁₈ Ti ₁₄ Nb ₄ Ga ₂ O ₆₀ --> 9Sr ₂₀ Ti ₁₄ Nb ₄ Ga ₂ O ₅₇ + 14TiO ₂ + 2Nb ₂ O ₅ + Ga ₂ O ₃ + 23O ₂	14.03
20% Ga- and 20% Nb-doped SrTiO ₃	10Sr ₁₈ Ti ₁₂ Nb ₄ Ga ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₂ Nb ₄ Ga ₄ O ₆₀ + 12TiO ₂ + 2Nb ₂ O ₅ + 2Ga ₂ O ₃ + 10O ₂	-2.81
	10Sr ₁₈ Ti ₁₂ Nb ₄ Ga ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₂ Nb ₄ Ga ₄ O ₅₉ + 12TiO ₂ + 2Nb ₂ O ₅ + 2Ga ₂ O ₃ + 29/2O ₂	1.21
	10Sr ₁₈ Ti ₁₂ Nb ₄ Ga ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₂ Nb ₄ Ga ₄ O ₅₈ + 12TiO ₂ + 2Nb ₂ O ₅ + 2Ga ₂ O ₃ + 19O ₂	5.21
	10Sr ₁₈ Ti ₁₂ Nb ₄ Ga ₄ O ₆₀ --> 9Sr ₂₀ Ti ₁₂ Nb ₄ Ga ₄ O ₅₇ + 12TiO ₂ + 2Nb ₂ O ₅ + 2Ga ₂ O ₃ + 47/2O ₂	9.82

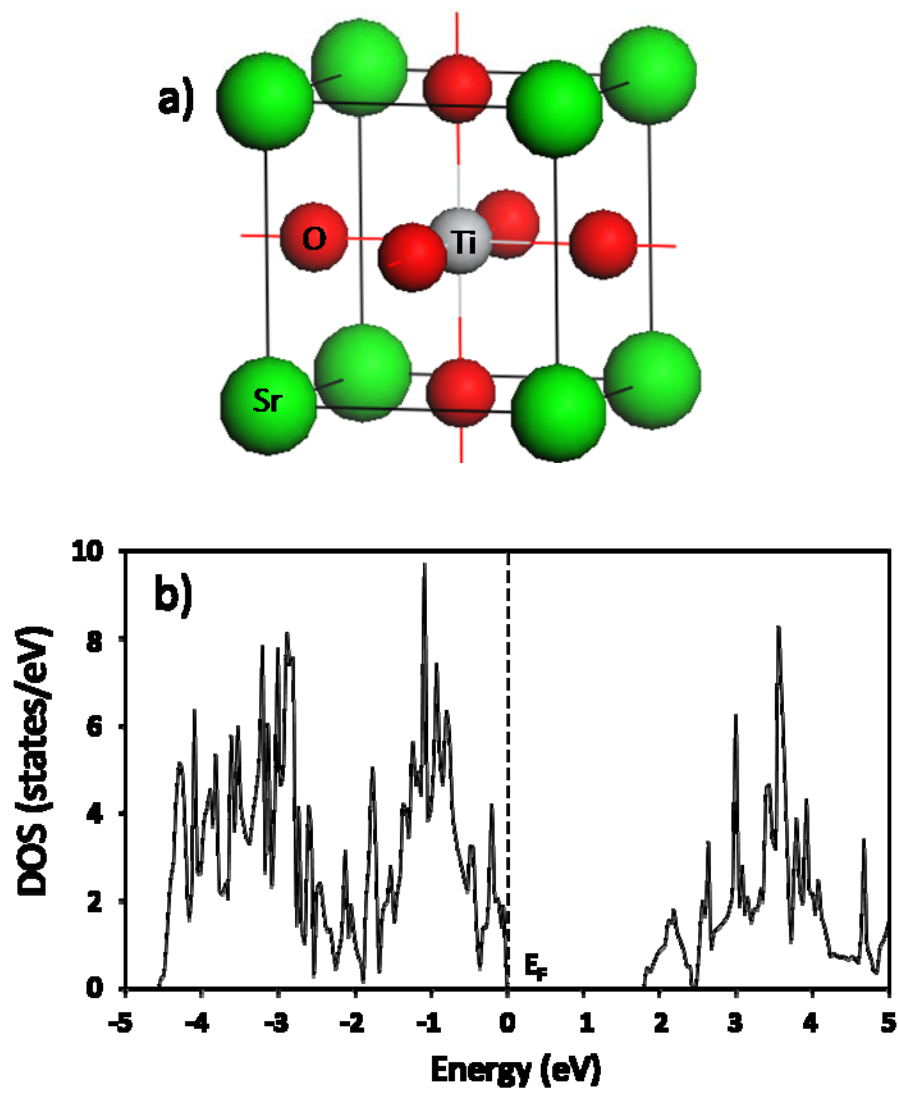


FIG. 1. (Color Online) a) Unit cell of SrTiO₃ perovskite oxide b) Density of states of stoichiometric SrTiO₃ with calculated band gap of 1.80 eV.

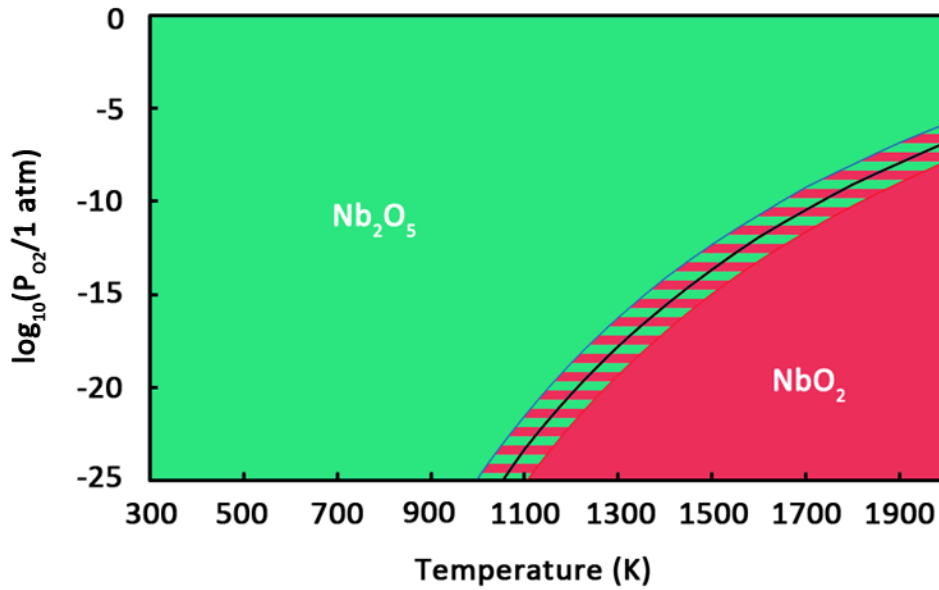


FIG. 2. (Color Online) Calculated phase diagram of $\text{Nb}_2\text{O}_5/\text{NbO}_2$. Differently shaded areas mark the stability regions of various structures for a given temperature and partial pressure of oxygen. The hatched area describes possible changes in the phase diagram if computed reaction energies shown in Table 1 are off by ± 0.2 eV (our estimated error bar). Green and red areas symbolize stability of Nb_2O_5 and NbO_2 , respectively.

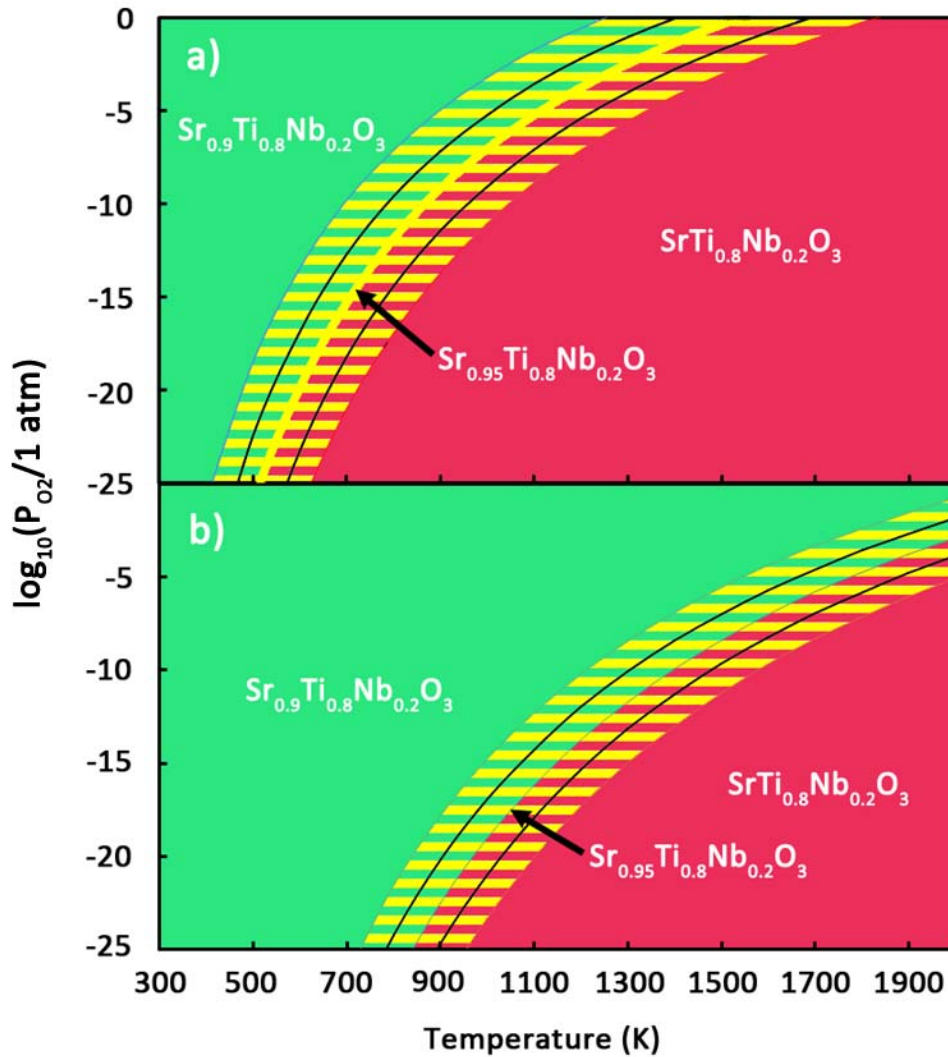


FIG. 3. (Color Online) Calculated phase diagram of 20% Nb-doped SrTiO₃ with a) SrO rich phase and b) TiO₂/niobium oxide rich phases. Differently shaded areas mark the stability regions of various structures for a given temperature and partial pressure of oxygen. The hatched area describes possible changes in the phase diagram if computed reaction energies shown in Table 1 are off by ± 0.2 eV (our estimated error bar). Green, yellow, and red areas symbolize stability of $\text{Sr}_{0.9}\text{Ti}_{0.8}\text{Nb}_{0.2}\text{O}_3$, $\text{Sr}_{0.95}\text{Ti}_{0.8}\text{Nb}_{0.2}\text{O}_3$, and $\text{SrTi}_{0.8}\text{Nb}_{0.2}\text{O}_3$, respectively.

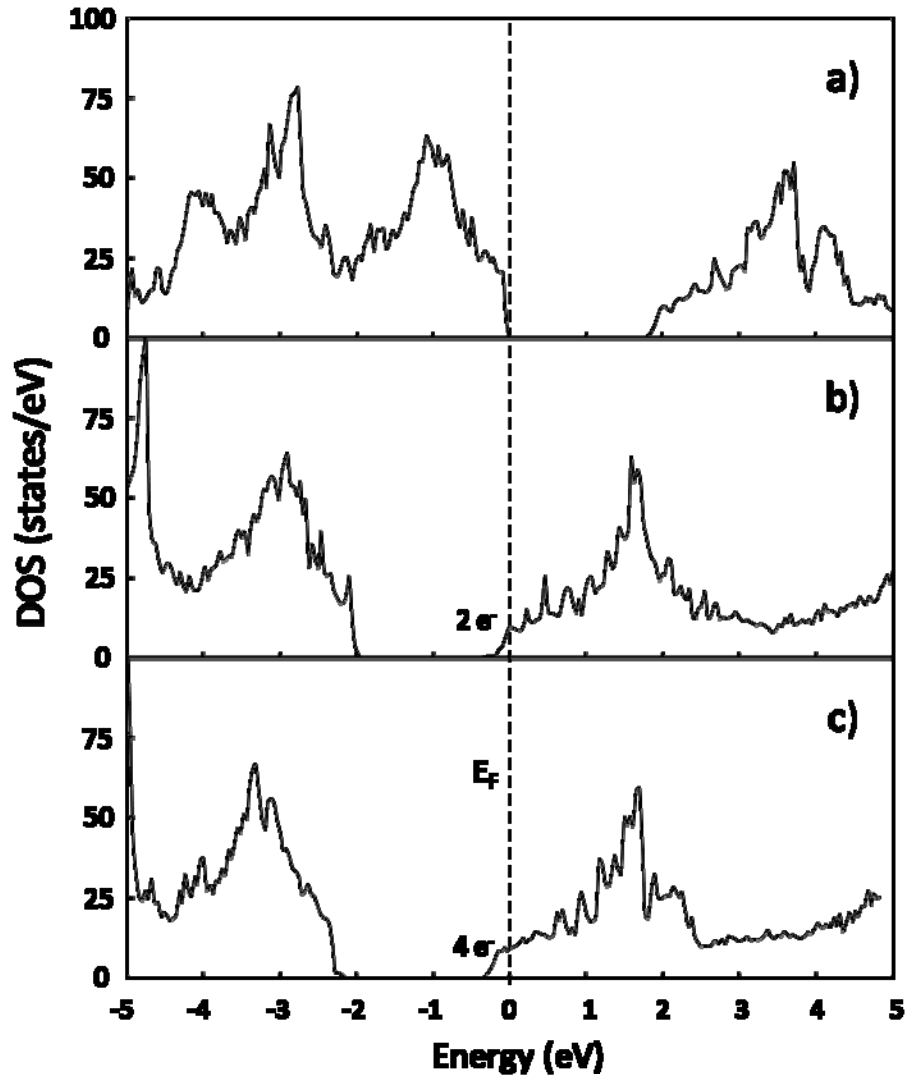


FIG. 4. Density of states of a) $\text{Sr}_{0.9}\text{Ti}_{0.8}\text{Nb}_{0.2}\text{O}_3$, b) $\text{Sr}_{0.95}\text{Ti}_{0.8}\text{Nb}_{0.2}\text{O}_3$ and c) $\text{SrTi}_{0.8}\text{Nb}_{0.2}\text{O}_3$. Fermi energy is set to zero on energy scale. Numbers of electrons shown in the figure indicate the integrated number of electrons per supercell for the specified DOS area, i.e., states in the band gap and states below the Fermi level.

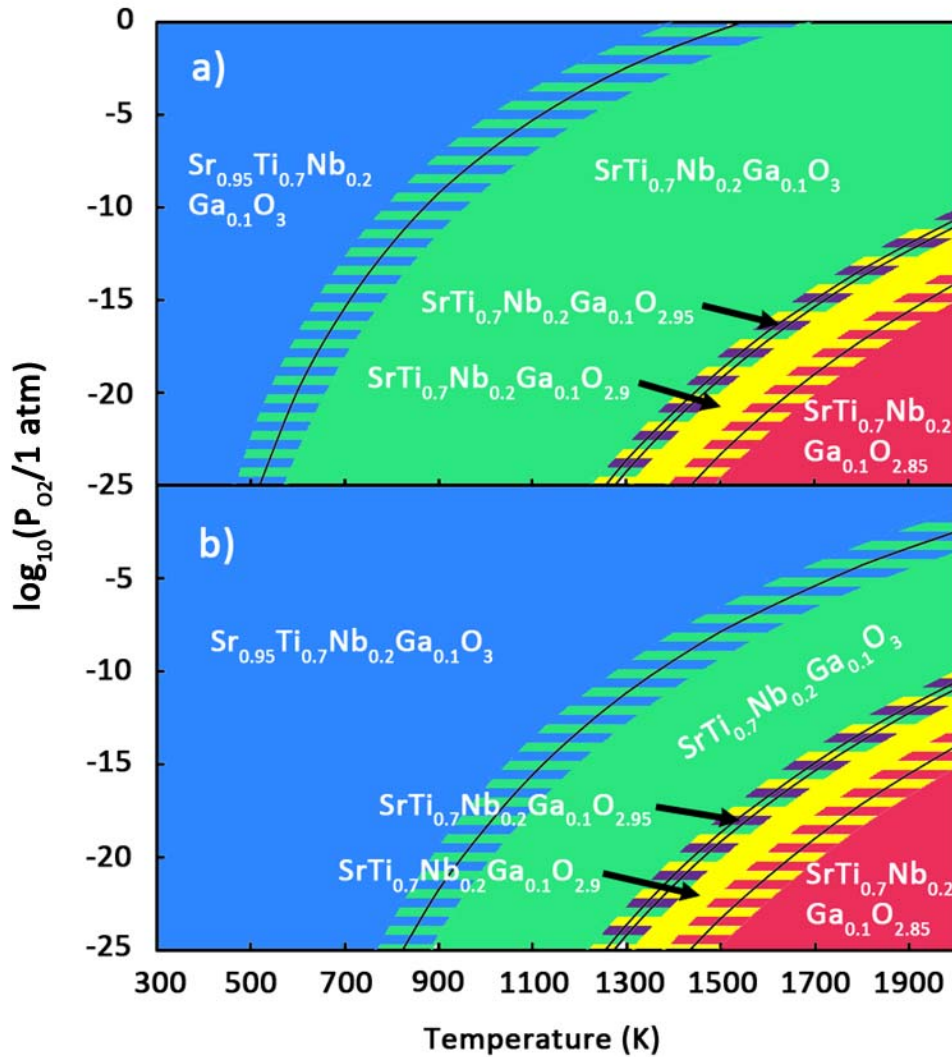


FIG. 5. (Color Online) Calculated phase diagram of 10% Ga- and 20% Nb-doped SrTiO₃ with a) SrO rich phase and b) TiO₂/Ga₂O₃/niobium oxide rich phases. Differently shaded areas mark the stability regions of various structures for a given temperature and partial pressure of oxygen. The hatched area describes possible changes in the phase diagram if computed reaction energies shown in Table 1 are off by ± 0.2 eV (our estimated error bar). Blue, green, yellow, and red areas symbolize stability of Sr_{0.95}Ti_{0.7}Nb_{0.2}Ga_{0.1}O₃, SrTi_{0.7}Nb_{0.2}Ga_{0.1}O₃, SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.9}, and SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.85}, respectively. The hatched violet area symbolizes the possible stability of a SrTi_{0.7}Nb_{0.2}Ga_{0.1}O_{2.95} phase.

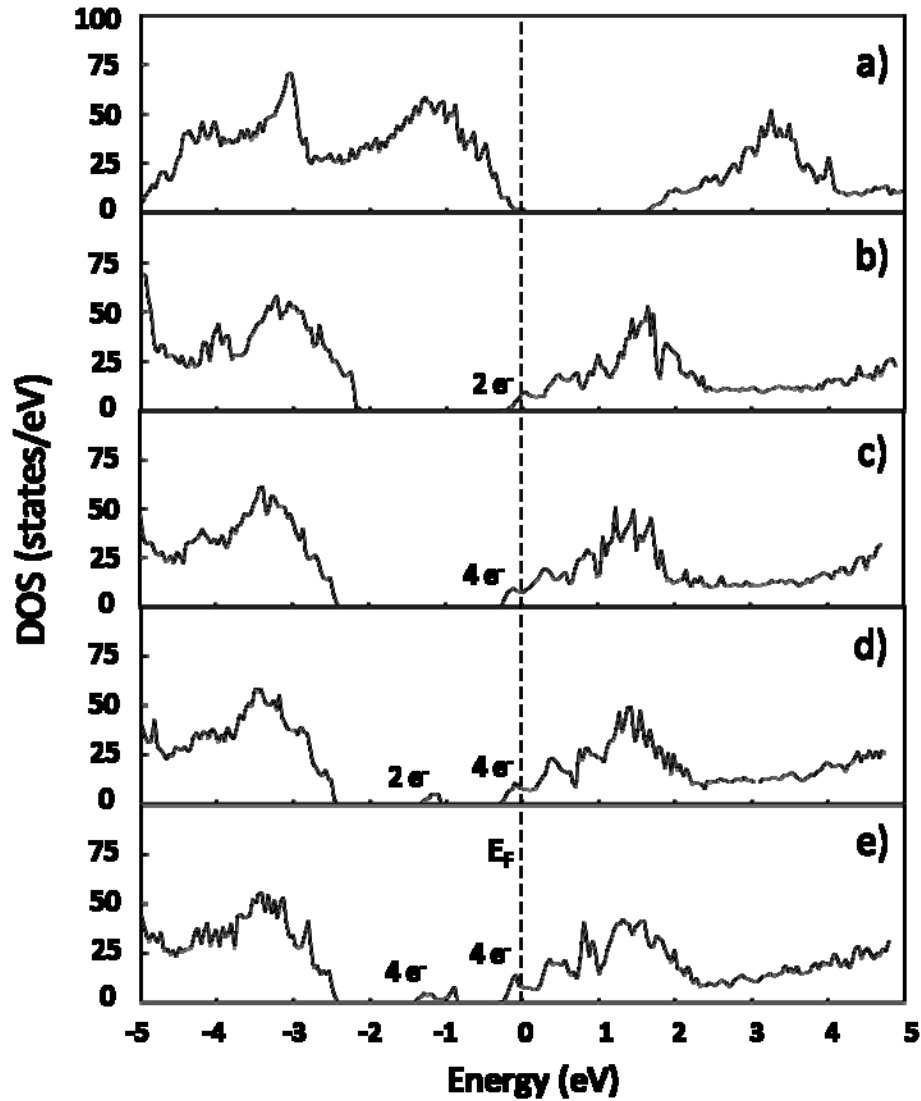


FIG. 6. Density of states of a) $\text{Sr}_{0.95}\text{Ti}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_3$, b) $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_3$, c) $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.95}$, d) $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.9}$ and e) $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.85}$. Fermi energy is set to zero on energy scale. Numbers of electrons shown in the figure indicate the integrated number of electrons per supercell for the specified DOS area, i.e., states in the band gap and states below the Fermi level.

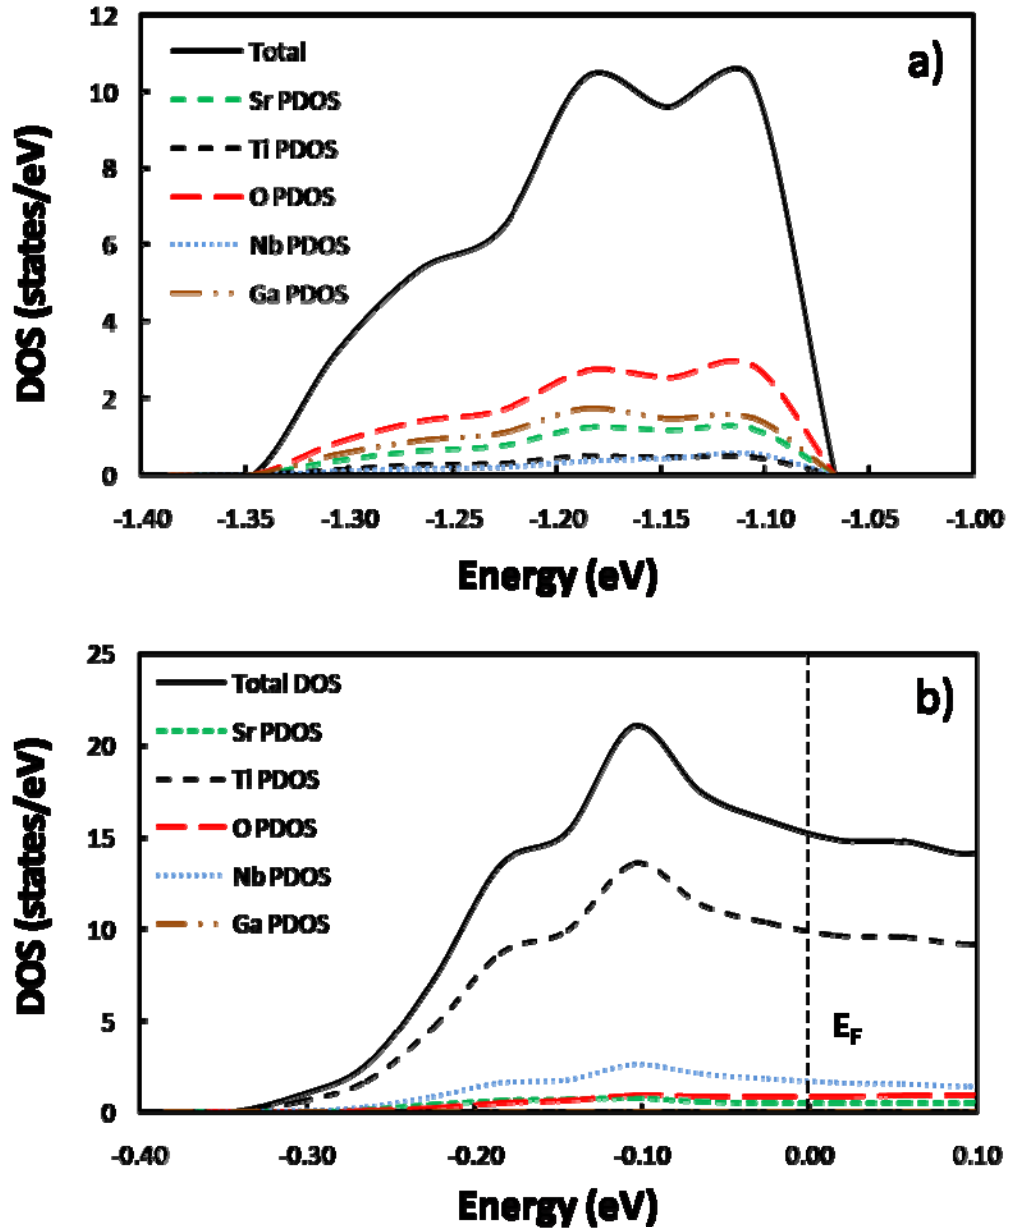


FIG. 7. (Color Online) Partial density of states (PDOS) of a) the gap states between the valence and conduction band and b) the states below the Fermi level in $\text{SrTi}_{0.7}\text{Nb}_{0.2}\text{Ga}_{0.1}\text{O}_{2.9}$.

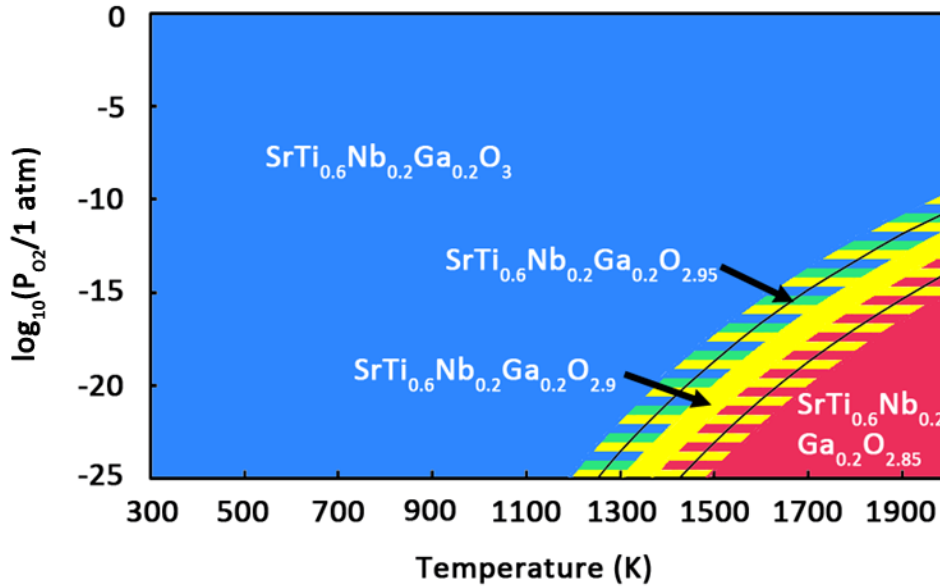


FIG. 8. (Color Online) Calculated phase diagram of 20% Ga- and 20% Nb-doped SrTiO_3 . Differently shaded areas mark the stability regions of various structures for a given temperature and partial pressure of oxygen. The hatched area describes possible changes in the phase diagram if computed reaction energies shown in Table 1 are off by ± 0.2 eV (our estimated error bar). Blue, yellow, and red areas symbolize stability of $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_3$, $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.9}$, and $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.85}$, respectively. The hatched green area symbolizes the stability of a $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.95}$ phase.

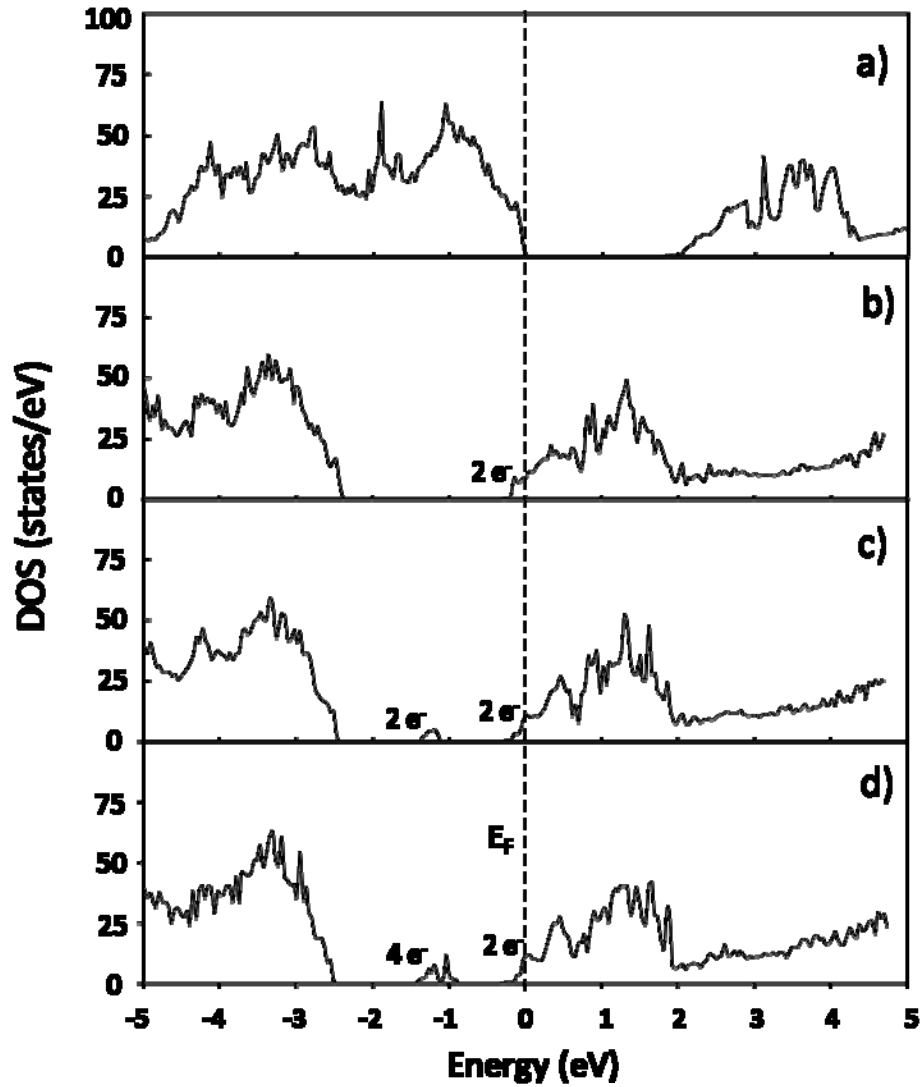


FIG. 9. Density of states of a) $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_3$, b) $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.95}$, c) $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.9}$, and d) $\text{SrTi}_{0.6}\text{Nb}_{0.2}\text{Ga}_{0.2}\text{O}_{2.85}$. Fermi energy is set to zero on the energy scale. Numbers of electrons shown in the figure indicate the integrated number of electrons per supercell for the specified DOS area, i.e., states in the band gap and states below the Fermi level.