

This is the accepted manuscript made available via CHORUS. The article has been published as:

Contribution of spin pairs to the magnetic response in a dilute dipolar ferromagnet

C. M. S. Gannarelli, D. M. Silevitch, T. F. Rosenbaum, G. Aeppli, and A. J. Fisher

Phys. Rev. B **86**, 014420 — Published 19 July 2012

DOI: [10.1103/PhysRevB.86.014420](https://doi.org/10.1103/PhysRevB.86.014420)

Contribution of spin pairs to the magnetic response in a dilute dipolar ferromagnet

C. M. S. Gannarelli,¹ D. M. Silevitch,² T. F. Rosenbaum,² G. Aeppli,¹ and A. J. Fisher^{1,*}

¹*London Centre for Nanotechnology and Department of Physics and Astronomy,
University College London, Gower Street, London, WC1E 6BT, United Kingdom*

²*The James Franck Institute and Department of Physics,
The University of Chicago, Chicago, Illinois 60637, USA*

(Dated: February 24, 2012)

We simulate the dc magnetic response of the diluted dipolar-coupled Ising magnet $\text{LiHo}_{0.045}\text{Y}_{0.955}\text{F}_4$ in a transverse field, using exact diagonalization of a two-spin Hamiltonian averaged over nearest-neighbour configurations. The pairwise model, incorporating hyperfine interactions, accounts for the observed drop-off in the longitudinal (c-axis) susceptibility with increasing transverse field; with the inclusion of a small tilt in the transverse field, it also accounts for the behavior of the off-diagonal magnetic susceptibility. The hyperfine interactions do not appear to lead to qualitative changes in the pair susceptibilities, although they do renormalize the crossover fields between different regimes. Comparison with experiment indicates that antiferromagnetic correlations are more important than anticipated based on simple pair statistics and our first-principles calculations of the pair response. This means that larger clusters will be needed for a full description of the reduction in the diagonal response at small transverse fields.

I. INTRODUCTION

The dipolar rare-earth magnetic salt LiHoF_4 orders at $1.53 \text{ K}^{1,2}$ to form an Ising-like ferromagnet with long, needle-shaped domains oriented along the Ising c -axis³. This system, and the dilution series $\text{LiHo}_x\text{Y}_{1-x}\text{F}_4$ with the magnetic Ho^{3+} ions replaced by non-magnetic Y^{3+} , have been studied for more than three decades⁴⁻¹⁸. The appeal of $\text{LiHo}_x\text{Y}_{1-x}\text{F}_4$ lies in its unique combination of interesting quantum as well as classical properties and detailed knowledge of the underlying Hamiltonian, including single-ion crystal-field and nuclear-hyperfine interaction terms and intersite dipolar couplings. For example, the pure ($x = 1$) compound displays an archetypical electronic quantum phase transition strongly influenced by the nuclear spin bath^{1,19}. For moderate dilution ($x > 30\%$) the system continues to behave as an Ising ferromagnet with a critical temperature suppressed in direct proportion to $x^{1,4,5,12}$; for smaller x it was reported to form a spin glass at low temperatures¹⁷. At $x = 4.5\%$ there is an accumulation of evidence for a novel *antiglass*⁶ in which the scaled distribution of relaxation times *loses* its low-frequency tail as the sample cools. In this phase the material was found to exhibit macroscopically long-lived magnetic excitations⁸ and a novel combination of strong features in the specific heat with a featureless magnetic susceptibility which could only be explained by positing long-range spin entanglement⁹. Other recent experiments report contrasting results—notably a featureless specific heat from $x = 1.8\%$ to $x = 8\%$ ¹³ and no narrowing of the absorption peak on the low-temperature side as the temperature lowers²⁰, suggesting that the conventional spin glass may persist to lower concentrations. Yet a third view has also been suggested: magnetization measurements by Jonsson *et al.* failed to find evidence for a spin-glass transition at either $x = 4.5\%$ or $x = 16.5\%$ ¹⁴. The interpretation of all these experiments is complicated by the need to work at extremely low frequencies and to achieve proper thermal equilibration; this has led to some controversy about the interpretation, with recent results supporting the original assignment of a spin-glass at $x = 16.7\%$ and $x = 19.8\%$ ²¹.

The differing interpretations on the experimental side have been accompanied by some confusion about the theory, with a number of classical Monte Carlo studies failing to find evidence of the expected spin-glass transition in a three-dimensional disordered dipolar Ising system^{22,23}. Most recently convincing numerical evidence of this transition has finally emerged²⁴ through finite-size scaling analysis of the spin-glass correlation length. But there is also dispute about whether the dipolar terms in the Hamiltonian are sufficient to describe the material even in zero transverse field, with some authors arguing that the role of transverse fields²⁵ that are key for entanglement effects⁹ and nuclear levels coupled by hyperfine interactions^{11,26} have been underestimated. Reference 27 is a recent review which concludes that further experiments are required, and that the inclusion of quantum effects and the role of hyperfine interactions (both originally delineated by 1) remain significant theoretical issues.

The dynamics in the dilute phases are particularly interesting and could be the key both to understanding these seemingly contradictory experiments and to determining the correct theoretical model. As well as the long-lived magnetic oscillations revealed by hole-burning experiments at $x = 4.5\%$ ⁸, cotunnelling of the electronic and nuclear moments on pairs of neighboring Ho^{3+} ions has been observed at the highest dilutions ($x = 0.1\%$)¹⁰ through its effect on the low-frequency zero-field susceptibility. It is appropriate to revisit the low-frequency susceptibility for several reasons. First, $\text{LiHo}_x\text{Y}_{1-x}\text{F}_4$ is expected to be a model for a wide class of transverse-field dipolar systems. Second, the observation of long decoherence times and signatures of long-range entanglement suggest the possibility of exploiting the Ho^{3+} ions as magnetic qubits. Finally, one would like to understand the precise role of the competition between the collective dipolar interaction, the nuclear spin bath and other decoherence pathways in determining the dynamics of the system¹⁹. Here we combine an experimental study of the magnetic response of the dilute system as we tilt the moment away from the Ising axis under large transverse fields with a theoretical analysis in which we average over all possible pairs. Our purpose is to establish—quantitatively—the extent to which collective (i.e. beyond-pair) effects are important for the behavior of the $x = 4.5\%$ compound by doing the most precise possible calculations of the pair susceptibility contribution at equilibrium. The outcome is that even for this relatively high level of dilution, the collective effects are important at low transverse fields.

We presented the experimental results and a short summary of the theoretical argument in Ref. 18. This paper gives full details of the model and is structured as follows. Section II summarizes the experimental techniques employed and captures briefly the relevant results; Section III describes the techniques employed in our calculations; Section IV sets out the computational results, comparing the susceptibilities with and without hyperfine interactions to each other and to the measured values; and Section V presents our conclusions. The Appendix presents details of the construction of a two-state model of the lowest crystal fields states of the Ho^{3+} ion, which is essential for making the sampling of a large number of pairs with hyperfine interactions computationally tractable.

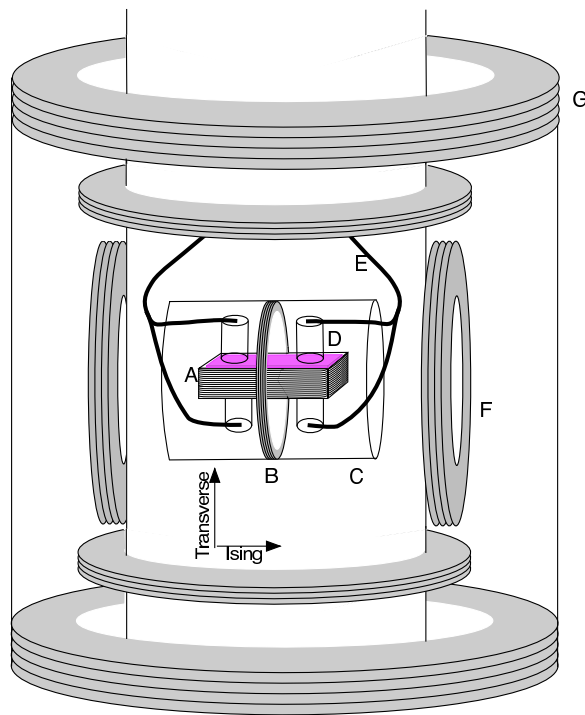


FIG. 1. (Color online) Schematic of the ac vector susceptometer used in the experiments. The sample sits inside nested pickup coils A and B, sensitive to magnetic response in the transverse and Ising directions, respectively. An ac magnetic field along the Ising axis is supplied by solenoid C; the sample is thermally sunk to the cryostat cold finger via sapphire rods D and copper wires E. A superconducting 3-axis Helmholtz coil F and an 8 T solenoid magnet G supply dc magnetic fields. G is almost, but not perfectly, aligned transverse to the c -axis of the sample.

II. SUSCEPTIBILITY MEASUREMENTS

A single $(5 \times 5 \times 10)$ mm³ crystal of $\text{LiHo}_{0.045}\text{Y}_{0.955}\text{F}_4$ was characterized using ac magnetic susceptibility in a helium dilution refrigerator. The magnetic response along the Ising axis and in the transverse plane was measured using a specially devised multi-axis ac susceptometer, as shown in Fig. 1. The sample was probed for a 101 Hz $2 \mu\text{T}$ ac magnetic field parallel to the Ising axis. A pair of nested inductive pickup coils allowed for simultaneous determination of the magnetic response parallel to and transverse to the Ising axis of the crystal. The crystal was thermally linked to the cold finger of the refrigerator via sapphire rods and heavy copper wires. A multi-axis set of 100 mT Helmholtz coils and an 8 T solenoid provided dc magnetic fields \mathbf{H}_{dc} parallel to and almost transverse to the Ising axis respectively; however, because of the difficulty in precisely aligning the crystal, we cannot exclude the possibility of a misalignment of the solenoid from the transverse axis occurring in a given experiment. For the experiments quoted here, the misalignment was measured as 0.6° . The effect on the predicted properties is discussed in §IV D below.

The measurement probes the diagonal and off-diagonal components respectively of the linear susceptibility tensor, but evaluated at the non-zero reference field \mathbf{H}_{dc} :

$$\chi_{zz} = \left. \frac{\partial M_z}{\partial H_z} \right|_{\mathbf{H}=\mathbf{H}_{\text{dc}}} ; \quad (1)$$

$$\chi_{xz} = \left. \frac{\partial M_x}{\partial H_z} \right|_{\mathbf{H}=\mathbf{H}_{\text{dc}}} . \quad (2)$$

$$(3)$$

Fig 2 shows our results for the real part of the longitudinal and transverse susceptibilities χ_{zz} and χ_{xz} as functions of \mathbf{H}_{dc} ¹⁸. These experimental results will be compared in section IV D to the predictions derived from the spin-pair model developed in the following sections. The off-diagonal linear susceptibility vanishes in the limit where \mathbf{H}_{dc} is exactly perpendicular to the Ising axis; as we shall see, a small component along z enables χ_{xz} to capture some of the

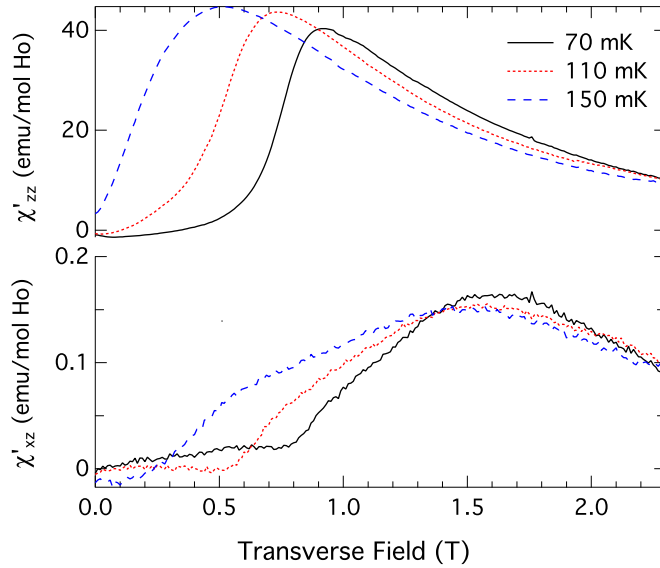


FIG. 2. (Color online) Measured longitudinal (top) and transverse (bottom) real susceptibility at 70, 110, and 150 mK (blue). (Adapted from Ref. 18)

non-linear dependence of \mathbf{M} on \mathbf{H} and hence to give information about clustering and correlation effects, as expected from previous work¹².

For ease of comparison with the literature, all computed and measured susceptibilities in this paper are reported in units of emu per mole of Ho^{3+} ions (1 emu mol^{-1} corresponds to a susceptibility of $4\pi \times 10^{-6} \text{ m}^3 \text{ mol}^{-1}$ in SI units). Note that because of the low concentration of Ho^{3+} , the quoted molar susceptibilities correspond to relatively small volume susceptibilities (of the order of 0.5 in SI units, or 0.04 emu cm^{-3} in the case of χ_{zz} , and 2.6×10^{-3} in SI or $2 \times 10^{-4} \text{ emu cm}^{-3}$ for χ_{xz}), and the samples are needle-shaped and elongated along the c -axis; therefore demagnetization corrections to the measured susceptibilities are negligible.

The choice of 101 Hz as the measurement frequency involves a compromise between the difficulty of performing accurate low-frequency measurements, and the desire to approach the static limit for the real part of χ as closely as possible. In assessing this the relevant comparison is with the characteristic frequency f_0 corresponding to onset of the sample's dissipative response; this slows dramatically as either field or temperature is reduced, but comparison with the previously published data^{17,21} shows that it lies well above 100 Hz even for temperatures as low as 60 mK provided that the transverse field exceeds about 3 kOe (0.3 T).

The imaginary part of the magnetic response was also measured¹⁸. Unlike the real part this remains strongly frequency dependent and, since the frequencies involved are small compared with all the energy scales of the microscopic Hamiltonian, a theoretical treatment depends on an understanding of the low-frequency relaxation dynamics of the Ho^{3+} ions and is not considered in the present paper.

III. Ho^{3+} PAIR MODEL

To construct a model for the susceptibility of Ho^{3+} pairs, we start with the complete microscopic Hamiltonian. The low-lying states of this Hamiltonian are then used to construct an effective 2-state H , which can be readily diagonalized for two interacting ions. If the hyperfine interactions from the microscopic single-ion Hamiltonian are added to this 2-state picture, the resulting H has 16 states, and the pair Hamiltonians are still numerically tractable. Finally, a weighting scheme is implemented that incorporates contributions for pairs beyond immediate nearest-neighbors.

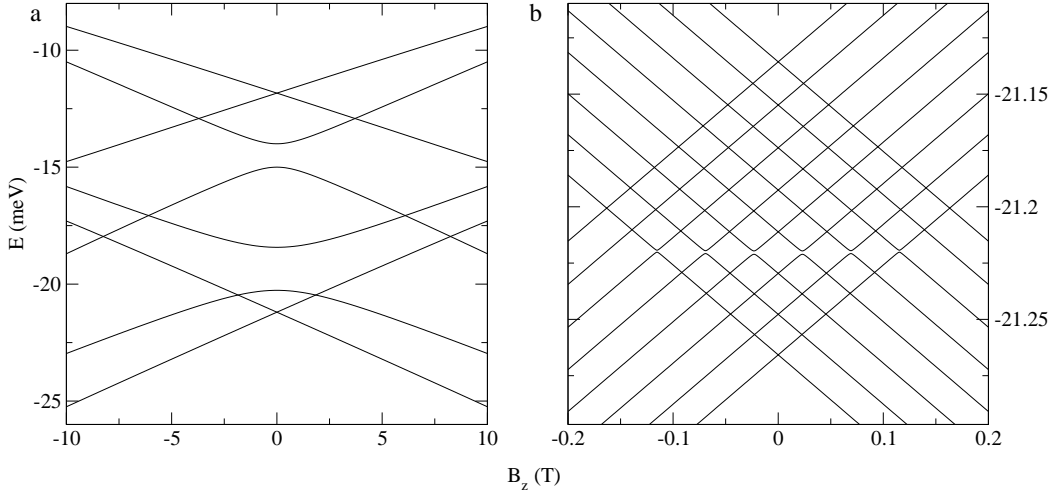


FIG. 3. Single-ion energy levels as a function of longitudinal magnetic field. (a) Lowest eight electronic crystal-field levels of the 5I_8 ground term as a function of field B_z parallel to the Ising axis. (b) Splitting of the two lowest electronic levels by the hyperfine interaction.

A. Microscopic Hamiltonian

The electronic Hamiltonian of a single Ho^{3+} ion in a magnetic field is

$$\begin{aligned} H_1 &= H_{\text{cf}} - \mathbf{m} \cdot \mathbf{B} \\ &= H_{\text{cf}} - \mu_B g_L \mathbf{J} \cdot \mathbf{B}, \end{aligned} \quad (4)$$

where $g_L = \frac{5}{4}$ is the Landé g factor. H_{cf} is the crystal field Hamiltonian, which splits the 17-fold degenerate 5I_8 ground term state of Ho, and is given by

$$H_{\text{cf}} = \sum_{l=2,4,6} B_l^0 O_l^0 + \sum_{l=4,6} B_l^4(c) O_l^4(c) + B_l^4(s) O_l^4(s), \quad (5)$$

where O_l^m are Stevens' operators²⁸. We follow Ref. 29 in taking the following values for the crystal-field parameters: $B_2^0 = -0.06$ meV, $B_4^0 = 3.5 \times 10^{-4}$ meV, $B_4^4 = 3.6 \times 10^{-3}$ meV, $B_6^0 = 4 \times 10^{-7}$ meV, $B_6^4(c) = 7.0 \times 10^{-5}$ meV and $B_6^4(s) = 9.8 \times 10^{-6}$ meV. (Note that despite the apparent smallness of the higher-order crystal field parameters, the normalization of the crystal-field parameters means that all these terms in fact make significant contributions to the spectrum.) The resulting electronic energy levels are shown in Figs. 3a and 4a as a function of fields parallel and transverse to the Ising axis.

The isotropic hyperfine coupling to the local $I = \frac{7}{2}$ Ho^{3+} nuclear spin can be included explicitly by defining

$$H_{\text{hf}} = H_{\text{cf}} \otimes \mathbb{I}_N + A \mathbf{J} \cdot \mathbf{I} + \mu_B g_L \mathbf{J} \cdot \mathbf{B} + \mu_N \mathbf{I} \cdot \mathbf{B}, \quad (6)$$

with $J_\alpha = j_\alpha \otimes \mathbb{I}_N$ and $A/k_B = 0.039$ K or $A = 3.4 \mu\text{eV}$. Figs. 3b and 4b show the effect of the hyperfine splitting on the lowest two crystal-field states (but computed using the entire single-ion Hamiltonian (6)). As emphasized by Ronnow *et al.*¹⁹ and Schechter and Stamp^{11,26}, although A is small compared with the characteristic intra-ion electronic energy scales, it is comparable to the inter-ion dipolar coupling (see §IV C). Its effect is to suppress the mixings between the two terms of the lowest electronic doublet at low temperatures, because the lowest electro-nuclear spin state in each branch has the nuclear and electronic moments anti-aligned and the nuclear moments cannot be reversed at low orders by any of the terms in equation (6).

The state-space required to correctly describe the 5I_8 ground term of Ho^{3+} in the presence of hyperfine splitting is then $(2 \times 8 + 1) \times (2 \times \frac{7}{2} + 1) = 136$. The full Hilbert space on an ion pair therefore has dimensionality $136^2 = 18496$, which is inconveniently large for the repeated exact diagonalizations required to treat a range of pair geometries and fields. We therefore proceed by truncating the model to a smaller state space while preserving the essential behavior.

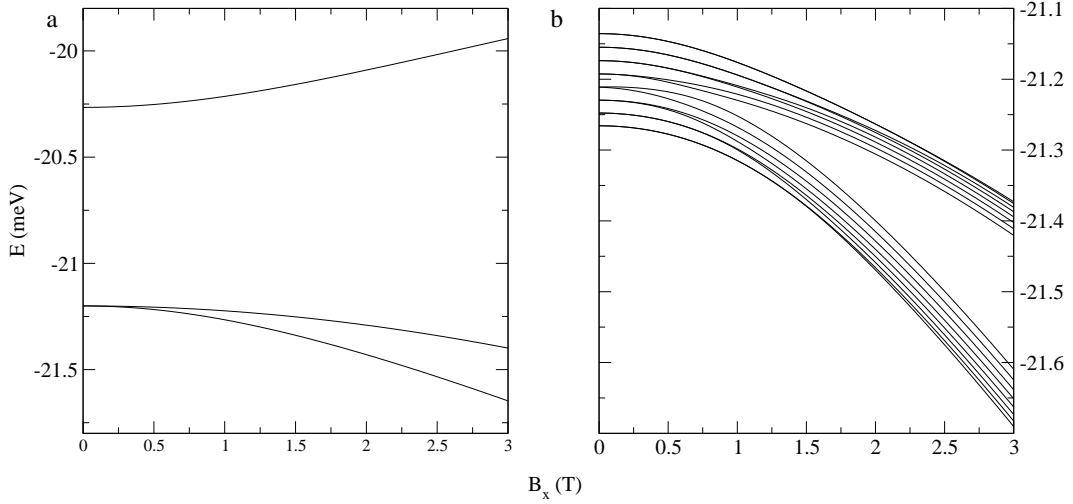


FIG. 4. Single-ion energy levels as a function of transverse magnetic field. (a) Lowest three electronic crystal-field levels in the presence of a field B_x transverse to the Ising axis. (b) Splitting of the two lowest electronic levels by the hyperfine interaction.

B. The electronic two-state system

Following Chakraborty *et al.*², we note the large (9.5 K) gap between the ground state doublet and the first excited crystal-field level (Fig. 4a). We therefore construct a Hamiltonian describing the low-energy behavior of the ion on a two-dimensional electronic Hilbert space, covering only these states. This is a parameterized model in which the inter-level repulsion shown in Fig. 4a is included explicitly as described below.

For a given value of transverse field B_x the following two-state Hamiltonian is defined:

$$H^{(2)} \equiv E_0(B_x)\mathbb{I}_2 + \frac{1}{2}\Delta(B_x)\sigma_x + \mu_B g_L \mathbf{j}_{\text{eff}} \cdot \mathbf{B}' . \quad (7)$$

Here \mathbb{I}_2 is the identity operator in two dimensions and σ_x is a spin-half Pauli operator. $E_0(B_x)$ is the mid-point of the lowest two energy levels and $\Delta(B_x)$ their splitting in that transverse field. The effective angular momentum operators \mathbf{j}_{eff} are chosen to reproduce the correct physical angular momentum matrix elements for the two states; their decomposition into Pauli operators is discussed in Ref. 2. Finally, the field \mathbf{B} has been replaced with the effective field $\mathbf{B}' \equiv \mathbf{B} - B_x \hat{\mathbf{i}}$, from which the x -component (now represented by the splitting $\Delta(B_x)$) has been removed. Further details of the two-state reduction, and a quantitative comparison of its spectrum with that of the full Hamiltonian, are given in Appendix A.

Note that at first sight one might expect that it would also be possible to construct a *three-state* model, including the two-fold degenerate ground state as well as the first excited state, which are relatively well separated from the rest of the spectrum (see Figure 3). However it turns out that level repulsion from the rest of the spectrum becomes significant at modest external fields², and for this reason it is preferable to parameterize a two-state effective Hamiltonian operator for every value of transverse field in order to incorporate all these effects.

In the presence of the $I = \frac{7}{2}$ hyperfine interaction, the two-state model becomes

$$H_{\text{hf}}^{(2)} \equiv E_0(B_x)\mathbb{I}_{16} + \frac{1}{2}\Delta(B_x)\sigma_x \otimes \mathbb{I}_8 + \mu_B g_L \mathbf{J}_{\text{eff}} \cdot \mathbf{B}' + \mu_N \mathbf{I} \cdot \mathbf{B} + A \mathbf{J}_{\text{eff}} \cdot \mathbf{I} , \quad (8)$$

with $\mathbf{J}_{\text{eff}} \equiv \mathbf{j}_{\text{eff}} \otimes \mathbb{I}_N$. This has a dimensionality of 16, and thus the Hamiltonian of a pair of spins will have a numerically tractable dimensionality of 256. In this paper we therefore retain the full nuclear Hilbert space when considering the hyperfine interaction, rather than restricting the model further to the lowest electro-nuclear doublet as in Ref. 26.

C. Intra-ion coupling

We neglect the small exchange interactions between the Ho^{3+} ions, so in our model pairs are coupled only by the magnetic dipole interaction. Angular momentum operators are constructed for each spin in a direct product Hilbert

space. The dipole coupling between spins at \mathbf{R}_1 and \mathbf{R}_2 is then

$$H_{12} = \frac{\mu_0(\mu_B g_L)^2}{R_{12}^3} \sum_{\alpha\beta} \left(\delta_{\alpha\beta} - \frac{3R_{12}^\alpha R_{12}^\beta}{R_{12}^2} \right) J_\alpha^{(1)} J_\beta^{(2)}, \quad (9)$$

where $\mathbf{R}_{12} \equiv \mathbf{R}_2 - \mathbf{R}_1$ and $J_\alpha^{(i)}$ is component α of the total angular momentum of ion i . The total Hamiltonian of the pair is

$$H_{\text{pair}} = H_1 + H_2 + H_{12}. \quad (10)$$

Note that for a given pair, the spin $J_\beta^{(2)}$ at site 2 gives rise to a pair interaction H_{12} containing an effective field at site 1

$$B_{\text{eff},\alpha}^{(1)} = \frac{\mu_0(\mu_B g_L)}{R_{12}^3} \sum_{\beta} \left(\delta_{\alpha\beta} - \frac{3R_{12}^\alpha R_{12}^\beta}{R_{12}^2} \right) J_\beta^{(2)}, \quad (11)$$

which in general contains a transverse component. Strictly, therefore, the field-dependent parameters in equation (7) should be computed incorporating this component. However, in practice this dependence is negligible for the applied fields of interest because the characteristic scale of $B^{(1)}$ is at most $\mu_0\mu_B g_L |J^{(2)}|/a^3 = 29 \text{ mT}$, while the experimental variation of χ is on the scale of fields that can mix the Ising doublet, of order 1 T (see Figures 2 and 4).

D. Computing the susceptibility

The isothermal susceptibility is defined as

$$\chi_{\alpha\beta} \equiv \frac{1}{V} \left(\frac{\partial \langle m_\alpha \rangle}{\partial H_\beta} \right)_T, \quad (12)$$

where \mathbf{m} is the total magnetic moment and V is the sample volume. We apply this by computing the field-dependent eigenstates of the pair Hamiltonian (10) and computing

$$\begin{aligned} \chi_{\alpha\beta} &= -\frac{1}{k_B T Z V} \sum_i \exp(-E_i/k_B T) \langle i | \Delta \hat{m}_\alpha | i \rangle \langle i | \Delta \hat{m}_\beta | i \rangle \\ &\quad + \frac{1}{Z V} \sum_i \exp(-E_i/k_B T) \sum_j ' 2\Re \left[\frac{\langle i | \hat{m}_\alpha | j \rangle \langle j | \hat{m}_\beta | i \rangle}{E_i - E_j} \right] \\ &= \chi_{\text{Langevin}} + \chi_{\text{Van Vleck}}, \end{aligned} \quad (13)$$

where the primed sum goes over all states i and j such that $E_i \neq E_j$, \Re denotes the real part, and $\Delta m_\alpha \equiv m_\alpha - \langle m_\alpha \rangle$. Matrix elements between degenerate states have been made to vanish by a choice of basis such that \hat{m}_β is diagonal in each degenerate subspace. Numerically we assume states i and j are degenerate if $E_j - E_i < \varepsilon$, a small value chosen such that the susceptibility is not sensitive to variations in ε ; in these results we used $\varepsilon = 10^{-7} \text{ meV}$. Note that in applying equation (12) we assume that the Ho^{3+} ions remain in thermal equilibrium over the timescales of the experiment, i.e. that all thermalizing relaxation processes operate on a timescale fast compared to the measurement.

E. A pair-ensemble weighting scheme

We wish not only to examine the behavior of specific pairs of spins, but also to calculate the average response for a distribution of spin pairs corresponding to the physical $\text{LiHo}_{0.045}\text{Y}_{0.955}\text{F}_4$ crystal. We proceed by assuming that at this dilute concentration the behavior of each spin is affected only by the closest spin and compute a weighted susceptibility. This is determined by computing the susceptibility of an exhaustive sample of pairs of spins up to some cutoff distance r_c and weighting each term by the probability that in a randomly populated set of sites in a lattice with mean fractional occupancy x , the chosen spin s_2 would be the nearest occupied site to the reference spin s_1 . If all the sites were at different distances, this would be given by the probability that no sites nearer to s_1 than s_2 are occupied, while the site s_2 itself is occupied. The weighting for a site s_j would then be

$$w_j = x(1-x)^{N_j}, \quad (14)$$

where N_j is the number of sites closer to s_1 than s_j . However in practice the sites s_2 occur in ‘shells’ with equal distance from s_1 ; if there are n_j sites in shell j , we ascribe a weighting to each site which is a fraction $1/n_j$ of the probability that there is at least one neighboring spin anywhere in the shell:

$$w_j = \left[\frac{1 - (1 - x)^{n_j}}{n_j} \right] (1 - x)^{N_j}. \quad (15)$$

The cutoff distance r_c is always chosen such that the probability of the nearest occupied site s_2 being more than r_c from s_1 does not significantly exceed 10^{-3} ; the required r_c therefore increases as x falls. For the calculations presented here we included 22 shells of neighbors containing 146 ions, corresponding to $r_c = 2.58a = 13.4 \text{ \AA}$. At the experimental spin concentration ($x = 0.045$) the probability that the pair separation exceeds r_c is then 1.20×10^{-3} .

IV. RESULTS

A. Contributions of individual pairs

The magnetic response of a pair of Ho spins depends strongly on their separation and orientation. Fig 5 shows the Ising-axis and transverse response of all pairs that make a significant contribution to the cluster ensemble. Although these plots are of illustrative value in demonstrating the wide range of behaviors arising from spin pairs, it is more useful to examine how these different responses contribute to the ensemble average. Fig 6 shows these averages by plotting the susceptibilities of each pair using the weighting w_i as a color map. Susceptibility bands appear in this weighted map due to particular closely neighboring spin pairs. It can also be seen that for every pair of spins with a transverse susceptibility $\chi_{xz}(B_x) = f(B_x)$, there exists a pair with $\chi_{xz}(B_x) = -f(B_x)$. It thus follows that an ensemble average as defined in Sec. III E will give a zero value of χ_{xz} for all values of field B_x . As discussed below, the measured response is well described by a small (0.6°) tilt of B_x , producing a polarizing field along the Ising axis. A comparison of the weighted susceptibilities with and without the incorporation of hyperfine effects suggests that the primary effect of the hyperfine term is to renormalize the transverse field; this behavior is discussed in more detail in Section IV C below.

B. Pair orientation and response

Depending on relative orientation, the dipole coupling can be either ferromagnetic or antiferromagnetic. A ferromagnetic pair has a susceptibility χ_{zz} which diverges in the limit of low temperatures and zero transverse field, whereas an antiferromagnetically coupled pair has vanishing susceptibility in the same limit. As can be seen from Fig. 2, antiferromagnetic behavior dictates the measured response of the sample of $\text{LiHo}_{0.045}\text{Y}_{0.955}\text{F}_4$, and as shown in Fig 5 certain pairs show a qualitatively similar magnetic response. As we shall see below, however, their contribution to the ensemble average used in this paper is not sufficient to make the overall average susceptibility agree with the measured one.

The relation of this behavior to the crystal structure can be understood from Fig. 7, showing the zero-field susceptibility at $T = 70 \text{ mK}$ of a pair of Ho^{3+} ions separated by a distance r in the a - b plane and z on the c -axis. The crossover between the ferromagnetic and antiferromagnetic couplings occurs along the line $z/r = 1/\sqrt{2}$; the strongly antiferromagnetic pairs are located in-plane at $(1, 0, 0)$ and $(2, 0, 0)$ and the most strongly ferromagnetic pair is the nearest-neighbor pair at $(\frac{1}{2}, 0, \frac{1}{4})$. Note that the on-axis pair $(0, 0, 1)$ is more weakly ferromagnetic at this temperature, owing to the larger spatial separation.

C. The effect of the hyperfine interaction

We now examine the role that hyperfine interactions play in determining the behavior of the system. It is important to understand whether these effects produce a qualitative change in the behavior, as expansion of this model to $n = 3$ and larger clusters of spins becomes numerically impractical if the hyperfine splittings are essential. Fig. 8 shows susceptibilities for high-weight spin pairs both with and without hyperfine effects. (Note that pairs such as $(\frac{1}{2}, 0, \frac{1}{4})$ and $(0, \frac{1}{2}, \frac{1}{4})$, which are equivalent at zero field, become inequivalent for non-zero fields, except when the field lies along symmetry directions such as $(1, 1, 0)$.) We see that the primary role of the hyperfine interactions is to renormalize the applied transverse field, rather than to introduce fundamentally different behavior. This in turn suggests that useful insights may be derived from considering larger spin clusters in the absence of the hyperfine splittings. It should be

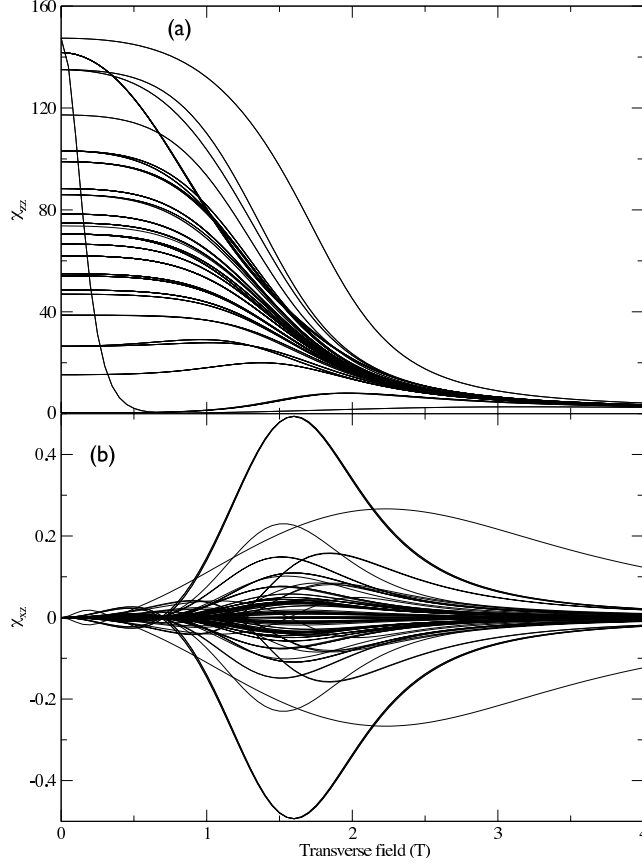


FIG. 5. Computed susceptibilities (in emu mol^{-1}) for all pairs of spins at $T=70$ mK, with hyperfine interactions included. (a) Diagonal response χ_{zz} . (b) Off-diagonal response χ_{xz} .

noted, however, that the strongly ferromagnetic $(\frac{1}{2}, 0, \frac{1}{4})$ pair does not show this renormalization when it is oriented so that the projection of the separation vector into the ab -plane lies along the transverse field direction.

D. The ensemble-averaged susceptibilities

Fig. 9 shows the experimental and ensemble-averaged longitudinal susceptibility χ_{zz} . The left panel shows computed and experimental results at temperatures of 70, 110 and 150 mK. Computed results include the effect of the hyperfine response, but omit in this panel the effect of tilting the field B_x . The model captures the overall temperature dependence of the data, but it cannot account for the low-field suppression of the susceptibility because the average is dominated by the contributions of ferromagnetic and effectively uncoupled pairs.

The right panel of Fig. 9 shows the effects of varying the parameters of the model at a constant $T=70$ mK. The dashed curves show the result of removing the hyperfine terms; for most of the field range, the renormalization seen in the individual pair susceptibilities is visible. At low field, the strongly ferromagnetic $(\frac{1}{2}, 0, \frac{1}{4})$ pairing dominates, and no renormalization is seen. The dotted curve shows the result of keeping the hyperfine effects and adding a 0.6° tilt to the applied field, with the attendant slight polarization along the Ising axis. We can see that this improves the match between the high-field behavior of the model and the experiment.

Fig. 10 displays similar information for χ_{xz} . Note that owing to the symmetry observed in Fig. 5(b), the ensemble average of χ_{xz} vanishes in the absence of a polarizing field. Thus, the only appropriate comparison is between the tilted-field computation and the measured value, as shown in the left pane of Fig. 10 for both single-ion and ensemble-pair-average computations. It is clear that the tilt is responsible for the measured effect, with the pair average providing a better match to the measured susceptibility than a single-ion calculation. The effect of the hyperfine response is the same renormalization of the field seen in the longitudinal response. The right pane of this figure shows the effect of temperature on both the measured and the pairwise average χ_{xz} .

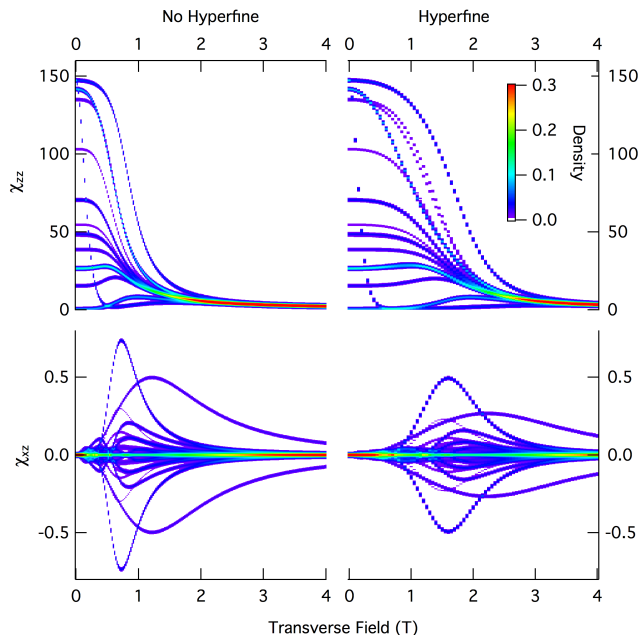


FIG. 6. (Color online) Contribution of the various pairs to the ensemble-averaged functions $\chi_{xz}(B_x)$ (top) and $\chi_{zz}(B_x)$ (bottom). The colour scale shows the total weighted contribution of all pairs to a given susceptibility at a given field. Left and right plots, respectively, show the effects of omitting and including the hyperfine term in the Hamiltonian. The temperature was $T = 70$ mK and the field was applied along $(1, 0, 0)$. Susceptibilities are given in emu mol^{-1} .

V. CONCLUSIONS

We have developed a spin-pair model for understanding the behavior of dilute $\text{LiHo}_x\text{Y}_{1-x}\text{F}_4$. A weighted ensemble average of all spin pairs reproduces the high-transverse-field experimental susceptibility, but not the low-field antiferromagnetic character of the data. Nonetheless, the rise in the longitudinal susceptibility at a transverse field of around 1 T, which looks like a signature of a spin gap, does correspond to the calculated susceptibility for certain antiferromagnetic pairs. This suggests that a full understanding of the system requires either the treatment of larger clusters, an extension which should be numerically feasible because of the observation that the primary effect of the hyperfine splitting in the dc susceptibility is to renormalize the transverse field. This will allow extension of the model to larger clusters of spins using the simplified 2-state description for individual spins rather than a full 16-state description. Ultimately, to reach the thermodynamic limit, it would still be necessary to generalize a scaling approach, such as the real-space renormalization group of Ref. 9, to include finite transverse fields.

Recent theoretical studies of the pure material ($x = 1$), in which a two-state reduced Ising model on a lattice is studied by classical Monte Carlo approaches^{2,16}, are complementary to the approach presented here because they include long-range dipolar physics missed by our cluster expansion, but at the cost of ignoring quantum corrections to the behaviour of individual pairs. It is interesting that these classical calculations disagree with experiment in some significant respects, especially at low transverse fields³⁰. It is still not clear whether this disagreement originates within the classical approximations made or in the underlying crystal-field model¹⁶; a scaling extension to our method, which should be most rapidly convergent in the high-dilution limit, could give additional insight in this problem. Such an extension would also sample somewhat different regions of the cluster configuration space, since Fig. 7 shows that the antiferromagnetic region extends considerably farther in distance than does the ferromagnetic region. This space is not sampled significantly in the pairwise model, owing to the rapid fall-off of the weighting function w_i with distance, but larger clusters can sample this interaction region far more extensively.

Additionally, it would be useful to consider the dynamics of the magnetic response at the lowest fields, where its characteristic timescale exceeds that of the experiments, in order to improve the agreement between experiment and theory in that region.

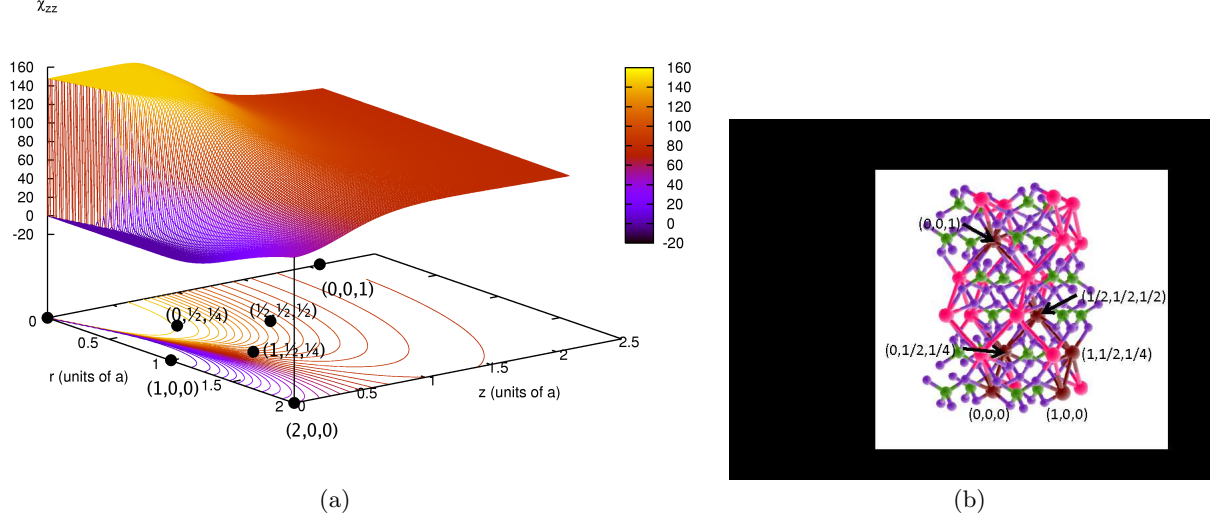


FIG. 7. (Color online) (a) The effect of geometry on χ_{zz} , computed in the absence of hyperfine interactions with zero transverse field and temperature $T = 70$ mK. Response is plotted for a pair of spins with axial separation z and in-plane separation r (units of lattice parameter a) with the marked points showing the locations of various near neighbors. The susceptibility is shown in units of emu/mol Ho. (b) View of the structure showing pairs marked in (a).

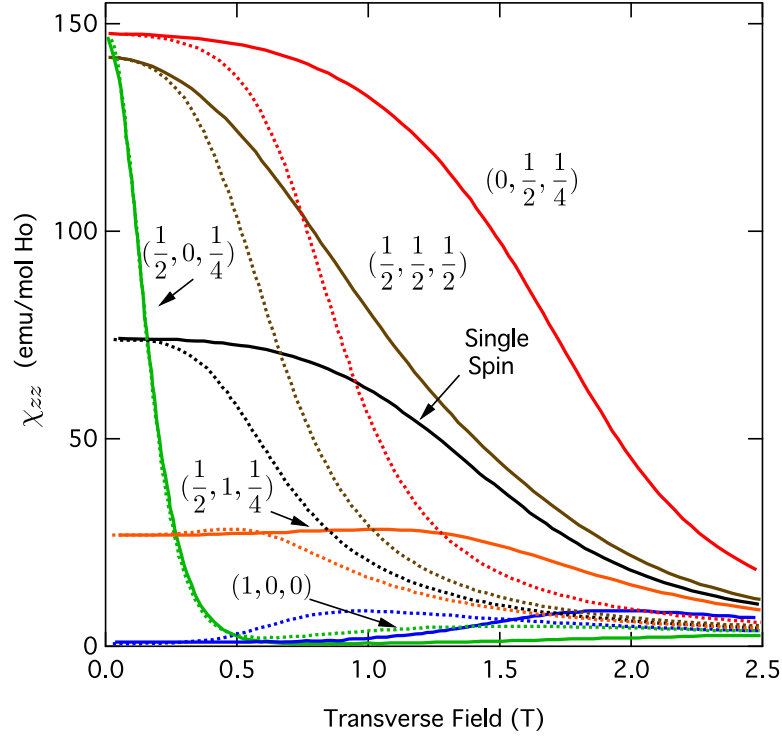


FIG. 8. (Color online) The magnetic response at $T = 70$ mK of certain important spin pairs, using a Hamiltonian which incorporates hyperfine effects (solid) and which omits these effects (dotted). The primary effect of adding the hyperfine splitting is to impose an effective renormalization of the transverse field scale. The transverse field is applied along the $(1, 0, 0)$ direction.

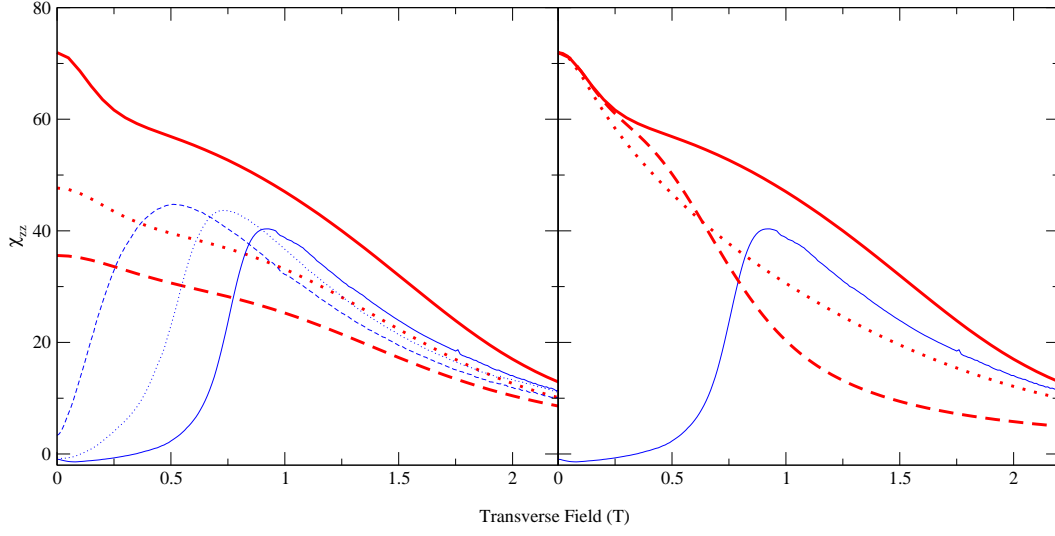


FIG. 9. (Color online) Measured and computed χ_{zz} (in units of emu/mol Ho). (left) Computed (heavy, red curves) and measured (blue, light) susceptibility. Solid, dotted and dashed curves are $T=70$ mK, 110 mK and 150 mK respectively. (Right) The effect of tilting the transverse field (dotted curve), and of omitting the hyperfine interaction (dashed), at $T=70$ mK. Unbroken red (heavy) and blue (light) curves, again show the computed (with hyperfine, no tilting) and measured susceptibilities respectively.

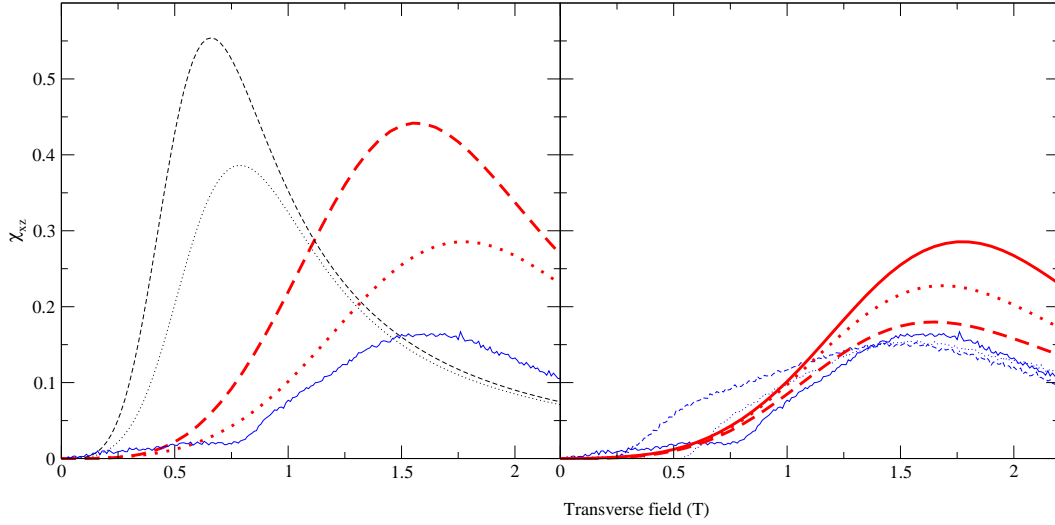


FIG. 10. (Color online) The apparent transverse susceptibility (in emu mol^{-1}) resulting from a transverse field tilted by 0.6° . (Left) Measured susceptibility (blue, thin, solid curve) is contrasted with the susceptibility of a single ion in a tilted field (dashed curves), and the pairwise average susceptibility (dotted). The heavy, red curves include hyperfine effects. The thin, grey curves do not. (Right) The effect of temperature. Measurements are shown as light, blue curves; calculations as heavy, red curves. Temperatures are 70 mK (solid curve), 110 mK (dotted) and 150 mK (dashed).

ACKNOWLEDGMENTS

The work at the University of Chicago was supported by U.S. DOE Basic Energy Sciences Grant No. DE-FG02-99ER45789, and that at UCL by the U.K. Engineering and Physical Sciences Research Council under grant EP/D049717/1.

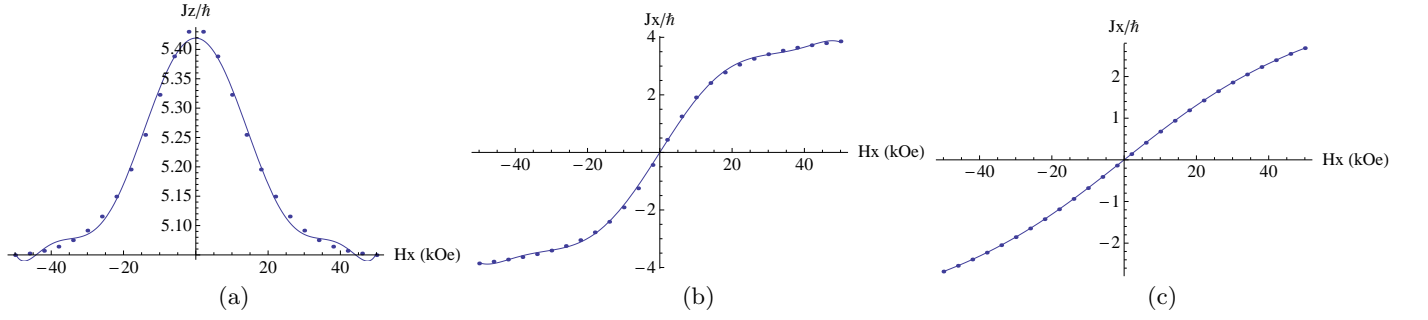


FIG. 11. Comparison of expectation values of electronic spin operators from a two-level fit and from a full crystal-field calculation, as a function of transverse field. (a) $\langle J_z \rangle$ in the basis state $|\uparrow\rangle$ (and hence also the off-diagonal matrix element of J_z between the states of the doublet); (b) expectation value of J_x in the lower state of the doublet; (c) expectation value of J_x in the upper state of the doublet. In all cases solid points are the full results and the lines are the two-level fits.

Appendix A: The two-state reduction

The prescription for the construction of the low-energy subspace is similar to that described in Ref. 2. The mean energy $E_0(B_x)$ and the splitting $\Delta(B_x)$ are tabulated as a function of B_x . The eigenstates $|\uparrow\rangle$ and $|\downarrow\rangle$ of the two-state pseudospin operator σ_z are then taken as

$$|\uparrow\rangle = \frac{1}{\sqrt{2}} (|0\rangle + e^{i\theta} |1\rangle); \quad |\downarrow\rangle = \frac{1}{\sqrt{2}} (|0\rangle - e^{i\theta} |1\rangle), \quad (\text{A1})$$

with the phase θ chosen to ensure that $|\uparrow\rangle$ and $|\downarrow\rangle$ also diagonalize the physical operator J_z (so the representation of J_z within this subspace corresponds to a multiple of the Pauli operator σ_z). The single-ion electronic Hamiltonian is then given by equation (7). Figure 11 shows how the matrix elements of the spin operators are reproduced in the fit.

By construction this two-level model gives an accurate description of a single ion at temperatures well below about 10 K (where excitations outside the ground-state doublet become important). We now need to check that it also gives an adequate representation of pairs, where the field on each ion contains a contribution from the other spin as well as from the external field. Figure 12 shows the lowest energy levels computed from a full electronic calculation and from the two-level system, both with and without the coupling to the nuclear spins; it can be seen that the splittings arising from the dipolar interactions of the pair are accurately reproduced.

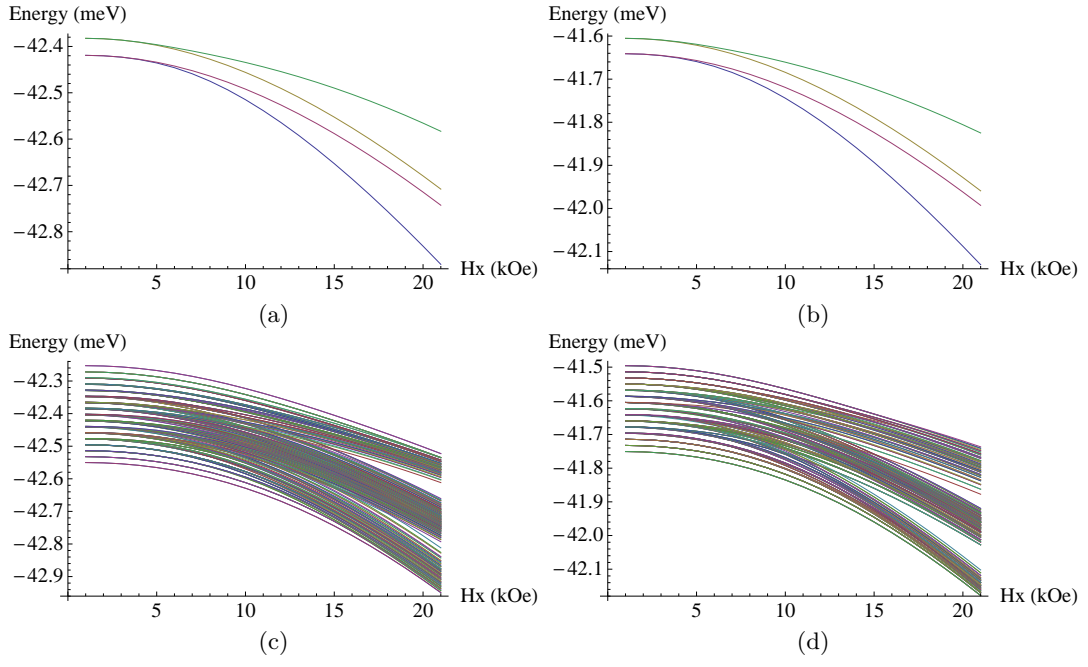


FIG. 12. Comparison between the full eigenvalue spectrum (left) for an ion pair separated by $(a, 0, 0)$ and the two-state reduction (right). The upper row (parts (a) and (b)) shows the four lowest electronic states only; the lower row (parts (c) and (d)) includes the hyperfine interaction with the nuclear states, showing the 256 corresponding hyperfine levels.

-
- * andrew.fisher@ucl.ac.uk
- ¹ D. Bitko, T. Rosenbaum, and G. Aeppli, Physical Review Letters, **77**, 940 (1996).
 - ² P. Chakraborty, P. Henelius, H. Kjonsberg, A. Sandvik, and S. Girvin, Physical Review B, **70**, 144411 (2004).
 - ³ A. H. Cooke, D. A. Jones, J. F. A. Silva, and M. R. Wells, Journal Of Physics C-Solid State Physics, **8**, 4083 (1975).
 - ⁴ P. Beauvillain, J. Renard, I. Laursen, and P. Walker, Physical Review B, **18**, 3360 (1978).
 - ⁵ G. Mennenga, L. de Jongh, and W. Huiskamp, Journal of Magnetism and Magnetic Materials, **44**, 59 (1984).
 - ⁶ D. H. Reich, T. F. Rosenbaum, and G. Aeppli, Physical Review Letters, **59**, 1969 (1987).
 - ⁷ R. Giraud, W. Wernsdorfer, A. Tkachuk, D. Mailly, and B. Barbara, Physical Review Letters, **87**, 057203 (2001).
 - ⁸ S. Ghosh, R. Parthasarathy, T. F. Rosenbaum, and G. Aeppli, Science, **296**, 2195 (2002).
 - ⁹ S. Ghosh, T. F. Rosenbaum, G. Aeppli, and S. N. Coppersmith, Nature, **425**, 48 (2003).
 - ¹⁰ R. Giraud, A. M. Tkachuk, and B. Barbara, Physical Review Letters, **91**, 257204 (2003).
 - ¹¹ M. Schechter and P. C. E. Stamp, Physical Review Letters, **95**, 267208 (2005).
 - ¹² D. M. Silevitch, D. Bitko, J. Brooke, S. Ghosh, G. Aeppli, and T. F. Rosenbaum, Nature, **448**, 567 (2007).
 - ¹³ J. Quilliam, C. Mugford, A. Gomez, S. Kycia, and J. Kycia, Physical Review Letters, **98**, 037203 (2007).
 - ¹⁴ P. Jönsson, R. Mathieu, W. Wernsdorfer, A. Tkachuk, and B. Barbara, Physical Review Letters, **98**, 256403 (2007).
 - ¹⁵ A. Biltmo and P. Henelius, Physical Review B, **78**, 054437 (2008).
 - ¹⁶ S. M. A. Tabei, M. J. P. Gingras, Y.-J. Kao, and T. Yavors'kii, Physical Review B, **78**, 184408 (2008).
 - ¹⁷ W. Wu, B. Ellman, T. Rosenbaum, G. Aeppli, and D. Reich, Physical Review Letters, **67**, 2076 (1991).
 - ¹⁸ D. M. Silevitch, C. M. S. Gannarelli, A. J. Fisher, G. Aeppli, and T. F. Rosenbaum, Physical Review Letters, **99**, 057203 (2007).
 - ¹⁹ H. Ronnow, R. Parthasarathy, J. Jensen, G. Aeppli, T. Rosenbaum, and D. McMorrow, Science, **308**, 389 (2005).
 - ²⁰ J. Quilliam, S. Meng, and C. Mugford, Physical Review Letters, **101** (2008).
 - ²¹ C. Ancona-Torres, D. Silevitch, and G. Aeppli, Physical Review Letters, **101**, 057201 (2008).
 - ²² J. Snider and C. Yu, Physical Review B, **72**, 214203 (2005).
 - ²³ A. Biltmo and P. Henelius, Physical Review B, **76**, 054423 (2007).
 - ²⁴ K.-M. Tam and M. J. P. Gingras, Physical Review Letters, **103**, 087202 (2009).
 - ²⁵ M. Schechter and N. Laflorencie, Physical Review Letters, **97**, 137204 (2006).
 - ²⁶ M. Schechter and P. C. E. Stamp, Physical Review B (Condensed Matter and Materials Physics), **78**, 054438 (2008).
 - ²⁷ M. J. P. Gingras and P. Henelius, Journal of Physics Conference Series, **320**, 012001 (2011).
 - ²⁸ J. Jensen and A. R. Mackintosh, *Rare Earth Magnetism: Structures and Excitations* (Clarendon Press, Oxford, 1991).
 - ²⁹ H. M. Ronnow, J. Jensen, R. Parthasarathy, G. Aeppli, T. F. Rosenbaum, D. F. McMorrow, and C. Kraemer, Physical Review B, **75**, 054426 (2007).
 - ³⁰ J. L. Dunn, C. Stahl, Y. Reshitnyk, W. Sim, and R. W. Hill, "Dilatometric Study of LiHoF₄ In a Transverse Magnetic Field," (2010), arXiv:1005.1935.