



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Checkerboard order in vortex cores from pair-density-wave superconductivity

Daniel F. Agterberg and Julien Garaud

Phys. Rev. B **91**, 104512 — Published 16 March 2015

DOI: [10.1103/PhysRevB.91.104512](https://doi.org/10.1103/PhysRevB.91.104512)

# Checkerboard order in vortex cores from pair density wave superconductivity

Daniel F. Agterberg<sup>1</sup> and Julien Garaud<sup>2,\*</sup>

<sup>1</sup>*Department of Physics, University of Wisconsin-Milwaukee, Milwaukee, WI 53211*

<sup>2</sup>*Department of Theoretical Physics, KTH-Royal Institute of Technology, Stockholm, SE-10691 Sweden*

(Dated: February 26, 2015)

We consider competing pair density wave (PDW) and  $d$ -wave superconducting states in a magnetic field. We show that PDW order appears in the cores of  $d$ -wave vortices, driving checkerboard charge density wave (CDW) order in the vortex cores, that is consistent with experimental observations. Furthermore, we find an additional CDW order that appears on a ring outside the vortex cores. This CDW order varies with a period that is twice that of the checkerboard CDW and it only appears where both PDW and  $d$ -wave order co-exist. The observation of this additional CDW order would provide strong evidence for PDW order in the pseudogap phase of the cuprates. We further argue that the CDW seen by nuclear magnetic resonance at high fields is due to a PDW state that emerges when a magnetic field is applied.

PACS numbers: 74.20.De, 74.20.Rp, 71.45.Lr

Pair density wave (PDW) superconducting order has emerged as a realistic candidate for order in the charge ordered region of the pseudogap phase of the cuprates near one eighth filling. It naturally accounts for both superconducting (SC) correlations and for static quasi-long-range charge density wave (CDW) order observed near this hole doping and at temperatures below approximately 150 K [1–7] and it can explain observed signatures of broken time-reversal symmetry [8–13]. Moreover, PDW can lead to the quantum oscillations seen in the cuprates [14] and can also explain anomalous quasi-particle properties observed by angle resolved photoemission (ARPES) measurements [7]. In addition, numerical simulations of theories of a doped Mott insulator reveal PDW order to be a competitive ground state to  $d$ -wave superconductivity [15]. It is therefore important to find experiments that can identify PDW order in the cuprates. Motivated by the observation of checkerboard CDW order inside  $d$ -wave vortex cores by scanning tunnelling microscopy (STM) [16, 17] and by nuclear magnetic resonance (NMR) [18, 19], we examine the competition between  $d$ -wave and PDW superconductivity in applied magnetic fields. Previous theoretical studies of competing orders in a magnetic field have emphasized competing spin density wave (SDW) [20, 21], CDW order [20–22], and staggered flux phases [23, 24] with  $d$ -wave superconductivity. Competing PDW and  $d$ -wave order has not been extensively studied (note that superconducting phase disordered PDW competing with  $d$ -wave order has been examined [25]). Here, we find that inside the vortex cores of  $d$ -wave superconductivity, PDW order drives the observed checkerboard CDW order and, in conjunction with  $d$ -wave superconductivity, it also drives an additional CDW order that appears in a ring-like region outside the vortex cores. This additional CDW order has twice the period of the observed checkerboard CDW order and serves as a smoking gun for PDW order.

In the following, we develop a phenomenological the-

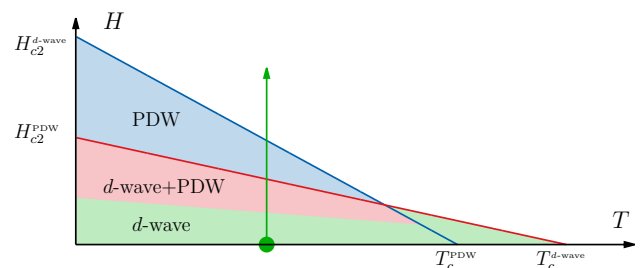


Figure 1. (Color online) – Sketch of the field/temperature phase diagram of the model with competing order. For low applied fields, the  $d$ -wave ( $\Delta_d$ ) is present, and it completely suppresses the PDW ( $\Delta_{\text{PDW}}$ ). This is the green (lower) region of the phase diagram. When increasing the external field, the  $d$ -wave order is substantially suppressed, eventually triggering a phase transition where the PDW overcomes the competition with the  $d$ -wave and develops a non-zero averaged density. For sufficiently low temperatures, the second critical field of the PDW order exceeds that of the  $d$ -wave order. As a result, further increase of the external field completely suppresses the  $d$ -wave order, leaving only  $\Delta_{\text{PDW}}$ , which survives up to  $H = H_{c2}^{\text{PDW}}$ , as shown in the blue (upper) region of the diagram. The PDW order qualitatively accounts for emergence of CDW at high fields, provided the superconducting order of the PDW is suppressed by phase fluctuations.

ory for competing PDW and  $d$ -wave superconductivity, sketched in Fig. 1. We assume that in zero field, only  $d$ -wave superconductivity appears at the expense of the PDW order. The PDW order can only appear when the  $d$ -wave order is weakened by the external field. This is followed by an analysis of the core structure of a single  $d$ -wave vortex, where we show that PDW order appears inside these cores, without any phase winding, generating the CDW order discussed above. Finally, we examine the behavior of this competing system as field is further increased and identify a transition at which PDW order develops phase coherence and forms a vortex phase. At the mean-field level, PDW order simultaneously breaks gauge invariance and translational symmetry. Fluctua-

tions can lead to two separate transitions: one for which gauge symmetry is broken and one for which translational symmetry is broken [26]. We argue that at high fields, the superconducting order is removed by phase fluctuations, leaving behind the CDW order seen through NMR experiments.

*Ginzburg Landau theory of competing d-wave and PDW superconductivity.* To investigate the physics resulting from the  $H$ - $T$  phase diagram shown in Fig. 1, we consider a model with competing  $d$ -wave and PDW superconductivity. The PDW order parameter is represented by a four component complex vector  $\Delta_{\text{PDW}}$ , defined as  $\Delta_{\text{PDW}}^\dagger = (\Delta_{\mathcal{Q}_x}^*, \Delta_{-\mathcal{Q}_x}^*, \Delta_{\mathcal{Q}_y}^*, \Delta_{-\mathcal{Q}_y}^*)$  and the  $d$ -wave by one complex (scalar) field  $\Delta_d$ . For an external applied field  $\mathbf{H}$ , which we will take to be along the  $z$ -axis:  $\mathbf{H} = H\mathbf{e}_z$ , the Ginzburg-Landau free energy density is

$$\mathcal{F} = \frac{\mathbf{B}^2}{2} - \mathbf{B} \cdot \mathbf{H} + \mathcal{F}_{d\text{-wave}} + \mathcal{F}_{\text{PDW}} + \mathcal{F}_{\text{Int}}, \quad (1)$$

where  $\mathbf{B} = \nabla \times \mathbf{A}$  is the magnetic field and  $\mathbf{A}$  its vector potential.  $\mathcal{F}_{\text{PDW}}$  describes the pair density wave  $\Delta_{\text{PDW}}$ , and  $\mathcal{F}_{\text{Int}}$  its coupling to the  $d$ -wave order that obeys

$$\mathcal{F}_{d\text{-wave}} = \frac{1}{2} |\mathbf{D}\Delta_d|^2 + \alpha_d |\Delta_d|^2 + \frac{\beta_d}{2} |\Delta_d|^4, \quad (2)$$

with  $\mathbf{D} = \nabla + ie\mathbf{A}$ . Symmetry arguments dictate the free energy of the PDW has the following structure [5]:

$$\begin{aligned} \mathcal{F}_{\text{PDW}} = & \frac{1}{2} \sum_{\hat{q}, j} k_{\hat{q}, j} |D_j \Delta_{\hat{q}}|^2 + \sum_{\hat{q}} \left( \alpha + \frac{\beta}{2} |\Delta_{\hat{q}}|^2 \right) |\Delta_{\hat{q}}|^2 \\ & + \gamma_1 (|\Delta_{\mathcal{Q}_x}|^2 |\Delta_{-\mathcal{Q}_x}|^2 + |\Delta_{\mathcal{Q}_y}|^2 |\Delta_{-\mathcal{Q}_y}|^2) \\ & + \gamma_2 (|\Delta_{\mathcal{Q}_x}|^2 + |\Delta_{-\mathcal{Q}_x}|^2) (|\Delta_{\mathcal{Q}_y}|^2 + |\Delta_{-\mathcal{Q}_y}|^2) \\ & + \frac{\gamma_3}{2} (\Delta_{\mathcal{Q}_x}^* \Delta_{-\mathcal{Q}_x}^* \Delta_{\mathcal{Q}_y} \Delta_{-\mathcal{Q}_y} + c.c.). \end{aligned} \quad (3)$$

Here, we neglect variations along  $z$ -axis, thus  $j = x, y$  is the spatial index, while  $\hat{q}$  is a wave-vector index:  $\hat{q} = \mathcal{Q}_x, -\mathcal{Q}_x, \mathcal{Q}_y, -\mathcal{Q}_y$ . In the following another convenient index,  $q = \mathcal{Q}_x, \mathcal{Q}_y$  will also be used. The coefficients  $k_{\hat{q}, j}$  of the kinetic term satisfy the following relation  $k_{\pm\mathcal{Q}_x, x} = k_{\pm\mathcal{Q}_y, y} \equiv 1 - k$  and  $k_{\pm\mathcal{Q}_x, y} = k_{\pm\mathcal{Q}_y, x} \equiv 1 + k$ , and  $k$  measures the anisotropy of the system [27]. Here  $\mathcal{Q}_x$  represents the wavevector  $\mathcal{Q}_x = (\mathcal{Q}, 0)$ ,  $\mathcal{Q}_y$  represents  $\mathcal{Q}_y = (0, \mathcal{Q})$ , and  $\Delta_{\mathcal{Q}_x}$  represents the gap associated with the pairing between the fermion states  $|\mathbf{k} + \mathcal{Q}_x, \uparrow\rangle$  and  $|\mathbf{k}, \downarrow\rangle$ , where  $\mathbf{k}$  is the momentum and  $\uparrow, \downarrow$  denote the spin-states. Our choice of the wavevectors and model for the PDW order is motivated by the recent proposal of Amperean pairing by P.A. Lee [7], for which it has been shown that PDW order can account both the anomalous quasi-particle properties observed by ARPES and the CDW order (at momenta  $2\mathcal{Q}_x$  and  $2\mathcal{Q}_y$ ) observed in the pseudogap phase of  $\text{Bi}_2\text{Sr}_{2-x}\text{La}_x\text{CuO}_{6+\delta}$  ( $\text{Bi}2201$ ). Depending on the parameters  $\gamma_i$ , the free energy of the PDW sector (3) allows five possible distinct

ground states [5]. We choose parameters such that, in the non-competing case, the PDW ground state has the form  $\Delta_{\text{PDW}}^\dagger = \Delta_0^*(1, 1, i, i)$ . This PDW ground state is the same as that proposed in Ref. 7 and is also found to be a ground state in the spin-fermion model [28, 29].

Both  $\Delta_d$  and  $\Delta_{\text{PDW}}$  interact with the magnetic field (through the kinetic terms) and are therefore indirectly coupled. They also directly interact through  $\mathcal{F}_{\text{Int}}$ :

$$\begin{aligned} \mathcal{F}_{\text{Int}} = & \gamma_4 |\Delta_d|^2 (|\Delta_{\mathcal{Q}_x}|^2 + |\Delta_{-\mathcal{Q}_x}|^2 + |\Delta_{\mathcal{Q}_y}|^2 + |\Delta_{-\mathcal{Q}_y}|^2) \\ & + \frac{\gamma_5}{2} \left( \left[ \Delta_{\mathcal{Q}_x}^* \Delta_{-\mathcal{Q}_x}^* + \Delta_{\mathcal{Q}_y}^* \Delta_{-\mathcal{Q}_y}^* \right] \Delta_d^2 + c.c. \right). \end{aligned} \quad (4)$$

The first term in (4) is a bi-quadratic coupling between the  $d$ -wave and the pair density wave  $\sim \gamma_4 |\Delta_d|^2 |\Delta_{\text{PDW}}|^2$ . Coexistence of both order parameters is penalized for positive values  $\gamma_4$ , and when strong enough, only one of the condensates supports a non-zero ground state density. Our choice of parameters is such that when  $H = 0$ ,  $\Delta_d$  has lower condensation energy and  $\Delta_{\text{PDW}}$  is completely suppressed, because of the interaction terms (4). Moreover, as CDW order emerges at high field, we require  $\Delta_{\text{PDW}}$  to have a higher second critical field ( $H_{c2}^{\text{PDW}}$ ) than  $\Delta_d$  ( $H_{c2}^{d\text{-wave}}$ ). These conditions lead to Fig. 1. We note that in principle, the existence of the competing PDW order can allow for the PDW driven CDW order to appear in zero field in the vicinity of inhomogeneities or due to fluctuations in some materials. Indeed CDW order has been observed in  $\text{YBa}_2\text{Cu}_3\text{O}_{6.67}$  in zero field through high energy X-ray diffraction [30] (this CDW order is enhanced by magnetic fields).

*PDW driven CDW order.* We take CDW order to be denoted by  $\rho(\mathbf{r}) = \sum_{\hat{q}} e^{i\hat{q}\cdot\mathbf{r}} \rho_{\hat{q}}$  (note that  $\rho_{-q} = \rho_q^*$ ). The coupling between  $\rho_{2q}$  (with  $q = \mathcal{Q}_x, \mathcal{Q}_y$ ) and PDW order is given by [5–7]:

$$\sum_{q=\mathcal{Q}_x, \mathcal{Q}_y} \alpha_2 |\rho_{2q}|^2 + \epsilon_2 (\rho_{2q} \Delta_{-q} \Delta_q^* + \rho_{-2q} \Delta_q \Delta_{-q}^*). \quad (5)$$

Assuming that the CDW order is induced by the PDW order, we find that

$$\rho_{\pm 2q} = \rho_{\mp 2q}^* = -\frac{\epsilon_2}{\alpha_2} \Delta_{\pm q} \Delta_{\mp q}^*. \quad (6)$$

The CDW order given by  $\rho_{2q}$  corresponds to that observed in the pseudogap phase in zero field and to the checkerboard order observed inside the  $d$ -wave vortex cores. An important feature of this work is that the interplay between  $d$ -wave and PDW orders gives rise to an additional contribution to the CDW order. In particular, this coupling is given by [5–7]

$$\begin{aligned} \sum_{q=\mathcal{Q}_x, \mathcal{Q}_y} \alpha_1 |\rho_q|^2 + \epsilon_1 \left( \rho_q [\Delta_{-q} \Delta_d^* + \Delta_q^* \Delta_d] \right. \\ \left. + \rho_{-q} [\Delta_q \Delta_d^* + \Delta_{-q}^* \Delta_d] \right). \end{aligned} \quad (7)$$

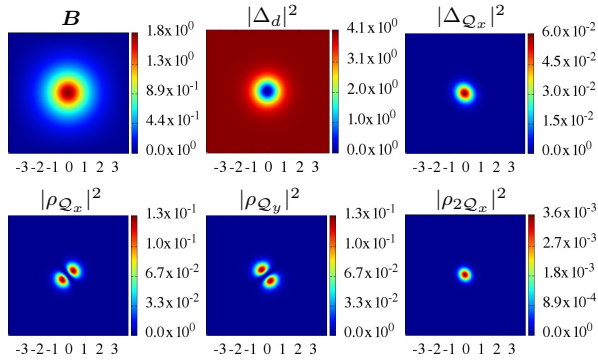


Figure 2. (Color online) – The core structure of a single  $d$ -wave vortex. The parameters are  $(\alpha, \beta) = (-5, 10)$  and  $\gamma_2 = \gamma_1/2 = 10\gamma_5 = 3$ , while the parameters for the  $d$ -wave order are  $(\alpha_d, \beta_d) = (-2.5, 0.61)$ . The parameters of the interaction (4) that directly couples the PDW and the  $d$ -wave order are  $\gamma_4 = 2$ ,  $\gamma_5 = 0.5$  and the gauge coupling constant is  $e = 0.4$ . The  $d$ -wave order has non-zero ground state density and has a vortex, while the components of the PDW are zero in the ground state. At the core of  $\Delta_d$  vortex, because there is less density, it is beneficial for the components  $\Delta_d$  of the PDW to condense, as shown in the right panel of the first line (here we show only  $\Delta_{Q_x}$  as the other components behave similarly). The second line displays the induced CDW:  $\rho_{2q}$  (6) and  $\rho_q$  (8) (note  $\rho_{2Q_y}$  is similar to  $\rho_{2Q_x}$ ).

Differentiation with respect to  $\rho_q^*$  and  $\rho_q$  yields the relations (this also assumes the CDW order is purely induced):

$$\rho_{\pm q} = \rho_{\mp q}^* = -\frac{\epsilon_1}{\alpha_1} (\Delta_{\pm q} \Delta_d^* + \Delta_d \Delta_{\mp q}^*). \quad (8)$$

The contributions  $\rho_Q$  and  $\rho_{2Q}$  to the CDW are reconstructed according to

$$\rho_{nQ} = \sum_{q=Q_x, Q_y} \rho_{nq} e^{in\mathbf{q}\cdot\mathbf{r}} + \rho_{-nq} e^{-in\mathbf{q}\cdot\mathbf{r}}, \quad (9)$$

that shows the  $n$ -th order contribution to the CDW. The CDW order  $\rho_Q$  has twice the periodicity of  $\rho_{2Q}$  and is not an induced order of the pure  $\Delta_{\text{PDW}}$ : it only appears when both  $\Delta_d$  and  $\Delta_{\text{PDW}}$  coexist. Consequently,  $\rho_Q$  is a signature of the appearance of  $\Delta_{\text{PDW}}$  in a  $d$ -wave superconductor. Note that the existence of  $\rho_Q$  requires superconducting phase coherence for both the PDW and  $d$ -wave orders (strictly speaking, coherence in the phase difference between these two orders will suffice). We note that an observation of  $\rho_Q$  has been reported [31], below we make predictions about the structure of  $\rho_Q$  around a vortex in  $\Delta_d$ .

*Vortex properties and checkerboard pattern.* In order to investigate the interplay of  $\Delta_{\text{PDW}}$  and  $\Delta_d$ , within the framework sketched in Fig. 1, we numerically minimize the free energy (1) both for single vortices and for a finite sample in external field. The theory is discretized within a finite element formulation [32] and minimized using a non-linear conjugate gradient algorithm (for detailed discussion on the numerical methods, see for example [33]).

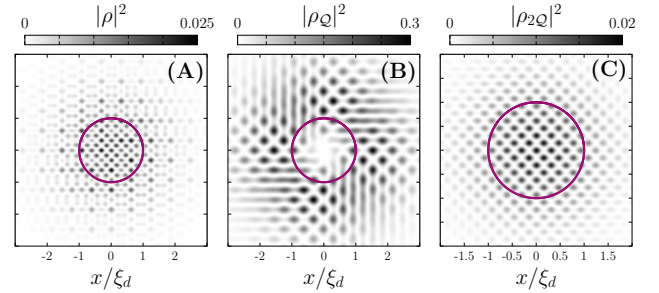


Figure 3. (Color online) – The charge density wave order (A) and the contributions of  $\rho_Q$  (B) and  $\rho_{2Q}$  (C), as defined in (9). The parameters are the same as in Fig. 2 except that  $\gamma_5 = 1.0$ . The circle of radius  $\xi_d$ , the coherence length of the  $d$ -wave, indicates the size of the vortex core.  $\rho_Q$  and  $\rho_{2Q}$  are shown for unit value of the ratios  $\epsilon_1/\alpha_1$  and  $\epsilon_2/\alpha_2$ , while  $\rho$ , the total charge density is shown for  $\epsilon_1/\alpha_1 = 1$  and  $\epsilon_2/\alpha_2 = 0.1$ . As a result,  $\rho$  shows checkerboard in vortex core. Furthermore, since  $\rho_Q$  varies with twice the wavelength as  $\rho_{2Q}$ , away from the core, every other peak in  $\rho$  is magnified.

Typical single vortex solutions, see Fig. 2, clearly show that the components of the PDW order acquire small, yet non-zero density at the center of the  $d$ -wave vortex core. As a result, the CDW order is also non-zero at the vortex core. Faraway from the vortex, the  $\Delta_{\text{PDW}}$  decays to zero, and the induced CDW is suppressed as well. Fig. 3 shows the magnitude of the total CDW order as well as the contributions from different orders in  $Q$ . Here, we used the values  $Q = \pi/d$  and  $d = 4a_0$ , where  $a_0$  is the Cu-Cu distance in cuprates and, in qualitative accordance with experimental data [34], we take the  $d$ -wave coherence length to be  $\xi_d = 13a_0$ .  $\rho_{2Q}$  forms a checkerboard pattern that extends significantly outside the vortex core, and this is consistent with the observations.

In addition to this checkerboard order, we also find that  $\rho_Q$ , which varies at twice the wave-length of  $\rho_{2Q}$ , is non-zero and also has a non-trivial structure. More precisely, at the singularity in the  $d$ -wave,  $\rho_Q = 0$ , and when  $\Delta_d$  becomes non-zero,  $\rho_Q$  also becomes non-zero. Since  $\Delta_{\text{PDW}}$  exhibits no phase winding,  $\rho_Q$  inherits the phase winding of  $\Delta_d$ . A phase winding in  $\rho_Q$  implies a dislocation in the corresponding real space order [35]. Consequently, the CDW order associated with  $\rho_Q$  has a dislocation at the vortex core. Since  $\rho_Q$  is suppressed in vortex cores, the checkerboard pattern that appears there, is essentially due to  $\rho_{2Q}$ . The contribution of  $\rho_Q$  to the CDW becomes important at distances larger than  $\xi_d$ . Moreover, as it varies with a doubled wave-length, every other charge peak is magnified in a region outside the core. Note that away from the vortex,  $\rho_Q$  is suppressed at a much slower rate than  $\rho_{2Q}$ . Furthermore, if  $\rho_Q$  is observable at all, then it should vanish at  $H_{c2}^{\text{d-wave}}$  while  $\rho_{2Q}$ , will persist to much higher fields.

*Field induced PDW and CDW orders.* To investigate the evolution of the PDW and  $d$ -wave orders in external field  $H$ , for parameters corresponding to Fig. 1, we min-

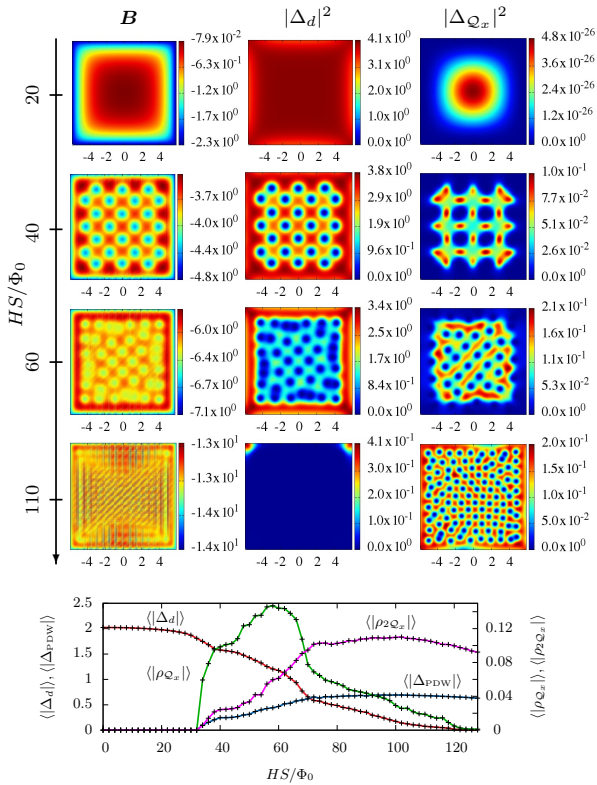


Figure 4. (Color online) – Simulation over a finite sample with increasing values of the external field (values are shown on the left) for the same parameters as in Fig. 3. The first column shows the magnetic flux, the second column shows  $|\Delta_d|^2$  and the last column shows  $|\Delta_{Q_x}|^2$  (other components of the PDW behave similarly to  $\Delta_{Q_x}$ ). The graph at the bottom shows order parameters averaged over the sample, as functions of the applied field. There, we show the densities of the  $d$ -wave and PDW order, as well as the induced CDW contributions  $\rho_{Q_x}$  and  $\rho_{2Q_x}$ . Above a certain external field (here  $HS/\Phi_0 = 32$ ), because of the suppression of the  $d$ -wave order, the PDW develops a non-zero expectation. The appearance of the PDW in external field is also accompanied by induced CDW order.

imize the free energy (1), while imposing  $\nabla \times \mathbf{A} = \mathbf{H}$  at the (insulating) boundary of the domain. We follow the vertical line sketched in Fig. 1. That is, starting from  $H = 0$ , the field is sequentially increased after the solution for the current value of  $H$  is found. Typical results illustrating such a simulation are shown in Fig. 4. In low fields, only  $\Delta_d$  has a non-zero ground state density and, as a result of the competition with  $\Delta_d$  in the interacting terms (4),  $\Delta_{PDW}$  is fully suppressed (or vanishingly small).

Above the first critical field, vortices in  $\Delta_d$ , carrying a small amount  $\Delta_{PDW}$  in their core, start entering the system. The averaged PDW over the whole sample  $\langle |\Delta_{PDW}| \rangle$  is still vanishingly small. With increasing field, the density of vortices increase and they start to overlap [36]. That is,  $|\Delta_{PDW}|$  and  $|\Delta_d|$  do not have ‘enough room’ to recover their ground-state values. At this point the lumps

of  $\Delta_{PDW}$ , previously isolated in vortex cores, interconnect and  $\Delta_{PDW}$  acquires a phase coherence globally. This behavior was also found to occur in a similar system with competing orders [37]. At this phase transition, not only  $\langle |\Delta_{PDW}| \rangle$  becomes non-zero but the induced CDW,  $\rho_{\pm q}$  and  $\rho_{\pm 2q}$  also become non-zero on average (see Fig. 4). We conjecture that this phase transition is related to that seen though NMR [38].

When the PDW order is on average non-zero, energetic considerations dictate that it should acquire phase winding as well. Indeed, when two condensates have non-zero density, the energy of configurations that has winding in only one condensate diverges (at least logarithmically) with the system size. As a result vortices in  $\Delta_{\hat{q}}$  are created when  $\langle |\Delta_{PDW}| \rangle \neq 0$  [37]. Note that, as it is still beneficial to have non-zero  $\Delta_{PDW}$  inside the vortex cores of  $\Delta_d$ , the singularities that are formed due to the winding in  $\Delta_{\hat{q}}$  do not overlap with those of  $\Delta_d$  (and they do not overlap with each other due to the terms  $\gamma_i$  in (3), that favor core splitting). Thus, the CDW order still appears within the vortex cores of  $\Delta_d$ . Since all the vortices that are created do not overlap with each other, the magnetic induction is smeared out and is much more spatially uniform than in usual vortex phases.

For fields above the second critical field of  $\Delta_d$ , only the PDW order survives. As a result, the contribution  $\rho_Q$  to the induced CDW also vanishes and the observed CDW order above  $H_{c2}^{d\text{-wave}}$  is solely that induced by the PDW (that is  $\rho_{2Q}$ ). In this state, at the mean-field level, the vortices in  $\Delta_{\hat{q}}$  do not overlap, as the terms with  $\gamma_i$  in (3) favor vortex core splitting. In principle, the parameters  $\gamma_i$  can also be chosen so that the  $\Delta_{\hat{q}}$  cores coincide for some or all PDW components. This will not change the qualitative physics associated with the competition between  $\Delta_d$  and  $\Delta_{PDW}$ . However, it will affect the resulting high field regime. In either case, we expect superconducting phase fluctuations to play an important role in the high field phase. In particular, it is known that for type II superconductors, high magnetic fields significantly enhance the role of fluctuations [39, 40]. Phase fluctuations will remove the superconducting long range order of the PDW state, but the CDW order can still survive [26]. A related mechanism was also considered in a different but related model of superconductivity [41].

*Conclusions.* We have considered a model of competing pair density wave and  $d$ -wave superconductivity. The superconducting state in the Meissner phase is purely  $d$ -wave. With increasing external field, vortices in the  $d$ -wave superconductor are formed and they carry PDW and induced CDW order in their core. When these vortices significantly interact, the lumps of PDW order acquire global phase coherence and both PDW and  $d$ -wave superconductivity coexist. In the regions where both PDW and  $d$ -wave order exist, the induced CDW order features a  $\rho_Q$  contribution that exists at twice the periodicity of the CDW order observed in the pseudogap

phase at zero fields. The observation of  $\rho_Q$  can serve to identify the existence of PDW order in the pseudogap phase.

We thank Egor Babaev, Andrey Chubukov, Marc-Henri Julien, Manoj Kashyap, Patrick Lee, and Yuxuan Wang for fruitful discussions. DFA acknowledges support from NSF grant No. DMR-1335215. JG was supported by National Science Foundation under the CAREER Award DMR-0955902 and by the Swedish Research Council grants 642-2013-7837, 325-2009-7664. The computations were performed on resources provided by the Swedish National Infrastructure for Computing (SNIC) at the National Supercomputer Center at Linköping, Sweden.

---

\* [garaud.phys@gmail.com](mailto:garaud.phys@gmail.com)

- [1] G. Ghiringhelli, M. Le Tacon, M. Minola, S. Blanco-Canosa, C. Mazzoli, N. B. Brookes, G. M. De Luca, A. Frano, D. G. Hawthorn, F. He, T. Loew, M. M. Sala, D. C. Peets, M. Salluzzo, E. Schierle, R. Sutarto, G. A. Sawatzky, E. Weschke, B. Keimer, and L. Braicovich, *Science* **337**, 821 (2012).
- [2] R. Comin, A. Frano, M. M. Yee, Y. Yoshida, H. Eisaki, E. Schierle, E. Weschke, R. Sutarto, F. He, A. Soumyanarayanan, Y. He, M. Le Tacon, I. S. Elfimov, J. E. Hoffman, G. A. Sawatzky, B. Keimer, and A. Damascelli, *Science* **343**, 390 (2014).
- [3] E. H. da Silva Neto, P. Aynajian, A. Frano, R. Comin, E. Schierle, E. Weschke, A. Gyenis, J. Wen, J. Schneeloch, Z. Xu, S. Ono, G. Gu, M. Le Tacon, and A. Yazdani, *Science* **343**, 393 (2014).
- [4] T. Wu, H. Mayaffre, S. Krämer, M. Horvatić, C. Berthier, W. N. Hardy, R. Liang, D. A. Bonn, and M.-H. Julien, *ArXiv e-prints* (2014), [arXiv:1404.1617](https://arxiv.org/abs/1404.1617) [cond-mat.supr-con].
- [5] D. F. Agterberg and H. Tsunetsugu, *Nature Physics* **4**, 639 (2008).
- [6] E. Berg, E. Fradkin, S. A. Kivelson, and J. M. Tranquada, *New Journal of Physics* **11**, 115004 (2009).
- [7] P. A. Lee, *Phys. Rev. X* **4**, 031017 (2014).
- [8] Y. Sidis and P. Bourges, *Journal of Physics: Conference Series* **449**, 012012 (2013).
- [9] J. Xia, E. Schemm, G. Deutscher, S. A. Kivelson, D. A. Bonn, W. N. Hardy, R. Liang, W. Siemons, G. Koster, M. M. Fejer, and A. Kapitulnik, *Phys. Rev. Lett.* **100**, 127002 (2008).
- [10] R.-H. He, M. Hashimoto, H. Karapetyan, J. D. Koralek, J. P. Hinton, J. P. Testaud, V. Nathan, Y. Yoshida, H. Yao, K. Tanaka, W. Meevasana, R. G. Moore, D. H. Lu, S.-K. Mo, M. Ishikado, H. Eisaki, Z. Hussain, T. P. Devereaux, S. A. Kivelson, J. Orenstein, A. Kapitulnik, and Z.-X. Shen, *Science* **331**, 1579 (2011).
- [11] A. Kaminski, S. Rosenkranz, H. M. Fretwell, J. C. Campuzano, Z. Li, H. Raffy, W. G. Cullen, H. You, C. G. Olson, C. M. Varma, and H. Hochst, *Nature* **416**, 610 (2002).
- [12] H. Karapetyan, J. Xia, M. Hücker, G. D. Gu, J. M. Tranquada, M. M. Fejer, and A. Kapitulnik, *Phys. Rev. Lett.* **112**, 047003 (2014).
- [13] D. F. Agterberg, D. S. Melchert, and M. K. Kashyap, *Phys. Rev. B* **91**, 054502 (2015).
- [14] M. Zelli, C. Kallin, and A. J. Berlinsky, *Phys. Rev. B* **86**, 104507 (2012).
- [15] P. Corboz, T. M. Rice, and M. Troyer, *Phys. Rev. Lett.* **113**, 046402 (2014).
- [16] J. E. Hoffman, E. W. Hudson, K. M. Lang, V. Madhavan, H. Eisaki, S. Uchida, and J. C. Davis, *Science* **295**, 466 (2002).
- [17] G. Levy, M. Kugler, A. A. Manuel, O. Fischer, and M. Li, *Phys. Rev. Lett.* **95**, 257005 (2005).
- [18] T. Wu, H. Mayaffre, S. Krämer, M. Horvatic, C. Berthier, W. N. Hardy, R. Liang, D. A. Bonn, and M.-H. Julien, *Nature* **477**, 191 (2011).
- [19] T. Wu, H. Mayaffre, S. Krämer, M. Horvatic, C. Berthier, P. L. Kuhns, A. P. Reyes, R. Liang, W. N. Hardy, D. A. Bonn, and M.-H. Julien, *Nature Communications* **4**, (2013).
- [20] Y. Zhang, E. Demler, and S. Sachdev, *Phys. Rev. B* **66**, 094501 (2002).
- [21] S. Sachdev and E. Demler, *Phys. Rev. B* **69**, 144504 (2004).
- [22] M. Einenkel, H. Meier, C. Pépin, and K. B. Efetov, *Phys. Rev. B* **90**, 054511 (2014).
- [23] P. A. Lee and X.-G. Wen, *Phys. Rev. B* **63**, 224517 (2001).
- [24] C. Weber, D. Poilblanc, S. Capponi, F. Mila, and C. Jaudet, *Phys. Rev. B* **74**, 104506 (2006).
- [25] H.-D. Chen, O. Vafek, A. Yazdani, and S.-C. Zhang, *Phys. Rev. Lett.* **93**, 187002 (2004).
- [26] E. Berg, E. Fradkin, and S. A. Kivelson, *Nature Physics* **5**, 830 (2009).
- [27] Although it is physically relevant, the anisotropy  $k$  has very little influence on the physics we describe here. We verified that indeed for  $k \neq 0$ , moderate anisotropies do not qualitatively change the physical properties we discuss. Thus in the rest of the paper, we consider only the isotropic case  $k = 0$ .
- [28] Y. Wang and A. Chubukov, *Phys. Rev. B* **90**, 035149 (2014).
- [29] Y. Wang, D. F. Agterberg, and A. Chubukov, *ArXiv e-prints* (2015), [arXiv:1501.07287](https://arxiv.org/abs/1501.07287) [cond-mat.str-el].
- [30] J. Chang, E. Blackburn, A. T. Holmes, N. B. Christensen, J. Larsen, J. Mesot, R. Liang, D. A. Bonn, W. N. Hardy, A. Watenphul, M. v. Zimmermann, E. M. Forgan, and S. M. Hayden, *Nat Phys* **8**, 871 (2012).
- [31] A. D. Beyer, M. S. Grinolds, M. L. Teague, S. Tajima, and N.-C. Yeh, *EPL (Europhysics Letters)* **87**, 37005 (2009).
- [32] F. Hecht, *J. Numer. Math.* **20**, 251 (2012).
- [33] D. F. Agterberg, E. Babaev, and J. Garaud, *Phys. Rev. B* **90**, 064509 (2014).
- [34] O. Fischer, M. Kugler, I. Maggio-Aprile, C. Berthod, and C. Renner, *Rev. Mod. Phys.* **79**, 353 (2007).
- [35] P. Chaikin and T. Lubensky, *Principles of Condensed Matter Physics* (Cambridge University Press, 2000).
- [36] Note that vortices here arrange as squares. In principle anisotropies or interactions originating in the complicated core structures can account for this. Here we believe this is merely a finite size effect. Indeed, the role of Meissner currents cannot be neglected and definite statements about the lattice structures cannot be safely made.

- [37] J. Garaud and E. Babaev, [Phys. Rev. B](#) **91**, 014510 (2015).
- [38] D. LeBoeuf, S. Kramer, W. N. Hardy, R. Liang, D. A. Bonn, and C. Proust, [Nat Phys](#) **9**, 79 (2013).
- [39] P. Lee and S. Shenoy, [Phys. Rev. Lett.](#) **28**, 1025 (1972).
- [40] G. Blatter, M. Feigel'man, V. Geshkenbein, A. Larkin, and V. Vinokur, [Rev. Mod. Phys.](#) **66**, 1125 (1994).
- [41] E. Babaev, [Nuclear Physics B](#) **686**, 397 (2004).