

This is the accepted manuscript made available via CHORUS. The article has been published as:

Electronic and magnetic structure of epitaxial
 $\text{Fe}_{\{3\}}\text{O}_{\{4\}}(001)/\text{NiO}$ heterostructures grown on
 $\text{MgO}(001)$ and Nb-doped $\text{SrTiO}_{\{3\}}(001)$

K. Kuepper, O. Kuschel, N. Pathé, T. Schemme, J. Schmalhorst, A. Thomas, E. Arenholz, M.

Gorgoi, R. Ovsyannikov, S. Bartkowski, G. Reiss, and J. Wollschläger

Phys. Rev. B **94**, 024401 — Published 1 July 2016

DOI: [10.1103/PhysRevB.94.024401](https://doi.org/10.1103/PhysRevB.94.024401)

Electronic and magnetic structure of epitaxial $\text{Fe}_3\text{O}_4(001)/\text{NiO}$ heterostructures grown on $\text{MgO}(001)$ and $\text{Nb-doped SrTiO}_3(001)$

K. Kuepper,^{1,*} O. Kuschel,¹ N. Pathé,¹ T. Schemme,¹ J. Schmalhorst,² A. Thomas,^{2,3} E. Arenholz,⁴ M. Gorgoi,⁵ R. Ovsyannikov,⁴ S. Bartkowski,¹ G. Reiss,² and J. Wollschläger¹

¹*Department of Physics and Center of Physics and Chemistry of New Materials, Osnabrück University, 49076 Osnabrück, Germany*

²*Center for Spinelectronic Materials and Devices, Physics Department, Bielefeld University, Universitätsstraße 25, 33615 Bielefeld, Germany*

³*Leibniz Institute for Solid State and Materials Research Dresden (IFW Dresden), Institute for Metallic Materials, Helmholtzstrasse 20, 01069 Dresden, Germany*

⁴*Advanced Light Source, Lawrence Berkeley National Laboratory, California 94720, USA*

⁵*Helmholtz-Zentrum für Materialien und Energie GmbH, 12489 Berlin, Germany*

(Dated: June 17, 2016)

We study the underlying chemical, electronic and magnetic properties of a number of magnetite based thin films. The main focus is placed onto $\text{Fe}_3\text{O}_4(001)/\text{NiO}$ bilayers grown on $\text{MgO}(001)$ and $\text{Nb-SrTiO}_3(001)$ substrates. We compare the results with those obtained on pure $\text{Fe}_3\text{O}_4(001)$ thin films. It is found that the magnetite layers are oxidized and Fe^{3+} dominates at the surfaces due to maghemite ($\gamma\text{-Fe}_2\text{O}_3$) formation, which decreases with increasing magnetite layer thickness. From a layer thickness of around 20 nm on the cationic distribution is close to that of stoichiometric Fe_3O_4 . At the interface between NiO and Fe_3O_4 we find the Ni to be in a divalent valence state, with unambiguous spectral features in the Ni 2p core level x-ray photoelectron spectra typical for NiO . The formation of a significant NiFe_2O_4 interlayer can be excluded by means of XMCD. Magneto optical Kerr effect measurements reveal significant higher coercive fields compared to magnetite thin films grown on $\text{MgO}(001)$, and an altered in-plane easy axis pointing in $\langle 100 \rangle$ direction. We discuss the spin magnetic moments of the magnetite layers and find that a thickness of 20 nm or above leads to spin magnetic moments close to that of bulk magnetite.

PACS numbers: 75.70.-i, 75.70.Rf, 78.20.Ls, 75.30.Gw, 75.47.Lx

I. INTRODUCTION

Transition metal oxides display a remarkable variety of properties as function of the complex interplay between the electron charge, spin and orbital degree of freedom. Among many other transition metal oxides as for instance perovskite based manganites, ferrites or cuprates, the oldest known magnetic material, namely magnetite (Fe_3O_4) is of special interest in current condensed matter and thin film physics. This fact stems partly from fundamental aspects as the high Curie temperature (860 K) for bulk material with a magnetic saturation moment of $4.07 \mu_B$ per formula unit,^{1,2} the Verwey transition taking place at around 120 K,^{3,4} as well as the predicted 100% spin polarization of Fe_3O_4 ,⁵ and partly this material is of special interest for various applications in medicine, catalysis and in particular for future spintronic devices such as spin valves or magnetic tunnel junctions.^{6,7,8,9} Recent approaches are pointing towards the synthesis of so-called all-oxide devices, e.g. by epitaxial growth of Fe_3O_4 on $\text{SrTiO}_3(001)$ substrates to obtain the desired magnetite properties for further incorporation into $\text{Fe}_3\text{O}_4/\text{La}_{0.7}\text{Sr}_{0.3}\text{MnO}_3$ spin valves.¹⁰ Another promising route to build a full oxide spin valve is to employ exchange bias between a ferro(i)magnetic and an antiferromagnetic oxide to manipulate the magnetization state of magnetite.¹¹ Such an exchange interaction can be realized by coupling of Fe_3O_4 with antiferromag-

TABLE I: Sample abbreviations (used in the text for brevity), and thin film thicknesses (in parentheses) as determined from X-ray reflectivity (XRR) experiments.

sample	substrate	thin film layer(s)
S1	SrTiO_3	Fe_3O_4 (12.3 nm)
S2	SrTiO_3	Fe_3O_4 (21.5 nm)
S3	SrTiO_3	Fe_3O_4 (33.0 nm)
SN1	SrTiO_3	NiO (5.0 nm) Fe_3O_4 (6.2 nm)
SN2	SrTiO_3	NiO (9.7 nm) Fe_3O_4 (9.6 nm)
SN3	SrTiO_3	NiO (10.3 nm) Fe_3O_4 (20.7 nm)
M1	MgO	Fe_3O_4 (20.0 nm)
MN1	MgO	NiO (5.2 nm) Fe_3O_4 (6.1 nm)
MN2	MgO	NiO (11.5 nm) Fe_3O_4 (10.5 nm)
MN3	MgO	NiO (8.2 nm) Fe_3O_4 (21.5 nm)

netic NiO in thin film heterostructures.^{11,12,13} However, for the optimization of such potential all-oxidic devices as mentioned above a detailed characterization and understanding of the underlying structural, chemical, electronic and magnetic properties of the thin films and the interfaces, e.g. between magnetite and the substrate or the antiferromagnetic NiO is indispensable.

The lattice mismatch between magnetite (bulk lattice constant 0.83963 nm) and the doubled MgO bulk lattice constant (0.42117 nm) is only 0.3%, making MgO an optimal candidate for epitaxial magnetite growth, which

has been demonstrated many times using various deposition techniques.^{14,15,16,17,18,19} There are quite a few works on $\text{Fe}_3\text{O}_4/\text{NiO}$ bilayers and multilayers, mostly grown on MgO , investigating the structural properties of the heterostructures and the nature of exchange interaction between magnetite and (the antiferromagnetic) nickel oxide.^{13,20,21,22}

Thin magnetite films grown on $\text{SrTiO}_3(001)$ allow tuning the conductivity via Nb-doping, which is of interest for some important applications. Quite a few studies reveal altered magnetic properties such as a strongly increased coercive field compared to films grown on MgO .^{23,24} Furthermore, Monti *et al.* recently report that the magnetic easy axis points along the in-plane $\langle 100 \rangle$ film directions²⁵ rather than the $\langle 110 \rangle$ directions for the easy axis mostly reported for SrTiO_3 ²⁶ and MgO .^{19,27} Despite the large lattice mismatch of -7.5% between the doubled SrTiO_3 bulk lattice constant (0.3905 nm) and magnetite at least some of the thin films appear to grow almost relaxed on the $\text{SrTiO}_3(001)$ surface,^{25,28} hence the reason of the altered magnetic properties including the role of epitaxial strain and potential formation of anti-phase domain boundaries (APB's) is still under discussion. As to coupled $\text{Fe}_3\text{O}_4/\text{NiO}$ bilayers grown on SrTiO_3 , up to now only Pilard *et al.* report on the magnetic properties of the $\text{Fe}_3\text{O}_4/\text{NiO}$ interface.²⁹ They find evidence for an 1.5 nm thick NiFe_2O_4 interfacial layer. An enhanced interfacial magnetization is also found by Krug *et al.*, they present a rather complete study of the interfacial coupling of ultrathin NiO films grown on differently oriented Fe_3O_4 single crystals.^{30,31}

Since the orientation of the interface is of utmost importance for the magnetic properties in oxidic thin film systems we want to perform a comprehensive study of $\text{Fe}_3\text{O}_4(001)/\text{NiO}$ bi-layers grown by reactive molecular beam epitaxy (RMBE) on $\text{MgO}(001)$ and Nb-doped $\text{SrTiO}_3(001)$ substrates, respectively. We investigate the electronic structure and the chemical composition by means of depth selective hard x-ray photoelectron spectroscopy (HAXPES) and x-ray magnetic circular dichroism (XMCD) at the $\text{Fe } L_{2,3}$ and $\text{Ni } L_{2,3}$ -edges. This complementary x-ray spectroscopic approach, along with magneto optical Kerr effect (MOKE) measurements allows us to develop a detailed picture of the overall electronic and magnetic structure of the magnetite based bilayers in question. We compare our results with those obtained on pure magnetite thin films grown under equivalent conditions on Nb- $\text{SrTiO}_3(001)$ and recent investigations reported in the literature.

II. EXPERIMENTAL AND THEORETICAL DETAILS

Preparation of the $\text{Fe}_3\text{O}_4/\text{NiO}$ heterostructures, and in situ characterization by means of LEED and XPS have been performed in a multichamber ultra-high vacuum system. The XPS system is equipped with a Pho-

bos HSA 150 hemispherical analyzer and an $\text{Al } K\alpha$ anode (1486.6 eV), leading to an information depth (~ 3 nm mean free path) of about 5 nm in case of magnetite. Prior to thin film deposition the $\text{MgO}(001)$ and SrTiO_3 (doped with 0.05 wt.% Nb) substrates were cleaned by heating them up to 400°C at an oxygen partial pressure of $1 \cdot 10^{-4}$ mbar for 1 hour. Afterwards the quality of the substrates has been checked by LEED. In a next step NiO layers were deposited under an oxygen partial pressure of $1 \cdot 10^{-5}$ mbar at a substrate temperature of 250°C (in order to prevent any Mg interdiffusion in case of MgO).³² After checking the quality of the NiO surfaces by LEED and XPS the magnetite layers have been grown on top of the NiO films at 250°C and an oxygen partial pressure of $5 \cdot 10^{-6}$ mbar. Subsequently LEED and XPS have been performed in situ in order to check the magnetite surface reconstruction and chemical composition, too.

Then the samples were transported under ambient conditions for further characterization. MOKE measurements have been conducted with a longitudinal setup and a HeNe laser. The Kerr rotation has been measured with help of a photoelastic modulator (PEM). For the HAXPES experiments we have used the HIKE endstation of the KMC-1 beamline of the BESSY II synchrotron facility.³³ Spectra have been recorded at photon energies ranging from 2.2 keV to 9.6 keV, using the Si double crystal monochromator with (111) orientation over the entire energy range. The samples have been aligned at 3° grazing incidence as to the incoming x-ray beam. The Scienta R4000 photoelectron analyzer has been normal to the sample surface, the analyzer resolution has been set to 0.25 eV. All HAXPES has been taken at room temperature, as well as the XMCD spectra performed at the $\text{Fe } L_{2,3}$ and $\text{Ni } L_{2,3}$ edges at beamline 6.3.1 of the Advanced Light Source, Lawrence Berkeley Laboratory. We have utilized total electron yield (TEY) as detection mode, which is mainly sensitive to the surface near region. The external magnetic field of 1.5 T has been aligned parallel to the x-ray beam and has been reversed at each energy. The angle between sample surface and x-ray beam was 30° . The degree of circular polarization has been about 55% .

For the analysis of the $\text{Fe } L_{2,3}$ XMCD spectra, we have performed corresponding model calculations within the atomic multiplet and crystal field theory including charge transfer using the program CTM4XAS.^{34,35}

III. RESULTS AND DISCUSSION

The $\text{Fe}_3\text{O}_4/\text{NiO}$ -bilayers have been synthesized using the same setup and using the same growth conditions described very recently by Schemme *et al.*,²² see also the experimental section. All cleaned $\text{MgO}(001)$ and $\text{SrTiO}_3(001)$ substrates are checked by means of LEED for the expected (1×1) structure. Subsequently to each layer deposition, the NiO and magnetite layers are investigated for the typical $\text{NiO } (1 \times 1)$ LEED pattern

and the characteristic ($\sqrt{2} \times \sqrt{2}$)R45° superstructure for Fe_3O_4 . Ni 2p and Fe 2p XPS core levels confirm the formation of stoichiometric NiO and Fe_3O_4 deposited on $\text{MgO}(001)$ and $\text{SrTiO}_3(001)$. These data are discussed in detail along with a comprehensive structural analysis elsewhere.³⁶ Here we only sum up the results for the layer thicknesses (determined by X-ray reflectivity XRR) in table I in order to report on the thickness dependence of the electronic structure and magnetic properties.

A. Electronic structure: Hard x-ray photoelectron spectroscopy (HAXPES)

In this section we want to clarify the chemical properties of the thin film surfaces and interfaces in detail. HAXPES measurements have been demonstrated to be a powerful tool for chemical depth profile and hence the characterization of buried layers and interfaces.^{37,38} All HAXPES measurements presented in Figs. 1 to 3 are recorded in the geometry described in section II. The probing, or information depth (ID(95)) is defined as the depth from which 95% of the photoelectrons of the spectra come from. ID(95) can be derived by the following equation:³⁹ $\text{ID}(95) = \lambda_{\text{IMFP}} \cos(\alpha) \ln(1 - 95/100)$. Here α represents the off-normal emission angle. λ_{IMFP} is the inelastic mean free path of the photoelectrons. We derive λ_{IMFP} for the Fe_3O_4 top layers of the thin films and bilayers by employing the TTP-2 equation^{40,41} and subsequently use the equation for calculating ID(95) to estimate the overall information depth. The resulting information depth for magnetite are denoted in Fig. 1a for each excitation energy, whereas in Fig. 1b the overall resolution (beamline plus analyzer) of the spectra are given.

Fig. 1 displays the Fe 2p spectra performed at excitation energies between 2200 eV and 9600 eV of samples **S1** and **S2**. The spectra have been normalized and re-scaled to the Fe $2p_{3/2}$ maximum, so comparison between the spectra is straightforward. For stoichiometric Fe_3O_4 one expects the Fe $2p_{3/2}$ binding energy at around 710.6 eV (0 eV on the relative binding energy scale chosen here), and a structureless region between the Fe $2p_{3/2}$ and the Fe $2p_{1/2}$ peaks without satellite peak as previously reported,⁴³ since the charge transfer satellites add up in such a way for a mixed valence state found in Fe_3O_4 . As to sample **S1** (12 nm) (Fig. 1a) there appears to be an excess of trivalent ions observed by means of the more surface sensitive 2200 eV photon energy. For $E_{\text{exc}} = 2200$ eV the typical Fe^{3+} charge transfer satellite is also visible at 8.5 eV above the Fe $2p_{3/2}$ maximum (see also gray vertical line, corresponding to a binding energy of around 719 eV). However, also a pronounced shoulder located around 2.2 eV at the low binding energy side (corresponding to 708.4 eV binding energy) is present indicating the presence of a significant amount of divalent iron ions.⁴⁴ We find no indications of metallic iron which should manifest itself at 707 eV and thus 3.6 eV below the Fe $2p_{3/2}$ maximum on the relative binding energy

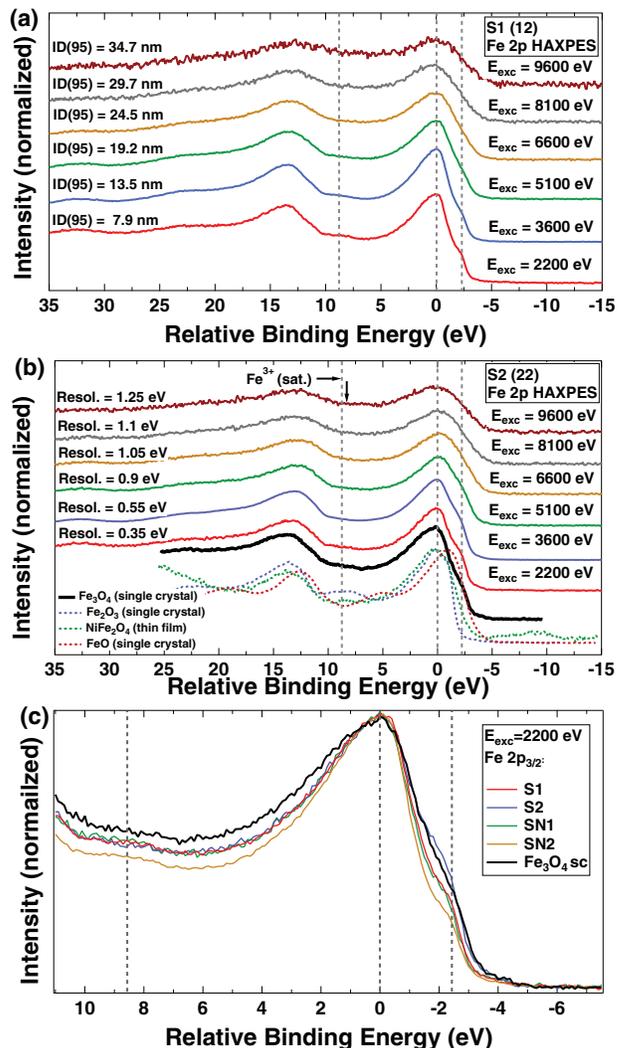


FIG. 1: Fe 2p HAXPES of samples **S1** (a) and **S2** (b) recorded at excitation energies between 2200 eV and 9600 eV. Reference spectra of FeO, Fe_3O_4 , NiFe_2O_4 , and Fe_2O_3 ⁴² are also shown for comparison. (c) Fe $2p_{3/2}$ core level of samples **S1**, **S2**, **SN1** and **SN2** recorded at $E_{\text{exc}} = 2200$ eV.

scale chosen here. At higher excitation energies the Fe^{3+} charge transfer satellite is not visible anymore and, the overall Fe 2p spectral shape indicates a stoichiometric 2:1 ratio of Fe^{3+} to Fe^{2+} ratio.

For the thicker Fe_3O_4 film **S2** (22 nm), the Fe^{3+} charge transfer satellite is less pronounced, while the feature stemming from Fe^{2+} is more pronounced in the $E_{\text{exc}} = 2200$ eV spectrum of **S2** compared to that of **S1** (see also Fig. 1c). Thus, the excess of Fe^{3+} in the surface near layers is significantly reduced in comparison with sample **S1**. At higher excitation energies (5100 eV and above) the Fe 2p spectra of **S1** resemble that of magnetite. The Fe^{2+} characteristic low binding energy shoulder becomes less visible due to the limited resolution of the spectra at higher excitation energies ($E_{\text{exc}} = 6600$ eV and above). It is also noteworthy that the Fe 2p spectra

of sample **S2** taken at 8100 eV and 9600 eV also exhibit a weak Fe^{3+} charge transfer satellite indicating a potential slight excess of Fe^{3+} close to or at the interface between the magnetite thin film and the SrTiO_3 . No such features are visible in the corresponding spectra of sample **S1**.

Very recently, Taguchi *et al.* reported a very interesting Fe 2p HAXPES-feature concerning a magnetite single crystal.⁴⁵ They find a double peak structure of the Fe $2p_{3/2}$ peak at higher excitation energies (approx. 6-8 keV) which is not present in the soft x-ray photoelectron spectra. They associate this effect with the two distinct Fe species and the charge modulation at the *B* site. The results are supported by complementary experiments on a magnetized 100 nm thick Fe_3O_4 thin film.⁴⁵ On the other hand Müller *et al.* performed Fe 2p HAXPES with excitation energies of 3-5 keV on 15-20 nm thick Fe_3O_4 thin films grown on ZnO and MgO ⁴⁶ which are very similar to the results presented here. We do not observe the bulk electronic state found by Taguchi *et al.* employing excitation energies up to 9600 keV. As to the beamline and analyzer settings used (cf. section II) the overall resolution of the spectra taken at $E_{exc} = 8100$ eV is ~ 1.1 eV (cf. Fig. 1b). Taguchi *et al.* obtained spectra with significant higher resolution (0.17 eV) at an excitation energy of 7.95 keV.⁴⁵ Hence, this might be one reason for not seeing the double peak in the spectra presented here, despite the two peaks are separated ~ 1.5 eV.⁴⁵ Another reason for this discrepancy might be the thin film thickness, as the bulk like features seem to be suppressed within a ~ 10 nm surface layer.⁴⁵ Detailed investigations of the bulk electronic structure of magnetite thin films in dependence of thin film thickness, substrate, temperature and magnetic state under consideration of the overall spectra resolution would be highly desirable.

Fig. 2 depicts the Fe 2p and Ni 2p HAXPES of samples **SN1** and **SN2**. Similar to samples **S1** and **S2** the Fe 2p spectra show a weak Fe^{3+} charge transfer satellite at $E_{exc} = 2200$ eV (Figs. 2a and c). At higher excitation energies the spectra are identical to that of Fe_3O_4 , despite in particular for sample **SN1** a weak Fe^{3+} charge transfer satellite is also present at higher excitation energies indicating a small excess of trivalent ions at the interface between Fe_3O_4 and NiO.⁴⁷ The corresponding Ni 2p spectra are overlapped by broad Fe 2s states (Figs. 2b and d). The overall shape of the Ni 2p spectra corresponds perfectly to that of NiO. Also the binding energies of the Ni $2p_{3/2}$ and Ni $2p_{1/2}$ main lines and the corresponding charge transfer satellites are typical for Ni^{2+} . Furthermore all Ni 2p spectra exhibit a prominent feature at the high binding energy side. The shoulder located 2 eV above the Ni $2p_{3/2}$ maximum (indicated by vertical lines in Figs. 2b and d) is a specific feature of bulk NiO,⁴⁸ which has been associated with a non-local screening effect. The double structure is clearly visible in all Ni 2p spectra, even in the $E_{exc} = 2200$ eV spectrum of sample **SN1** due to the small Fe_3O_4 film thickness despite the rather poor signal to noise ratio. For sample **SN2** there is only the rather broad Fe 2s peak visible as the

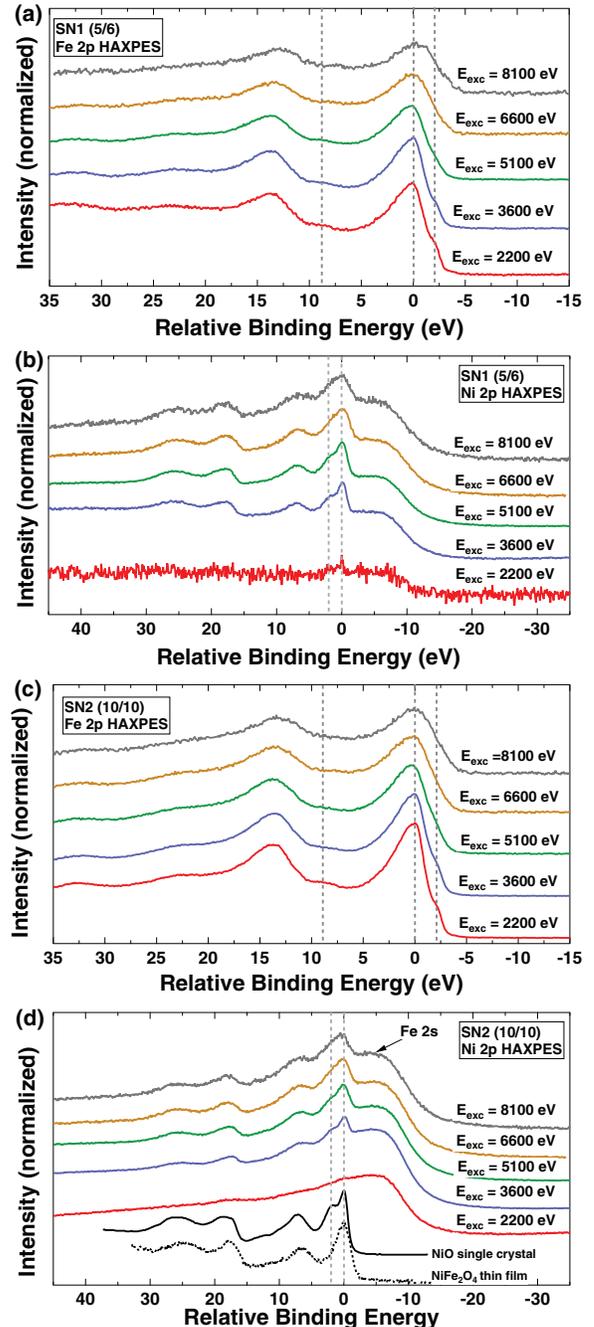


FIG. 2: HAXPE-spectra of samples **SN1** and **SN2** recorded at excitation energies between 2200 eV and 8100 eV. (a) and (b) Fe 2p and Ni 2p HAXPES of sample **SN1**. (c) and (d) Fe 2p and Ni 2p HAXPES of sample **SN2**, reference spectra of NiO⁴⁷ and NiFe_2O_4 ⁴² are also shown for comparison.

information depth is too low to probe the NiO layer at excitation energy 2200 eV.

The Fe 2p and Ni 2p HAXPES results confirm that stoichiometric Fe_3O_4 layers are formed on all samples investigated by HAXPES. Only small traces of Fe^{3+} excess might be found at the interface between Fe_3O_4 and SrTiO_3 of sample **S2**, and the $\text{Fe}_3\text{O}_4/\text{NiO}$ interface of

sample **SN1**. At the surface of all magnetite top layers a certain degree of Fe^{3+} excess is found indicating a potential maghemite ($\gamma\text{-Fe}_2\text{O}_3$) formation at the surface. It seems that thinner magnetite layers tend to enhanced $\gamma\text{-Fe}_2\text{O}_3$ formation or, respectively, to an increased amount of trivalent iron ions in the surface near layers. All Ni 2p spectra are, independent of the excitation energy, a quite perfect fingerprint of bulk NiO within the limits of this experiment. Hence, the formation of a NiFe_2O_4 interface layer or considerable amounts of NiFe_2O_4 islands or clusters can be rather excluded. Moreover, no Fe or Ni metallic contributions are investigated in the HAXPES spectra.

Next we will discuss the occupied total densities of states (tDOS) along the measured XPS valence band spectra (Fig. 3) in order to learn details about the electronic structure at the $\text{Fe}_3\text{O}_4/\text{NiO}$ interface.

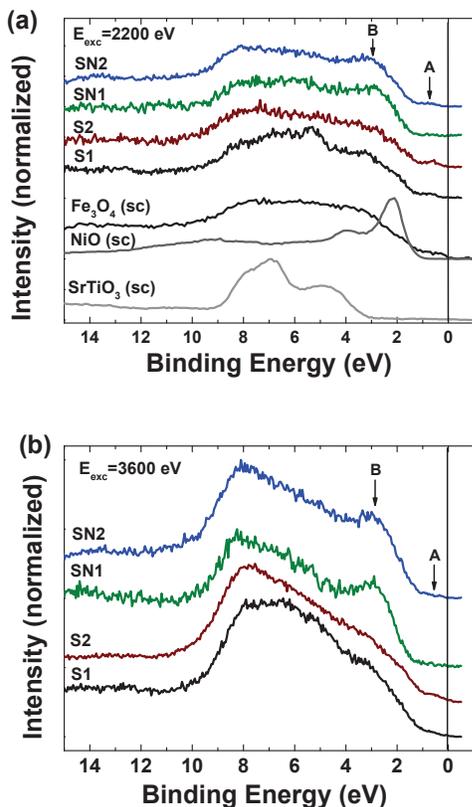


FIG. 3: HAXPES valence bands of samples **S1**, **S2**, **SN1** and **SN2** recorded at excitation energies of 2200 eV (a) and 3600 eV (b). Reference spectra of SrTiO₃, NiO⁴⁷ and Fe₃O₄ are also shown for comparison.

Fig. 3a depicts the total densities of states of samples **S1**, **S2**, **SN1**, and **SN2** with those of Fe₃O₄, NiO, and SrTiO₃ single crystals. The latter spectra have been performed with a lab based monochromatized Al K α source (1486.6 eV). The valence band spectrum of sample **S2** is very similar to that of the Fe₃O₄ single crystal. For

sample **S1** the region between 5-9 eV shows somewhat more intensity compared to single crystal Fe₃O₄, likely due to contributions from the SrTiO₃ substrate. The valence band spectra of the double layers **SN1** and **SN2** are also quite similar to that of magnetite. However, in particular in the valence band of sample **SN1** there are a few differences in detail. It appears that feature A is almost vanished in the valence band of sample **SN1**. As to theory^{49,50} this feature stems mainly from t_{2g} spin down states of octahedrally coordinated Fe cations. This trend is confirmed by the spectra taken at $E_{exc} = 3600$ eV (Fig. 3b). Whereas feature A becomes weaker or vanishes in the XPS valence bands of samples **SN1** and **SN2**, feature B, representing the (localized) Ni 3d states of NiO becomes stronger, confirming that also the interface and the underlying NiO layer is probed. The overall shape of the valence band spectra becomes different at excitation energy 3600 eV which is due to the different atomic cross sections at higher energies.

The valence band spectra presented in Fig. 3 recorded at $E_{exc} = 2200$ eV and 3600 eV can be understood as being a superposition of the electronic density of states of the Fe₃O₄ thin films including the interfaces and partly the NiO buffer layers or the SrTiO₃ substrates, respectively. Therefore we can not unambiguously discriminate between interface effects and size effects in the magnetite layer. We want to point out that a low density of states at the interface between Fe₃O₄ and NiO has been investigated before by growing ultrathin NiO layers onto an Fe₃O₄ single crystal and employing ultraviolet photoelectron spectroscopy (UPS).⁵¹ Another possible reason for the observed behavior is that thinner Fe₃O₄ films (e.g. 6 nm (sample **SN1**)) are different compared to somewhat thicker magnetite layers as to their electrical properties.⁵² To further elucidate potential influences of different substrates or the presence of a buffer layer like NiO on the electronic structure near Fermi energy and hence the electrical properties further complementary experiments such as resistivity measurements are highly desirable.

B. Magnetic properties: MOKE

Figure 4 depicts the magnetization curves for the $\langle 100 \rangle$ and $\langle 110 \rangle$ in-plane magnetic easy and hard directions of samples **MN3**, **SN3** and **S2** probed by MOKE.

Firstly, a significant increase of the coercive field is found compared to Fe₃O₄ films on MgO(001).²² This accounts in particular for the samples grown on Nb-SrTiO₃(001) substrates (**S2** and **SN3**). It is also noteworthy that a NiO buffer layer leads to an increase of the coercive field compared to corresponding Fe₃O₄ single layers in case of MgO(001) substrates but to a decrease of the coercive field in case of Nb-SrTiO₃(001) substrates. Whereas for Fe₃O₄/MgO(001) the magnetic in-plane easy axis (high coercive field) are aligned along the magnetite $\langle 110 \rangle$ direction,^{19,53,54} the other samples pre-

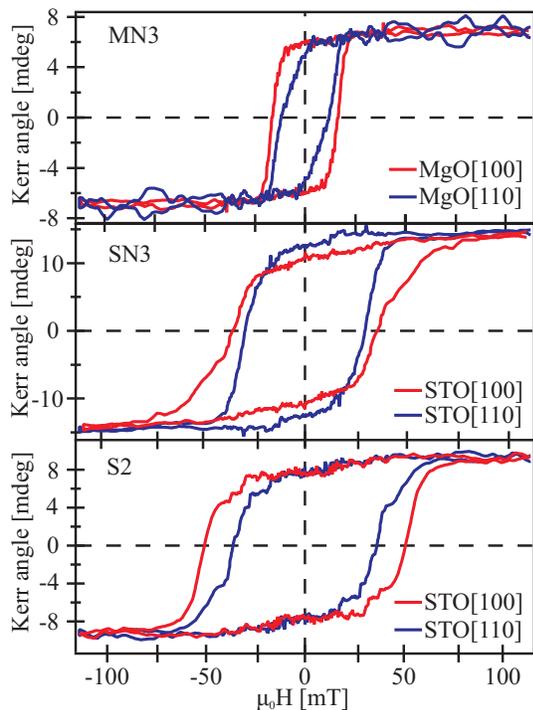


FIG. 4: Magnetization curves along the substrates [100] and [110] directions of samples **MN3** (top), **SN3** (center), and **S2** (bottom).

sented here have $\langle 100 \rangle$ in-plane magnetic easy axis as concluded from the higher coercive fields in these directions. The strong increase of the coercive field to around 50 mT in the easy magnetic direction as well as the rotated magnetic easy axis along the $\langle 100 \rangle$ in-plane directions have been recently also reported for thicker magnetite thin films (50-160 nm) grown by pulsed laser deposition on Nb-SrTiO₃(001).²⁵ Obviously, a NiO buffer layer between the magnetite layer and the substrate seems to lead to a 45° rotated magnetic easy in-plane axis independent of the MgO or SrTiO₃(001) substrate compared to Fe₃O₄/MgO(001). Furthermore, assuming the one-domain Wohlfahrt-Stoner model, one would expect a remanent magnetization M_r of $M_s/\sqrt{2}$ with respect to the saturation magnetization M_s for a hard magnetic direction due to geometric reasons. Smaller values of M_r , however, point to the formation of multi domains. However, the remanence is about the same value in easy and hard direction for all three samples discussed here (cf. Fig. 4). Such an effect can be also seen for 20 nm thin magnetite films grown on SrTiO₃ (100) and BaTiO₃ (100).⁵⁴ Potential reasons for this behavior concerning the magnetic easy axis rotation and remanent signal may stem from structural parameters such as interface structure and roughness or epitaxial strain,⁵⁵ or from potential presence of anti-phase domain boundaries (APBs) which may form during epitaxial thin film growth.²⁵ Another intriguing potential reason for the magnetic properties observed here is the fact that Krug *et al.* investigated an

impact of the interface orientation on the magnetic coupling in particular in case of the (100) interface between NiO and magnetite.³¹ They find a noncollinear orientation between the spin axis of the Fe₃O₄ and the NiO which they associate with spin-flop coupling at the interface of ultrathin NiO films grown on (100) oriented Fe₃O₄ single crystals.³¹ A more complete study of the magnetic anisotropy, e.g. by means of angular resolved MOKE measurements and ferromagnetic resonance (FMR) experiments is ongoing and will be presented elsewhere.³⁶ Moreover, despite the closer investigation of APB formation is an obstacle, further work to understand and analyse the role of APBs by means of high resolution TEM, or LEEM/PEEM experiments during thin film growth would be desirable for thin magnetite films and heterostructures.^{25,31,56,57,58,59}

C. Magnetic properties: X-ray magnetic circular dichroism (XMCD)

Fig. 5 presents the Ni L_{2,3}-edge XA-spectra of sample **MN1** recorded at room temperature in an external magnetic field of ± 1.5 T with circularly polarized light. The spectra show only a residual dichroic signal of 0.85%. The TEY detection mode is interface sensitive due to the $1/e$ probing depth.⁶⁰ Furthermore, the Ni L_{2,3}-XMCD should be rather strong in case of a NiFe₂O₄ interlayer formation since in case of ultrathin films or spinel interfaces, a strongly enhanced magnetic moment due to proximity effects has been reported,⁶¹ and also found for ultrathin Fe₃O₄(110) films grown on NiO.³⁰ Krug *et al.* could even quantify the NiFe₂O₄ interlayer reconstruction to around one monolayer and deduced the Ni magnetic moments from the sum rules.³⁰ In contrast, the very weak Ni L₃-XMCD, and within the experimental signal to noise ratio vanishing Ni L₂-XMCD (Fig. 5) indicate that there is no substantial formation of a NiFe₂O₄ interlayer or clusters at the interface between the Fe₃O₄(100) and the NiO layers studied in the present work. This result confirms the Ni 2p HAXPE-spectra of samples **SN1** and **SN2**, as the corresponding Ni 2p HAXPES results of **SN1** and **SN2** indicate charge transfer satellites typical for NiO.

Turning to the Fe L_{2,3} edges, Fig. 6a depicts the XA-spectra taken at ± 1.5 T of sample **MN1**, the resulting XMCD difference spectrum and the integral of the XMCD. The lower panel of Fig. 6 shows the experimental XMCD of **MN1** along with the best fit obtained from an appropriate superposition of the single ion charge transfer multiplet simulations plotted below.

The charge transfer multiplet spectra are calculated in the following way. In a first step, the Slater integrals and the spin-orbit couplings are calculated in spherical symmetry. The $d-d$ and $p-d$ integrals are reduced to 80% of their atomic value in order to account for screening, whereas the spin-orbit parameters are not reduced. Then crystal fields of $10Dq=1.0$ eV (Fe_{oct}²⁺, Fe_{oct}³⁺), and -0.6 eV for the Fe_{tet}³⁺ using the crystal field approach of Kuiper

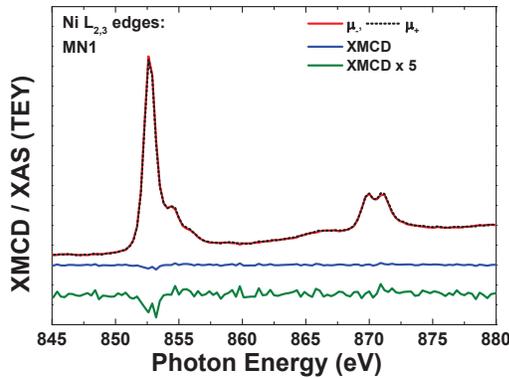


FIG. 5: Polarization dependent X-ray absorption spectra performed at the Ni $L_{2,3}$ edges of samples MN1 along with the resulting XMCD difference spectrum. The latter has been also multiplied by a factor of five for better visibility.

*et al.*⁶² as starting point. An exchange field $g\mu_B=0.03$ eV is also applied. In a last step, charge transfer is considered. We find $\Delta=6.0$ eV to lead to best agreement with the experimental data. We extract charge transfer configurations of 89.7% $3d^6$ plus 10.3% $3d^7\bar{L}$ for Fe_{oct}^{2+} , 90.4% $3d^5$ plus 9.6% $3d^6\bar{L}$ for Fe_{oct}^{3+} , and an 89.6% $3d^5$ plus 10.4% $3d^6\bar{L}$ for Fe_{tet}^{3+} . At the Fe L_3 -edge the calculated XMCD exhibits the typical three peaks expected for the inverse spinel structure of magnetite indicating the antiferromagnetic alignment of the octahedrally coordinated Fe_{oct}^{2+} (feature A) and Fe_{oct}^{3+} (C) ions with the tetrahedrally coordinated Fe_{tet}^{3+} ions (B). The sum of the three calculated spectra, which may be shifted as to the energy scale since chemical bonding and band-like effects are not considered by the localized model,⁶² is used to fit the experimental spectra and estimate the cationic distribution of each magnetite thin film.

Fig. 7a displays the Fe $L_{2,3}$ XMCD spectra and the corresponding fits for all samples discussed in this work. The cation distributions found are presented in a diagram (Fig. 7b). We see that the iron cation distribution is significantly different from ideal magnetite for samples S1, SN1, MN1, i.e. those samples with the thinnest iron oxide layers. These samples exhibit a lack of Fe_{oct}^{2+} but an excess of Fe_{oct}^{3+} . With increasing film thickness of the iron oxide layers the cation distribution converge towards that of stoichiometric Fe_3O_4 , whereas a slight excess of Fe_{oct}^{3+} ions remains. The excess of Fe_{oct}^{3+} found in particular in the thinner films can likely be attributed to maghemite ($\gamma\text{-}Fe_2O_3$) formation. The thickness dependence points to the fact that the maghemite is located at the thin film surfaces. Such an effect has been very recently investigated by Fleischer *et al.*^{19,63} employing Raman spectroscopy. Fleischer *et al.* found on uncapped 4 nm Fe_3O_4 films on MgO(001) that most of the maghemite formation occurs within days under ambient conditions and then slows significantly down in the time-frame of months.⁶³ As to the samples studied in this work, se-

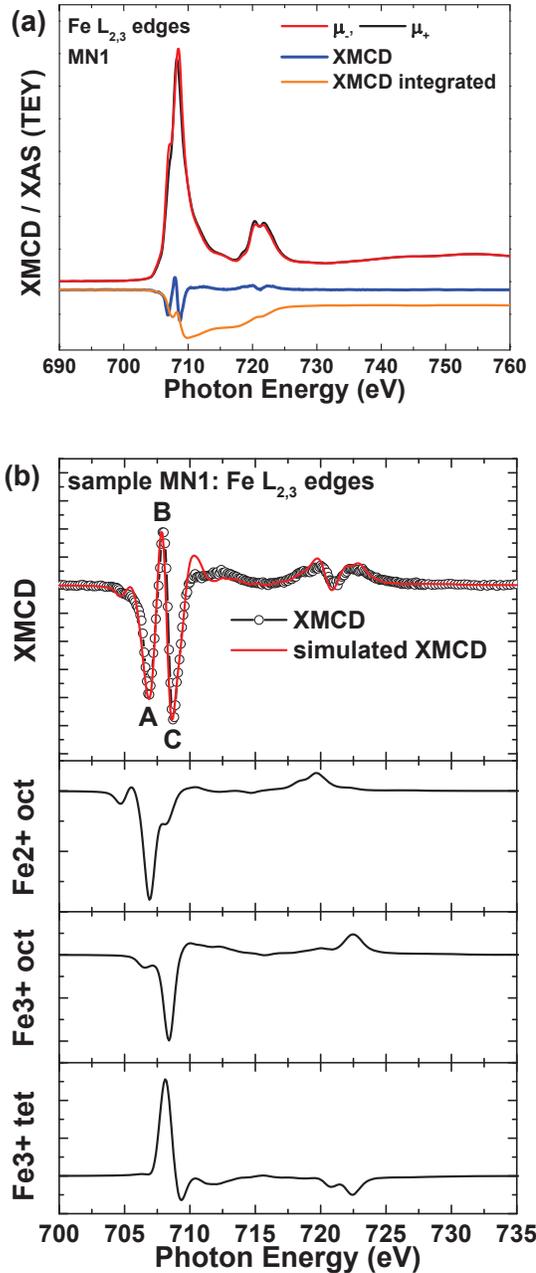


FIG. 6: (a) Polarization dependent XA-spectra performed at the Fe $L_{2,3}$ edges of sample MN1 along with the resulting XMCD and its integral. (b) XMCD difference spectra and corresponding simulated fit as a result from summarizing the suitable amounts of the charge transfer multiplet simulations of Fe^{2+} ions in octahedral coordination, and Fe^{3+} ions in octahedral and tetrahedral coordination, respectively.

ries S has been grown around 4 month, series SN and MN around 2-3 weeks prior to the XMCD experiments. The HAXPES experiments have been performed quite some time (over one year) after the thin film synthesis. Our experiments confirm a potential maghemite formation on the magnetite surfaces as to the cationic distri-

bution determined from the XMCD experiments and the HAXPES spectra recorded at lower excitation energies. This applies in particular to the thin magnetite layers (~ 5 -10 nm). However, thicker Fe_3O_4 thin films appear to be much more stable also at their surfaces. This is obviously also the fact a couple of month and over one year after synthesis (see e.g. Fe $L_{2,3}$ -XMCD analysis of samples **S2** and **S3** and HAXPES results of sample **S2**). Furthermore the total electron yield used to measure the XMCD spectra is known to be rather surface sensitive in the soft x-ray regime. For the Fe $L_{2,3}$ resonances of iron oxides the probing depth has been estimated to be around 0.8-3 nm.^{64,65} As the thinnest magnetite layers investigated here are around 6 nm (**MN1** and **SN1**) we can assume that the XA- and XMCD spectra stem from the first few nm and are not influenced by the substrate or the interface to the NiO buffer layer. Hence, we find a very different rate of maghemite formation within the first few 2-3 nm of the magnetite layers in dependence of the overall film thickness. Within the limits of the experiment, Fe_3O_4 layers with thickness ≥ 20 nm exhibit an almost stoichiometric magnetite cation distribution, independently from the substrate or the presence of a NiO buffer layer (see also Fig. 7b). Similar results have been recently reported for magnetite thin films directly deposited in MgO(001) substrates.¹⁹

Next we will discuss the magnetic spin moments determined by the spin sum rule. We limit our analysis to the spin magnetic moment which represents approximately 90% or more of the overall magnetic moment in iron oxides. We want to note that the orbital moment in magnetite is still under discussion in the literature,^{64,66,67} but a precise determination would require more intricate experiments and an extended energy range, which are beyond the scope of this work.

In order to extract the spin magnetic moments we use the spin sum rule developed by Chen *et al.*⁶⁸ The number of holes are determined from the charge transfer multiplet simulations for each sample. We also account for the core hole interactions which mix the character of the L_3 and L_2 edges^{69,70} by considering the spin sum rule correction factors obtained by Teramura *et al.*⁶⁹ The spin magnetic moments are depicted in Fig. 8. One can see that an increasing magnetite layer thickness results in a higher spin moment. Samples **S2**, **SN3** and **MN3** exhibit spin magnetic moments of 3.3, 3.6, and 3.8 $\mu_B/\text{f.u.}$, respectively. These results (excluding the orbital magnetic moment) are rather close to the bulk magnetic moment of Fe_3O_4 .¹ The thinner films have decreased spin moments, which might be partly due to maghemite formation on the very surface layer of these films. However, this cannot explain in particular the rather low spin moment found for sample **SN1** (which exhibits a very similar cationic distribution as sample **MN1**), 1.45 $\mu_B/\text{f.u.}$, which is the same value reported for a 2.5 nm Fe_3O_4 thin film on BaTiO_3 .⁷¹ One possible reason for this might stem from epitaxial strain.³⁶ However, as well as sample **SN1** also samples **SN2** and **SN3** show slight ten-

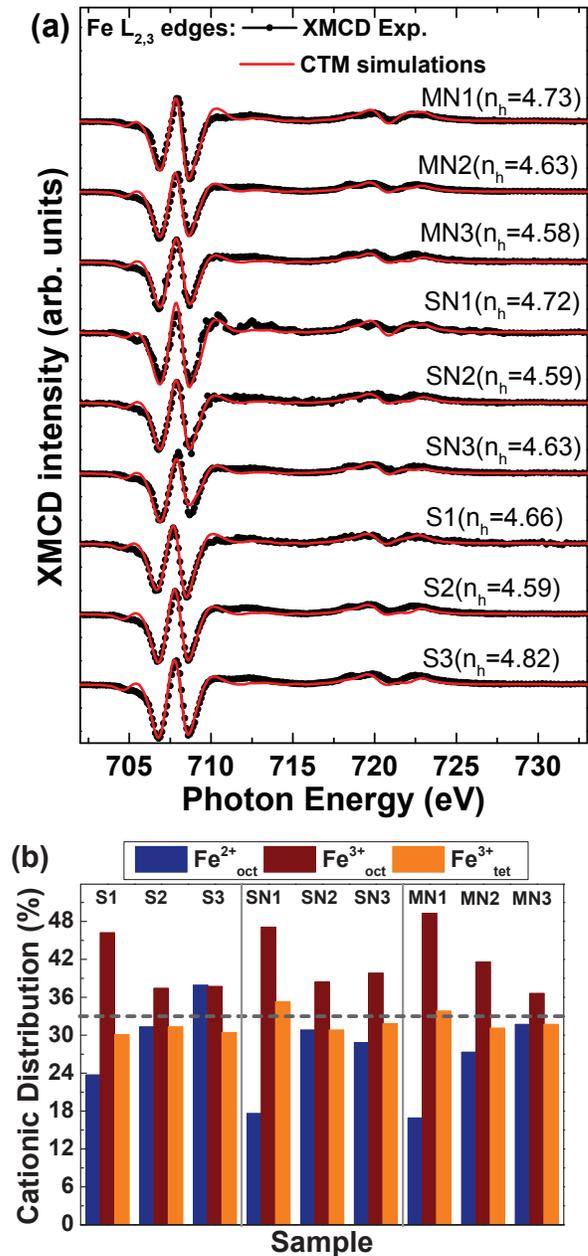


FIG. 7: (a) Fe $L_{2,3}$ -XMCD spectra and the corresponding fits from CTM simulations for all samples investigated in this work. The average number of holes (n_h) per Fe atom as derived from the CTM simulations is also given in parentheses. (b) Cationic distribution of the divalent and trivalent iron ions in octahedral and tetrahedral coordination as derived from the CTM simulations.

sile strain³⁶ of less than 1% compared to the bulk value of Fe_3O_4 and have spin magnetic moments close to that found for the respective samples from series **MN**, the latter ones exhibit slight compressive strain³⁶ of less than 1% in vertical direction. Another potential reason for this reduced spin moment might be connected with the

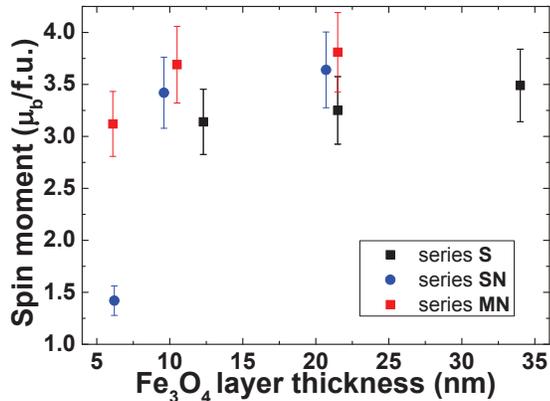


FIG. 8: Calculated magnetic spin moments in $\mu_B/\text{f.u.}$ from the XMCD spin sum rule.

higher roughness of the Fe_3O_4 layer which is found to be 0.45 nm for sample **SN1**, since all other magnetite layers from series **SN** and **MN** have lower roughnesses of approximately 0.3 nm.³⁶ Finally, the formation of antiphase boundaries within magnetite thin films has been previously attributed to reduced magnetic moments.^{10,72} The spin moment of sample **MN1** (3.1 $\mu_B/\text{f.u.}$) is comparable to that very recently reported for $\text{Fe}_3\text{O}_4(001)$ thin films grown on $\text{Ag}(001)$ of similar thicknesses.⁶⁵ Except for sample **SN1** we find significant higher spin magnetic moments for our thin films than observed for similar (001) oriented Fe_3O_4 films grown on $\text{MgO}(001)$ substrates.⁷²

IV. SUMMARY

In summary, we performed a comprehensive electronic and magnetic structure investigation of thin magnetite films and $\text{Fe}_3\text{O}_4(001)/\text{NiO}$ bilayers grown on $\text{MgO}(001)$ and $\text{Nb-SrTiO}_3(001)$ by means of RMBE. In-situ characterization using LEED and XPS shows formation of epitaxial and stoichiometric NiO layers and Fe_3O_4 thin films. Thickness of the NiO layers is varied between 6 and 12 nm and that of the Fe_3O_4 layers between 5 and 33 nm as to XRR measurements. Further electronic and chemical properties are tackled by HAXPES experiments with variable excitation energy. All thin films appear to comprise stoichiometric magnetite and NiO in deeper layers and at the interface. However, thinner Fe_3O_4 films (below 10 nm) tend to form Fe^{3+} on the very sur-

face, likely in form of maghemite. MOKE magnetization curves show significant increased magnetic coercive field and that the in-plane magnetic axis are aligned in (100) in-plane directions, whereas the remanence has the same value along the magnetic easy and hard axis. Reasons for this magnetic behavior might be due to different reasons such as anti-phase domain boundaries (APBs) or spin-flop coupling at the (100) interface between magnetite and NiO . We employ element specific XMCD at the $\text{Fe } L_{2,3}$ edges to tackle the iron cationic distribution in detail. In agreement with the HAXPES we find a lack of Fe^{2+} at the surface of in particular the thinner magnetite layers investigated in the framework of this study. Thicker films are close to stoichiometric cation distribution also at their surface and exhibit spin magnetic moments close to that known from bulk material, whereas thinner samples ($< 10\text{nm}$) show only somewhat reduced spin moments. The only exception is the sample with 5 nm NiO and 6 nm Fe_3O_4 bilayer grown on $\text{Nb-SrTiO}_3(001)$ (**SN1**), here a significantly reduced spin moment is found.

In conclusion we demonstrate that the interface of ferromagnetic Fe_3O_4 and antiferromagnetic NiO leads to a low concentration of $\text{Fe } t_{2g}$ spin down states present directly at the interface. The $\gamma\text{-Fe}_2\text{O}_3$ formation seems to be less intense on the surface of thicker (uncapped) magnetite layers ($\geq 20\text{nm}$) than found for thin layers even in time frames of several months of one year under ambient conditions which might be interesting for potential applications. The altered electronic and magnetic properties as the density of states near Fermi level, magnetic coercive field and anisotropy deserve further future investigations. An improved understanding could open an avenue of tailoring the desired magnetic properties by choosing an appropriate set of substrate, layer thicknesses, and preparation parameters.

Acknowledgments

Financial support by the Deutsche Forschungsgemeinschaft (DFG) (KU2321/2-1) is gratefully acknowledged. Part of this work has been performed at the Advanced Light Source, ALS, Lawrence Berkeley National Laboratory, Berkeley, USA; which is operated under contract No. DE-AC03-76SF00098. We acknowledge the Helmholtz-Zentrum Berlin for provision of synchrotron radiation beam time at beamline KMC-1 of Bessy II.

* Electronic address: kkuepper@uos.de

¹ P. Weiss and R. Forrer, Ann. Phys. (Paris) **12**, 279 (1929).

² P. I. Slick, *Ferromagnetic Materials: A Handbook on the Properties of Magnetically Ordered Substances* (Wohlfarth (ed.), E. P., North-Holland Publishing Company, Amsterdam, 1980).

³ E. J. W. Verwey, Nature **144**, 327 (1939).

⁴ M. S. Senn, J. P. Wright, and J. P. Attfield, Nature **481**, 173 (2012).

⁵ M. I. Katsnelson, V. Y. Irkhin, L. Chioncel, A. I. Lichtenstein, and R. A. de Groot, Rev. Mod. Phys. **80**, 315 (2008).

- ⁶ I. Zutic, J. Fabian, and S. Das Sarma, *Rev. Mod. Phys.* **76**, 323 (2004).
- ⁷ V. Drewello, M. Schaefers, O. Schebaum, A. A. Khan, J. Muenchenberger, J. Schmalhorst, G. Reiss, and A. Thomas, *Phys. Rev. B* (2009).
- ⁸ R. Bliem, E. McDermott, P. Ferstl, M. Setvin, O. Gamba, J. Pavelec, M. A. Schneider, M. Schmid, U. Diebold, P. Blaha, et al., *Science* **346**, 1215 (2014).
- ⁹ J. M. Byrne, N. Klueglein, C. Pearce, K. M. Rosso, E. Appel, and A. Kappler, *Science* **347**, 1473 (2015).
- ¹⁰ J. A. Moyer, R. Gao, P. Schiffer, and L. W. Martin, *Scientific Reports* **5**, 10363 (2015).
- ¹¹ H.-C. Wu, O. N. Mryasov, M. Abid, K. Radican, and I. V. Shvets, *Scientific Reports* **3**, 1830 (2013).
- ¹² A. E. Berkowitz and K. Takano, *Journal of Magnetism and Magnetic Materials* **200**, 552 (1999).
- ¹³ C. Gatel, E. Snoeck, V. Serin, and A. R. Fert, *European Physical Journal B* **45**, 157 (2005).
- ¹⁴ K. Balakrishnan, S. K. Arora, and I. V. Shvets, *Journal of Physics Condensed Matter* **16**, 5387 (2004).
- ¹⁵ G. E. Sterbinsky, J. Cheng, P. T. Chiu, B. W. Wessels, and D. J. Keavney, *Journal of Vacuum Science Technology B: Microelectronics and Nanometer Structures* **25**, 1389 (2007).
- ¹⁶ F. Bertram, C. Deiter, O. Hoefert, T. Schemme, F. Timmer, M. Suendorf, B. Zimmermann, and J. Wollschläger, *Journal of Physics D Applied Physics* **45**, 395302 (2012).
- ¹⁷ F. Bertram, C. Deiter, T. Schemme, S. Jentsch, and J. Wollschläger, *J. Appl. Phys.* **113**, 184103 (2013).
- ¹⁸ J. A. Moyer, S. Lee, P. Schiffer, and L. W. Martin, *Phys. Rev. B* **91**, 064413 (2015).
- ¹⁹ T. Schemme, N. Pathé, G. Niu, F. Bertram, T. Kuschel, K. Kuepper, and J. Wollschläger, *Materials Research Express* **2**, 016101 (2015).
- ²⁰ J. A. Borchers, R. W. Erwin, S. D. Berry, D. M. Lind, J. F. Ankner, E. Lochner, K. A. Shaw, and D. Hilton, *Phys. Rev. B* **51**, 8276 (1995).
- ²¹ J. Keller, P. Miltényi, B. Beschoten, G. Güntherodt, U. Nowak, and K. D. Usadel, *Phys. Rev. B* **66**, 014431 (2002).
- ²² T. Schemme, O. Kuschel, F. Bertram, K. Kuepper, and J. Wollschläger, *Thin Solid Films* **589**, 526 (2015).
- ²³ Y. Z. Chen, J. R. Sun, Y. N. Han, X. Y. Xie, J. Shen, C. B. Rong, S. L. He, and B. G. Shen, *Journal of Applied Physics* **103**, 07D703 (2008).
- ²⁴ A. D. Wei, J. R. Sun, Y. Z. Chen, W. M. Lü, and B. G. Shen, *Journal of Physics D Applied Physics* **43**, 205004 (2010).
- ²⁵ M. Monti, M. Sanz, M. Oujja, E. Rebollar, M. Castillejo, F. J. Pedrosa, A. Bollero, J. Camarero, J. L. F. Cuñado, N. M. Nemes, et al., *J. Appl. Phys.* **114**, 223902 (2013).
- ²⁶ S. Kale, S. M. Bhagat, S. E. Lofland, T. Scabarozzi, S. B. Ogale, A. Orozco, S. R. Shinde, T. Venkatesan, B. Hannyoy, B. Mercey, et al., *Phys. Rev. B* **64**, 205413 (2001).
- ²⁷ A. Brandlmaier, S. Geprägs, M. Weiler, A. Boger, M. Opel, H. Huebl, C. Bihler, M. S. Brandt, B. Botters, D. Grundler, et al., *Phys. Rev. B* **77**, 104445 (2008).
- ²⁸ J. Rubio-Zuazo, L. Onandia, E. Salas-Colera, A. Muñoz-Noval, and G. R. Castro, *J. Phys. Chem. C* **119**, 1108 (2015).
- ²⁹ M. Pilard, O. Ersen, S. Cherifi, B. Carvello, L. Roiban, B. Muller, F. Scheurer, L. Ranno, and C. Boeglin, *Phys. Rev. B* **76**, 214436 (2007).
- ³⁰ I. P. Krug, F. U. Hillebrecht, H. Gomonaj, M. W. Haverkort, A. Tanaka, L. H. Tjeng, and C. M. Schneider, *Europhys. Lett.* **81**, 17005 (2008).
- ³¹ I. P. Krug, F. U. Hillebrecht, M. W. Haverkort, A. Tanaka, L. H. Tjeng, H. Gomonay, A. Fraile-Rodríguez, F. Nolting, S. Cramm, and C. M. Schneider, *Phys. Rev. B* **78**, 064427 (2008).
- ³² N.-T. H. Kim-Ngan, A. G. Balogh, J. D. Meyer, J. Brötz, M. Zajac, T. Ślęzak, and J. Korecki, *Surface Science* **603**, 1175 (2009).
- ³³ M. Gorgoi, S. Svensson, F. Schaefers, G. Ohrwall, M. Mertin, P. Bressler, O. Karis, H. Siegbahn, A. Sandell, H. Rensmo, et al., *Nucl. Instrum. Methods Phys. Res. Sect. A* **601**, 48 (2009).
- ³⁴ F. M. F. de Groot, *Coord. Chem. Rev.* **249**, 31 (2005).
- ³⁵ E. Stavitski and F. M. F. de Groot, *Micron* **41**, 687 (2010).
- ³⁶ O. Kuschel, T. Schemme, N. Pathé, T. Kuschel, R. Buess, K. Kuepper, and J. Wollschläger, to be submitted (2016).
- ³⁷ R. Claessen, M. Sing, M. Paul, G. Berner, A. Wetscherek, A. Müller, and W. Drube, *New Journal of Physics* **11**, 125007 (2009).
- ³⁸ M. Hoppe, S. Döring, M. Gorgoi, S. Cramm, and M. Müller, *Phys. Rev. B* **91**, 054418 (2015).
- ³⁹ C. J. Powell and A. Jablonski, *Nuclear Instruments and Methods in Physics Research A* **601**, 54 (2009).
- ⁴⁰ S. Tanuma, C. J. Powell, and D. R. Penn, *Surf. Interface Anal.* **11**, 577 (1988).
- ⁴¹ S. Tanuma, T. Shiratori, T. Kimura, K. Goto, S. Ichimura, and C. J. Powell, *Surf. Interface Anal.* **37**, 833 (2005).
- ⁴² C. Klewe, M. Meinert, A. Boehnke, K. Kuepper, E. Arenholz, A. Gupta, J.-M. Schmalhorst, T. Kuschel, and G. Reiss, *J. Appl. Phys.* **115**, 123903 (2014).
- ⁴³ T. Yamashita and P. Hayes, *Appl. Surf. Sci.* **254**, 2441 (2008).
- ⁴⁴ M. C. Biesinger, B. P. Payne, A. P. Grosvenor, L. W. M. Lau, A. R. Gerson, and R. S. C. Smart, *Appl. Surf. Sci.* **257**, 2717 (2011).
- ⁴⁵ M. Taguchi, A. Chainani, S. Ueda, M. Matsunami, Y. Ishida, R. Eguchi, S. Tsuda, Y. Takata, M. Yabashi, K. Tamasaku, et al., *Phys. Rev. Lett.* **115**, 256405 (2015).
- ⁴⁶ A. Müller, A. Ruff, M. Paul, A. Wetscherek, G. Berner, U. Bauer, C. Praetorius, K. Fauth, M. Przybylski, M. Gorgoi, et al., *Thin Solid Films* **520**, 368 (2011).
- ⁴⁷ S. Uhlenbrock, C. Scharfschwerdt, M. Neumann, G. Illing, and H.-J. Freund, *J. Phys.: Condens. Matter* **4**, 7973 (1992).
- ⁴⁸ D. Alders, F. C. Voogt, T. Hibma, and G. A. Sawatzky, *Phys. Rev. B* **54**, 7716 (1996).
- ⁴⁹ V. I. Anisimov, I. S. Elfimov, N. Hamada, and K. Terakura, *Phys. Rev. B* **54**, 4387 (1996).
- ⁵⁰ M. Fonin, R. Pentcheva, Y. S. Dedkov, M. Sperlich, D. V. Vyalikh, M. Scheffler, U. Rüdiger, and G. Güntherodt, *Phys. Rev. B* **72**, 104436 (2005).
- ⁵¹ H.-Q. Wang, E. I. Altman, and V. E. Henrich, *Applied Physics Letters* **92**, 012118 (2008).
- ⁵² W. Eerenstein, T. T. Palstra, T. Hibma, and S. Celotto, *Phys. Rev. B* **66**, 201101 (2002).
- ⁵³ D. T. Margulies, F. T. Parker, and A. E. Berkowitz, *Journal of Applied Physics* **75**, 6097 (1994).
- ⁵⁴ J. Cheng, G. E. Sterbinsky, and B. W. Wessels, *Journal of Crystal Growth* **310**, 3730 (2008).
- ⁵⁵ T. Schemme, A. Krampf, F. Bertram, T. Kuschel, K. Kuepper, and J. Wollschläger, *J. Appl. Phys.* **118**, 113904 (2015).
- ⁵⁶ D. T. Margulies, F. T. Parker, M. L. Rudee, F. E. Spada,

- J. N. Chapman, P. R. Aitchison, and A. E. Berkowitz, *Physical Review Letters* **79**, 5162 (1997).
- ⁵⁷ W. Eerenstein, T. Palstra, T. Hibma, and S. Celotto, *Phys. Rev. B* **68**, 014428 (2003).
- ⁵⁸ L. McGuigan, R. C. Barklie, R. G. S. Sofin, S. K. Arora, and I. V. Shvets, *Phys. Rev. B* **77**, 174424 (2008).
- ⁵⁹ K. P. McKenna, F. Hofer, D. Gilks, V. K. Lazarov, C. Chen, Z. Wang, and Y. Ikuhara, *Nat. Commun.* **5**, 5740 (2014).
- ⁶⁰ H. Ohldag, T. J. Regan, J. Stöhr, A. Scholl, F. Nolting, J. Lüning, C. Stamm, S. Anders, and R. L. White, *Physical Review Letters* **87**, 247201 (2001).
- ⁶¹ B. B. Nelson-Cheeseman, R. V. Chopdekar, J. M. Iwata, M. F. Toney, E. Arenholz, and Y. Suzuki, *Phys. Rev. B* **82**, 144419 (2010).
- ⁶² C. Kuiper, B. G. Searle, L.-C. Duda, R. M. Wolf, and P. J. van der Zaag, *J. Electr. Spectr. Rel. Phenom.* **86**, 107 (1997).
- ⁶³ K. Fleischer, O. Mauit, and I. V. Shvets, *Applied Physics Letters* **104**, 192401 (2014).
- ⁶⁴ E. Goering, S. Gold, M. Lafkioti, and G. Schütz, *EPL (Europhysics Letters)* **73**, 97 (2006).
- ⁶⁵ G. F. M. Gomes, T. E. P. Bueno, D. E. Parreiras, G. J. P. Abreu, A. de Siervo, J. C. Cezar, H.-D. Pfannes, and R. Paniago, *Phys. Rev. B* **90**, 134422 (2014).
- ⁶⁶ D. J. Huang, C. F. Chang, H.-T. Jeng, G. Y. Guo, H.-J. Lin, W. B. Wu, H. C. Ku, A. Fujimori, Y. Takahashi, and C. T. Chen, *Phys. Rev. Lett.* **93**, 077204 (2004).
- ⁶⁷ L. Martín-García, R. Gargallo-Caballero, M. Monti, M. Forster, J. F. Marco, L. Aballe, and J. de la Figuera, *Phys. Rev. B* **91**, 020408 (2015).
- ⁶⁸ C. T. Chen, Y. U. Idzerda, H.-J. Lin, N. V. Smith, G. Meigs, E. Chaban, G. H. Ho, E. Pellegrin, and F. Sette, *Phys. Rev. Lett.* **75**, 152 (1995).
- ⁶⁹ Y. Teramura, A. Tanaka, and T. Jo, *J. Phys. Soc. Jap.* **65**, 4, 1053 (1996).
- ⁷⁰ C. Piamonteze, P. Miedema, and F. M. F. de Groot, *Phys. Rev. B* **80**, 184410 (2009).
- ⁷¹ V. Hari Babu, R. K. Govind, K.-M. Schindler, M. Welke, and R. Denecke, *Journal of Applied Physics* **114**, 113901 (2013).
- ⁷² J. Orna, P. A. Algarabel, L. Morellón, J. A. Pardo, J. M. de Teresa, R. López Antón, F. Bartolomé, L. M. García, J. Bartolomé, J. C. Cezar, et al., *Phys. Rev. B* **81**, 144420 (2010).