

This is the accepted manuscript made available via CHORUS. The article has been published as:

Ginzburg-Landau theory of the superheating field anisotropy of layered superconductors

Danilo B. Liarte, Mark K. Transtrum, and James P. Sethna

Phys. Rev. B **94**, 144504 — Published 12 October 2016

DOI: [10.1103/PhysRevB.94.144504](https://doi.org/10.1103/PhysRevB.94.144504)

Ginzburg-Landau theory of the superheating field anisotropy of layered superconductors

Danilo B. Liarte^{1,*} and James P. Sethna^{1,†}

¹*Laboratory of Atomic and Solid State Physics, Cornell University, Ithaca, NY, USA*

We investigate the effects of material anisotropy on the superheating field of layered superconductors. We provide an intuitive argument both for the existence of a superheating field, and its dependence on anisotropy, for $\kappa = \lambda/\xi$ (the ratio of magnetic to superconducting healing lengths) both large and small. On the one hand, the combination of our estimates with published results using a two-gap model for MgB₂ suggests high anisotropy of the superheating field near zero temperature. On the other hand, within Ginzburg-Landau theory for a single gap, we see that the superheating field shows significant anisotropy only when the crystal anisotropy is large and the Ginzburg-Landau parameter κ is small. We then conclude that only small anisotropies in the superheating field are expected for typical unconventional superconductors near the critical temperature. Using a generalized form of Ginzburg Landau theory, we do a quantitative calculation for the anisotropic superheating field by mapping the problem to the isotropic case, and present a phase diagram in terms of anisotropy and κ , showing type I, type II, or mixed behavior (within Ginzburg-Landau theory), and regions where each asymptotic solution is expected. We estimate anisotropies for a number of different materials, and discuss the importance of these results for radio-frequency cavities for particle accelerators.

I. INTRODUCTION

A superconductor in a magnetic field parallel to its surface can be metastable to flux penetration up to a (mis-named) *superheating field* H_{sh} , which is above the field at which magnetism would penetrate in equilibrium ($H_{\text{sh}} > H_c$ and $H_{\text{sh}} > H_{c1}$ for type-I and type-II superconductors, respectively). Radio-frequency cavities used in current particle accelerators routinely operate in this metastable regime, which has prompted recent attention on theoretical calculations of this superheating field^{1,2}. The first experimental observation of the superheating field dates back to 1952³, and a quantitative description has been given early by Ginzburg in the context of Ginzburg-Landau (GL) theory⁴. Since then, there have been many calculations of the superheating field within the realm of GL^{5–12}. In particular, Transtrum et al.² studied the dependence of the superheating field on the GL parameter κ . Here we use their results and simple re-scaling arguments to study the effects of material anisotropy in the superheating field of layered superconductors.

The layered structure of many unconventional superconductors is not only linked with the usual high critical temperatures of these materials; it also turned small corrections from anisotropy effects into dominant properties¹³. For instance, the critical current of polycrystalline magnesium diboride is known to vanish far below the upper critical field, presumably due to anisotropy of the grains (the boron layers inside each grain start superconducting at different temperatures, depending on the angle between the grain layers and the external field)^{14,15}. Cuprates, such as BSCCO, exhibit even more striking anisotropy, with the upper critical field varying by two orders of magnitude depending on the orientation of the crystal with respect to the direction of the applied mag-

netic field¹³.

One would expect that such anisotropic crystals also display strong anisotropy on the superheating field. Here we show that this is typically not true near the critical temperature. Type II superconductors, which often display strong anisotropic properties, also have a large ratio between penetration depth and coherence length (the GL parameter κ), which, as we shall see, considerably limits the effects of the Fermi surface anisotropy on the superheating field. At low temperatures, heuristic arguments suggest that crystal anisotropy might be important for the superheating field of multi-band superconductors, such as MgB₂ (section IV).

It is usually convenient to characterize crystalline anisotropy by the ratio of the important length scales of superconductors, within Ginzburg-Landau theory,

$$\gamma = \frac{\lambda_c}{\lambda_a} = \frac{\xi_a}{\xi_c} = \sqrt{\frac{m_c}{m_a}}, \quad (1)$$

where λ is the penetration depth, ξ is the coherence length, m is the effective mass, and the indices c and a are associated with the layer-normal axis \mathbf{c} , and an in-plane axis, respectively. Note that λ_i is associated with the screening by supercurrents flowing along the i -th axis¹³. Hence for a magnetic field parallel to a flat surface of superconductor, $\lambda = \lambda_c$ only when \mathbf{c} is perpendicular to both the magnetic field and the surface normal; counter-intuitively, $\lambda = \lambda_a$ for \mathbf{c} parallel to the magnetic field or the surface normal. In this paper, we show that the anisotropy of H_{sh} is larger for larger γ and smaller κ_{\parallel} , and behaves asymptotically as: $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} \approx 1$ for $\kappa_{\parallel} \gg 1/\gamma$, and $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} \approx \gamma^{1/2}$, for $\kappa_{\parallel} \ll 1$. We begin with a simple qualitative calculation that explains the two limiting regimes in an intuitive picture. We shall then turn to the full GL calculation, which we map, using a suitable change of variables and rescaling of the vector potential,

onto an isotropic free energy, and discuss the implications of these results for several materials. We then discuss a generalization of our simple estimates for MgB_2 at lower temperatures, using results from a two-gap model, and make some concluding remarks.

II. SIMPLE ESTIMATIONS OF H_{sh} IN THE LARGE AND SMALL- κ REGIMES

Let the superconductor occupy the half space $x > 0$, and the magnetic field \mathbf{H} be parallel to the z axis. Figure 1 illustrates vortex nucleation in a type-II superconductor for this configuration. With this choice for the system geometry, we neglect effects of field bending over sample corners, which can play a very important role in the flux penetration of real samples. However, we note that these effects are not appreciable for RF cavities for particle accelerators, which have an approximate cylindrical shape in the regions of high magnetic fields.

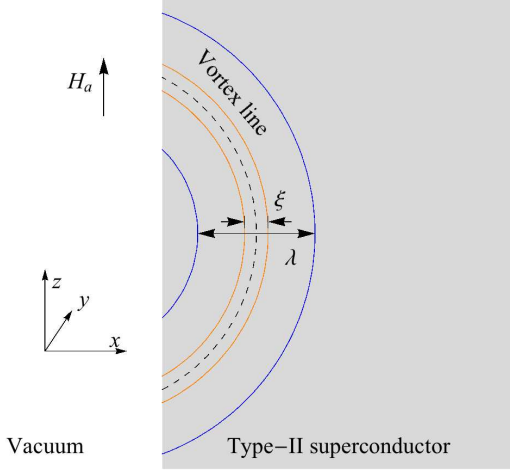


FIG. 1. (Color online) Illustrating vortex nucleation in a type-II superconductor occupying the half space $x > 0$, and subject to a magnetic field parallel to the vacuum-superconductor interface.

Let us start with a heuristic estimate of the superheating field for type I superconductors. At an interface between superconductor and insulator (or vacuum), the order parameter ψ is not suppressed; however, if we force a slab of magnetic field into the superconductor thick enough to force the surface to go normal and $\psi \rightarrow 0$, the superconductivity will be destroyed over a depth ξ , the coherence length of the SC, with energy cost per unit area $[H_c^2/(8\pi)]\xi_i$, with $i = a$ and $i = c$, for $\mathbf{c} \parallel \mathbf{z}$ and $\mathbf{c} \perp \mathbf{z}$, respectively. The necessary width of the magnetic slab should be set by the Meissner magnetic penetration depth λ , with approximate energy gain per unit area, given by the magnetic pressure times the depth, or: $[H_{\text{sh}}/(4\pi)](H_{\text{sh}}\lambda_i)$. Thus $H_{\text{sh}}/(\sqrt{2}H_c) \approx (1/2)(\lambda_i/\xi_i)^{-1/2} = (1/2)\kappa_i^{-1/2}$, which is close to the exact result: $H_{\text{sh}}/(\sqrt{2}H_c)(\kappa \ll 1) =$

$2^{-3/4}\kappa^{-1/2}$ for isotropic Fermi surfaces². The anisotropy of the superheating field is then proportional to $\gamma^{1/2}$, assuming $\kappa \ll 1$ for \mathbf{c} parallel and perpendicular to the magnetic field.

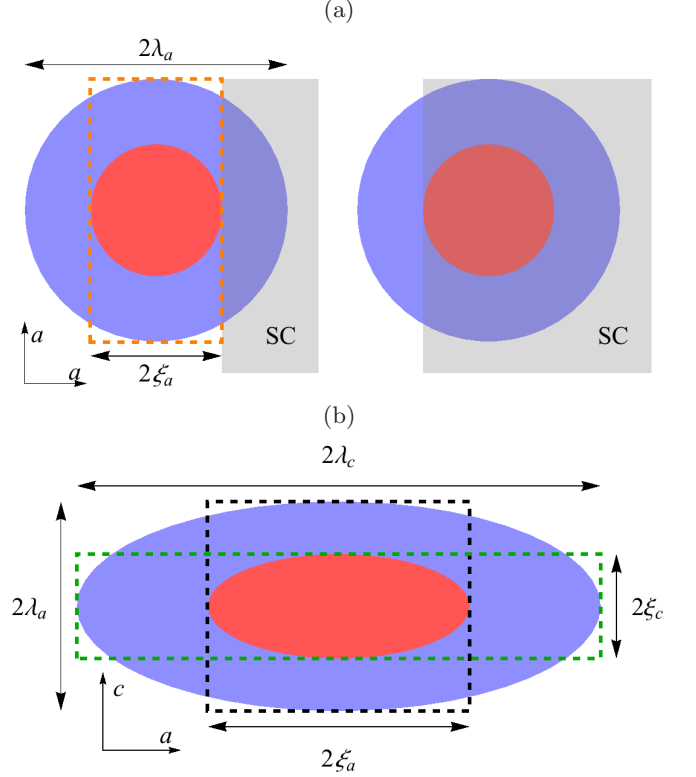


FIG. 2. (Color online) (a) Illustration of the penetration of a vortex core into a type-II anisotropic superconductor with anisotropy axis $\mathbf{c} \parallel \mathbf{z}$ (perpendicular to the plane of the figure). (b) Vortex and vortex core acquire an ellipsoidal shape when \mathbf{c} lies in the xy plane. Here the superconductor surface lies horizontally and vertically, for \mathbf{c} parallel to x and y , respectively. The magnetic field is parallel to z for both (a) and (b). We can estimate the superheating field from the calculation of the work necessary to push a vortex core into the superconductor, thus destroying the Meissner state. For anisotropic vortices, the superheating field turns out to be proportional to the area of the green (black) boxes for the superconductor boundary surface parallel (perpendicular) to the \mathbf{c} axis. These estimates simplify the calculations of Bean and Levington¹⁶, which consider the vanishing of the surface energy barrier felt by a single penetrating vortex in a type-II superconductor. More generally, the Ginzburg-Landau approach takes into account the cooperative effects due to the penetration of multiple vortices².

For type II superconductors, consider the penetration of a vortex core into the superconductor, as illustrated in FIG. 2a. The vortex and vortex core correspond to the blue and red regions, respectively. The magnetic field \mathbf{H} is again parallel to z (perpendicular to the plane of the figure), and the anisotropy axis \mathbf{c} is either parallel (FIG. 2a) or perpendicular (FIG. 2b) to z ; the gray region in FIG. 2a illustrates a superconductor occupying

the semi-infinite space $x > 0$. Vortex and vortex core acquire an ellipsoidal shape when \mathbf{c} lies in the xy plane (FIG. 2b); here the superconductor surface lies horizontally and vertically when $\mathbf{c} \parallel x$ and $\mathbf{c} \parallel y$, respectively. We can estimate the superheating field by comparing the work (per unit length) that is necessary to push a vortex core into the superconductor (thus destroying the Meissner state) with the condensation energy:

$$\frac{H_{\text{sh}}}{4\pi} \Delta H \approx \frac{H_c^2}{8\pi} S_{\text{vc}}, \quad (2)$$

where S_{vc} is the area of the vortex core (red region in FIG. 2), and ΔH is given by

$$\Delta H = \frac{\Phi_0}{S_v} S_\Delta, \quad (3)$$

where Φ_0 is the fluxoid quantum¹³. S_v is the total sectional area of the vortex; e.g. $S_v = \pi \lambda^2$ for isotropic superconductors. S_Δ is the amount of vortex area that penetrates when the vortex core is pushed into the superconductor; it is approximately equal to the areas of the green, black, and orange dashed rectangles in FIG. 2, for $\mathbf{c} \parallel x$, y and z , respectively. Table I shows equations for S_v , S_{vc} and S_Δ in terms of the penetration and coherence lengths, with \mathbf{c} parallel to each cartesian axis. Equations (2-3) then read:

$$H_{\text{sh}} = \frac{H_c^2 \pi^2}{8 \Phi_0} \times \begin{cases} \lambda_c \xi_c, & \text{if } \mathbf{c} \parallel y, \\ \lambda_a \xi_a, & \text{if } \mathbf{c} \parallel x \text{ or } z. \end{cases} \quad (4)$$

Interestingly, for $\mathbf{c} \parallel y$, the penetrating vortex area is the area of the *black* dashed box (see FIG. 2b), whereas the superheating field is proportional to the area of the dashed *green* box. Conversely, for $\mathbf{c} \parallel x$, the penetrating vortex area is the area of the *green* dashed box, whereas the superheating field is proportional to the area of the dashed *black* box. Within GL theory, $\lambda_a \xi_a = \lambda_c \xi_c$, suggesting that the superheating field is isotropic. Plugging $\Phi_0 = 2 \sqrt{2} \pi H_c \lambda_i \xi_i$ into Eq. (4), we find $H_{\text{sh}}/(\sqrt{2} H_c) \approx 0.1$, which is independent of κ , as in the exact calculations for isotropic Fermi surfaces², but off by an overall factor of five from the linear stability results: $H_{\text{sh}}/(\sqrt{2} H_c)(\kappa \gg 1) \approx 0.5$. In section III, we show that H_{sh} is isotropic on GL for $\kappa \gg 1$. In section IV, we discuss recent work at lower temperatures using the two-band model for MgB₂, which then suggests a substantial anisotropy.

	$\mathbf{c} \parallel x$	$\mathbf{c} \parallel y$	$\mathbf{c} \parallel z$
S_v	$\pi \lambda_a \lambda_c$	$\pi \lambda_a \lambda_c$	$\pi \lambda_a^2$
S_{vc}	$\pi \xi_a \xi_c$	$\pi \xi_a \xi_c$	$\pi \xi_a^2$
S_Δ	$4 \lambda_c \xi_c$	$4 \lambda_a \xi_a$	$4 \lambda_a \xi_a$

TABLE I. Area of the vortex (S_v), area of the vortex core (S_{vc}) and approximated penetrating field area (S_Δ ; area of the dashed rectangles in FIG. 2) for \mathbf{c} parallel to each cartesian axis.

III. GINZBURG-LANDAU THEORY OF THE SUPERHEATING FIELD ANISOTROPY

Let us flesh out these intuitive limits into a full calculation. A phenomenological generalization of GL theory that incorporates the anisotropy of the Fermi surface was initially proposed by Ginzburg¹⁷, and revisited later, using the microscopic theory, by several authors¹⁸⁻²⁰. In this approach, the gauge-invariant derivative terms are multiplied by an anisotropic effective mass *tensor* that depends on integrals over the Fermi surface (see e.g. Eq. 2 of Ref.²⁰). The mass tensor is a multiple of the identity matrix for cubic crystals, such as Nb, Nb₃Sn and NbN, which belong to the next generation of superconducting accelerator cavities. In this case, the dominant effects of the Fermi surface anisotropy are higher-order multipoles, which may be added using, e.g. nonlocal terms of higher gradients²¹. On the other hand, as it should be anticipated, mass anisotropy can lead to important effects on layered superconductors, such as MgB₂ and some iron-based superconductors (also considered for RF cavities), at least insofar as the GL formalism is accurate. Simple arguments within GL theory can be used to show that the anisotropy of the upper-critical and lower-critical fields is proportional to γ ; i.e. $H_{c2}^\perp/H_{c2}^\parallel = \gamma = H_{c1}^\parallel/H_{c1}^\perp$, where the perpendicular (parallel) symbol indicates that the applied magnetic field is perpendicular (parallel) to the \mathbf{c} axis. The effects of Fermi surface anisotropy on the properties of superconductors have been theoretically studied by many authors^{17,19-23}.

One possible generalization of the Ginzburg-Landau free energy to incorporate anisotropy effects has been written down by Tilley²⁰:

$$f_s - f_n = \sum_{i,j \in \{x,y,z\}} \frac{1}{2m_{ij}} \left(-\frac{\hbar}{i} \frac{\partial \psi^*}{\partial x_i} - \frac{e^*}{c} A_i \psi^* \right) \times \left(\frac{\hbar}{i} \frac{\partial \psi}{\partial x_j} - \frac{e^*}{c} A_j \psi \right) + \alpha |\psi|^2 + \frac{\beta}{2} |\psi|^4 + \frac{(\mathbf{H}_a - \nabla \times \mathbf{A})^2}{8\pi}, \quad (5)$$

where f_s and f_n are the free energy densities of the superconducting and normal phases, respectively; ψ is the superconductor order parameter, \mathbf{A} is the vector potential, and \mathbf{H}_a is an applied magnetic field. Anisotropy is incorporated in the effective mass tensor $M = ((m_{ij}))$, whose components can be conveniently expressed as a ratio of integrals over the Fermi surface (see Eq. (2) of Ref.²⁰). e^* is the effective charge, α and β are energy constants, and \hbar and c are Planck's constant (divided by 2π) and the speed of light, respectively. The thermodynamic critical field is given by¹³: $H_c = \sqrt{4\pi\alpha^2/\beta}$, independent of mass anisotropy. Eq. (5) can then be written in a

more convenient form:

$$\frac{(f_s - f_n)}{H_c^2/(4\pi)} = \sum_i \left[\left(\xi_i \frac{\partial f}{\partial x_i} \right)^2 + \left(\xi_i \frac{\partial \phi}{\partial x_i} - \frac{A_i}{\sqrt{2}H_c\lambda_i} \right)^2 f^2 \right] + \frac{1}{2} (1 - f^2)^2 + \frac{1}{2H_c^2} (\mathbf{H}_a - \nabla \times \mathbf{A})^2, \quad (6)$$

where we have assumed a layered superconductor with the anisotropy axis \mathbf{c} aligned with one of the three Cartesian axes, so that $i \in \{x, y, z\}$ in the first term of the right-hand side, and we have dropped an irrelevant additive constant $1/2$. Also, we have rewritten the order parameter as $\psi = |\psi_\infty| f e^{i\phi}$, where f and ϕ are scalar fields, and $\psi_\infty = -\alpha/\beta$ is the solution infinitely deep in the interior of the superconductor¹³. The anisotropic penetration depth and coherence lengths are given by $\lambda_i = (m_i c^2 / (4\pi |\psi_\infty|^2 e^{*2}))^{1/2}$, and $\xi_i = (\hbar^2 / (2m_i (-\alpha)))^{1/2}$, respectively.

Let the pairs of characteristic lengths (λ_c, ξ_c) and (λ_a, ξ_a) be associated with the layer-normal and an in-plane axis, respectively. Define:

$$\kappa_{\parallel} \equiv \frac{\lambda_a}{\xi_a}, \quad \kappa_{\perp} \equiv \frac{\lambda_c}{\xi_a} = \frac{\lambda_a}{\xi_c} = \gamma \kappa_{\parallel}, \quad (7)$$

where the last two relations can be verified using the definition of λ_i , ξ_i , and γ . Following previous calculations of the superheating field^{1,2}, we also let \mathbf{H}_a be parallel to z , and the superconductor occupy the half-space region $x > 0$, so that symmetry constraints imply that $A_z = 0$, and all fields should be independent of z . Thus, if the anisotropy axis \mathbf{c} is parallel to z , our GL free energy (Eq. 6) is directly mapped into the isotropic free energy of Transtrum et al.², with ξ and λ replaced by ξ_a and λ_a , respectively. In particular, the solution for the superheating field H_{sh} as a function of κ is given in Ref.² using κ_{\parallel} instead of κ . If \mathbf{c} is parallel to x or y , there are a number of scaling arguments that can be used to map the anisotropic free energy into the isotropic one²⁴. Here we consider the change of coordinates and rescaling of the vector potential:

$$\mathbf{r} = \begin{pmatrix} \xi_x \tilde{x} \\ \xi_y \tilde{y} \\ \xi_z \tilde{z} \end{pmatrix}, \quad \mathbf{A} = \begin{pmatrix} \tilde{A}_x \\ \xi_y \tilde{A}_y \\ \tilde{A}_z \end{pmatrix}. \quad (8)$$

Note that this change of variables does not change the magnetic field, since \mathbf{H}_a is aligned with the z axis, so that the z -component of the field is given by: $\partial A_y / \partial x - \partial A_x / \partial y = \partial \tilde{A}_y / \partial \tilde{x} - \partial \tilde{A}_x / \partial \tilde{y}$. This coordinate transformation maps the anisotropic free energy into an isotropic one with ξ_y and λ_x replacing ξ and λ . In particular, now the solution for the superheating field is given in Ref.² using $\kappa_{\perp} = \gamma \kappa_{\parallel}$ instead of κ . In this paper, we only consider the two representative cases: $\mathbf{c} \parallel z$ and $\mathbf{c} \perp z$, as we do not expect appreciable qualitative changes for arbitrary orientations of \mathbf{c} with respect to the z axis. Notice the interesting fact that a crystal might be a type I superconductor ($\kappa_{\parallel} < 1/\sqrt{2}$) when \mathbf{c} is parallel to z , and yet be a type II superconductor if $\gamma \kappa_{\parallel} > 1/\sqrt{2}$ when \mathbf{c}

is perpendicular to z (see Fig. 3). This interesting property of anisotropic superconductors has been discussed in Ref.²⁵, and confirmed experimentally in the work of Ref.²⁶.

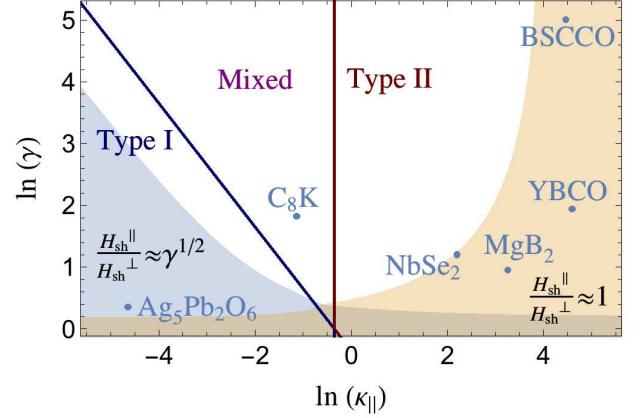


FIG. 3. (Color online) Showing regions in $\kappa_{\parallel} \times \gamma$ space where the crystal is always type I (left region to blue solid lines), always type II (right region to red solid lines), or might be of either type (region between red and blue lines), depending on the orientation of the crystal. The shaded blue and orange regions correspond to regions where the Ginzburg-Landau superheating field anisotropy can be approximated by $\gamma^{1/2}$ and 1, respectively, within 10% of accuracy.

Now we turn our attention to the anisotropy of the superheating field:

$$\frac{H_{sh}^{\parallel}}{H_{sh}^{\perp}} = \frac{H_{sh}(\kappa_{\parallel})}{H_{sh}(\kappa_{\perp})} = \frac{H_{sh}(\kappa_{\parallel})}{H_{sh}(\gamma \kappa_{\parallel})}. \quad (9)$$

For general κ , approximate solutions for the superheating field for isotropic systems are given by Eqs. (10) and (11) of Ref.², which we reproduce here for convenience:

$$\frac{H_{sh}}{\sqrt{2}H_c} \approx 2^{-3/4} \kappa^{-1/2} \frac{1 + 4.6825120 \kappa + 3.3478315 \kappa^2}{1 + 4.0195994 \kappa + 1.0005712 \kappa^2}, \quad (10)$$

for small κ , and

$$\frac{H_{sh}}{\sqrt{2}H_c} \approx \frac{\sqrt{10}}{6} + 0.3852 \kappa^{-1/2}, \quad (11)$$

for large κ . We can use approximations (10) and (11) to find asymptotic solutions for the superheating field anisotropy:

$$\frac{H_{sh}^{\parallel}}{H_{sh}^{\perp}} \approx \begin{cases} \gamma^{1/2}, & \text{for } \kappa \ll 1/\gamma, \\ 1, & \text{for } \kappa \gg 1, \end{cases} \quad (12)$$

with $\gamma > 1$. These asymptotic solutions span a large region in the phase diagram of Fig. 3, with the shaded blue and orange regions corresponding to regions where the superheating field anisotropy can be approximated by $\gamma^{1/2}$ and 1, respectively. Figure 4 shows a plot of

the anisotropy of the superheating field as a function of the mass anisotropy for several values of κ_{\parallel} . The dotted lines are asymptotic solutions given by Eq. (12). In order to make this plot we considered the solution for the superheating field to be given by Eqs. (10) and (11) for $\kappa < \kappa_{\text{th}}$ and $\kappa \geq \kappa_{\text{th}}$, respectively, where the threshold $\kappa_{\text{th}} \approx 0.56$ is found by equating the right-hand sides of the two approximate solutions. It is clear that the combination of large γ and small κ yields the largest anisotropy of H_{sh} . Notice that the deviation from the simple asymptotic solution at small κ_{\parallel} scales as $(H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} - \gamma^{1/2})/\gamma^{1/2} = \mathcal{O}(\kappa\gamma)$.

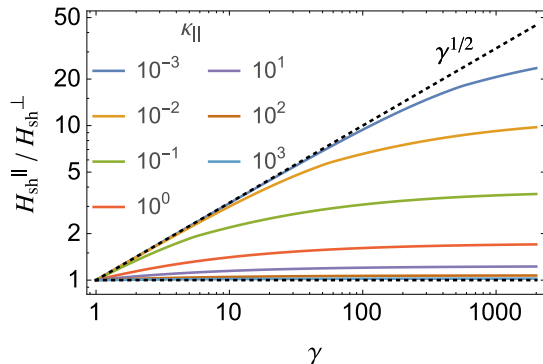


FIG. 4. (Color online) Anisotropy of the Ginzburg-Landau superheating field as a function of mass anisotropy for several values of κ_{\parallel} . The dotted lines are the limiting solutions given by Eq. 12.

Material	κ_{\parallel}	γ	$H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp}$
Ag ₅ Pb ₂ O ₆ (Ref. ²⁷)	~ 0.0096	~ 1.43	~ 1.2
C ₈ K (Ref. ²⁶)	~ 0.32	~ 6.2	~ 1.6
NbSe ₂ (Ref. ²⁸)	~ 9	~ 3.33	~ 1.1
MgB ₂ (Refs. ^{23,29})	~ 26	~ 2.6	~ 1.05
BSCCO (Refs. ^{13,30})	~ 87	~ 150	~ 1.07
YBCO (Refs. ^{13,30})	~ 99	~ 7	~ 1.04

TABLE II. Ginzburg-Landau parameter κ_{\parallel} with \mathbf{c} parallel to the z axis, mass anisotropy γ , and superheating field anisotropy for different materials.

In Table II we compare the anisotropy of the superheating field for different materials; we also present the values that we used for κ_{\parallel} and γ in each case. As we have stressed before, the superheating field anisotropy is largest for small κ_{\parallel} and large γ . Note that even though type-I superconductors have small κ , we have not found anisotropy parameters for elemental superconductors in the literature, probably because anisotropy plays a minor role for most of them. Just a few well-studied non-elemental superconductors are of type I, such as the layered silver oxide Ag₅Pb₂O₆, with a mass anisotropy of about 1.43, and $\kappa_{\parallel} \approx 0.01 < 1/\sqrt{2}$. On the other

hand, type-II superconductors are known for their large anisotropies. The critical fields of BSCCO, for instance, can vary by two orders of magnitude depending on the orientation of the crystal. Yet the anisotropy effects on the superheating field are undermined (Eq. (9)) by the flat behavior of H_{sh} at large κ . These effects are also illustrated in Fig. 5, where we plot the solution $H_{\text{sh}}/(\sqrt{2}H_c)$ as a function of κ , using the asymptotic solutions given by Eqs. (10) and (11) for $\kappa \leq 0.56$ and $\kappa > 0.56$, respectively (this approximated solution is remarkably close to the exact result²). Note that within GL theory H_{sh}/H_c depends on material properties only through the parameter κ . The points in FIG. 5 correspond to the solutions of the superheating field using κ_{\parallel} and κ_{\perp} for Ag₅Pb₂O₆ (blue), C₈K (purple), MgB₂ (red), BSCCO (dark red). Superconductors with $\kappa_{\parallel} \approx 1$ can have an enormous anisotropy γ , say $\sim 10^5$, and yet the superheating field will be nearly isotropic.

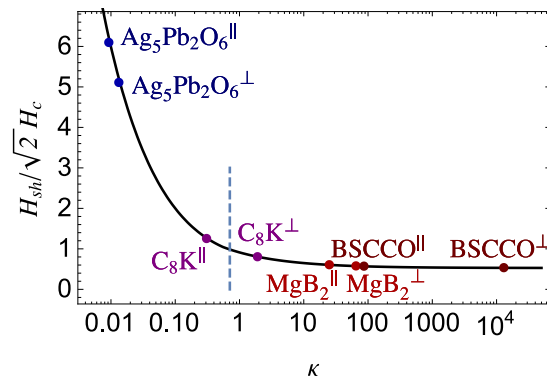


FIG. 5. (Color online) Ginzburg-Landau superheating field $H_{\text{sh}}/(\sqrt{2}H_c)$ as a function of κ . The points correspond to the solutions using κ_{\parallel} and κ_{\perp} for Ag₅Pb₂O₆ (blue), C₈K (purple), MgB₂ (red), BSCCO (dark red).

One should bear in mind that GL formalism is accurate only in the narrow ranges of temperatures near the critical point. Beyond this range, one must rely either on generalizations of GL to arbitrary temperatures^{31,32}, or more complex approaches using BCS theory, Eilenberger semi-classical approximation and strong-coupling Eliashberg theory. However, note that GL and Eilenberger theories yield similar quantitative results for the temperature dependence of the superheating in the limit of large κ for isotropic Fermi surfaces (see e.g. Ref.¹).

IV. LOW-TEMPERATURE ANISOTROPY OF THE SUPERHEATING FIELD FOR MgB₂

Another limitation of GL theory at low temperatures is related to the assumption: $\lambda_c/\lambda_a = \xi_a/\xi_c$, which originates in the mass dependence of the penetration and coherence lengths ($\lambda \sim m^{1/2}$ whereas $\xi \sim m^{-1/2}$), in the

context of the anisotropic formulation of GL equations. Experiments^{33–38} and theoretical calculations^{23,39,40} for MgB₂ suggest that this relation is violated at lower temperatures; the anisotropies of λ and ξ exhibit opposite temperature dependences, with

$$\gamma_\lambda = \lambda_c/\lambda_a \quad (13)$$

increasing, whereas

$$\gamma_\xi = \xi_a/\xi_c \quad (14)$$

decreases⁴¹ with temperature. Figure 6 shows an illustration of a vortex section near $T = 0$. Using calculations from Ref.²³, γ_λ and γ_ξ become equal only at $T = T_c$.

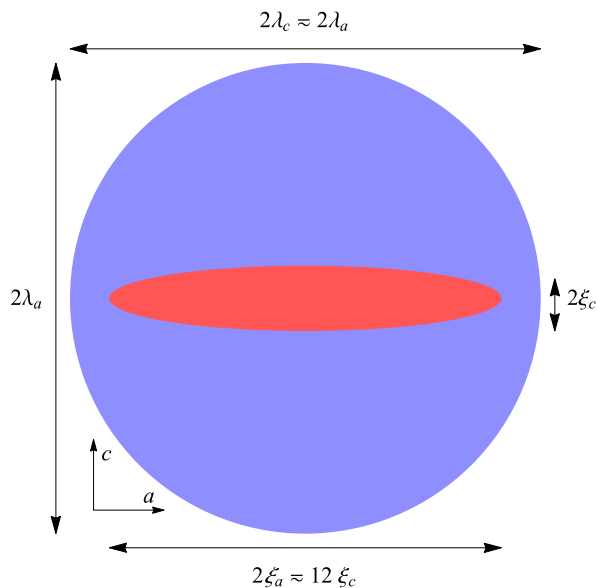


FIG. 6. (Color online) Illustrating a vortex and vortex core (blue and red regions) of MgB₂ near $T = 0$ (we increased ξ_a by a factor of 30 with respect to λ_a , so that the core features become discernible). Near zero temperature, the field penetration region is calculated to be nearly isotropic ($\lambda_a \approx \lambda_c$), whereas the core shape anisotropy is predicted to reach a maximum ($\xi_a \approx 6\xi_c$) (Ref.²³).

We can estimate the low-temperature superheating field anisotropy by relaxing the constraint $\lambda_c \xi_c = \lambda_a \xi_a$ in Eq. (4) of section II, resulting,

$$\frac{H_{\text{sh}}^{c\perp y}}{H_{\text{sh}}^{c\parallel y}} = \frac{\gamma_\xi}{\gamma_\lambda}. \quad (15)$$

Here $H_{\text{sh}}^{c\perp y}$ means either $H_{\text{sh}}^{c\parallel x}$ or $H_{\text{sh}}^{c\parallel z}$. H_{sh} is isotropic near $T = T_c$, since $\gamma_\xi \approx \gamma_\lambda$. Near $T = 0$, however, the theoretical calculations of Ref.²³ using a two-gap model for MgB₂ suggest that $\gamma_\xi \approx 6$ and $\gamma_\lambda \approx 1$, so that, according to our intuitive arguments: $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} \approx 6$, which is quite large. Experimental results agree with the theoretical predictions near zero temperature, with γ_λ being almost isotropic^{35,36}, and $\gamma_\xi \approx 6 - 7$ (see e.g. Ref.³⁸). However, beware that reported experimental results for

γ_ξ range from ≈ 1 to ≈ 13 (see Ref.²³ and references therein). Using $H_c(0) = 0.26$ T from Ref.⁴², we find $H_{\text{sh}} \approx 0.006$ (0.04) T for the anisotropy axis c parallel (perpendicular) to y . Recall that our estimates were off actual GL calculations by a factor of five. If we extrapolate this discrepancy to lower temperatures, we find $H_{\text{sh}} 0.03$ Tesla for the anisotropy axis c parallel to the y direction (perpendicular to the surface normal and the field), and 0.2 Tesla for the anisotropy axis c perpendicular to y . In comparison, for Nb the superheating field from Ginzburg-Landau theory extrapolated to low temperature is 0.24 Tesla⁴³. This result has important consequences for superconducting RF cavities for particle accelerators, as one achieve fields about a factor of six higher by a proper alignment of the anisotropy axis; the penetration field is lowest when c is parallel to the beam direction in the cavity. It would be interesting to establish this result using linear stability analysis in the context of more sophisticated approaches, such as multi-band models in BCS theory or Eliashberg theory.

V. CONCLUDING REMARKS

To conclude, we used a generalized Ginzburg-Landau approach to investigate the effects of Fermi surface anisotropy on the superheating field of layered superconductors. Using simple scaling arguments, we mapped the anisotropic problem into the isotropic one, which has been previously studied by Transtrum et al.², and show that the superheating field anisotropy depends only on two parameters, $\gamma = \lambda_c/\lambda_a$ and $\kappa_{\parallel} = \lambda_a/\xi_a$. $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp}$ is larger when γ is large and κ_{\parallel} is small, and displays the asymptotic behavior $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} \approx 1$ for $\kappa_{\parallel} \gg 1/\gamma$, and $H_{\text{sh}}^{\parallel}/H_{\text{sh}}^{\perp} \approx \gamma^{1/2}$, for $\kappa_{\parallel} \ll 1$, suggesting that the superheating field is typically isotropic for most layered unconventional superconductors, even for very large γ (see Table II), when GL is valid. We surmise that the anisotropy of the superheating field is even smaller for cubic crystals, where higher-order and/or non-linear terms have to be included in the GL formalism.

As a practical question, accelerator scientists have explored stamping radio-frequency cavities out of single-crystal samples, to test whether grain boundaries were limiting the performance of particle accelerators. Our study was motivated by the expectation that one could use this expertise to control the surface orientation in the cavity. Such control likely may yield benefits through either optimizing anisotropic surface resistance or optimizing growth morphology, for deposited compound superconductors (growing Nb₃Sn from a Sn overlayer). Our calculations suggest that, for the high- T_c , high- κ materials under consideration for the next generation of superconducting accelerator cavities, that the theoretical bounds for the maximum sustainable fields will not have a significant anisotropy near $T = T_c$. However, the extension of our intuitive arguments for MgB₂ to low temper-

atures, using results from a two-gap model within BCS theory (Ref.²³), suggest a high value for the anisotropy of H_{sh} near $T = 0$, which motivates further investigations by means of more sophisticated approaches and experiments controlling surface orientation.

ACKNOWLEDGMENTS

We would like to thank G. Catelani, M. Liepe, S. Posen, J. She, and M. Transtrum for useful conversations. This work was supported by the DOE under Grant No. DE-FG02-07ER46393.

-
- * dl778@cornell.edu
† sethna@lassp.cornell.edu
- ¹ G. Catelani and J. P. Sethna, Phys. Rev. B **78**, 224509 (2008).
 - ² M. K. Transtrum, G. Catelani, and J. P. Sethna, Phys. Rev. B **83**, 094505 (2011).
 - ³ M. P. Garfunkel and B. Serin, Phys. Rev. **85**, 834 (1952).
 - ⁴ V. L. Ginzburg, Soviet Phys.—JETP **7**, 78 (1958).
 - ⁵ L. Kramer, Phys. Rev. **170**, 475 (1968).
 - ⁶ P. de Gennes, Solid State Communications **3**, 127 (1965).
 - ⁷ V. P. Galaiko, Sov. Phys. JETP **23**, 475 (1966).
 - ⁸ L. Kramer, Zeitschrift für Physik **259**, 333 (1973).
 - ⁹ H. J. Fink and A. G. Presson, Phys. Rev. **182**, 498 (1969).
 - ¹⁰ P. Christiansen, Solid State Communications **7**, 727 (1969).
 - ¹¹ S. J. Chapman, SIAM Journal on Applied Mathematics **55**, 1233 (1995).
 - ¹² A. J. Dolgert, S. J. Di Bartolo, and A. T. Dorsey, Phys. Rev. B **53**, 5650 (1996).
 - ¹³ M. Tinkham, *Introduction to Superconductivity*, 2nd ed. (McGraw-Hill, New York, 1996).
 - ¹⁴ S. Patnaik, L. D. Cooley, A. Gurevich, A. A. Polyanskii, J. Jiang, X. Y. Cai, A. A. Squitieri, M. T. Naus, M. K. Lee, J. H. Choi, L. Belenky, S. D. Bu, J. Letteri, X. Song, D. G. Schlom, S. E. Babcock, C. B. Eom, E. E. Hellstrom, and D. C. Larbalestier, Superconductor Science and Technology **14**, 315 (2001).
 - ¹⁵ M. Eisterer, M. Zehetmayer, and H. W. Weber, Phys. Rev. Lett. **90**, 247002 (2003).
 - ¹⁶ C. P. Bean and J. D. Livingston, Phys. Rev. Lett. **12**, 14 (1964).
 - ¹⁷ V. L. Ginzburg, Zh. Eksper. Teor. Fiz. **23**, 236 (1952).
 - ¹⁸ C. Caroli, P. G. de Gennes, and J. Matricon, Physik Kondensierten Materie **1**, 176 (1966).
 - ¹⁹ L. P. Gor'kov and T. K. Melik-Barkhudarov, Zh. Eksper. Teor. Fiz. **45**, 1493 (1964).
 - ²⁰ D. R. Tilley, Proceedings of the Physical Society **86**, 289 (1965).
 - ²¹ P. C. Hohenberg and N. R. Werthamer, Phys. Rev. **153**, 493 (1967).
 - ²² J. Daams and J. Carbotte, Journal of Low Temperature Physics **43**, 263 (1981).
 - ²³ V. Kogan and S. Budko, Physica C: Superconductivity **385**, 131 (2003).
 - ²⁴ For instance, Blatter et al. recognized that by making a change of coordinates and redefining the magnetic field and vector potential, one could make isotropic the derivative term by introducing anisotropy in the magnetic energy terms^{13,44}.
 - ²⁵ V. G. Kogan and R. Prozorov, Phys. Rev. B **90**, 054516 (2014).
 - ²⁶ Y. Koike, H. Suematsu, K. Higuchi, and S. Tanuma, Physica B+C **99**, 503 (1980).
 - ²⁷ P. Mann, M. Sutherland, C. Bergemann, S. Yonezawa, and Y. Maeno, Physica C: Superconductivity and its Applications **460462**, Part 1, 538 (2007), proceedings of the 8th International Conference on Materials and Mechanisms of Superconductivity and High Temperature Superconductors M2S-HTSC {VIII}.
 - ²⁸ P. de Trey, S. Gyax, and J.-P. Jan, Journal of Low Temperature Physics **11**, 421 (1973).
 - ²⁹ X. H. Chen, Y. Y. Xue, R. L. Meng, and C. W. Chu, Phys. Rev. B **64**, 172501 (2001).
 - ³⁰ S. Stintzing and W. Zwerger, Phys. Rev. B **56**, 9004 (1997).
 - ³¹ L. Tewordt, Phys. Rev. **132**, 595 (1963).
 - ³² N. R. Werthamer, Phys. Rev. **132**, 663 (1963).
 - ³³ M. Angst, R. Puzniak, A. Wisniewski, J. Jun, S. M. Kazakov, J. Karpinski, J. Roos, and H. Keller, Phys. Rev. Lett. **88**, 167004 (2002).
 - ³⁴ S. L. Bud'ko and P. C. Canfield, Phys. Rev. B **65**, 212501 (2002).
 - ³⁵ R. Cubitt, S. Levett, S. L. Bud'ko, N. E. Anderson, and P. C. Canfield, Phys. Rev. Lett. **90**, 157002 (2003).
 - ³⁶ R. Cubitt, M. R. Eskildsen, C. D. Dewhurst, J. Jun, S. M. Kazakov, and J. Karpinski, Phys. Rev. Lett. **91**, 047002 (2003).
 - ³⁷ L. Lyard, P. Szabó, T. Klein, J. Marcus, C. Marcenat, K. H. Kim, B. W. Kang, H. S. Lee, and S. I. Lee, Phys. Rev. Lett. **92**, 057001 (2004).
 - ³⁸ S. L. Bud'ko and P. C. Canfield, Physica C: Superconductivity and its Applications **514**, 142 (2015), superconducting Materials: Conventional, Unconventional and Undetermined.
 - ³⁹ V. G. Kogan, Phys. Rev. B **66**, 020509 (2002).
 - ⁴⁰ V. G. Kogan, Phys. Rev. Lett. **89**, 237005 (2002).
 - ⁴¹ Here we assume that the anisotropy $\gamma_\xi = \xi_a/\xi_c$ is equivalent to the anisotropy of the upper-critical field $\gamma_H = H_{c2,a}/H_{c2,c}$, as in the work of Ref.⁴⁰.
 - ⁴² Y. Wang, T. Plackowski, and A. Junod, Physica C: Superconductivity **355**, 179 (2001).
 - ⁴³ H. Padamsee, *RF Superconductivity: Science, Technology, and Applications* (WILEY-VCH Verlag GmbH & Co. KGaA, Weinheim, 2009).
 - ⁴⁴ G. Blatter, V. B. Geshkenbein, and A. I. Larkin, Phys. Rev. Lett. **68**, 875 (1992).