

This is the accepted manuscript made available via CHORUS. The article has been published as:

Phase stability and large in-plane resistivity anisotropy in
the 112-type iron-based superconductor

$\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$

Chang-Jong Kang, Turan Birol, and Gabriel Kotliar

Phys. Rev. B **95**, 014511 — Published 17 January 2017

DOI: [10.1103/PhysRevB.95.014511](https://doi.org/10.1103/PhysRevB.95.014511)

Phase stability and large in-plane resistivity anisotropy in the 112-type iron-based superconductor $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$

Chang-Jong Kang

Department of Physics and Astronomy, Rutgers University, Piscataway, New Jersey 08854, USA

Turan Birol

Department of Physics and Astronomy, Rutgers University, Piscataway, New Jersey 08854, USA and

*Department of Chemical Engineering and Materials Science,
University of Minnesota, Minneapolis, Minnesota 55455, USA*

Gabriel Kotliar

Department of Physics and Astronomy, Rutgers University, Piscataway, New Jersey 08854, USA and

*Condensed Matter Physics and Materials Science Department,
Brookhaven National Laboratory, Upton, New York 11973, USA*

(Dated: December 20, 2016)

The recently discovered high- T_c superconductor $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ is a unique compound not only because of its low symmetry crystal structure, but also because of its electronic structure which hosts Dirac-like metallic bands resulting from (spacer) zig-zag As chains. We present a comprehensive first principles theoretical study of the electronic and crystal structures of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. After discussing the connection between the crystal structure of the 112 family, which $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ is a member of, with the other known structures of Fe pnictide superconductors, we check the thermodynamic phase stability of CaFeAs_2 , and similar hypothetical compounds SrFeAs_2 and BaFeAs_2 which, we find, are slightly higher in energy. We calculate the optical conductivity of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ using the DFT + DMFT method, and predict a large in-plane resistivity anisotropy in the normal phase, which does not originate from electronic nematicity, but is enhanced by the electronic correlations. In particular, we predict a 0.34 eV peak in the yy component of the optical conductivity of the 30% La doped compound, which corresponds to coherent interband transitions within a fast-dispersing band arising from the zig-zag As-chains which are unique to this compound. We also study the Landau free energy for $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ including the order parameter relevant for the nematic transition and find that the free energy does not have any extra terms that could induce ferro-orbital order. This explains why the presence of As chains does not broaden the nematic transition in $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$.

PACS numbers:

INTRODUCTION

The discovery of high temperature superconductivity in the iron based materials [1] triggered a large number of investigations [2–5]. The basic ingredient of this class of materials is square nets of iron tetrahedrally coordinated by a pnictide or a chalcogenide. By now this ingredient has been realized in multiple prototypical structures, such as the original realization in the 1111 structure, the 111 structure of LiFeAs , the 11 structure such as that of FeSe , and the 122 structure such as in BaFe_2As_2 .

The possibility of superconductivity in iron based compounds with a 112 structure was suggested based on electronic structure calculations in Ref. [6], where it was pointed out that this structure would support metallic spacer layers which could aid in elucidating the mechanism for high temperature superconductivity. Attempts to synthesize iron pnictide compounds in this structure were not originally successful, but new Mn based materials in this structure were found [7, 8] and it was observed theoretically [7] and experimentally [8–11] that the spacer layers exhibit Dirac cones [12]. Recently, Fe

superconductors in the 112 structure were synthesized, $(\text{Ca},\text{Pr})\text{FeAs}_2$ [13], and $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ [14].

These materials form in a structure where the As in the CaAs layers are distorted in zig zag chains, i.e. the space group $P2_1$ or $P2_1/m$ rather than the originally assumed tetragonal structure [13, 14]. Second harmonic generation experiments confirmed the space group $P2_1$ for La doped compounds [15]. More recently, theoretical studies focusing on the spacer layers determined that the As p_x and p_y orbitals are responsible for the Dirac cones, and the spin orbit coupling can open a gap and induce topological phases on these layers, suggesting the 112 compounds as prime candidates for proximity induced topological superconductivity [16, 17].

These works motivate us to revisit the early theoretical predictions in the light of these experimental developments to address some basic questions. (1) The original density functional theory (DFT) calculations focused on the FeAs layers only. A natural question is what would be the result of a full relaxation of the crystal structure? (2) Parent compounds such as CaFeAs_2 have so far not been synthesized, and a rare earth is needed to facilitate

the synthesis [18]. Raising the question of relative stability of these compounds, what is the role of the rare earth like La in stabilizing the structure? (3) Photoemission experiments, confirmed the theoretical prediction of the existence of metallic spacer layers (with Fermi pockets of As p_z and Ca character, in addition to the Dirac cones) [19, 20], however, it is not clear from them what the role of doping is, since in the 112 structure both the CaAs and the FeAs layers can accommodate carriers. (4) It would also be useful to establish consequences of the anisotropy introduced by the formation of the CaAs chains, which should be visible in the optical response, and elucidate how this anisotropy couples to the nematic order parameter whose origin is a subject of intensive discussion. In this paper we answer these questions and determine how this iron pnictide fits with the other families already studied within dynamical mean-field theory (DFT+eDMFT). We conclude that in spite of the strong anisotropy induced by the As zig zag chains, the 112 compounds are very similar to the rest of the iron pnictide superconductors, indicating the superconductivity resides essentially on the FeAs layers unaffected by spacers.

In this work, we (1) present a detailed explanation of the crystal structure of CaFeAs_2 , and elucidate the connection of it with other pnictide superconductors, (2) check the phase stability of CaFeAs_2 , as well as SrFeAs_2 and BaFeAs_2 at the level of DFT by finding the optimum first principles structure via an evolutionary structure search, and then building the convex hull, (3) systematically study the electronic structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ using state of the art DFT + embedded DMFT (eDMFT) to understand the effect of carrier doping, and (4) for the first time predict the optical conductivity of this compound at the level of DFT + eDMFT. We show that the presence of metallic As chains on the spacer layer gives rise to a strong in-plane anisotropy even at high temperatures, distinct from that driven by the nematic transition. Comparing DFT and eDMFT results, we further show that this anisotropy is enhanced by the electronic correlations.

METHODS

DFT calculations are performed using the projector augmented wave method as implemented in the Vienna Ab Initio Simulation Package (VASP) [21–24]. A plane wave cutoff of 500 eV and the generalized gradient approximation of Perdew-Burke-Ernzerhof (PBE) are used [25].

To obtain the lowest energy structures, an *ab initio* evolutionary search algorithm [26] as implemented in the USPEX package [27] is used in conjunction with VASP. In these calculations, initial structures are randomly generated and the next generations are generated using mutations of the previous ones and new random

structures. Once the stable structural phases are obtained from the evolutionary search, corresponding formation energies are calculated with a dense Monkhorst-Pack sampling grid with a resolution of $2\pi \times 0.02\text{\AA}^{-1}$ for the k -space integrations.

For the phonon dispersion calculations, the PHONOPY code [28] is used to build the supercells, and to find the minimum number of ionic displacements required. The *direct method* is used to calculate the forces in these supercells, as opposed to the Density Functional Perturbation Theory. The force constants and the dynamical matrices are obtained from the Hellmann-Feynman forces in these $(2 \times 2 \times 2)$ supercells (16 formula units). A $6 \times 6 \times 2$ k -point mesh is used in these supercell calculations.

To treat correlation effects in the $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ compounds, the fully charge self-consistent scheme DFT + eDMFT [29, 30] (for a review see Ref. [31]) is used as implemented in Ref. [32, 33] with the hybridization expansion continuous-time quantum Monte Carlo [34] as the impurity solver as implemented in Ref. [35]. We use the Coulomb interaction $U = 5.0$ eV and the Hund's coupling $J = 0.8$ eV, which were shown to describe $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ compounds [19, 36]. The temperature is set to $T = 116$ K. The experimental crystal structure determined by X-ray diffraction [14] is used. The virtual crystal approximation is adopted to investigate the electronic structure of the La doped compounds.

CRYSTAL STRUCTURE OF CaFeAs_2 AND ITS CONNECTION TO OTHER PNICTIDES

In this section, we explain the details of the crystal structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ and its connection to the 1111 family of superconductors with the ZrCuSiAs -type

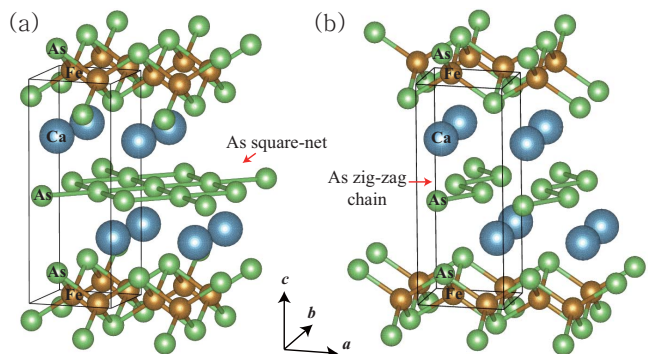
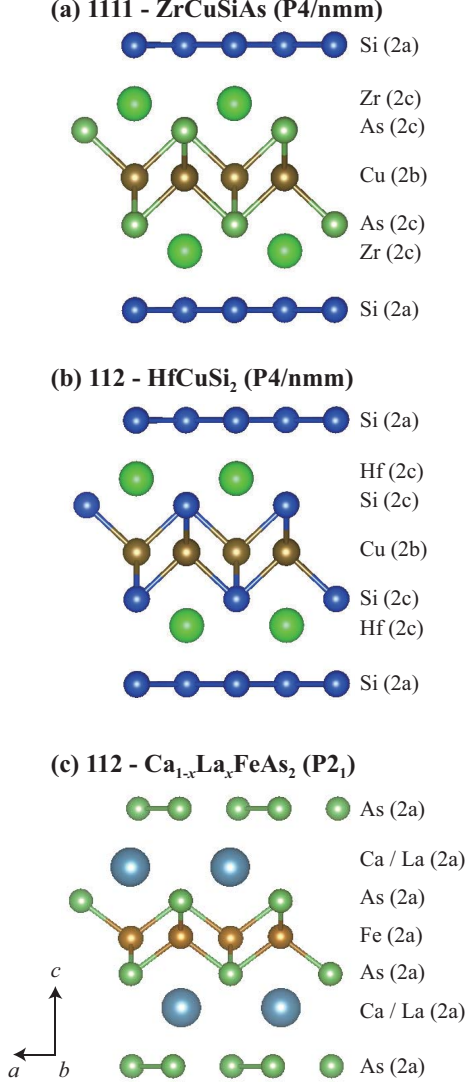


FIG. 1: (Color Online) (a) Tetragonal crystal structure with $P4/nmm$ of CaFeAs_2 . (b) Monoclinic crystal structure with $P2_1/m$ of CaFeAs_2 . The black lines represent the unit cell in both (a) and (b). The As square-net is clearly shown in (a), whereas, the zig-zag As chain appears in (b). Both spacers, As square-net and the zig-zag As chain, are metallic.

	Space Group	Ion - Wyckoff Position			
ZrCuSiAs	P4/nmm (#129)	Zr - 2c	Cu - 2b	Si - 2a	As - 2c
LaFePO	P4/nmm (#129)	La - 2c	Fe - 2b	O - 2a	P - 2c
HfCuSi ₂	P4/nmm (#129)	Hf - 2c	Cu - 2b	Si - 2a	Si - 2c
Ca _{1-x} La _x FeAs ₂	P2 ₁ (#4)	Ca/La - 2a	Fe - 2a	As - 2a	As - 2a
h-CaFeAs ₂	P4/nmm (#129)	Ca - 2c	Fe - 2b	As - 2a	As - 2c

TABLE I: Structural information on iron 1111 and 112 phase systems.

FIG. 2: Crystal structures related to iron 1111 and 112 phase systems. Crystal structures of (a) ZrCuSiAs ($P4/nmm$), (b) HfCuSi₂ ($P4/nmm$), and (c) Ca_{1-x}La_xFeAs₂ ($P2_1$).

structure (see Fig. 2 and Table I). The ZrCuSiAs-type structure has the simple tetragonal space group $P4/nmm$ (number #129) with two formula units per primitive unit cell. In the superconducting pnictides with this structure, the Fe ion occupies the same Wyckoff position as Cu in ZrCuSiAs, 2b ($1/4, 3/4, 1/2$) with no internal parameter, and forms a layer with the pnictogen in the

same Wyckoff position as As in ZrCuSiAs, 2c ($1/4, 1/4, z$). The internal parameter z determines the pnictogen height, which is shown to be sensitively linked to superconducting T_c in these compounds (Fig. 14). In this layer, the Fe cations form a square plane with pnictogen ions above and below. The pnictogen ions form edge-sharing tetrahedra around the Fe ions. The other two ions are a cation on the 2c position and an anion on the 2a ($3/4, 1/4, 0$) position. While in certain compounds these two ions can form a tightly bound layer together, depending on the particular atoms there may or may not be any significant bonding between them, and this gives rise to a wide range of internal parameter z for the cation on the 2c position.

Having the same anions on both 2c and the 2a positions in the ZrCuSiAs-type structure gives rise to the HfCuSi₂-type structure. Note that in this structure, while both anions (Si) are the same, their environments are significantly different. The 2a position has both atoms in one unit cell on the same layer (with coordinates ($3/4, 1/4, 0$) and ($1/4, 3/4, 0$)), but the 2c position corresponds to atoms on two separate layers (with coordinates ($1/4, 1/4, z$) and ($3/4, 3/4, -z$)) with the Fe (Cu in HfCuSi₂) layer in between. The anions on the 2a site form a dense square net, and often have strong covalent bonds between themselves, whereas the anions on the 2c site hybridize with the transition metals on the 2b site. Compounds with the HfCuSi₂-type structure has been studied extensively (for example see [37, 38]), and hypothetical BaFeAs₂ and BaFeSb₂ with this structure has been proposed to be high T_c superconductors if synthesized [6]. The physics that emerges from this square net of covalently bound anions has drawn particular attention in the literature. It has been shown that this layer can support conventional superconductivity [39], as well as Weyl semimetallic phases [40]. The wide bands that are formed from the p orbitals of the main-block elements on the square net also commonly give rise to Peierls type instabilities that lead to the distortions of the crystal structure [41], which have been studied in detail in various compounds with a similar structure, including various arsenides [42–45]. These studies show that the distortions on the As layers can be tuned by both doping and pressure, and studying the similar distortion present in CaFeAs₂ and its effect on superconductivity can be important.

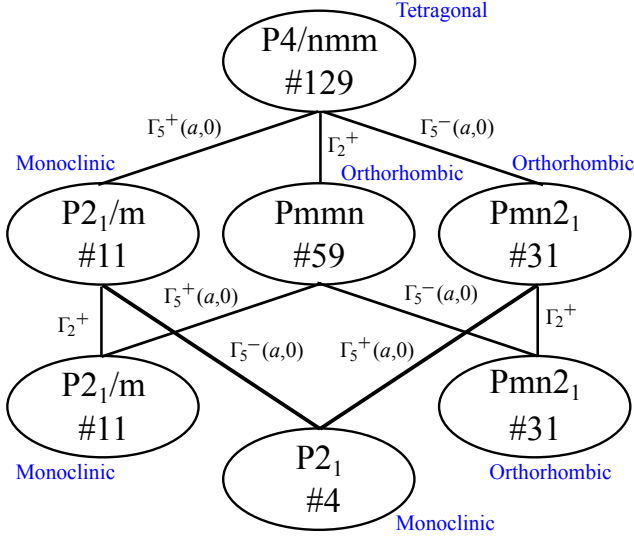


FIG. 3: (Color Online) Group table showing the relevant structural phase transitions between the tetragonal $P4/nmm$ and the monoclinic $P2_1$ structures. The space group numbers are also shown below the Hermann-Mauguin notation. Other possible structural phase transitions are also shown with the corresponding symmetry of the lattice distortion.

Difference between the structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ and the HfCuSi_2 -type structure

There are two very similar structures reported in the literature for lanthanide doped CaFeAs_2 : A noncentrosymmetric structure with space group $P2_1$ (number #4) and a centrosymmetric structure with space group $P2_1/m$ (number #11). (The former structure is reported, for example, for the La doped compound in Ref. [14], and the latter is reported, for example, for the Pr doped compound in Ref. [13]. While second harmonic generation verifies the lack of inversion symmetry in the La doped compound [15], no similar study exists for the Pr doped compound.) There is a group-subgroup relationship between these two space groups, and the only difference between the structures is a polar distortion, discussed at the end of this subsection.

The main feature that differentiates the structure of $\text{Ca}_{1-x}\text{RE}_x\text{FeAs}_2$ from the HfCuSi_2 -type structure is a Peierls type distortion on the As square net as well (Fig. 5). This distortion is at the Γ point of the unit cell and transforms as the Γ_5^+ irreducible representation (irrep) (Fig. 4 (d)). (Throughout this study, we label the irreps corresponding to structural distortions using their labels for the space group #129.) This distortion form zig-zag chains from the As atoms, and decreases the symmetry of the crystal significantly. (Even though this distortion also displaces the Fe atoms to form Fe-Fe chains in a similar fashion, and the Ca ions are also displaced, the amplitude of these displacements, though nonzero by

symmetry, are found to be very small in the experimental structure and we hence ignore them.) The Γ_5^+ distortion by itself breaks the four-fold rotational symmetry, and renders $\text{Ca}_{1-x}\text{RE}_x\text{FeAs}_2$ unique in the sense that it is the only pnictide superconductor with broken four-fold rotational symmetry even above the nematic transition. (The effect of this symmetry breaking (or lack thereof) on the nematic transition will be discussed latter.)

The structure that is obtained from the high symmetry reference #129 by freezing in the Γ_5^+ has the space group $P2_1/m$ (#11). This symmetry is low enough that a distortion that transforms as another irrep, Γ_2^+ (Fig. 4(b)), can also have a nonzero amplitude without reducing the symmetry any further. This irrep involves Fe and As (which is in the CaAs layer) layers' rumpling: For example the two Fe ions in the same unit cell are displaced by $\sim 0.01\text{\AA}$ in opposite directions along the c axis. While in general it might be important that the Fe ions no longer form a perfect plane, this rumpling is so small that it can safely be ignored. The small amplitude of this rumpling also suggests that there is no driving force for the

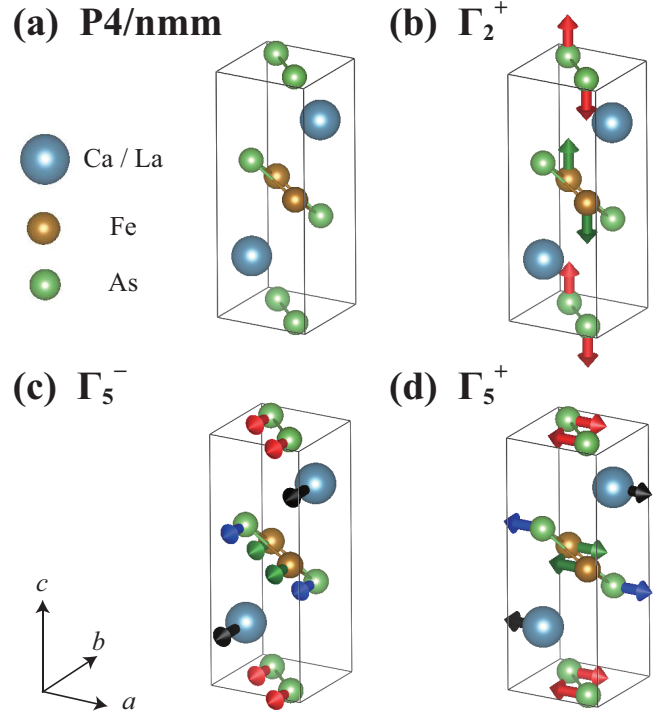


FIG. 4: (Color Online) The sketch of the three different distortions present in the structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ with respect to the reference HfCuSi_2 -type structure with space group #129. (a) The structure sketched with the Fe layer in the center. (b) The Γ_2^+ irrep involves a rumpling of the Fe and the As (which is in the CaAs layer) layers. (c) The Γ_5^- irrep is the in-plane polar irrep that involves a displacement of all the ions along the same direction. (d) The Γ_5^+ irrep involves pair of ions moving opposite to each other in the same plane. This irrep is responsible of the formaion of the As chains.

Γ_2^+ distortion, but it is there only due to the low symmetry induced by Γ_5^+ , very much like a secondary order parameter in a structural phase transition.

The structure that is obtained by the Γ_2^+ and Γ_5^+ distortions starting from the tetragonal HfCuSi_2 -like reference structure is the centrosymmetric structure observed for some of the rare earth doped CaFeAs_2 compounds. But, as mentioned before, some of these compounds actually have even lower symmetries. The irrep that corresponds to the other structural distortion present in these structures is the in-plane polar irrep Γ_5^- (Fig. 4(c)). This distortion is a overall displacement of all the atoms parallel (or antiparallel) to each other and breaks the inversion symmetry. While, by symmetry, every ion is displaced by this irrep, a symmetry mode amplitude analysis of the experimental structure indicates that this displacement is more than 80% on the Ca layer, i.e. it is the Ca (and the La atoms) that are displaced by far the most according to this irrep. This is a very interesting observation given the fact that Ca is by far the most electropositive element in this compound and has a closed shell configuration, and as a result, is not chemically active and should not be the driving force of a polar distortion. It is neither in a particular coordination geometry that is known to give rise to some type of geometric-ferroelectricity, which would be robust even though the compound is conducting [46, 47].

Given the fact that this polar distortion is quite small on the Fe and As layers, we do not analyse its effect on the electronic structure in detail, and consider a complete study of the driving force behind it beyond the scope of this work. However, in passing, we note that the evolutionary structure search we performed for CaFeAs_2 , discussed in the following sections, does not predict a polar ground state. Given the electropositivity of La, it would be surprising if it was the driving ion for polarization in this compound. The only possibility left seems to be that the ordering of the La ions in the Ca layer gives rise to the polar distortion. This possibility is consistent with the fact that the ionic radius of Pr is closer to Ca than La and therefore it is less likely to cause cation ordering when substituting for Ca, however, these differences are all very small and it is not possible to go beyond the level of speculation at this point.

Lack of tetragonal symmetry and relation to electronic nematicity

Figure 3 shows various irreducible representations that correspond to structural distortions from the tetragonal $P4/nmm$ structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. Even though there are orthorhombic phases listed in this figure, these phases are different from (i.e. they belong to different space groups) the orthorhombic phases realized below the structural transitions in, for example, LaFeAsO , where the transition is from the tetragonal $P4/nmm$ to the or-

thorhombic $Cmma$ (# 67) structure [48]. Similarly, in the 122 compounds that have a tetragonal structure with the ThCr_2Si_2 type (space group $Fmmm$) at high temperature, an electronic nematic phase breaks the four-fold rotational symmetry and hence induces the structural transition to an orthorhombic space group [49–51]. In the case of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$, the monoclinic structure is stable up to at least 450 K [14], and no transition to the tetragonal phase is reported. Given the one order of magnitude lower critical temperature of the nematic transition in other iron pnictides, the monoclinic phase in CaFeAs_2 certainly does not have a nematic origin. As we discussed before, it is most likely due to a Peierls-like mechanism, active on the As layer that forms the zig-zag chains.

$\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ also undergoes a structural transition near its antiferromagnetic ordering temperature [19]. This transition is from monoclinic to triclinic symmetry. However, the argument for electronic nematicity is not straightforward for this transition either because the four-fold symmetry is already broken above this transition, in the monoclinic structure. We address this problem in the final section and show that the free energy expression for CaFeAs_2 does not contain any terms that

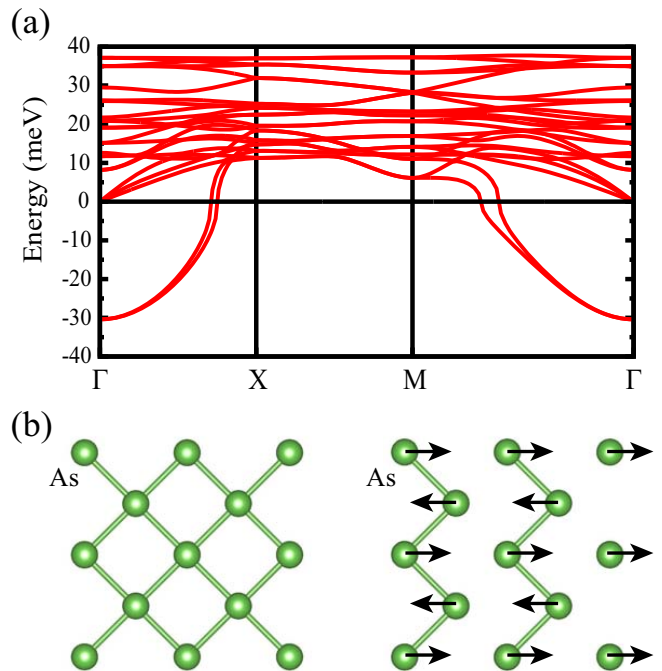


FIG. 5: (Color Online) (a) Phonon dispersion curve for the hypothetical tetragonal structure with $P4/nmm$ of CaFeAs_2 . The gamma-point phonon instability is clearly shown, and the unstable phonon bands have the As square-net character. (b) The corresponding unstable phonon normal mode. The main lattice distortion occurs in the As square-net. Black arrows represent the direction of the lattice distortion. The As square-net is changed into the zig-zag As chain.

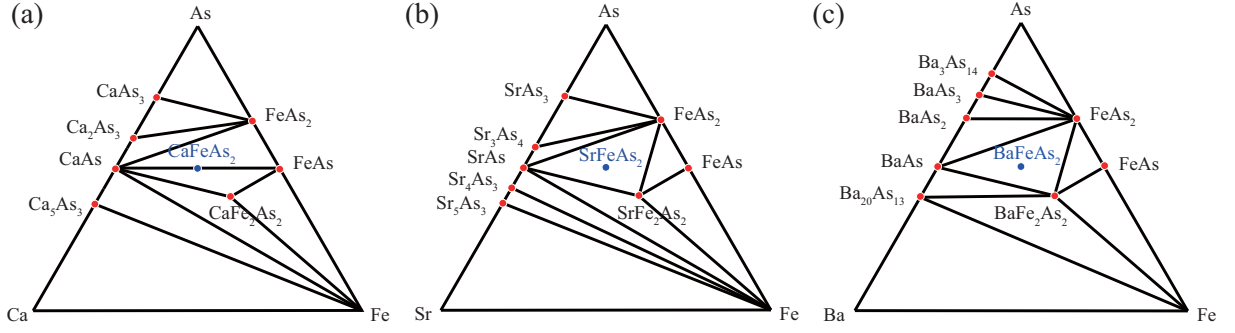


FIG. 6: (Color Online) Ternary phase diagram for (a) CaFeAs_2 , (b) SrFeAs_2 , and (c) BaFeAs_2 . Red and blue dots represent thermodynamically stable and unstable phases, respectively. CaFeAs_2 , SrFeAs_2 , and BaFeAs_2 are put above the convex-hull, and the energies above hull are 13 meV/atom, 24 meV/atom, and 17 meV/atom, respectively.

can give rise to a different character of the nematic transition than the other iron pnictide superconductors. This justifies the studies such as references [52–54] which compare the phase diagram of this compound with other iron pnictide compounds.

FIRST PRINCIPLES RESULTS

Crystal Structure of CaFeAs_2

The hypothetical, tetragonal high-symmetry phase of CaFeAs_2 has the $P4/nmm$ symmetry (Fig. 1(a)), and it is the same structure as the one proposed by Shim *et al.* [6] for the Ba compounds with the same stoichiometry. In order to check the stability of this structure with respect to structural transitions, we calculated its phonon frequencies with DFT. We present the resulting phonon dispersion curves in Figure 5(a). There is a single, but two-fold degenerate Γ -point unstable phonon, which is the *chain-forming* instability that transforms as Γ_5^+ . There is no unstable Γ_2^+ mode, consistent with our claim in the previous section that this irrep exists in the lower symmetry structure only because of its coupling with the Γ_5^+ and not because there is a separate driving force for this distortion.

The evolutionary structure prediction performed by USPEX predicts the lowest energy crystal structure to have the $P2_1/m$ symmetry (Fig. 1(b)). The predicted lattice constants are $a = 3.962\text{\AA}$, $b = 3.896\text{\AA}$, $c = 10.057\text{\AA}$, and $\beta = 91.135^\circ$ ($\alpha = \gamma = 90^\circ$). This result is based on the spin non-polarized GGA functional. Spin polarized GGA and GGA + U ($U = 2, 4$ eV) schemes combined with USPEX give the same space group $P2_1/m$ with the similar (but, of course, different) lattice constants. Note that the existence of the zig-zag As chains is also captured by the evolutionary structure search, but the predicted structure is centrosymmetric, both in line with the phonon calculations.

The experimental structural data for the La-doped

compound ($\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$) measured by X-ray diffraction has the monoclinic $P2_1$ symmetry with the lattice constants are $a = 3.94710\text{\AA}$, $b = 3.87240\text{\AA}$, $c = 10.3210\text{\AA}$, and $\beta = 91.415^\circ$ ($\alpha = \gamma = 90^\circ$) [14]. The other X-ray diffraction experiment on Pr-doped compounds ($\text{Ca}_{1-x}\text{Pr}_x\text{FeAs}_2$) were reported to have the monoclinic structure with $P2_1/m$ having the inversion symmetry [13]. (The measured lattice constants are $a = 3.9163\text{\AA}$, $b = 3.8953\text{\AA}$, $c = 10.311\text{\AA}$, and $\beta = 90.788^\circ$.) The strong optical second-harmonic response was recently observed in $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$, clearly implying that the crystal does not have the inversion symmetry [15], but similar data does not exist for $\text{Ca}_{1-x}\text{Pr}_x\text{FeAs}_2$ to the best of our knowledge. Hence, the first principles predicted structure is quite similar to the experimental structure, except that it does not capture the possible inversion symmetry breaking.

Thermodynamic stability and convex hull construction

Even though the methods we used so far can predict what the crystal structure of CaFeAs_2 will be *if it forms*, they do not address the possibility of the constituent elements phase separating into different compounds. In order to check the phase stability of CaFeAs_2 , we build the convex-hull for all known binary and ternary compounds formed by these elements. The convex-hull construction evaluates the stability of a given compound against any linear combination of possible compounds effectively [55–59]. Hence, it is possible to determine whether a given compound is stable or prefers to decompose to other compounds (within the accuracy of DFT and the approximations to the exchange correlation functional). We show in Fig. 6(a) the Ca-Fe-As phase diagram constructed from the calculated GGA(PBE) total energy of all relevant phases listed in the materials database [60]. Since the additional symmetry breaking due to magnetic order (for example, antiferromagnetic order) is not considered in

the structural prediction performed by USPEX, we take into account stripe magnetic order in the predicted monoclinic $P2_1/m$ structure of CaFeAs_2 . Due to the stripe magnetic order, the monoclinic $P2_1/m$ structure is further relaxed into a triclinic $P\bar{1}$ structure having lower symmetry. The magnetic moment is $1.95 \mu_B/\text{Fe}$ and the total energy is lower by 19.50 meV/atom. CaFeAs_2 with the stripe magnetic order is computed to be 13 meV/atom above the convex hull, that is, it has a decomposition energy of 13 meV/atom to CaAs and FeAs phases. Reference [61] has systematically studied the error of DFT in similar predictions, and found that the errors can be modeled by a normal distribution with a mean close to zero and a standard deviation of 24 meV/atom. Using this error bar, our calculation indicates that the undoped CaFeAs_2 compound is, within the error bar, on the stability boundary. It is possible that doping it with rare earth ions helps its stability.

Apart from a possible energetic gain, an effect of La doping would be an entropic gain if there is no ordering of the La atoms. (A complete ordering of La is unlikely because of its similar ionic radius to Ca.) The corresponding free energy is $-TS = -k_B T \ln N$, where T , S , k_B , and N are temperature, entropy, Boltzmann constant, and configuration number, respectively. For example, in order to simulate the phase stability of 25% La-doped compounds, we used a $2 \times 2 \times 1$ supercell. This supercell contains 8 Ca atoms, and there are $\binom{8}{2} = 28$ configurations for substituting 2 La atoms for Ca. Hence, we set the configuration number N as 28 and use $T = 1000$ K, which is an estimate of synthesis temperature [18]. The resulting entropy contribution for the La-doped compound is about -9 meV/atom. This could render the compound marginally stable according to our calculations, however, a more detailed study is necessary to address the energetics of doping in this compound.

Hypothetical SrFeAs_2 and BaFeAs_2 compounds

To the best of our knowledge, there exists no report of the synthesis of the Sr or Ba variants of CaFeAs_2 even with doping. This is surprising given that Sr usually easily substitutes for Ca, a fact that is supported by data-mining studies of existing crystal structures [62]. In order to see if it is possible, in theory, to synthesize these compounds, and whether they would have a crystal structure that is favorable for pnictide superconductivity, we also investigate the ground state structure for Sr and Ba compounds using the evolutionary structure search method with several schemes for the DFT part, such as spin non-polarized GGA, spin polarized GGA, and GGA + U schemes. For the Sr compound, the lowest energy crystal structure for the spin non-polarized GGA functional is the monoclinic structure with the space group $P2_1/m$, which is the same as the Ca compound. This

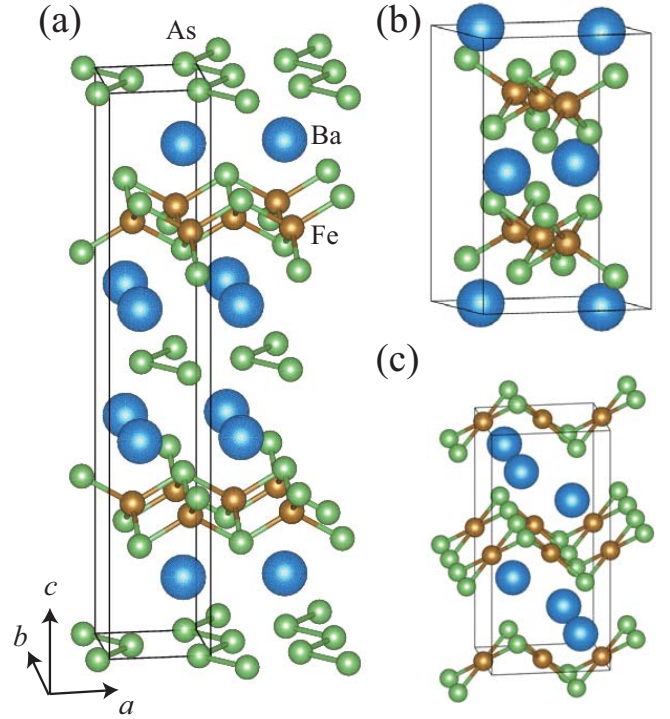


FIG. 7: (Color Online) Crystal structures of BaFeAs_2 having the lowest energy based on (a) spin non-polarized GGA, (b) spin polarized GGA, and (c) GGA + U ($U = 2, 4$ eV) schemes. All of them are orthorhombic and their space groups are $Im2$ (# 44), $Cmma$ (# 67), and $Cmcm$ (# 63), respectively.

monoclinic structure with $P2_1/m$ is robust with other spin polarized GGA and GGA + U schemes. Considering the stripe magnetic order in the monoclinic $P2_1/m$ structure of SrFeAs_2 , the triclinic $P\bar{1}$ structure with the magnetic moment of $2.09 \mu_B/\text{Fe}$ is obtained. The total electronic energy is lower by 23.08 meV/atom compared to the monoclinic $P2_1/m$ structure with no magnetic order (the nonmagnetic state). As shown in Fig. 6(b), SrFeAs_2 with the stripe magnetic order is unstable with 24 meV/atom above the convex hull. This energy above the convex hull is higher than that of the CaFeAs_2 compound, which might explain why the Sr compound is not synthesized so far.

The situation for the Ba compound is quite different, and different choices for the DFT scheme gives different results for the preferred structure. The evolutionary structure search with the spin non-polarized GGA functional gives the orthorhombic structure with the space group $Im2$ (# 44) (Fig. 7(a)) as the ground state structure. The obtained lattice constants are $a = 4.059 \text{ \AA}$, $b = 3.984 \text{ \AA}$, $c = 23.161 \text{ \AA}$, and two FeAs layers and As zig-zag chains are contained in the unit cell. This orthorhombic structure does not have inversion symmetry. Evolutionary search using the spin polarized GGA functional gives a structure that is orthorhombic and has the

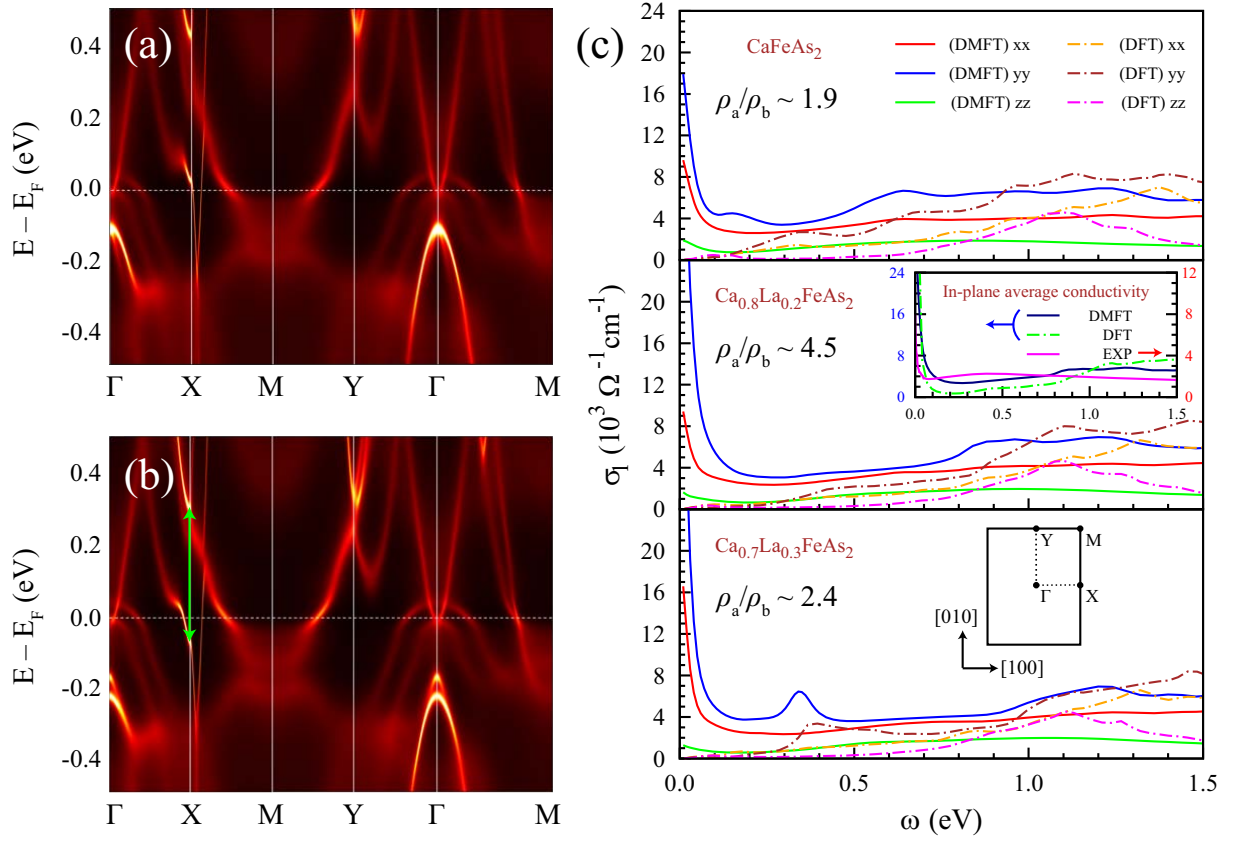


FIG. 8: (Color Online) (a) $A(\mathbf{k}, \omega)$ of $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ at $T = 116\text{K}$ as computed by DFT + eDMFT. The Brillouin zone is shown in inset in the bottom of (c). (b) $A(\mathbf{k}, \omega)$ of $\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$ at $T = 116\text{K}$ as computed by DFT + eDMFT. (The $A(\mathbf{k}, \omega)$ of the 30% doped compound is also presented in Ref. [19] with orbital projection onto the in-plane p orbitals of As ions forming the chains.) (c) Optical conductivities within DFT + eDMFT method of CaFeAs_2 (top), $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ (middle), and $\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$ (bottom). Optical conductivities (interband contributions only) within DFT method are also shown for comparison. (Intraband transitions within DFT give a delta function-like contribution at the zero frequency.) The values of in-plane resistivity anisotropy ρ_a/ρ_b correspond to the eDMFT results. The in-plane average conductivity is shown in inset for comparison between eDMFT, DFT, and experiment. We used 0.01 eV for the broadening of intraband contributions in DFT. Experiment data is for $\text{Ca}_{0.77}\text{Nd}_{0.23}\text{FeAs}_2$ at $T = 125\text{K}$, and digitized from Ref. [63]. For $\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$, there is a low-energy peak of 0.34 eV in the optical conductivity, which corresponds to the transition marked by the green arrow in (b).

space group $Cmma$ (# 67). Its lattice constants are $a = 6.617\text{\AA}$, $b = 5.977\text{\AA}$, $c = 10.316\text{\AA}$ (Fig. 7(b)). In this orthorhombic structure, Fe atom is surrounded by As anions tetrahedrally, however these tetrahedra form chains instead of a 2D FeAs layer, which is not a structure that would favor high T_c superconductivity even if it actually formed. Finally, the evolutionary structure search with GGA + U ($U = 2, 4\text{ eV}$) gives the orthorhombic structure with space group $Cmcm$ (# 63) (Fig. 7(c)) as the lowest energy structure. The lattice constants of this structure are $a = 6.086\text{\AA}$, $b = 5.501\text{\AA}$, $c = 12.621\text{\AA}$. Each Fe ion is again coordinated by 4 As ions, but the coordination geometry is square rather than a tetrahedron. This is not a commonly observed geometry for Fe, and this structure, even if it is synthesized, would surely not favor high temperature superconductivity.

We consider the various possible magnetic orderings among several predicted structures in BaFeAs_2 and cal-

culate the total electronic energies. Among them, the antiferromagnetic order (with the magnetic moment of $2.17\text{ }\mu_B/\text{Fe}$) in the orthorhombic $Imm2$ (#44) has the lowest energy. This antiferromagnetic order has the spins aligned the same way as a single stripe magnetic order within the ab plane, but they are ferromagnetic along the c axis. Therefore, this order is different from the single stripe magnetic order exhibited in most iron pnictide superconductors, where the spins are ordered in an antiferromagnetic fashion along the c -axis as well. The inter FeAs layer distance in the orthorhombic $Imm2$ is $11.55\text{ }\text{\AA}$, so that the quite large inter-layer distance might affect the inter-layer magnetic ordering.

We construct the convex hull for BaFeAs_2 compound with the stripe magnetic order. As shown in Fig. 6(c), BaFeAs_2 compound is unstable with 17 meV/atom above the convex hull. The energy above the hull is somewhat higher than that of CaFeAs_2 , however, it is quite re-

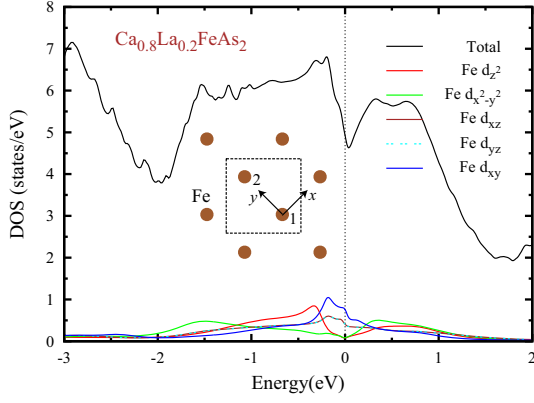


FIG. 9: (Color Online) DOS of $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$. Total and projected DOS of Fe 3d orbitals calculated by DFT + eDMFT at $T = 116$ K. The inset shows the direction of local axes for the projected DOS of Fe 3d orbitals. Our choice of Cartesian axes are 45 degrees rotated with respect to the $\langle 100 \rangle$ axes. The occupations of Fe d_{xz} and d_{yz} are same, giving the zero orbital polarization.

duced compared to that of SrFeAs_2 . We predict that the rare-earth doped BaFeAs_2 might be possible to synthesize considering that the rare-earth doping makes Fe 112 phase be more stable (for example, the energetic gain from entropy as discussed before). From Fig. 6, we can get some information about mixtures of the essential compounds to grow the target material. Since the reaction $\text{CaAs} + \text{FeAs} \rightarrow \text{CaFeAs}_2$ has the minimum enthalpy of formation of 13 meV/atom (Fig. 6(a)) and the rare-earth doping makes this enthalpy of formation be lower, heating (supplying energy) a mixture of CaAs, FeAs, and rare-earth compounds is essential to grow the rare-earth doped CaFeAs_2 compound [13, 18]. On the other hand, BaFeAs_2 compound would decompose into BaAs, FeAs_2 , and BaFe_2As_2 .

Electronic structure of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$

Figure 8(a) shows the momentum-resolved electronic spectral function $A(\mathbf{k}, \omega)$ of $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ at $T = 116$ K as computed by DFT + eDMFT. A fast-dispersing band near the X point has the dominant character of the zig-zag As chain [19, 20], and this band goes down below the Fermi level upon doping as shown in Fig. 8(b), indicating that the spacer of the zig-zag As chain has a crucial role in doping [19]. The electronic anisotropy is evident in the band structures, especially along Γ -X and along Γ -Y directions, as shown in Figs. 8(a) and (b). In order to clarify the origin of the anisotropy, we calculated the orbital polarization between the Fe d_{xz} and d_{yz} orbitals, $\phi = (n_{xz} - n_{yz})$, where $n_{xz}(n_{yz})$ denotes the occupation of the Fe $d_{xz}(d_{yz})$ orbital. ϕ is zero for all compositions at given temperature $T = 116$ K (Fig. 9). Therefore, the

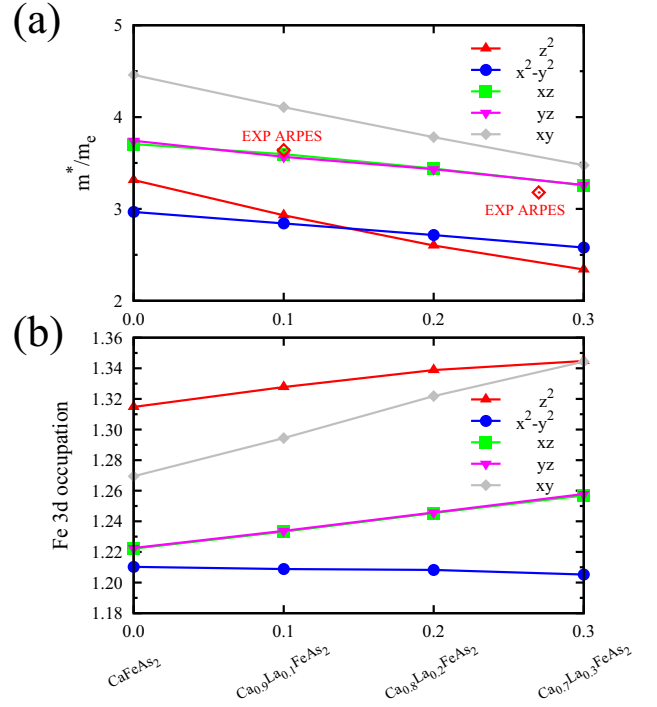


FIG. 10: (Color Online) (a) The mass enhancement m^*/m_e of the iron 3d orbitals upon doping calculated by the DFT + eDMFT. The experimental data (open diamond) are obtained from angle-resolved photoemission spectroscopy experiments in Refs. [19, 20]. (b) The orbital occupation of the iron 3d orbitals upon doping.

anisotropy does not originate from the electronic nematic phase and it is due to the structural anisotropy arising from the zig-zag As chain.

This anisotropy is also reflected in the optical conductivity. Figure 8(c) illustrates the doping dependence in the optical conductivity. Comparing the optical conductivity of CaFeAs_2 to that of $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$, the xx and zz components does not change much upon doping. However, there is a significant change in the yy component upon doping, and the dc conductivity is enhanced significantly. This results in a large in-plane resistivity anisotropy as much as $\rho_a/\rho_b \approx 4.5$, where ρ_a and ρ_b are dc resistivities along a -axis (x -axis) and b -axis (y -axis), respectively. The in-plane resistivity anisotropy has only a structural origin, and it is different from a electronic nematicity driven anisotropy which was found in $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ [49]. The metallic zig-zag As chain is formed along the b -axis, so that it gives the higher conductivity along the b -axis. Note that the average in-plane optical conductivity for $\text{Ca}_{0.77}\text{Nd}_{0.23}\text{FeAs}_2$ was recently reported experimentally [63], and it is consistent with our calculated optical conductivity for $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ as shown in inset of Fig. 8(c).

For further La-doping ($\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$), only the in-plane xx component of the dc conductivity changes sig-

nificantly. Besides, a low-energy peak of 0.34 eV appears in the yy component of the optical conductivity. The low-energy peak of 0.34 eV corresponds to the coherent interband transition within the zig-zag As chain, which is marked by the green arrow in Fig. 8(b).

Since the parent compound of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ is regarded as $\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$ [19], the superconductivity in $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ arises from the hole doping through Ca substitution on the La sites. The resistivity anisotropy is a nonmonotonic function of doping as shown in Fig. 8(c), and it reaches a maximum near the superconducting dome [49].

The plasma frequencies [64] $\omega_{p,xx}$, $\omega_{p,yy}$, and $\omega_{p,zz}$ in the x , y , and z directions obtained by DFT calculations are 2.47 (2.56), 3.36 (3.56), and 0.57 (0.52) eV, respectively, for $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ ($\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$). The estimated in-plane resistivity anisotropy in DFT calculations $\rho_a/\rho_b \simeq \omega_{p,yy}^2/\omega_{p,xx}^2$ is about 1.85 (1.94) for $\text{Ca}_{0.8}\text{La}_{0.2}\text{FeAs}_2$ ($\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$). The in-plane resistivity anisotropy is diminished compared to the eDMFT result giving the quite large in-plane resistivity anisotropy. The anisotropy difference between DFT and eDMFT calculations comes from the correlation effect on iron $3d$ orbitals. The resistivity along b -axis (ρ_b) is almost dominated by the non-correlated zig-zag As chain. However, the resistivity along a -axis (ρ_a) is enhanced by the correlated FeAs layer in the systems. Therefore the correlation effect enhances the in-plane resistivity anisotropy ρ_a/ρ_b induced by the structural anisotropy exhibited in the systems. Compared eDMFT with DFT optical conductivities, the eDMFT calculations show higher spectral weights at low energy. It is due to the incoherent spectral weight induced from the local correlation effect, which is well described by eDMFT, however is not present in DFT. The incoherent spectral weight is also clearly shown in inset of Fig. 8(c), where we have compared the eDMFT and DFT calculations with the measured in-plane average conductivity. Based on the high spectral weight at low energy (~ 0.4 eV) in experiment, eDMFT calculations gives better description rather than DFT. But still, eDMFT and experiment seem to have rather different positions of maxima, at 1.2 eV and at 0.4 eV, respectively. Note that when CaFeAs_2 is doped, its crystal structure could change as well. However, we do not take this effect into account, and the change in the anisotropy we observe is purely due to changes in the electronic structure, and not due to changes in the crystal structure.

The mass enhancement m^*/m_e of the iron $3d$ orbitals is reduced upon doping as shown in Fig. 10(a). This means that the band becomes more coherent upon doping and this leads to enhance the Drude peak in the optical conductivity upon doping in Fig. 8(c). Note that the mass enhancement is not equal in all orbitals, and t_{2g} orbitals have larger enhancement than e_g orbitals. Among the t_{2g} orbitals, the xy orbital has the largest mass enhancement.

These behaviors are quite consistent with the previous eDMFT calculation in iron-based superconductors [65–69]. We also show the mass enhancement extracted from angle-resolved photoemission spectroscopy (ARPES) experiments [19, 20]. (With help of polarization-dependent ARPES experiments [20], it is possible to extract the band dispersion having iron d_{xz} and d_{yz} orbital characters near the Fermi level and calculate the corresponding mass enhancement for individual orbitals.) A good agreement between the eDMFT and experiment is shown in Fig. 10(a).

Figure 10(b) shows the orbital occupation of iron $3d$ orbitals. Upon doping the $x^2 - y^2$ orbital has almost constant occupation, and xz/yz and z^2 orbitals have the similar increment in the orbital occupation. (The increment from $x = 0$ to $x = 0.3$ compound is 0.030 for z^2 , and 0.035 for xz/yz orbitals.) The largest increment in the orbital occupation of iron $3d$ orbitals is the xy orbital and is 0.075 from $x = 0$ to $x = 0.3$ compound. Since this system has the metallic As spacer, there is some additional charge in the spacer As $4p$ orbitals upon doping. The change in the charge on the As $4p$ orbitals between $x = 0$ and $x = 0.3$ is about 0.05. This shows, again, that the metallic As spacer has an important role in the doping process.

Note that two orbitals z^2 and xy have very different mass enhancements among other $3d$ orbitals and their enhancements change a lot as a function of doping. The orbital occupation of z^2 is the largest among other $3d$ orbitals over the doping ratio up to 30 % and that of xy is significantly increased upon doping. These are effects beyond DFT and are very important for the resistivity anisotropy realized in eDMFT calculations.

LANDAU FREE ENERGY

In this section, we outline the basics of a Landau free energy relevant to $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$, as well as other ternary iron pnictide superconductors. The reason for such a study is that the absence of the C_4 symmetry in the high-temperature phase of CaFeAs_2 might lead a misconception that the nematic transition in this compound has to be significantly different from its counterpart in other tetragonal iron pnictides. Below, we show that this is not the case. Even though there have been various studies which wrote down the Landau theory for these systems, such as references [70–72], to the best of our knowledge there are no studies which emphasize the difference between ferro- and antiferro-orbital orders and their connection with the nematicity.

We start by writing a Landau free energy expansion around a high symmetry tetragonal phase of these compounds. (A tetragonal phase only serves as a reference structure.) The point we would like to emphasize is that the primitive unit cell of this high symmetry phase con-

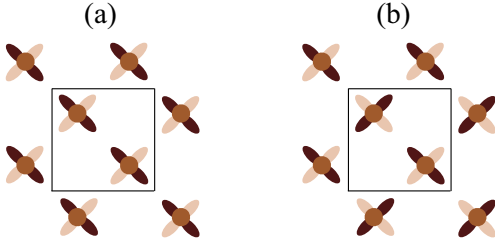


FIG. 11: (a) The ferro and (b) the antiferro orbital orders.

tains two formula units. As a result, even though many model tight-binding studies usually consider a single Fe atom, we need to consider a two-Fe primitive cell (inset of Fig. 9) when building a Landau theory. We label the two Fe atoms with numbers 1 and 2, and choose cartesian axes such that x and y directions point towards nearest neighbors (inset of Fig. 9). We define the orbital polarization for each atom, ϕ_i ($i = 1, 2$), as the difference between the occupations of d_{xz} and d_{yz} orbitals:

$$\phi_i = n_{i,xz} - n_{i,yz}. \quad (1)$$

The two cases where the signs of the orbital polarization of the two atoms are the same or opposite correspond to the ferro- and antiferro-orbital orders (Fig. 11). We label the corresponding order parameters by ϕ_+ and ϕ_- as follows:

$$\phi_+ = \frac{\phi_1 + \phi_2}{2}, \quad (2)$$

$$\phi_- = \frac{\phi_1 - \phi_2}{2}. \quad (3)$$

While the onset of either ϕ_+ or ϕ_- would break the symmetry between d_{xz} and d_{yz} orbitals on an individual Fe ion, these two order parameters break different space group symmetries of the crystal. The nematic transition commonly observed in iron pnictides involve the ferro orbital order ϕ_+ . This order parameter breaks the four-fold rotational symmetry in a specific way - it chooses one of the x or y cartesian axes over the other, and hence can couple bilinearly with the shear strain, which we denote as η_s (Fig. 12(b)), so the free energy has a term $\sim \eta_s \phi_+$.

At this point, we would like to note that the effect of the shear strain η_s on the iron sublattice is to convert it from a square to a tetragonal one. As a result, for models considering a single-Fe unit cell, the strain relevant to the nematic transition is a normal strain, but not a shear strain. However, the normal strain in the actual crystallographic unit cell (Fig. 12(c)) is totally different. It is this normal strain η_n that is present at high temperature in $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. While η_n also breaks the four-fold rotational symmetry, it does in a different way than η_s and does not differentiate between d_{xz} and d_{yz} orbitals on the Fe atoms. As a result, there is no bilinear coupling $\sim \eta_n \phi_+$ in the Landau free energy.

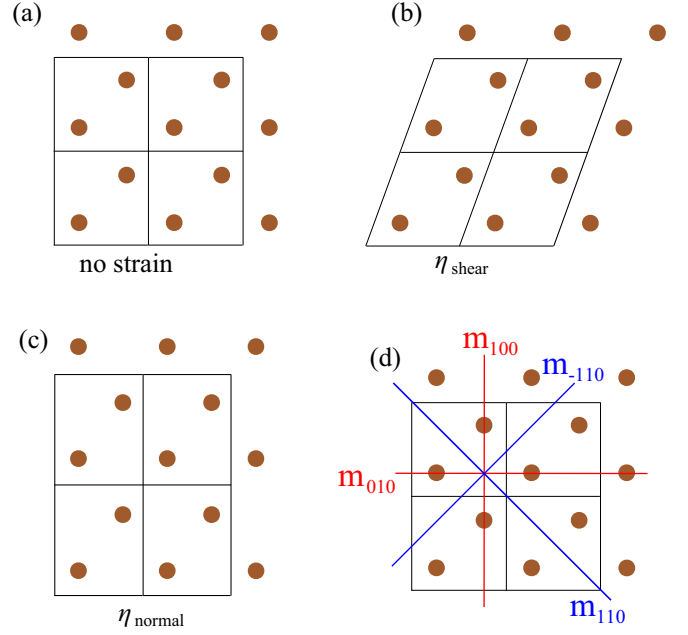


FIG. 12: Sketch of the Fe plane with (a) no strain, (b) shear strain, and (c) normal strain. While there are multiple components of possible shear and normal strains, we only show the relevant ones, the η_{12} shear strain and η_{11} normal strain. (d) In the nonstrained structure, there are four mirror planes that are not parallel to $[001]$. Normal strain breaks the mirror symmetry of only two of these planes (\mathbf{m}_{110} and $\mathbf{m}_{\bar{1}10}$, shown in blue) whereas the shear strain breaks only the other two (\mathbf{m}_{100} and \mathbf{m}_{010} , shown in red).

Another way to think about the shear and normal strains is to consider the mirror planes present in the reference structure. In the tetragonal structure of iron pnictides, there are 4 mirror planes that are perpendicular to the Fe layers (Fig. 12(d)). The presence of \mathbf{m}_{100} and \mathbf{m}_{010} (shown in red in the figure) flips the x and y axes on a Fe atom and as a result imposes the condition that $\phi_i = 0$. The normal strain breaks the \mathbf{m}_{110} and $\mathbf{m}_{\bar{1}10}$ mirror symmetries but preserves \mathbf{m}_{100} and \mathbf{m}_{010} . So, even though it breaks the C_4 symmetry, it does not create an orbital order. The shear strain does the opposite, it breaks the \mathbf{m}_{100} and \mathbf{m}_{010} mirror symmetries but preserves \mathbf{m}_{110} and $\mathbf{m}_{\bar{1}10}$. This gives rise to not only a nonzero ϕ_i but also a nonzero ϕ_+ .

The stripe antiferromagnetic (AFM) order observed in iron pnictides has a k -vector along the $\langle 110 \rangle$ family of directions, and involves a doubling of the unit cell. We denote the AFM order parameters with different wave vectors as L_x and L_y (Fig. 13) [74]. At the lowest order, there is no $\sim L_\alpha$ term in the free energy since there is no other parameter that breaks the time reversal symmetry. However, the onset of the AFM order breaks the four-fold rotational symmetry and differentiates between x and y axes. It also breaks the \mathbf{m}_{100} and \mathbf{m}_{010} mirror symmetries. (Whether the AFM order breaks the other mirror

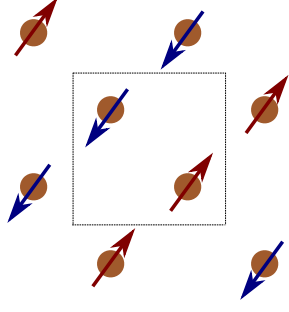


FIG. 13: The stripe AFM order with its wave vector along the $[\bar{1}10]$ direction (L_y). Note that in our theory we do not take into account the spin orbit coupling and consider only collinear spin arrangements. While the relative orientations of the spin moments are meaningful, the direction that all the spins are parallel or antiparallel to is not. The stripe AFM order breaks the \mathbf{m}_{100} and \mathbf{m}_{010} mirror symmetries.

symmetries, \mathbf{m}_{110} and $\mathbf{m}_{\bar{1}10}$, depends on the direction of the magnetic moments. Even though the wave vector of the AFM order is preserved by these two mirror operations, depending on the magnetic easy axis, they might lead to a rotation of the magnetic moments, and hence these mirror symmetries too might be broken by the onset of magnetic order.) As a result, L_α can couple with η_s at linear order and it leads free energy to have terms that go as $\sim (L_x^2 - L_y^2)\eta_s$. Similarly, terms such as $\sim (L_x^2 - L_y^2)\phi_+$ also exist. However, the staggered orbital order ϕ_- does not couple to any of these parameters at linear order, and only biquadratic couplings such as $\sim (L_x^2 + L_y^2)\phi_-^2$ exist, since such biquadratic couplings exist between any two order parameters.

Gathering all these terms together, we obtain the following free energy expression valid for a high symmetry (tetragonal) pnictide, that takes into account all the terms that couple to the ferro-orbital order:

$$\begin{aligned} \mathcal{F} = & a_+\phi_+^2 + b_+\phi_+^4 + a_-\phi_-^2 + b_-\phi_-^4 + c(\phi_+^2\phi_-^2) \\ & + d_{s+}(\eta_s\phi_+) + e_{s+}(\eta_s\phi_+^2) + e_{n+}(\eta_n\phi_+^2) + e_{s-}(\eta_s\phi_-^2) + e_{n-}(\eta_n\phi_-^2) \\ & + f_+((L_x^2 - L_y^2)\phi_+) + g_+((L_x^2 + L_y^2)\phi_+^2) + g_-((L_x^2 + L_y^2)\phi_-^2) \\ & + h((L_x^2 - L_y^2)\eta_s). \end{aligned} \quad (4)$$

Here, we denote the coupling constants by lowercase Latin letters. In the high-temperature phase of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$, the space group is not tetragonal but monoclinic ($P2_1$, #4) and so there are various nonzero strain components with respect to a tetragonal reference structure. The number of symmetry operations is also reduced greatly, and the only symmetry operation apart from identity and translations is the screw rotation around the $[010]$ axis. However, this operation has a crucial effect for the nematic transition in this compound: It connects the two Fe atoms in the unit cell to each other and flips the x and y axes. As a result, the presence of this symmetry operation at the high temperature phase ensures that the ferro-orbital polarization ϕ_+ is zero. However, there is no symmetry operation that ensures that ϕ_- is not zero, and as a result, one needs to take into account an additional $\sim \phi_-$ term in the free energy in order to consider the lower than tetragonal symmetry of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ compound.

In summary, we have listed the order parameters that are relevant for the nematic transition in iron pnictide superconductors, and showed that the free energy expression does not include any terms linearly coupled to ϕ_+ in the compound under study, $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. Therefore there will be a sharp phase transition between a phase

with $\phi_+ = 0$ at high T and a low T phase with $\phi_+ \neq 0$ like in all other iron pnictide materials.

SUMMARY AND CONCLUSIONS

We have checked the phase stability of CaFeAs_2 and $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ compounds. The spacer, zig-zag As chain, nearly has the 1- valence state, so that it does not form the As square-net, which is reminiscent of the Peierls type instability. According to the convex-hull construction, CaFeAs_2 is above the hull with 13 meV/atom. Further stabilization is possible with rare earth doping in CaFeAs_2 material. We have also calculated the optical conductivity of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ based on the DFT + eDMFT method, and found a large in-plane resistivity anisotropy. This large anisotropy does not originate from electronic nematicity, but from the structural anisotropy arising from the zig-zag As chain. The electronic correlations do not induce but nevertheless enhance this anisotropy, as seen from the difference of DFT and eDMFT results. For $\text{Ca}_{0.7}\text{La}_{0.3}\text{FeAs}_2$ compound, we found a low-frequency peak of 0.34 eV in the in-plane yy component of the optical conductivity. This peak corresponds to the coherent interband transition within the

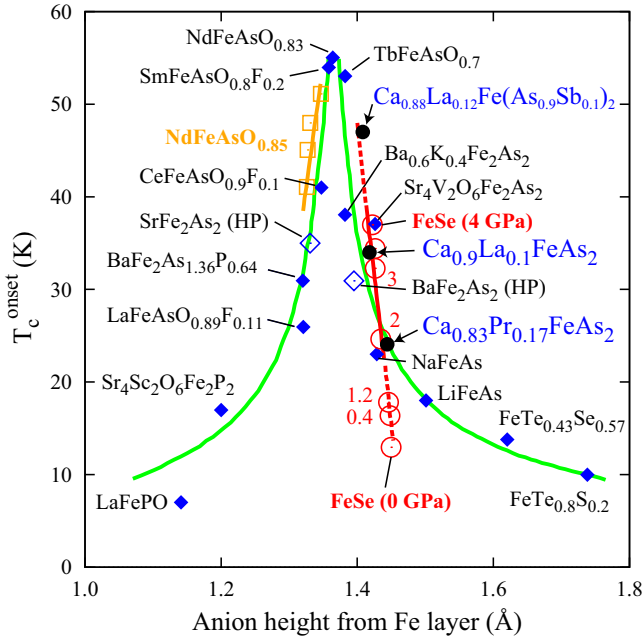


FIG. 14: (Color Online) T_c vs. Anion height in iron pnictide and chalcogenide superconductors. (Reproduced with permission from Ref. [73].) The three data points we added (black) for the 112 superconductors display a similar trend as the other iron based high T_c superconductors. This suggests that the metallic spacer layer in the 112 family does not influence superconductivity.

zig-zag As chain.

In Fig. 14 we reproduce the plot of the distance between the anion and Fe layers and T_c in iron pnictide superconductors. The three data points we add from published data falls perfectly on the lines that were drawn to underline the striking correlation with this single structural parameter and the superconducting critical temperature. This suggests that despite being noncentrosymmetric and having a metallic spacer layer, the superconductivity in the rare-earth doped CaFeAs_2 is no different that in other iron pnictide superconductors. This supports the spin-fluctuation based theories as opposed to theories that rely on charge fluctuations.

ACKNOWLEDGMENTS

C.-J. Kang and G. Kotliar were supported by the DOE EFRC CES program. T. Birol acknowledges the support of the Center for Materials Theory at Rutgers University.

- [1] Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).
- [2] D. N. Basov and A. V. Chubukov, *Nature Phys.* **7**, 272 (2011).

- [3] P. J. Hirschfeld, M. M. Korshunov, and I. I. Mazin, *Rep. Prog. Phys.* **74**, 124508 (2011).
- [4] G. R. Stewart, *Rev. Mod. Phys.* **83**, 1589 (2011).
- [5] A. Charnukha, *J. Phys.: Condens. Matter.* **26**, 253203 (2014).
- [6] J. H. Shim, K. Haule, and G. Kotliar, *Phys. Rev. B* **79**, 060501(R) (2009).
- [7] J. K. Wang, L. L. Zhao, Q. Yin, G. Kotliar, M. S. Kim, M. C. Aronson, and E. Morosan, *Phys. Rev. B* **84**, 064428 (2011).
- [8] J. Park, G. Lee, F. Wolff-Fabris, Y. Y. Koh, M. J. Eom, Y. K. Kim, M. A. Farhan, Y. J. Jo, C. Kim, J. H. Shim, and J. S. Kim, *Phys. Rev. Lett.* **107**, 126402 (2011).
- [9] Y. J. Jo, J. Park, G. Lee, M. J. Eom, E. S. Choi, J. H. Shim, W. Kang, and J. S. Kim, *Phys. Rev. Lett.* **113**, 156602 (2014).
- [10] L.-L. Jia, Z.-H. Liu, Y.-P. Cai, T. Qian, X.-P. Wang, H. Miao, P. Richard, Y.-G. Zhao, Y. Li, D.-M. Wang, J.-B. He, M. Shi, G.-F. Chen, H. Ding, and S.-C. Wang, *Phys. Rev. B* **90**, 035133 (2014).
- [11] Y. Feng, Z. Wang, C. Chen, Y. Shi, Z. Xie, H. Yi, A. Liang, S. He, J. He, Y. Peng, X. Liu, Y. Liu, L. Zhao, G. Liu, X. Dong, J. Zhang, C. Chen, Z. Xu, X. Dai, Z. Fang, and X. J. Zhou, *Sci. Rep.* **4**, 5385 (2014).
- [12] G. Lee, M. A. Farhan, J. S. Kim, and J. H. Shim, *Phys. Rev. B* **87**, 245104 (2013).
- [13] H. Yakita, H. Ogino, T. Okada, A. Yamamoto, K. Kishio, T. Tohei, Y. Ikuhara, Y. Gotoh, H. Fujihisa, Kunimitsu Kataoka, H. Eisaki, and J.-i. Shimoyama, *J. Am. Chem. Soc.* **136**, 846 (2014).
- [14] N. Katayama, K. Kudo, S. Onari, T. Mizukami, K. Sugawara, Y. Sugiyama, Y. Kitahama, K. Iba, K. Fujimura, N. Nishimoto, M. Nohara, and H. Sawa, *J. Phys. Soc. Jpn.* **82**, 123702 (2013).
- [15] J. W. Harter, H. Chu, S. Jiang, N. Ni, and D. Hsieh, *Phys. Rev. B* **93**, 104506 (2016).
- [16] X. Wu, C. Le, Y. Liang, S. Qin, H. Fan, and J. Hu, *Phys. Rev. B* **89**, 205102 (2014).
- [17] X. Wu, S. Qin, Y. Liang, C. Le, H. Fan, and J. Hu, *Phys. Rev. B* **91**, 081111(R) (2015).
- [18] A. Sala, H. Yakita, H. Ogino, T. Okada, A. Yamamoto, K. Kishio, S. Ishida, A. Iyo, H. Eisaki, M. Fujioka, Y. Takano, M. Putti, and J. Shimoyama, *Appl. Phys. Express* **7**, 073102 (2014).
- [19] S. Jiang, C. Liu, H. Cao, T. Birol, J. M. Allred, W. Tian, L. Liu, K. Cho, M. J. Krogstad, J. Ma, K. M. Taddei, M. A. Tanatar, M. Hoesch, R. Prozorov, S. Rosenkranz, Y. J. Uemura, G. Kotliar, and N. Ni, *Phys. Rev. B* **93**, 054522 (2016).
- [20] M. Y. Li, Z. T. Liu, W. Zhou, H. F. Yang, D. W. Shen, W. Li, J. Jiang, X. H. Niu, B. P. Xie, Y. Sun, C. C. Fan, Q. Yao, J. S. Liu, Z. X. Shi, and X. M. Xie, *Phys. Rev. B* **91**, 045112 (2015).
- [21] P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994).
- [22] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996).
- [23] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- [24] G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [25] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [26] A. R. Oganov and C. W. Glass, *J. Chem. Phys.* **124**, 244704 (2006).
- [27] C. W. Glass, A. R. Oganov, and N. Hansen, *Comput.*

- Phys. Commun. **175**, 713 (2006).
- [28] A. Togo, F. Oba, and I. Tanaka, Phys. Rev. B **78**, 134106 (2008).
- [29] V. I. Anisimov, A. I. Poteryaev, M. A. Korotin, A. O. Anokhin, and G. Kotliar, J. Phys.: Condens. Matter. **9**, 7359 (1997).
- [30] S. Y. Savrasov and G. Kotliar, Phys. Rev. B **69**, 245101 (2004).
- [31] G. Kotliar, S. Y. Savrasov, K. Haule, V. S. Oudovenko, O. Parcollet, and C. A. Marianetti, Rev. Mod. Phys. **78**, 865 (2006).
- [32] K. Haule, C.-H. Yee, and K. Kim, Phys. Rev. B **81**, 195107 (2010).
- [33] [<http://hauleweb.rutgers.edu/downloads/>].
- [34] P. Werner, A. Comanac, L. de' Medici, M. Troyer, and A. J. Millis, Phys. Rev. Lett. **97**, 076405 (2006).
- [35] K. Haule, Phys. Rev. B **75**, 155113 (2007).
- [36] We used Ising-type Coulomb interaction in the DFT + eDMFT calculations, as done in the early eDMFT calculation in Ref. [19].
- [37] Yu. Verbovitsky, K. Łatka, J. Przewoźnik, N. Leal, A. P. Gonçalves, Intermetallics **20**, 176 (2012).
- [38] M. Brylak, M. H. Möller, W. Jeitschko, J. Solid State Chem. **115**, 305 (1995).
- [39] H. Mizoguchi, T. Kamiya, H. Hosono, Solid State Commun. **152**, 666 (2012).
- [40] S. Borisenko, D. Evtushinsky, Q. Gibson, A. Yaresko, T. Kim, M. N. Ali, B. Büchner, M. Hoesch, R. J. Cava, arXiv:1507.04847 (2015).
- [41] G. A. Papoian and R. Hoffmann, Angew. Chem. Int. Ed. **39**, 2408 (2000).
- [42] Y. Mozharivskyj, D. Kaczorowski, and H. F. Franzen, Z. Anorg. Allg. Chem. **627**, 2163 (2001).
- [43] Y. Mozharivskyj, D. Kaczorowski, and H. F. Franzen, J. Solid State Chem. **155**, 259 (2000).
- [44] D. Rutzinger, C. Bartsch, Th. Doert, and M. Ruck, Acta Crystallogr. Sect. B-Struct. Sci. **65**, 527 (2009).
- [45] D. Rutzinger, Th. Doert, and M. Ruck, Acta Crystallogr. Sect. B-Struct. Sci. **65**, 519 (2009).
- [46] N. A. Benedek and T. Birol, J. Mater. Chem. C **4**, 4000 (2016).
- [47] C. Ederer and N. A. Spaldin, Phys. Rev. B **74**, 024102 (2006).
- [48] T. Nomura, S. W. Kim, Y. Kamihara, M. Hirano, P. V. Sushko, K. Kato, M. Takata, A. L. Shluger, and H. Hosono, Supercond. Sci. Technol. **21**, 125028 (2008).
- [49] J.-H. Chu, J. G. Analytis, K. D. Greve, P. L. McMahon, Z. Islam, Y. Yamamoto, and I. R. Fisher, Science **329**, 824 (2010).
- [50] J.-H. Chu, H.-H. Kuo, J. G. Analytis, and R. Fisher, Science **337**, 710 (2012).
- [51] S. Kasahara, H. J. Shi, K. Hashimoto, S. Tonegawa, Y. Mizukami, T. Shibauchi, K. Sugimoto, T. Fukuda, T. Terashima, A. H. Nevidomskyy, and Y. Matsuda, Nature **486**, 382 (2012).
- [52] S. Kawasaki, T. Mabuchi, S. Maeda, T. Adachi, T. Mizukami, K. Kudo, M. Nohara, and G.-q. Zheng, Phys. Rev. B **92**, 180508(R) (2015).
- [53] S. Jiang, L. Liu, M. Schütt, A. M. Hallas, B. Shen, W. Tian, E. Emmanouilidou, A. Shi, G. M. Luke, Y. J. Uemura, R. M. Fernandes, N. Ni, arXiv:1603.04899 (2016).
- [54] Y. Zhou, S. Jiang, Q. Wu, V. A. Sidorov, J. Guo, W. Yi, S. Zhang, Z. Wang, H. Wang, S. Cai, K. Yang, S. Jiang, A. Li, N. Ni, G. Zhang, L. Sun, and Z. Zhao, arXiv:1603.05740 (2016).
- [55] S. P. Ong, L. Wang, B. Kang, and G. Ceder, Chem. Mater. **20**, 1798 (2008).
- [56] S. P. Ong, A. Jain, G. Hautier, B. Kang, and G. Ceder, Electrochem. Commun. **12**, 427 (2010).
- [57] R. C. Longo, F. T. Kong, S. KC, M. S. Park, J. Yoon, D.-H. Yeon, J.-H. Park, S.-G. Doo, and K. Cho, Phys. Chem. Chem. Phys. **16**, 11218 (2014).
- [58] K. Hoang, Phys. Rev. Appl. **3**, 024013 (2015).
- [59] W. D. Richards, T. Tsujimura, L. J. Miara, Y. Wang, J. C. Kim, S. P. Ong, I. Uechi, N. Suzuki, and G. Ceder, Nat. Commun. **7**, 11009 (2016).
- [60] [<http://www.materialsproject.org/>].
- [61] G. Hautier, S. P. Ong, A. Jain, C. J. Moore, and G. Ceder, Phys. Rev. B **85**, 155208 (2012).
- [62] G. Hautier, C. Fischer, V. Ehrlicher, A. Jain, and G. Ceder, Inorg. Chem. **50**, 656 (2011).
- [63] R. Yang, B. Xu, Y. Dai, W. Zhang, J. Liu, Z. Qiu, and X. Qiu, Phys. Rev. B **93**, 245110 (2016).
- [64] C. Ambrosch-Draxl and J. O. Sofo, Comput. Phys. Commun. **175**, 1 (2006).
- [65] Z. P. Yin, K. Haule, and G. Kotliar, Nat. Mater. **10**, 932 (2011).
- [66] S. L. Skornyakov, N. A. Skorikov, A. V. Lukoyanov, A. O. Shorikov, and V. I. Anisimov, Phys. Rev. B **81**, 174522 (2010).
- [67] Z. P. Yin, K. Haule, and G. Kotliar, Nature Phys. **7**, 294 (2011).
- [68] J. Ferber, K. Foyevtsova, R. Valentí, and H. O. Jeschke, Phys. Rev. B **85**, 094505 (2012).
- [69] J. M. Tomczak, M. van Schilfgaarde, and G. Kotliar, Phys. Rev. Lett. **109**, 237010 (2012).
- [70] S.-H. Baek, D. V. Efremov, J. M. Ok, J. S. Kim, J. van den Brink, and B. Büchner, Nat. Mater. **14**, 210 (2015).
- [71] A. Cano, M. Civelli, I. Eremin, and I. Paul, Phys. Rev. B **82**, 020408 (2010).
- [72] R. M. Fernandes and J. Schmalian, Supercond. Sci. Technol. **25**, 084005 (2012).
- [73] Y. Mizuguchi, Y. Hara, K. Deguchi, S. Tsuda, T. Yamaguchi, K. Takeda, H. Kotegawa, H. Tou, and Y. Takano, Supercond. Sci. Technol. **23**, 054013 (2010).
- [74] Note that unlike many other studies where the site magnetic moments ($m_i = n_{i\uparrow} - n_{i\downarrow}$) are introduced, we work directly with the AFM order parameters, since there is no other magnetic order that is relevant to these compounds.