



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Detecting topological superconductivity using low-frequency doubled Shapiro steps

Jay D. Sau and F. Setiawan

Phys. Rev. B **95**, 060501 — Published 3 February 2017

DOI: [10.1103/PhysRevB.95.060501](https://doi.org/10.1103/PhysRevB.95.060501)

Detecting topological superconductivity using **low-frequency** doubled Shapiro steps

Jay D. Sau¹ and F. Setiawan¹

¹*Condensed Matter Theory Center and Joint Quantum Institute,
Department of Physics, University of Maryland, College Park, Maryland 20742, USA*

(Dated: December 21, 2016)

The fractional Josephson effect has been observed in many instances as a signature of a topological superconducting state containing zero-energy Majorana modes. We present a non-topological scenario which can produce a fractional Josephson effect generically in semiconductor-based Josephson junctions, namely a resonant impurity bound state weakly coupled to a highly transparent channel. We show that the fractional ac Josephson effect can be generated by the Landau-Zener processes which flip the electron occupancy of the impurity bound state. The Josephson effect signature for Majorana modes become distinct from this non-topological scenario only at low frequency. We prove that a variant of the fractional ac Josephson effect, namely the low-frequency doubled Shapiro steps, can provide a more reliable signature of the topological superconducting state.

PACS numbers: 74.45.+c, 03.67.Lx, 05.40.Ca, 71.10.Pm

Superconductors supporting Majorana zero modes (MZMs)[1–4] at defects provide one of the simplest examples of topological superconductors (TSs) [5, 6]. In fact, a number of proposals [7–12] to realize such MZMs have met with considerable success [13–18]. Such systems containing MZMs are particularly interesting [19–25] because of the topologically degenerate Hilbert space and non-Abelian statistics associated with them that make such MZMs useful for realizing topological quantum computation [26]. While preliminary evidence for MZMs in the form of a zero-bias conductance peak have already been observed [13–18, 27–31], confirmatory signatures of the topological nature of MZMs are still lacking.

The zero-bias conductance peak provides evidence for the existence of zero-energy end modes which can arise not only from TSs but also from a variety of non-topological features associated with details of the end of the system [32–35]. In contrast, the topological invariant of a TS, being a bulk property, is not affected by the details of the potential at the end. The topological invariant of a one-dimensional TS can be determined from the change in the fermion parity of the Josephson junction (JJ) [3]. Specifically, the fermion parity of a topological JJ changes when the superconducting phase of the left superconductor ϕ of the JJ winds adiabatically by $\delta\phi = 2\pi$ [2, 3]. Such a change in fermion parity of the JJ may be detected from the resulting 4π -periodic component in the current-phase relation of the topological JJ [3, 36]. This is referred to as the fractional Josephson effect and can be detected using the fractional ac Josephson effect (FAJE).

The FAJE involves applying a finite dc voltage V across the junction so that the superconducting phase across the junction varies in time as $\phi(t) = \Omega_J t$ [37]. Here $\Omega_J = V$ is the Josephson frequency, where we have set $\hbar = 1$ and the charge of the Cooper pair $2e = 1$. The 4π -periodic current-phase relation characteristic of a topological JJ results in a current that

has a component at half the Josephson frequency, i.e., at $\omega = \Omega_J/2$ instead of $\omega = \Omega_J$ characteristic of conventional JJs [3, 11, 12, 36, 38, 39]. In principle, the resulting ac current may be detected by a measurement of the radiation emitted from the junction [40, 41]. Alternatively, the fractional Josephson effect can also be detected by measuring the size of the voltage steps, known as Shapiro steps [42, 43]. For topological JJs, these voltage steps have been numerically found to be $\delta V = 2\Omega_J$ which is doubled the voltage steps for the conventional JJs [44, 45].

Interestingly, evidence for both the FAJE [41] and doubled Shapiro steps [42, 43, 46] have been seen in TSs that are expected to support MZMs. However, there is evidence that such signatures might appear in non-topological systems as well. For example, both the signatures seem to also appear in the TS experiments when the devices are not in the topological parameter regime [41, 43, 46, 47]. One possible spurious source of FAJE is the period-doubling transition seen in certain JJ systems [48]. In addition, the FAJE and doubled Shapiro steps are known (both experimentally [40] and theoretically [49, 50]) to arise from Landau-Zener (LZ) processes in certain ranges of frequency. Avoiding such LZ processes might require particularly low frequencies in low-noise systems with multiple MZMs [51]. While the LZ process is known to potentially lead to FAJE [40, 49], there have not been any generic non-topological scenarios presented in the literature so far.

In this Letter, we start by discussing a generic model of a resonant impurity coupled to a JJ [shown in Fig. 1(a)], which has a weakly avoided crossing in the energy spectrum as a function of phase [see Fig. 1(b)]. The present scenario requires only the coexistence of a highly transparent channel in a JJ (as seen in recent measurements of ABS spectra [52]) and a weakly coupled impurity bound state. Such a coexistence can be found in a multichannel semiconductor-based JJ with a spatially varying den-

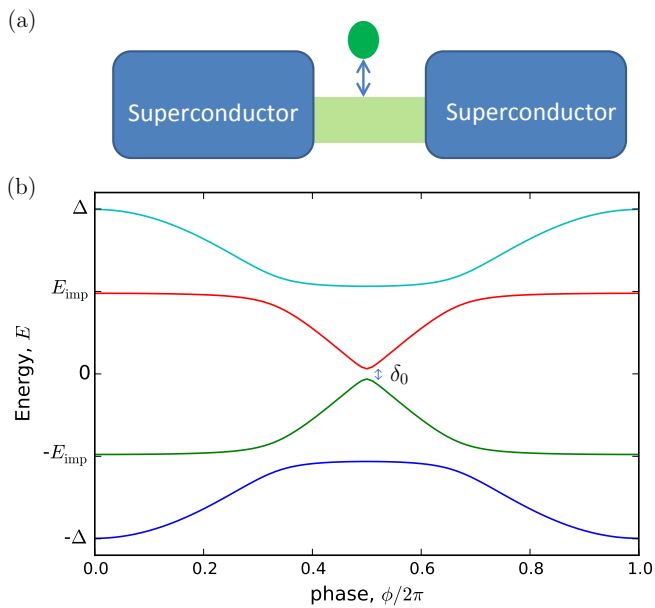


FIG. 1: (Color online) (a) JJ configuration showing FAJE consists of a high transparency channel connecting two superconductors. The channel is tunnel coupled to an impurity bound state (shown as a disc adjoining wire). (b) Computed Andreev bound state spectrum for setup in (a) shows a weakly avoided crossing at $E = 0$ and a gap to higher energy states generated by a larger avoided crossing with the flat impurity bound state. The weakly avoided crossing can lead to an FAJE at finite voltages.

sity as is the case of all of the recent experiments [41–43, 46]. We use a scattering-matrix approach to show that this relatively generic situation can lead to an FAJE over a frequency range of a factor of a few even in the absence of any TS. In order to distinguish between this non-topological scenario from TS, it is important to be able to go to ultra-low MHz frequencies in the FAJE measurements. Shapiro steps provide the setup where such a large range of frequencies spanning three orders of magnitudes (MHz-GHz) are possible [53]. In the second part of this Letter, we provide the first rigorous framework connecting Shapiro steps to TS where we show that the **low-frequency** doubled Shapiro steps are guaranteed to appear in the overdamped driven measurements of topological JJs.

Let us first understand how an FAJE can occur in a non-topological setup such as the setup in Fig. 1(a). For simplicity, we consider the superconductors to be s -wave with a highly transparent normal channel in between together with a subgap impurity bound state. Highly transparent channel supports Andreev bound states (ABSs) in the junction that approach zero-energy (see Fig. 1(b)) when the phase ϕ crosses $\phi = \pi$ [54]. Applying a finite voltage V across the junction causes the superconducting phase ϕ to vary in time as $\phi(t) = Vt$. This leads to the possibility of LZ processes exciting Cooper pairs across

the superconducting gap. In general, these Cooper pairs are transported across the entire superconducting gap via multiple Andreev reflections [55, 56] ultimately leading to a dissipative but otherwise conventional ac Josephson effect [55]. This situation is modified when the junction is tunnel coupled to impurity bound states. As shown in Fig. 1(b), the ABS spectrum of the JJ varies with phase ϕ where it crosses the relatively flat impurity bound state with energy E_{imp} at pairs of points. At such crossings, the junction exchanges a Cooper pair with the flat impurity state. When $\phi = \pi$, the ABS loses Cooper pair to the condensate through a LZ process across the zero-energy gap δ_0 . As the ABS energy approaches the second avoided crossing with the impurity bound state at energy E_{imp} , the ABS restores its Cooper pair at the expense of leaving the impurity bound state empty. Thus, the impurity bound state electron occupancy is flipped via the LZ process as the phase varies over a period of $\phi = 0$ to $\phi = 2\pi$ which is restored during the next 2π cycle. Therefore, while the spectrum of the junction is 2π periodic, the occupation of the impurity bound state is 4π periodic. Since the total energy E which includes the spectrum and occupation of the ABS and impurity bound states determines the supercurrent $I(\phi)$ by $I(\phi) \sim \partial_\phi E(\phi)$, $I(\phi)$ would also be 4π periodic with the phase ϕ . This manifests as a peak in the radiation spectrum from the current at a frequency of $\omega = \Omega_J/2$ instead of the usual Josephson frequency $\omega = \Omega_J$ peak.

While the qualitative argument in the previous paragraph suggests the possibility of an FAJE occurring in non-topological semiconductor systems, it assumes the zero-energy LZ processes to be perfect and all other LZ processes to be completely avoided. In the following, we perform a completely unbiased quantitative analysis of the FAJE for the JJ shown in Fig. 1. To begin with, we note that at any finite voltage V , the occupation of an ABS fluctuates due to excitations out of the bulk gap (via multiple Andreev reflections). The quasiparticle fluctuations ensure that the system equilibrates to grand canonical ensemble (with no conserved fermion parity) such that the expectation value of the current is 2π periodic as in the conventional system [57]. Thus, strictly speaking, the FAJE at any finite voltage is subject to random fluctuations and can only appear in the noise spectrum of the current [58, 59]. To assess the range of voltage over which the JJ shown in Fig. 1(a) exhibits an FAJE, we compute the noise spectrum of the current

$$P(\omega) = \int d\tau e^{i\omega\tau} [\langle I(t)I(t+\tau) \rangle - \langle I(t) \rangle \langle I(t+\tau) \rangle], \quad (1)$$

where $\langle \dots \rangle$ denotes the averaging over time t . The current [55] and its noise spectrum [58, 59] can be computed by considering the scattering of quasiparticles between the superconducting leads, which are at different voltages. This approach has the advantage of including the contribution of not only the low-

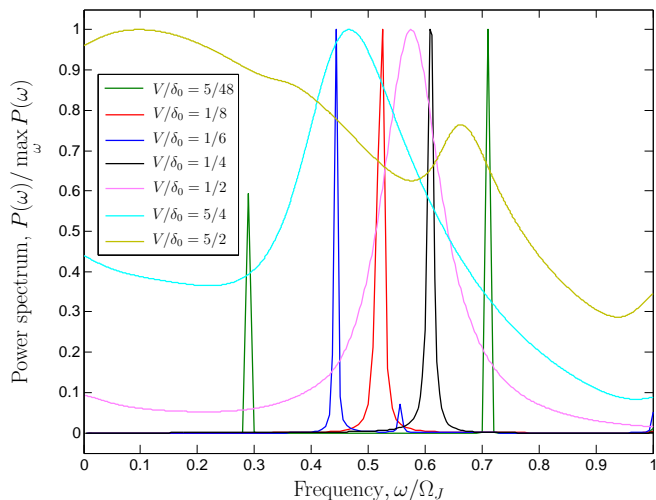


FIG. 2: (Color online) Power radiated $P(\omega)$ as a function of frequency ω/Ω_J for different ratios of the applied voltage V relative to the zero-energy gap δ_0 . The power spectrum $P(\omega)$ shows a fractional ac Josephson peak at $\omega = \Omega_J/2$ for a range of values of V/δ_0 . The peak broadens out at higher voltages and shifts towards a more conventional peak at $\omega = \Omega_J$ at lower frequency (while becoming smaller). $P(\omega)$ has been rescaled so that all peaks are clearly visible.

energy ABSs but also all bound and scattering states in the junction. We have expanded this formalism to general superconductor-normal-superconductor junctions [60]. Our general framework can be easily implemented with Kwant [61] which supplies the normal-superconductor scattering matrices. The resulting power spectrum $P(\omega)$ is plotted against the frequency scaled by the Josephson frequency, i.e., ω/Ω_J in Fig. 2 for various voltages for the system depicted in Fig. 1(a) with the spectrum shown in Fig. 1(b). The power spectrum at high voltages is quite broad, which becomes narrower at lower frequency and develops peaks in the vicinity of $\omega/\Omega_J = 1/2$ before splitting off to different values. The high-frequency spectrum is also several orders smaller in magnitude, which is expected in the adiabatic limit when fluctuations in the ABS occupation are small. While some of the peaks appear to move away from the ideal fractional value and come back, this might be difficult to resolve at a high level of broadening arising from nearby energy states and circuit-noise induced broadening.

The spurious FAJE peaks in Fig. 2 resulting from the LZ mechanism appears over a frequency range narrower compared to the parametrically large frequency range (i.e. $(\Gamma, \delta \leq \omega \leq \Delta)$) of the FAJE in a high quality TS [58, 59, 62, 63]. Here, Δ is the induced superconducting gap, which is a relatively large frequency (\sim GHz), Γ and δ are respectively the quasiparticle poisoning rate and the MZM overlap that become vanishingly small (\lesssim MHz) in high quality TSs.

It is clear from Fig. 2 that distinguishing a bona-fide

TS from an LZ-type mechanism induced by resonant bound states requires low-frequency ($\lesssim 50$ MHz) measurements of high quality TS devices with $\Delta \gg \delta, \Gamma$. The FAJE which involves measuring small oscillating currents is difficult to perform for low frequencies because such small oscillating currents are typically measured using an on-chip detectors [40, 64] that are suited to measure relatively high frequencies (\sim GHz). On the other hand, the Shapiro step [37], which is a variant of the FAJE, has been demonstrated over a large range of frequencies from several MHz to GHz [53]. While this makes the Shapiro step promising for the detection of TSs, a rigorous proof establishing the doubled Shapiro step as a signature of TS is still missing from the literature. Below, we demonstrate analytically for the first time that the low-frequency doubled Shapiro steps can be used as a reliable signature of TS.

We begin by considering the Shapiro step experiment where a JJ shunted with a resistance R is biased with a time-varying current $I_{\text{bias}}(t) = I_{\text{dc}} + I_{\text{ac}} \cos(\Omega_J t)$ with I_{dc} and I_{ac} being dc and ac bias currents, respectively. For the following analysis, we make a *key assumption* that we are working in the limit of low frequency Ω_J so that the Josephson current $I_J(\phi(t))$ can be taken to be in equilibrium, apart from the conserved local fermion parity. The assumption of being at sufficiently low frequency can only be justified by studying the Shapiro steps over a few orders of magnitude in frequency (from $\Delta \sim$ GHz to $\delta, \Gamma \sim$ MHz). Using this assumption and the result of Bloch [57], we can establish that $I_J(\phi)$ for any non-topological system must be 2π periodic and thus rule out any non-topological FAJE such as those from the LZ mechanism.

Furthermore, assuming that the shunt resistance R is small enough to allow the JJ to be overdamped, the equation of motion for $\phi(t)$ for the resistively shunted JJ takes the standard form [37]

$$\frac{d\phi}{dt} = R[I_{\text{bias}}(t) - I_J(\phi(t))]. \quad (2)$$

For illustration purposes, we will choose a simple case of $I_J(\phi) = I_0 \cos(2\pi\phi) + I_{\text{top}} \cos(\pi\phi)$ where I_0 and I_{top} are the 2π - and 4π -periodic component of the critical current of the adiabatic current-phase relation, respectively. However, our results hold generally and do not depend on this parameter choice as is proven by the analytic arguments in Ref. [65]. The dc voltage V across the JJ is calculated by considering the average change of the phase

$$V = \lim_{t \rightarrow \infty} \frac{\phi(t) - \phi(0)}{t}, \quad (3)$$

where the limit is computed by choosing a sufficiently long simulation time for Eq. 2.

We will now show that overdamped JJs constructed out of TSs are generically characterized by a dou-

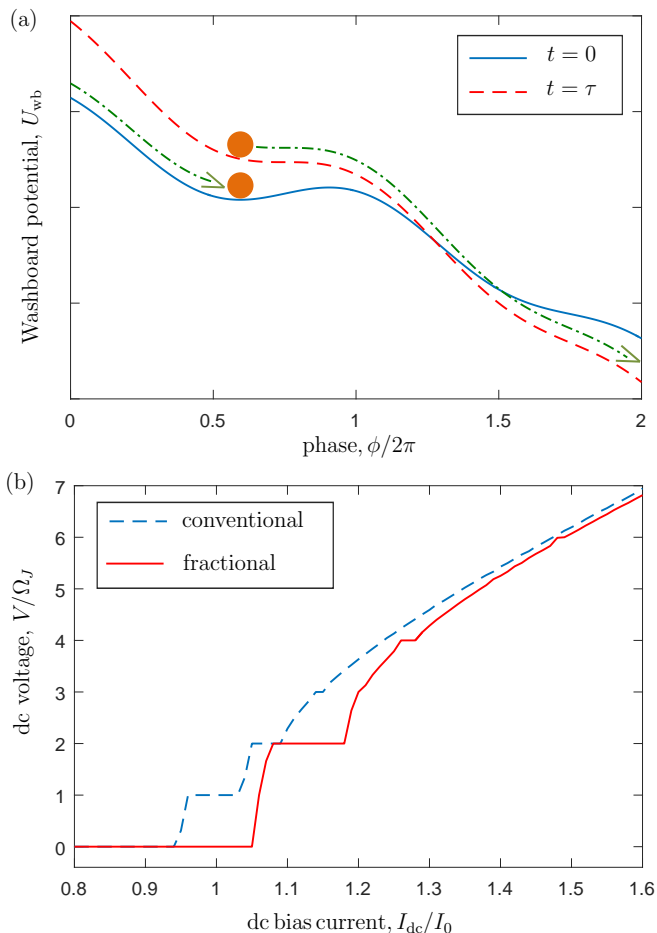


FIG. 3: (Color online) (a) Schematic of a phase particle (orange disc) on a tilted washboard potential that describes the phase dynamics in an overdamped JJ. As the bias current increases from $t = 0$ to $t = \tau$, the phase particle is released from the local minimum and traverses the trajectory along the green dash-dot arrow, and stops when the current bias is back to its value at $t = 0$ and the phase particle has travelled by 4π (for the TS case shown here). This corresponds to a voltage step of $2\Omega_J$. (b) Shapiro step calculated numerically for a putative fractional Josephson system shows doubled Shapiro steps (see also Ref. 44) as opposed to a conventional system with all integer Shapiro steps for an overdamped JJ. Here $I_{ac} = 0.1I_0$, $R = 25$, $I_{top} = 0.15I_0$ (for fractional), and $I_{top} = 0$ (for conventional).

bled Shapiro step in the strongly overdamped and low-frequency limit (i.e., $\Omega_J/I_J R \ll 1$). The dynamics of $\phi(t)$ described by Eq. 2 can be understood simply by an analogy of a “phase particle” rolling down a washboard potential according to the equation $\phi(t) = -\partial_\phi U_{wb}(\phi, t)$, where the washboard potential is written as $U_{wb} = -R[I_{bias}(t)\phi - \int d\phi I_J(\phi)]$. As seen in Fig. 3(a), because of the ac drive, the potential $U_{wb}(\phi, t)$ varies in time with local minima at each cycle when $\phi(t) = \phi_0$ such that

$$I_{bias}(t) - I_J(\phi_0) = 0. \quad (4)$$

In the adiabatic limit (i.e., $\Omega_J/I_J R \ll 1$), one can show that the phase particle approaches the minimum of the washboard potential exponentially in time once every period of the drive. This leads to a well-defined voltage that appears as a sharp plateau in the Shapiro steps [65].

Let us for now assume that [65] the phase particle approaches a minimum of U_{wb} during the time interval when such exists. In the conventional case of a 2π -periodic function I_J , this can occur once in a 2π period provided the critical current $I_{J,max} > (I_{dc} - I_{ac})$. This will certainly occur if I_{dc} is small enough. In addition, if $I_{dc} > (I_{J,max} - I_{ac})$, then there will be a range of time when U_{wb} has no minimum and the adiabatic solution breaks down. In this case, $\phi(t)$ will wind by a multiple of 2π and collapse to ϕ_0 after a winding of $2\pi n$. The result is that an integer voltage appears across the JJ. In the case of a topological JJ, the current-phase relation $I_J(\phi)$ has a 4π -periodic component and one can define two critical currents $I_{J,max}$ and $I'_{J,max}$, one associated with the range $\phi \in [4n\pi, (4n+2)\pi]$ and the other in the range $\phi \in [(4n-2)\pi, 4n\pi]$. In our simple model $I_{J,max}, I'_{J,max} = I_0 \pm I_{top}$. As in the conventional case, the dc bias current must satisfy $I_{dc} > (I_{J,max} - I_{ac})$ (assuming $I_{J,max} > I'_{J,max}$) to exit the zero-voltage state even in the TS case. On the other hand, if $2I_{ac} < (I_{J,max} - I'_{J,max})$ then $I_{dc} > I'_{J,max} + I_{ac}$ so that the phase particle can not stop at one half of the minima. This leads to a doubled voltage step for the topological case as seen from the numerical solution of Eq. 2 [see Fig. 3(b)].

In summary, we have shown that while the FAJE can be viewed as a smoking gun for the TS with MZMs, a detailed study of the frequency dependence of the FAJE is necessary before concluding a system to have realized the TS. We have shown this by considering a generic model of a high transparency channel in a JJ coupled weakly to a resonant impurity. We find this model to show an FAJE quite generically in semiconductor-based JJs, similar to the TS case with MZMs. Nevertheless, TSs are expected to show FAJE over a parameterically larger range of frequency. We argue that current-phase relation over such a range of frequency, particularly at the low-frequency end is better studied by considering the Shapiro step experiment. We present a way of understanding the Shapiro step experiment in terms of the tilted washboard potential that guarantees that the necessary and sufficient condition for the existence of doubled Shapiro steps in the low-frequency limit is that the JJ is formed from a TS. Thus, low-frequency Shapiro steps which have been demonstrated in conventional systems can serve as a smoking gun for MZMs.

This work is supported by Microsoft Station Q, Sloan Research Fellowship, NSF CAREER Award and JQI-NSF-PFC. We acknowledge enlightening discussions with Anton Akhmerov, Julia Meyer, Leo Kouwenhoven, Attila Geresdi, Yuli Nazarov, Chang-Yu Hou, Sergey Frolov, Ramon Aguado, and Roman Lutchyn in the course of

this work. J. D. S. is grateful to the Aspen Center for Physics where part of this work was completed.

-
- [1] M. Salomaa and G. Volovik, *Physical Review B* **37**, 9298 (1988).
- [2] N. Read and D. Green, *Physical Review B* **61**, 10267 (2000).
- [3] A. Y. Kitaev, *Physics-Uspexhi* **44**, 131 (2001).
- [4] K. Sengupta, I. Zutić, H.-J. Kwon, V. M. Yakovenko, and S. D. Sarma, *Physical Review B* **63**, 144531 (2001).
- [5] A. P. Schnyder, S. Ryu, A. Furusaki, and A. W. Ludwig, *Physical Review B* **78**, 195125 (2008).
- [6] A. Y. Kitaev, *AIP Conf. Proc.* **1134**, 22 (2009).
- [7] L. Fu and C. L. Kane, *Physical review letters* **100**, 096407 (2008).
- [8] J. D. Sau, R. M. Lutchyn, S. Tewari, and S. D. Sarma, *Physical review letters* **104**, 040502 (2010).
- [9] J. D. Sau, S. Tewari, R. M. Lutchyn, T. D. Stanescu, and S. D. Sarma, *Physical Review B* **82**, 214509 (2010).
- [10] Jason Alicea, *Phys. Rev. B* **81**, 125318 (2010).
- [11] Roman M. Lutchyn, Jay D. Sau, and S. Das Sarma., *Phys. Rev. Lett.* **105**, 077001 (2010).
- [12] Yuval Oreg, Gil Refael, and Felix von Oppen., *Phys. Rev. Lett.* **105**, 177002 (2010).
- [13] V. Mourik, K. Zuo, S. M. Frolov, S. R. Plissard, E. P. A. M. Bakkers and L. P. Kouwenhoven., *Science* **336**, 1003 (2012).
- [14] M. T. Deng, C. L. Yu, G. Y. Huang, M. Larsson, P. Caroff, and H. Q. Xu., *Nano Lett.* **12**, 6414 (2012).
- [15] Anindya Das, Yuval Ronen, Yonatan Most, Yuval Oreg, Moty Heiblum and Hadas Shtrikman., *Nat. Phys.* **8**, 887 (2012).
- [16] H. O. H. Churchill, V. Fatemi, K. Grove-Rasmussen, M. T. Deng, P. Caroff, H. Q. Xu, and C. M. Marcus, *Phys. Rev. B* **87**, 241401 (2013).
- [17] A. D. K. Finck, D. J. Van Harlingen, P. K. Mohseni, K. Jung, and X. Li, *Phys. Rev. Lett.* **110**, 126406 (2013).
- [18] E. J. Lee, X. Jiang, M. Houzet, R. Aguado, C. M. Lieber, and S. De Franceschi, *Nature nanotechnology* **9**, 79 (2014).
- [19] J. Alicea, *Reports on Progress in Physics* **75**, 076501 (2012).
- [20] C. W. J. Beenakker, *Annual Review of Condensed Matter Physics* **4**, 113 (2013).
- [21] M. Leijnse and K. Flensberg, *Semiconductor Science and Technology* **27**, 124003 (2012).
- [22] T. D. Stanescu and S. Tewari, *Journal of Physics: Condensed Matter* **25**, 233201 (2013).
- [23] S. R. Elliott and M. Franz, *Reviews of Modern Physics* **87**, 137 (2015).
- [24] S. D. Sarma, M. Freedman, and C. Nayak, *NPJ Quantum Information* **1**, 15001 (2015).
- [25] C. W. J. Beenakker and L. Kouwenhoven, *Nature Physics* **12**, 618 (2016).
- [26] C. Nayak, S. H. Simon, A. Stern, M. Freedman, and S. D. Sarma, *Reviews of Modern Physics* **80**, 1083 (2008).
- [27] S. Nadj-Perge, I. K. Drozdov, J. Li, H. Chen, S. Jeon, J. Seo, A. H. MacDonald, B. A. Bernevig, and A. Yazdani, *Science* **346**, 602 (2014).
- [28] Q. L. He, L. Pan, A. L. Stern, E. Burks, X. Che, G. Yin, J. Wang, B. Lian, Q. Zhou, E. S. Choi, *et al.*, arXiv preprint arXiv:1606.05712 (2016).
- [29] H.-H. Sun, K.-W. Zhang, L.-H. Hu, C. Li, G.-Y. Wang, H.-Y. Ma, Z.-A. Xu, C.-L. Gao, D.-D. Guan, Y.-Y. Li, *et al.*, *Physical Review Letters* **116**, 257003 (2016).
- [30] H. Zhang, Ö. Gül, S. Conesa-Boj, K. Zuo, V. Mourik, F. K. de Vries, J. van Veen, D. J. van Woerkom, M. P. Nowak, M. Wimmer, D. Car, S. Plissard, E. P. Bakkers, M. Quintero-Perez, S. Goswami, K. Watanabe, T. Taniguchi, and L. P. Kouwenhoven, arXiv preprint arXiv:1603.04069 (2016).
- [31] S. Albrecht, A. Higginbotham, M. Madsen, F. Kuemmeth, T. Jespersen, J. Nygård, P. Krogstrup, and C. Marcus, *Nature* **531**, 206 (2016).
- [32] J. Liu, A. C. Potter, K. T. Law, and P. A. Lee, *Phys. Rev. Lett.* **109**, 267002 (2012).
- [33] D. Bagrets and A. Altland, *Phys. Rev. Lett.* **109**, 227005 (2012).
- [34] Jay D. Sau and P. M. R. Brydon, *Phys. Rev. Lett.* **115**, 127003 (2015).
- [35] G. Kells, D. Meidan, and P. W. Brouwer, *Phys. Rev. B* **86**, 100503(R) (2012).
- [36] H.-J. Kwon, K. Sengupta, and V. M. Yakovenko, *The European Physical Journal B-Condensed Matter and Complex Systems* **37**, 349 (2004).
- [37] M. Tinkham, *Introduction to Superconductivity*, 2nd ed. (Dover, Mineola, New York, 2004).
- [38] L. Fu and C. L. Kane, *Physical Review B* **79**, 161408 (2009).
- [39] B. Zocher, M. Horsdal, and B. Rosenow, *Physical review letters* **109**, 227001 (2012).
- [40] P.-M. Billangeon, F. Pierre, H. Bouchiat, and R. Deblock, *Physical review letters* **98**, 216802 (2007).
- [41] R. S. Deacon, J. Wiedenmann, E. Bocquillon, T. M. Klapwijk, P. Leubner, C. Brüne, S. Tarucha, K. Ishibashi, H. Buhmann, and L. W. Molenkamp, arXiv preprint arXiv:1603.09611 (2016).
- [42] L. P. Rokhinson, X. Liu, and J. K. Furdyna, *Nature Physics* **8**, 795 (2012).
- [43] J. Wiedenmann, E. Bocquillon, R. S. Deacon, S. Hartinger, O. Herrmann, T. M. Klapwijk, L. Maier, C. Ames, C. Brüne, C. Gould, A. Oiwa, K. Ishibashi, S. Tarucha, H. Buhmann, and L. W. Molenkamp, *Nature communications* **7** (2016).
- [44] F. Domínguez, F. Hassler, and G. Platero, *Physical Review B* **86**, 140503 (2012).
- [45] M. Maiti, K. M. Kulikov, K. Sengupta, and Y. M. Shukrinov, *Phys. Rev. B* **92**, 224501 (2015).
- [46] V. S. Pribiag, A. J. Beukman, F. Qu, M. C. Cassidy, C. Charpentier, W. Wegscheider, and L. P. Kouwenhoven, *Nature nanotechnology* **10**, 593 (2015).
- [47] While these systems have been shown to be topological for the correct gate voltages, the fractional Josephson signature appears also for gate voltages where the conductance is not at the topologically quantized value. Disorder scattering between the implied additional modes and the topological edge modes ultimately limit the topological robustness of the system to short time scale.
- [48] K. Wiesenfeld and B. McNamara, *Physical review letters* **55**, 13 (1985).
- [49] J. D. Sau, E. Berg, and B. I. Halperin, arXiv preprint arXiv:1206.4596 (2012).
- [50] B. Sothmann, J. Li, and M. Büttiker, *New Journal of*

- Physics **15**, 085018 (2013).
- [51] D. Sticlet, C. Bena, and P. Simon, Physical Review B **87**, 104509 (2013).
- [52] W. Chang, V. Manucharyan, T. S. Jespersen, J. Nygård, and C. M. Marcus, Physical review letters **110**, 217005 (2013).
- [53] S. Hebboul, D. Harris, and J. Garland, Physica B: Condensed Matter **165**, 1629 (1990).
- [54] C. W. J. Beenakker, Physical review letters **67**, 3836 (1991).
- [55] D. Averin and A. Bardas, Physical review letters **75**, 1831 (1995).
- [56] T. Klapwijk, G. Blonder, and M. Tinkham, Physica (Amsterdam) **109-110B+C**, 1657 (1982).
- [57] F. Bloch, Physical Review B **2**, 109 (1970).
- [58] D. M. Badiane, M. Houzet, and J. S. Meyer, Physical review letters **107**, 177002 (2011).
- [59] D. M. Badiane, L. I. Glazman, M. Houzet, and J. S. Meyer, Comptes Rendus Physique **14**, 840 (2013).
- [60] Details of the computation of the power spectrum in Eq.1 that is used to plot Fig. 2 are given in section I of the Supplemental Material at [URL will be inserted by the publisher].
- [61] C. W. Groth, M. Wimmer, A. R. Akhmerov, and X. Waintal, New Journal of Physics **16**, 063065 (2014).
- [62] D. Pikulin and Y. V. Nazarov, Physical Review B **86**, 140504 (2012).
- [63] P. San-Jose, E. Prada, and R. Aguado, Physical review letters **108**, 257001 (2012).
- [64] R. Deblock, E. Onac, L. Gurevich, and L. P. Kouwenhoven, Science **301**, 203 (2003).
- [65] We prove analytically in the section II of the Supplemental Material at [URL will be inserted by the publisher] that the period of the Shapiro step is generically doubled for the topological case in the adiabatic limit.