

This is the accepted manuscript made available via CHORUS. The article has been published as:

Magnon-magnon interactions in a room-temperature magnonic Bose-Einstein condensate

Oleksandr Dzyapko, Ivan Lisenkov, Patrik Nowik-Boltyk, Vladislav E. Demidov, Sergej O. Demokritov, Benny Koene, Andrei Kirilyuk, Theo Rasing, Vasyl Tiberkevich, and Andrei Slavin

Phys. Rev. B **96**, 064438 — Published 30 August 2017

DOI: [10.1103/PhysRevB.96.064438](https://doi.org/10.1103/PhysRevB.96.064438)

Magnon-magnon interactions in a room-temperature magnonic Bose-Einstein condensate

Oleksandr Dzyapko¹, Ivan Lisenkov^{2,3,*}, Patrik Nowik-Boltyk¹, Vladislav E. Demidov¹, Sergej O. Demokritov^{1,4}, Benny Koene⁵, Andrei Kirilyuk⁵, Theo Rasing⁵, Vasyl Tiberkevich⁶, Andrei Slavin⁶

¹ Institute for Applied Physics and Center for Nanotechnology, University of Muenster, 48149 Muenster, Germany

² School of Electrical Engineering and Computer Science, Oregon State University, Oregon 97331, USA

³ Kotelnikov Institute of Radio-engineering and Electronics of RAS, 11-7 Mokhovaya street, Moscow, 125009, Russia

⁴ Institute of Metal Physics, Ural Division of RAS, Yekaterinburg 620041, Russia

⁵ Radboud University Nijmegen, Institute for Molecules and Materials, 6525 AJ Nijmegen, The Netherlands

⁶ Department of Physics, Oakland University, 146 Library Drive, Rochester, Michigan, 48309-4479, USA

* ivan.lisenkov@phystech.edu

Abstract

Bose-Einstein condensate of magnons (mBEC) that is formed at room temperature in parametrically pumped magnetic films is double-degenerate: it is formed simultaneously in two spectral minima corresponding to the lowest energy magnons propagating in opposite directions along the in-plane bias magnetic field. In this work the interactions of magnons in the mBEC are studied both theoretically and experimentally. It is shown by direct calculation that the magnons residing in each of the degenerate spectral minima of mBEC form a practically ideal magnon gas, as the attractive self-interaction between these magnons is very weak. At the same time, the interaction between the magnons residing in different spectral minima, corresponding to the opposite directions of the magnon wave vector, is relatively strong and repulsive, leading to a repulsive total inter-magnon interaction. By measuring the spectral characteristics of the mBEC it is shown, that with the increased magnon density the energy per magnon in the mBECs increases, thus confirming experimentally that the net inter-magnon interaction in a double-degenerate mBEC is repulsive.

I. Introduction

Bose-Einstein condensate (BEC) is a system of (quasi-) particles, where most of the particles occupy a single quantum state in the momentum space [1, 2]. During the last 20 years BEC was observed in many kinds of gases, consisting of different real atoms, as well as of quasi-particles, namely, polaritons [3, 4], excitons [5], or magnons. In particular, BEC of magnons (mBEC) was observed in ³He super-fluid at extremely low temperatures [6], **quantum magnets**

[7], and in ferrite films at room temperature [8-11]. It was found that microwave magnons created by external parametric pumping after thermalization form a state of coherent precession with a phase and frequency independent on the external pumping signal.

In the process of a BEC the density of quasi-particles drastically increases [11], and the interactions between the quasi-particles start to play an important role in the dynamics of the BEC. Usually, the interaction between atoms in BEC is described in a "hard-spheres" model, introducing a non-linear energy term in the Hamiltonian in a form [12-14]:

$$W_{\text{int}}(\mathbf{r}'-\mathbf{r}) = \frac{4\pi\hbar^2 a}{m} \delta(\mathbf{r}'-\mathbf{r}) = g\delta(\mathbf{r}'-\mathbf{r}) \quad (1)$$

where m is the particle mass and a is the "scattering length"[14]. The inter-particle interaction coefficient g [12] (called in wave physics a "nonlinear coefficient") is directly related to the scattering length a . This coefficient g defines both the strength and the character of the inter-particle interaction. If $g < 0$, the interaction is attractive (while if $g > 0$ it is repulsive), meaning that the addition of particles into the same volume decreases (increases) the energy per particle in the BEC. For BEC of atoms the change of sign of the scattering length a (and coefficient g) from positive to negative results in a global collapse of an untapped condensate [15, 16]. In fact, the discovery of the Feshbach resonance [17] has recently opened a way to study quantum liquids and coherent states of matter in widely varying circumstances with positive, negative, and zero values of the scattering length a (and, correspondingly, of g) in a single experiment [18, 19]. The potential (1) can still be used for modeling the interaction between the quasi-particles, but in the case of quasi-particles the mass m denotes an effective mass of a quasi-particle. The effective quasi-particle mass can be negative (e.g. in periodic potentials [4]), but regardless of the sign of the effective mass, the sign of the interaction coefficient g defines whether the interaction is attractive or repulsive, and, therefore, serves as a good indicator of the possibility of the BEC collapse.

At the same time, it is well known, that the interaction between magnons in relatively thick ferromagnetic films is attractive [20]. Thus, the energy per particle of the condensate should decrease with increasing density, which, in principle, should lead to a collapse of the mBEC [12]. However, in the experiments [8-11], the observed mBEC was stable. A possible explanation to this contradiction can be found by taking into account an important peculiarity of the mBEC: the magnonic spectrum in an in-plane magnetized film has two degenerate minima with the wave numbers k_{BEC} and $-k_{\text{BEC}}$, see Fig. 1. Under a parametric excitation [8-11, 20] magnons have an equal probability to populate both minima forming *two* mBECs simultaneously. The nonlinear dynamics in this mixture of two mBEC is determined not only by the magnon self-action (which is attractive), but also by the mutual interaction (cross-interaction) of magnons in both minima.

Indeed, if this cross-interaction is repulsive and strong, then, under certain conditions, it can become more important than the attractive self-action, leading to the resultant repulsion between the interacting magnons, and increase of the energy per particle in both condensates [21, 22]. Fortunately, in the case of a magnon BEC by measuring the mBEC frequency with the increasing BEC density it is possible to directly access the energy of magnons in the mBEC [23], and check this hypothesis.

Calculations show, however, that this nonlinear frequency shift is quite low ($\delta\omega/(2\pi) \approx 3\text{MHz}$) at the mBEC frequency of $\omega/(2\pi) \approx 6\text{GHz}$. To check experimentally the above presented hypothesis of the dominant role of the cross-interaction between magnons with opposite wave vectors in the nonlinear frequency shift of mBEC we build a setup based on the recently developed heterodyne technique which employs magneto-optical Kerr-effect [24]. This novel technique has the frequency resolution of $\delta\omega/\omega = 10^{-8}$, which is sufficient to reliably detect the expected frequency shift of mBEC. Using this setup we measured the frequency of the mBEC while varying the pumping power, and found that the frequency of mBEC linearly increases with the pumping power (proportional to the magnon density), confirming the repulsive nature of the resultant inter-magnon interaction in the mBEC.

II. Theory of magnon interactions in mBEC

We consider a BEC of magnons residing in two spectral minima and having the wave vectors k_{BEC} and $-k_{\text{BEC}}$. This system can be considered as a gas made of particles of two different kinds (species) [12, 25]. The dynamics of such a two-component BEC can be understood using the same model of "hard spheres", but assuming that the interaction coefficients are different for the particles of different kinds: $W_{\text{int}}^{i,j}(\mathbf{r}-\mathbf{r}') = g^{i,j} \delta(\mathbf{r}-\mathbf{r}')$, where $i, j = \{1, 2\}$. In particular, the case of an untrapped BEC formed from a two-component gas of interacting particles (or quasi-particles) can be described by equations of coupled harmonic oscillators, which in the representation of second quantization have the form [11]:

$$\begin{aligned} i\hbar\dot{b}_1 &= \left(\hbar\omega_0 + g \frac{b_1^* b_1}{V} + 2g^{12} \frac{b_2^* b_2}{V} \right) b_1, \\ i\hbar\dot{b}_2 &= \left(\hbar\omega_0 + g \frac{b_2^* b_2}{V} + 2g^{12} \frac{b_1^* b_1}{V} \right) b_2, \end{aligned} \quad (2)$$

where b_i is the complex amplitudes of (quasi)-particles of the kind i , normalized by the condition $b_i^* b_i = N_i$, N_i is the number of particles of the i -th type, ω_0 is the lowest frequency of the single-particle spectrum, V is the volume occupied by the two-component BEC.

The presence of a interaction between the particles in the BEC results in the change of the net energy per particle in the system, which can be measured experimentally. Assuming that the two-component BEC is spatially uniform with the density $\rho_i = b_i^* b_i / V = \rho$ it is possible to evaluate the nonlinear frequency shift of the two-component BEC as:

$$\delta\omega = \omega - \omega_0 = (g / \hbar)\rho + (2g^{12} / \hbar)\rho. \quad (3)$$

Thus, if $g^{12} > 0$ and $g^{12} \gg |g|$ the net energy per particle $E = \hbar\omega$ increases with the increase of the BEC density, and the collapse of BEC is avoided.

Magnons in a mBEC interact with each other in the nonlinear processes that conserve both energy and linear momentum [20]. Thus, we are interested only in the processes between the magnons either having the same wavevector $k, k \rightarrow k, k$ ($g(k)$ self-interaction of magnons in one spectral minimum), or having opposite wavevectors $k, -k \rightarrow k, -k$ ($g^{12}(k)$ cross-interaction of magnons belonging to different spectral minima). To calculate the magnon-magnon interaction coefficients $g(k)$ and $g^{12}(k)$ we used a standard Hamiltonian approach [20-22, 25-27] (see Supplementary Materials [28] for details). For relatively large magnon wavenumbers k corresponding to the spectral minima, where the BEC of magnons is **formed** (note, that these wave numbers are still substantially smaller than the reciprocal vectors of the YIG crystal lattice) the magnetization precession has a practically circular polarization. In this approximation, it is possible to obtain the following approximate expressions for the above coefficients, describing magnons in the in-plane magnetized magnetic film, in a simple analytical form:

$$\begin{aligned} g(k) &\approx -\frac{\omega_0(k) - \omega_H}{\omega_M} \mu_0 \hbar^2 \gamma^2, \\ 2g^{12}(k) &\approx (4\lambda_{\text{ex}}^2 k^2 + Q(2k)) \mu_0 \hbar^2 \gamma^2 + g(k), \end{aligned} \quad (4)$$

where $\omega_0(k)$ is the dispersion of magnons in the fundamental (uniform along the film thickness) mode, $\omega_M = \gamma \mu_0 M_s$, M_s is the saturation magnetization of the ferromagnetic film, $\omega_H = \gamma \mu_0 H$, H is the applied magnetic field, γ is the gyromagnetic ratio, λ_{ex} is the exchange length, $Q(k) = (-1 + kL + e^{-kL})/(kL)$ in the matrix element of the dipole-dipole interaction, and L is the film thickness. More accurate full expressions for these coefficients that take into account the real elliptical polarization of the magnetization precession are provided in the Supplemental Materials [28], and the wave number dependences of these more accurately calculated coefficients are presented in Fig. 2.

It is clear from Eq. (4) and Fig. 2 that the self-action coefficient $g(k)$ is negative in the full interval of the magnon wave number variation, since $\omega_0(k) > \omega_H$ (see Fig. 1), so the interaction between the magnons belonging to the same spectral minimum is always attractive. At the point of the BEC formation, this attractive interaction is, however, *very weak*, making the single-component magnon gas practically *ideal*.

In contrast, the coefficient of interaction $g^{12}(k)$ between the magnons belonging to different spectral minima behaves in a different way: it changes sign from negative to positive with the increase on the magnon wavenumber. In particular, at the point $k = k_{\text{BEC}}$, where the mBEC is formed, the coefficient $g^{12}(k)$ is positive, and is much larger than $g(k)$. Thus, the strong repulsive interaction between the magnons belonging to different spectral minima with the wave numbers k_{BEC} and $-k_{\text{BEC}}$ is dominant in this two-component mBEC, and determines the overall nonlinear behavior of the mBEC. It is also worth noting, that the magnitude of the self-action coefficient $g(k)$ rapidly increases when the magnon wavenumber is shifted away from the spectral minima. This increased inter-magnon interaction is the origin of the strong four-magnon scattering leading to a fast thermalization of magnons, which is necessary for the formation of BEC in a gas of parametrically pumped magnons in the first place [8, 9, 11].

For a typical density of a mBEC of $\rho = 5 \times 10^6 \mu\text{m}^{-3}$ [11, 29] the frequency shift associated with the magnon self-action is $g(k_{\text{BEC}})\rho / (2\pi) \approx -0.14 \text{ MHz}$, which is comparable to the intrinsic linewidth of magnons in a ferrite (YIG) film. At the same time, the coefficient $g^{12}(k)$, describing the cross-interaction between the different components of the magnon BEC, is positive and has a significant magnitude, thus totally dominating the nonlinear dynamics of magnons in a two-component BEC of magnons. The frequency shift associated with this cross-interaction is $2g^{12}(k)\rho / (2\pi) \approx 3.0 \text{ MHz}$.

Thus, by a direct measurement of the nonlinear frequency shift of the magnon BEC one can check the above presented hypothesis, and find out experimentally whether the cross-interaction of magnons belonging to the two spectral minima in the magnon BEC is, indeed, repulsive and dominant. **The absolute value of the measured nonlinear frequency shift is proportional to the magnon density (3), which cannot be measured directly and independently with a sufficient accuracy. However, (i) the magnon density was estimated previously by measuring the chemical potential in mBEC [29], and (ii) the interaction coefficients describing the self- and cross- interaction between the magnons existing in condensates with positive k_{BEC} and negative $-k_{\text{BEC}}$ wave vectors have a different signs. Thus, their effect on the total experimentally measured nonlinear frequency shift can be elucidated from the qualitative behavior of this shift (positive or negative).**

III. Experimental measurement of the nonlinear frequency shift in mBEC

The above predicted magnitudes of the nonlinear frequency shifts of a magnon BEC are rather small: they constitute only a small fraction $\delta\omega / \omega \approx 10^{-4}$ of the BEC frequency ω corresponding to the degenerate magnon spectral minima. The measurement of such a small frequency shift for magnons having rather large wavenumber constitutes a very challenging experimental problem, since the traditional high-frequency-resolution microwave spectroscopy is not sensitive to magnons with large wavenumbers. The state-of-the-art Brillouin light scattering (BLS) setups, while having a very high amplitude sensitivity, usually, have a frequency resolution of upward of 50 MHz [7, 29], which is definitely not sufficient for the studies of such delicate nonlinear effects. To meet this experimental challenge, we used a recently developed heterodyne magneto-optical Kerr-effect (MOKE) frequency detection technique [23] (see Fig. 4(a)).

The schematic of the experimental setup, (described in detail in [23]), is shown in Fig. 3(a). A microstrip-based microwave resonator parametrically pumps magnons in an YIG film. The sample is placed in a static magnetic field H . Linearly polarized laser pulses with a wavelength of 490 nm (after frequency doubling), a duration of 100 fs, and a highly stabilized repetition frequency $\omega_L / (2\pi) = 82.379 \text{ MHz}$ are focused onto the sample near the pumping resonator. **The Bose-Einstein condensation of magnons in ferromagnetic films takes place for the magnons having wavenumbers $k_{\text{BEC}} \approx 5 \times 10^4 \text{ cm}^{-1}$. This range of magnon wave numbers is fully accessible for the experimental technique of Brillouin Light Scattering with the light wavelength**

of 490 nm [10, 23, 29]. After passing through the sample, the light is sent through the second polarizer (analyzer), and directed to a photomultiplier with a frequency band of about 100 MHz. The output electronic signal is analyzed by a radio-frequency spectrum analyzer. The YIG film used in our experiments was fabricated by liquid phase epitaxy on a gadolinium gallium garnet (GGG) substrate. Both materials (YIG and GGG) are optically transparent, which allowed us to analyze the translucent light beam. The collection optic elements are mounted on a rotational arm with the rotation axis at the condensate position, which enables detection and analysis of light scattered by the magnons with the wave number $k_{\text{BEC}} = 5 \times 10^4 \text{ cm}^{-1}$. Due to the MOKE, the output light becomes modulated in amplitude with the frequency of the detected magnons $\omega(k)$, which is superimposed with the repetition frequency ω_L . The Fourier spectrum of the output signal consists of the equidistant harmonics $n\omega_L$ each of them having two (Stokes and anti-Stokes) satellites with frequency shifts $n\omega_L \pm \Delta\omega$, of $\Delta\omega = |\omega(k) - N\omega_L|$ with N being the nearest integer to $\omega(k)/\omega_L$. Thus, a standard heterodyne scheme is used to reach a resolution of $\delta\omega/(2\pi) \approx 100 \text{ Hz}$, as demonstrated by independent experiments [23] (see inset in Fig. 3(a)).

To obtain the information on the nonlinear frequency shift of the BEC, several spectra were recorded at a constant magnetic field of $H_0 = 113.91 \text{ kA/m}$, but for different values of the pumping power P_p , see Fig. 4(b). It is clear from Fig. 3(b) that the central frequency of the signal obtained from the magnons situated in the spectral minimum, at first, drops with increasing power, but at a certain threshold power of $P_{\text{th}} \approx 19 \text{ mW}$ it starts to increase, as demonstrated in Fig. 4(a) in detail. The initial drop in the magnon frequency is connected with the fact that before the condensation of magnons starts to happen, the chemical potential of the magnon gas raises, and the particle-energy distribution in a gas of magnons changes, resulting in a continuously increasing population of the states close to the spectral minima [8].

Then, for $P > P_{\text{th}}$, the BEC of magnons is formed, so the magnons become “densely packed” near the spectral minima, and the interactions between them start to strongly influence the magnon frequency and play a significant role in the magnon dynamics. Although the exact quantitative relation between the pumping power and the density of the mBEC strongly depends on the experimental details, it has been shown in previous experiments performed at similar moderate magnitudes of the pumping power, that the BEC density is approximately proportional to $P_p - P_{\text{th}}$, if $P_p > P_{\text{th}}$ [21]. It is seen from Fig. 4(a) that the measured magnon frequency shift for $P_p > P_{\text{th}}$ increases linearly with the pumping power, therefore confirming the theoretical dependence (3) and (4). On the other hand, the magnon-magnon interaction should also increase the linewidth of the fundamental magnonic mode [30]. The measured dependence of the magnon linewidth on the pumping power is shown in Fig. 4(b). Indeed, before the threshold power P_{th} of the BEC formation, the linewidth of the magnon mode drops with the increase of power, but, above the BEC threshold it starts to increase due to the BEC nonlinearity. It is important to note, that the qualitative change of slope in the power dependences of both the magnon nonlinear frequency shift and the magnon linewidth takes place *at the same magnitude* of the pumping power, leaving a “smoking gun” of both the formation of a magnon BEC at this power and the appearance of a strong repulsive interaction between the magnons residing in the two degenerate spectral minima.

IV. Discussion and conclusions

The above presented theory and experiment clearly demonstrate that the per particle energy of a mBEC increases with the magnon density. Thus the mBEC cannot collapse explosively with a rapid increase of the magnon density. However, other types of instabilities can take place in the mBEC.

In this paper we considered magnon-magnon interactions of a spatially uniform mBECs. The underlying physics and, in particular, the mBEC stability analysis become much more complicated if a possible spatial non-uniformity of the magnon wave-function in the mBEC is taken into account. In particular, the repulsive cross-interaction between the magnons residing in the degenerate spectral minima can lead to the phase separation in a multi-component BEC [31, 32]. Such a phase separation can lead to the formation of “domains” of magnons with different density of magnons having opposite wave numbers, and, as a consequence, to the reduction of the per-particle energy. A strong phase separation of magnons in mBEC is not observed in our experiments with spatial resolution [33,34], possibly because the relaxation time for magnons ($0.5\mu s$ for YIG) is of the same order as the phase-separation time ($2\pi / \delta\omega = 0.3\mu s$), and the pronounced domains cannot be formed under a relatively low pumping rate used in our experiments.

In general, the detailed information about the properties of the BEC of magnons at room temperature can be found in the review chapter [35].

In conclusion, we studied both theoretically and experimentally interaction of magnons in magnonic condensate. We were able to show that the repulsive interaction existing between the magnons with opposite wave vectors residing in two degenerate spectral minima of mBEC is dominant in comparison to the weak attractive self-action of magnons residing in each of the spectral minima.

Using a novel measurement setup, that combines the magneto-optical Kerr-effect (MOKE) with a homodyne detection technique and provides a record-high frequency resolution, we experimentally measured the nonlinear frequency shift and the linewidth of the mBEC at room temperature, and confirmed experimentally that the energy of the mBEC increases with the increase of the pumping power creating the microwave magnons in the studied system.

This work was supported in part by the Deutsche Forschungsgemeinschaft, the program Megagrant № 14.Z50.31.0025 of the Russian Ministry of Education and Science, the Russian Scientific Foundation under the Grant #14-19-00760, by the National Science Foundation of the USA (EFMA-1641989, ECCS-1708982), by a grant from DARPA, and by a grant from the Center for NanoFerroic Devices (CNFD) and Nanoelectronics Research Initiative (NRI), This work was also supported by the Foundation for Fundamental Research on Matter (FOM), de Nederlandse Organisatie voor Wetenschappelijk Onderzoek (NWO), the European Unions Seventh Framework Program (FP7/2007-2013) grant No. 281043 (FemtoSpin) and the European Research Council grant No. 339813 (Exchange).

References

- [1] A. Einstein. Quantentheorie des einatomigen idealen gases. *Sitzungsberichte der Preussischen Akademie der Wissenschaften 1914-1932*, pages 237–244, Sep 1925.
- [2] S. N. Bose. Plancks Gesetz und Lichtquantenhypothese. *Zeitschrift für Physik*, 26(1):178-181, Dec 1924.
- [3] J. Kasprzak, M. Richard, S. Kundermann, A. Baas, P. Jeambrun, J. M. J. Keeling, F. M. Marchetti, M. H. Szymanska, R. Andre, J. L. Staehli, and et al. Bose–Einstein condensation of exciton polaritons. *Nature*, 443(7110):409–414, Sep 2006.
- [4] D. N. Krizhanovskii, E. A. Cerda-Mendez, S. Gavrilov, D. Sarkar, K. Guda, R. Bradley, P. V. Santos, R. Hey, K. Biermann, M. Sich, and et al. Effect of polariton-polariton interactions on the excitation spectrum of a nonequilibrium condensate in a periodic potential. *Physical Review B*, 87(15):155423, Apr 2013.
- [5] L. V. Butov, C. W. Lai, A. L. Ivanov, A. C. Gossard, and D. S. Chemla. Towards Bose–Einstein condensation of excitons in potential traps. *Nature*, 417(6884):47–52, May 2002.
- [6] A. S. Borovik-Romanov, Yu. M. Bunkov, V. V. Dmitriev, Yu. M. Mukharskiy, *JETP Lett.* (40):1033 (1984).
- [7] V. Zapf, M. Jaime, and C. D. Batista Bose-Einstein condensation in quantum magnets. *Rev. Mod. Phys.* 86, 563 May 2014
- [8] S. O. Demokritov, V. E. Demidov, O. Dzyapko, G. A. Melkov, A. A. Serga, B. Hillebrands, and A. N. Slavin. Bose–Einstein condensation of quasi-equilibrium magnons at room temperature under pumping. *Nature*, 443(7110):430–433, Sep 2006.
- [9] A. A. Serga, V. S. Tiberkevich, C. W. Sandweg, V. I. Vasyuchka, D. A. Bozhko, A. V. Chumak, T. Neumann, B. Obry, G. A. Melkov, A. N. Slavin, and B. Hillebrands. Bose–Einstein condensation in an ultra-hot gas of pumped magnons. *Nature Communications*, (5): 3452, Mar 2014
- [10] D. A. Bozhko, A. A. Serga, P. Clausen, V. I. Vasyuchka, F. Heussner, G. A. Melkov, A. Pomyalov, V. S. Lvov and B. Hillebrands, *Nature Physics* (12): 1057 2016
- [11] O. Dzyapko, V. E. Demidov, S. O. Demokritov, G. A. Melkov, and A. N. Slavin. Direct observation of Bose–Einstein condensation in a parametrically driven gas of magnons. *New Journal of Physics*, 9(3):64–64, Mar 2007.
- [12] L. Pitaevskii and S. Stringari. *Bose–Einstein Condensation (International Series of Monographs on Physics)*. Clarendon Press, 2003.
- [13] L. P. Pitaevskii. Vortex lines in an imperfect bose gas. *JETP Letters*, 13(2):451–454, Aug 1961.
- [14] F. Dalfovo, S. Giorgini, L. P. Pitaevskii, and S. Stringari. Theory of Bose–Einstein condensation in trapped gases. *Rev. Mod. Phys.*, 71(3):463–512, Apr 1999.
- [15] Yu. Kagan, A. Muryshev, and G. Shlyapnikov. Collapse and Bose-Einstein condensation in a trapped Bose gas with negative scattering length. *Physical Review Letters*, 81(5):933–937, Aug 1998.
- [16] J. L. Roberts, N. R. Claussen, S. L. Cornish, E. A. Donley, E. A. Cornell, and C. E. Wieman. Controlled collapse of a Bose-Einstein condensate. *Physical Review Letters*, 86(19):4211–4214, May 2001.
- [17] S. Inouye, M. R. Andrews, J. Stenger, H.-J. Miesner, D. M. Stamper-Kurn, and W. Ketterle. Observation of Feshbach resonances in a Bose–Einstein condensate. *Nature*, 392(6672):151–154, Mar 1998.

- [18] Ph. Courteille, R. S. Freeland, D. J. Heinzen, F. A. van Abeelen, and B. J. Verhaar. Observation of a feshbach resonance in cold atom scattering. *Physical Review Letters*, 81(1):69–72, Jul 1998.
- [19] J. L. Roberts, N. R. Claussen, James P. Burke, Chris H. Greene, E. A. Cornell, and C. E. Wieman. Resonant magnetic field control of elastic scattering in cold rb85. *Physical Review Letters*, 81(23):5109–5112, Dec 1998.
- [20] V. S. L'vov. Wave turbulence under parametric excitation. *Springer Series in Nonlinear Dynamics*, 1994.
- [21] I.S. Tupitsyn, P.C.E. Stamp, and A.L. Burin, Stability of Bose-Einstein Condensates of Hot Magnons in Yttrium Iron Garnet Films, *Phys Rev Lett* 100: 257202, 2008
- [22] F. Li, W. M. Saslow and V. L. Pokrovsky, Phase Diagram for Magnon Condensate in Yttrium Iron Garnet Film *Scientific Reports* 3, 1372 (2013)
- [23] Yu. Bunkov, Magnon BEC Versus Atomic BEC *J. Low Temp. Phys.*, 183:399, 2016.
- [24] O. Dzyapko, P. Nowik-Boltyk, B. Koene, V. E. Demidov, J. Jersch, A. Kirilyuk, T. Rasing, and S. O. Demokritov. High-resolution magneto-optical kerr-effect spectroscopy of magnon Bose–Einstein condensate. *IEEE Magnetics Letters*, 7:1–5, 2016.
- [25] S. Hooley and K. A. Benedict. Dynamical instabilities in a two-component Bose–Einstein condensate in a one-dimensional optical lattice. *Physical Review A*, 75(3):033621, Mar 2007.
- [26] A.N. Slavin and I.V. Rojdestvenski. ``bright" and ``dark" spin wave envelope solitons in magnetic films. *IEEE Transactions on Magnetics*, 30(1):37–45, 1994.
- [27] Pavol Krivosik and Carl E. Patton. Hamiltonian formulation of nonlinear spin-wave dynamics: Theory and applications. *Physical Review B*, 82(18):184428, Nov 2010.
- [28] See Supplemental Material at [URL will be inserted by publisher] for the Hamiltonian formalism used to derive Eq (4) and obtain curves plotted in Fig. 2.
- [29] O. Dzyapko, V. E. Demidov, S. O. Demokritov, G. A. Melkov, and A. N. Slavin *J. of Appl. Phys.* 101, 09C103 (2007);
- [30] S.O. Demokritov and V.E. Demidov. Micro-brillouin light scattering spectroscopy of magnetic nanostructures. *IEEE Transactions on Magnetics*, 44(1):6–12, Jan 2008.
- [31] A. Slavin and V. Tiberkevich. Nonlinear auto-oscillator theory of microwave generation by spin-polarized current. *IEEE Transactions on Magnetics*, 45(4):1875–1918, Apr 2009.
- [32] Y. Li, L.P. Pitaevskii, and S. Stringari, Quantum Tricriticality and Phase Transitions in Spin-Orbit Coupled Bose-Einstein Condensates, *Phys. Rev. Lett.* 108:225301, 2012
- [33] F. Li, W. M. Saslow and V. L. Pokrovsky Phase Diagram for Magnon Condensate in Yttrium Iron Garnet Film. *Scientific Reports* 3: 1372, 2013
- [34] P. Nowik-Boltyk, O. Dzyapko, V. E. Demidov, N. G. Berloff, and S. O. Demokritov. Spatially non-uniform ground state and quantized vortices in a two-component Bose–Einstein condensate of magnons. *Scientific Reports*, 2, Jun 2012.
- [35] O. Dzyapko, V. E. Demidov, S. O. Demokritov, G. A. Melkov, and A. N. Slavin, “ Bose–Einstein condensation of magnons at room temperature”, Chapter 20 in the book “ Novel Superfluids: Vol. 2 “, Karl-Heinz Bennemann and John Ketterson (Eds.), Oxford University Press 2014, ISBN-13: 9780198719267.

Figures

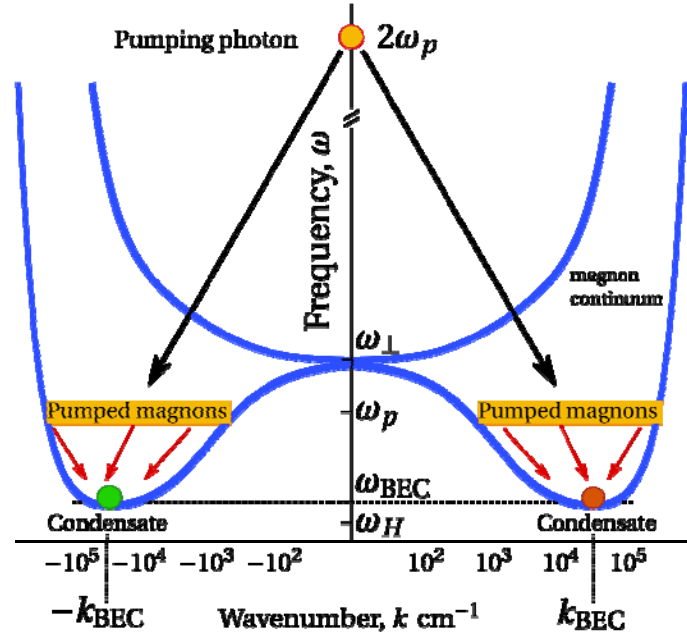


Figure 1: Schematic representation of the magnon dispersion $\omega_0(k)$ in an in-plane magnetized magnetic film for magnons propagating along the bias magnetic field (backward volume magnetostatic wave geometry) illustrating formation of a two-component BEC of magnons in the two degenerate spectral minima. Parametric pumping at the frequency $2\omega_p$ excites magnons of the frequency ω_p in the magnon spectrum (orange shaded areas in the plot), which, due to the thermalization in a magnon gas form a two-component BEC at the spectral minima with wavenumbers $\pm k_{\text{BEC}}$ and the same frequency ω_{BEC} , indicated by green and red dots. Here $\omega_H = \gamma\mu_0 H$, $\omega_{\perp} = \sqrt{\omega_H(\omega_H + \omega_M)}$, $\omega_M = \gamma\mu_0 M_s$, γ is the gyromagnetic ratio, H is the applied magnetic field, and M_s is the saturation magnetization.

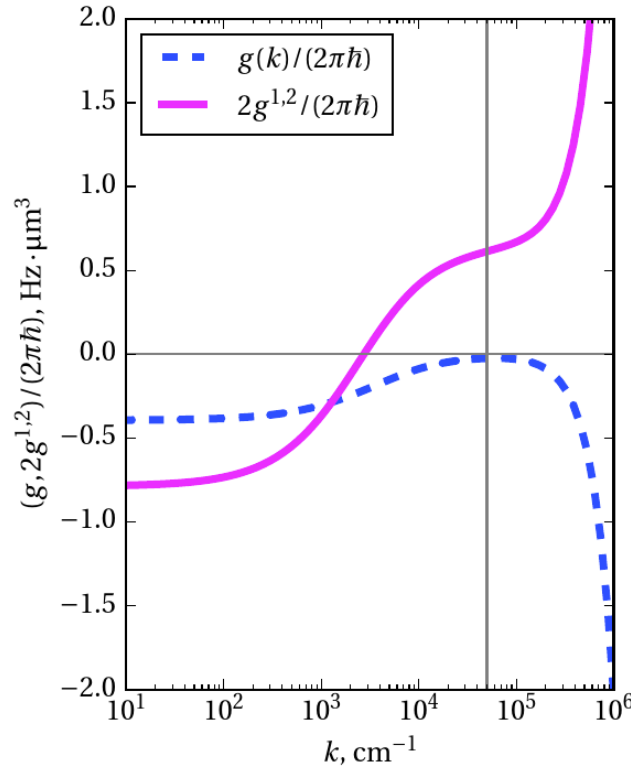


Figure 2: Magnon interaction coefficients versus wavenumbers: $g(k)$ - describing the self-action of magnons inside one of the spectral minima (dashed blue curve), and $g^{1,2}(k)$ - describing the interaction of magnons with opposite wave vectors and belonging to different spectral minima (see Fig. 1). The nonlinear coefficients are presented in the units of frequency.

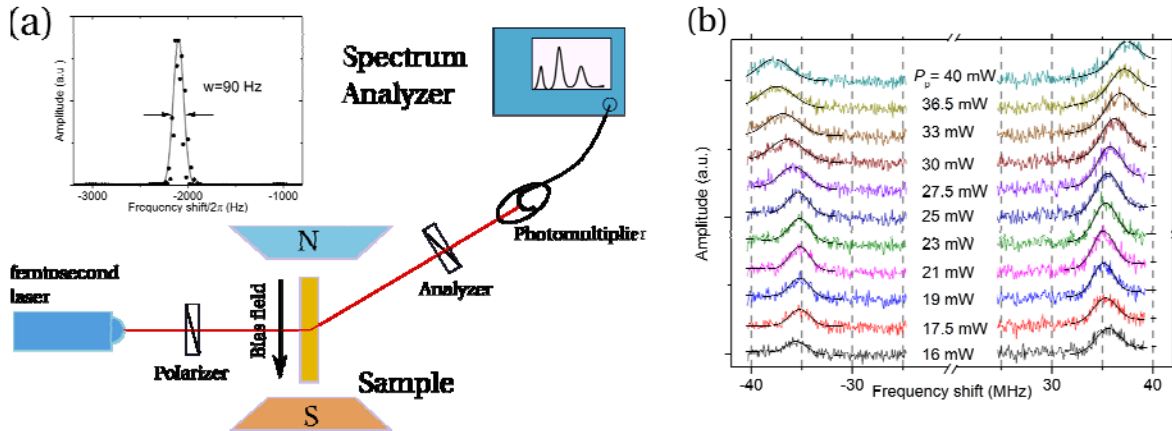


Figure 3: (a) Experimental setup. A beam from a femtosecond laser is focused on a ferrite film magnetized by an electromagnet. The scattered light is collected by a photomultiplier, and the output signal is analyzed by a spectrum analyzer. The inset shows a measured reference spectrum with the linewidth of 90 Hz; (b) Measured spectra of the magnonic BEC for different values of the pumping power. Solid black lines indicate fitting done for revealing the frequency.

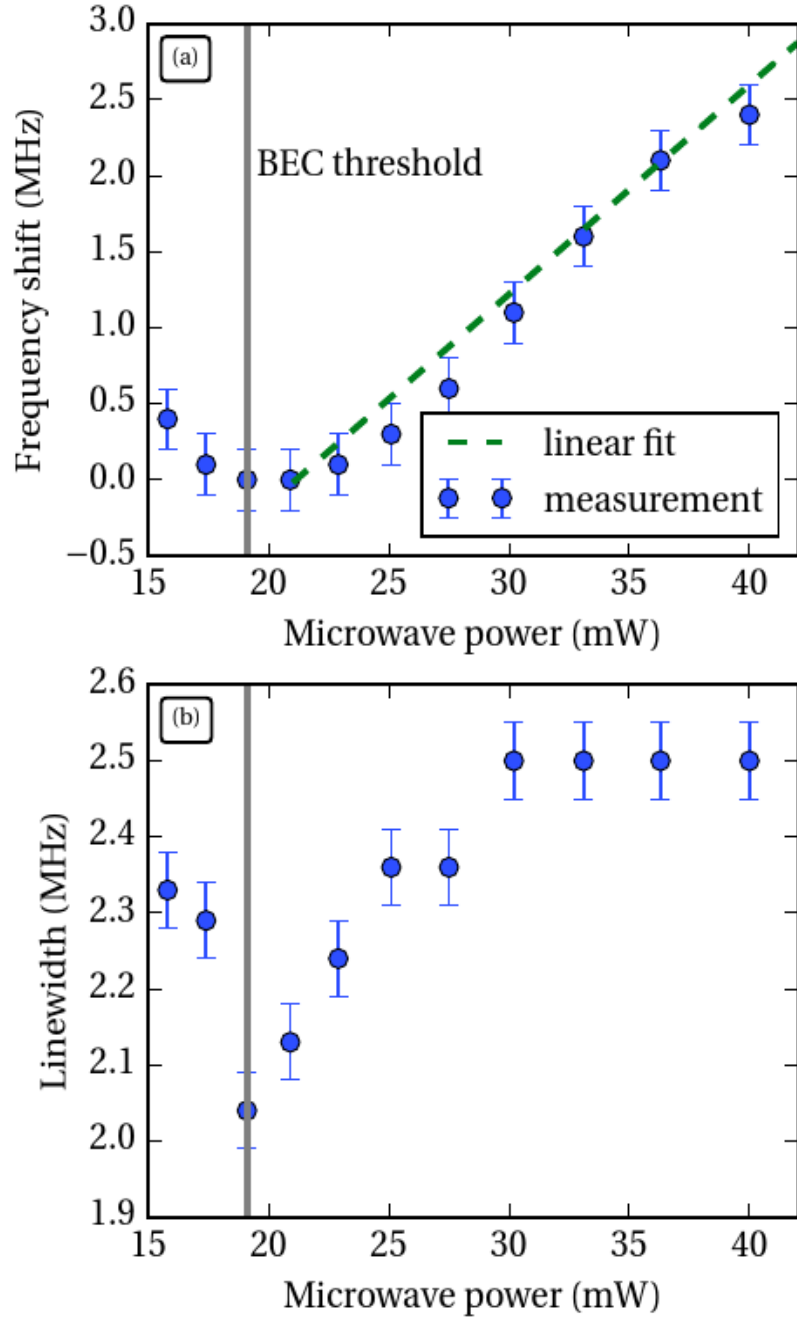


Figure 4: Measured frequency shift (a) and linewidth (b) of the magnonic BEC as a function the pumping power (dots). The gray line corresponds to the threshold power of the BEC formation, green dashed line is a linear trend for the frequency dependence on the pumping power in the super-critical regime $P_p > P_{th}$.