



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Effect of anti-site disorder on magnetism in $\text{La}_{2}\text{NiMnO}_{6}$

Somnath Pal, Sharada Govinda, Manik Goyal, Soham Mukherjee, Banabir Pal, Rana Saha, A. Sundaresan, Somnath Jana, Olof Karis, John W. Freeland, and D. D. Sarma

Phys. Rev. B **97**, 165137 — Published 25 April 2018

DOI: [10.1103/PhysRevB.97.165137](https://doi.org/10.1103/PhysRevB.97.165137)

# Effect of anti-site disorder on magnetism in $\text{La}_2\text{NiMnO}_6$

Somnath Pal,<sup>1</sup> Sharada Govinda,<sup>1</sup> Manik Goyal,<sup>1</sup> Soham Mukherjee,<sup>1</sup> Banabir Pal,<sup>1</sup> Rana Saha,<sup>2</sup> A. Sundaresan,<sup>2</sup> Somnath Jana,<sup>3</sup> Olof Karis,<sup>3</sup> John W. Freeland,<sup>4</sup> and D. D. Sarma<sup>1,\*</sup>

<sup>1</sup>*Solid State and Structural Chemistry Unit,*

*Indian Institute of Science, Bengaluru 560012, India*

<sup>2</sup>*Jawaharlal Nehru Centre for Advanced Scientific Research, Jakkur, Bengaluru 560064, India*

<sup>3</sup>*Molecular and Condensed Matter Physics,*

*Department of Physics and Astronomy,*

*Uppsala University, Box 516, 75120 Uppsala, Sweden*

<sup>4</sup>*Argonne National Laboratory, Argonne, IL 60439, USA*

(Dated: February 20, 2018)

## Abstract

$\text{La}_2\text{NiMnO}_6$  has been reported to exhibit a paramagnetic to ferromagnetic transition with a transition temperature of  $\sim 260$  K. However, most of its magnetic properties, such as the saturation magnetization and even the transition temperature, appear to vary considerably among different reports. This is possibly because the crystallographic structure as well as the extent of the anti-site disorder (ASD) at the Ni/Mn sites are strongly influenced by the choice of synthesis routes. There are diverse reports connecting the extent of ASD to the valencies of Ni and Mn ion, such as,  $\text{Ni}^{2+} - \text{Mn}^{4+}$  and  $\text{Ni}^{3+} - \text{Mn}^{3+}$  including suggestions of thermally induced valence transitions. Consequently, these reports arrive at very different conclusions on the mechanism behind magnetic properties of  $\text{La}_2\text{NiMnO}_6$ . To address the correlation between ASD and valency, we have carried out a comparative study of two monoclinic  $\text{La}_2\text{NiMnO}_6$  polycrystal with different degrees of ASD. Using a combination of x-ray absorption spectroscopy, x-ray magnetic circular dichroism and magnetometry, we conclude that the valency of the transition metal ions, and the transition temperature are insensitive to the extent of ASD. However, we find the magnetic moment decreases strongly with an increasing ASD. We attribute this effect to the introduction of antiferromagnetic interactions in the anti-site disordered regions.

## INTRODUCTION

$\text{La}_2\text{NiMnO}_6$  is a ferromagnetic insulating double-perovskite, that has been widely investigated over the last decade<sup>1-11</sup>.  $\text{La}_2\text{NiMnO}_6$  can form in two distinct crystallographic forms, a monoclinic  $P2_1/n$  structure or in a rhombohedral  $R\bar{3}$  structure. The unusual behaviour in magnetic and dielectric properties of this material in nano, thin film, single crystal and polycrystalline phases has attracted attention from many different groups<sup>8,12-19</sup>. It is found that the dielectric, magnetic, and the magnetoresistance properties of these compounds are closely coupled. The origin of unusual magnetic and magneto-electric behaviour have been extensively discussed in the literature, and there are many conflicting experimental results with widely varying explanations. As an example of the discrepancies found, we note that the field cooled (FC) and zero field cooled (ZFC) magnetic properties of  $\text{La}_2\text{NiMnO}_6$  as a function of temperature differs significantly between different reports<sup>20-24</sup>. These specific differences can most likely be attributed to different synthesis conditions used in these different works. Further, conflicting point of views have been reported in the literature regarding the valence state of the magnetic ions, Mn and Ni, and the origin of a magnetically ordered state. A ferromagnetic transition with a Curie temperature,  $T_C$ , of 280 K, was first reported and explained to be due to  $\text{Ni}^{3+}-\text{O}^{2-}-\text{Mn}^{3+}$  super-exchange interactions by Goodenough *et al.*<sup>25</sup>. Later, Blasse *et al.*<sup>26</sup> suggested that the super-exchange interaction in  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Mn}^{4+}$  causes the ferromagnetic ordering. Since then, there are many reports of favouring one or the other mechanism<sup>20,21,23,27-29</sup>. Though the valence states of the magnetic cations and the origin of magnetism have been discussed in many reports, the valency of Ni and Mn was only recently clarified in an x-ray absorption spectroscopy (XAS) study by Choudhury *et al.*<sup>8</sup>.

The origin of ferromagnetism has also been investigated with the help of  $^{55}\text{Mn}$  NMR<sup>30,31</sup>, neutron diffraction studies<sup>32</sup> and first principle calculations<sup>8,33</sup>. In ref. 33, it was furthermore concluded that the origin of ferromagnetism in  $\text{La}_2\text{NiMnO}_6$  is super-exchange mediated through the  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Mn}^{4+}$  interaction. There are also reports about two ferromagnetic transitions in a single system<sup>23,28</sup> - one at a higher temperature ( $T_C \sim 270$  K) and another at a lower temperature ( $\sim 100$  K). The latter was attributed to inhomogeneities in the sample with two phases ( $\text{Ni}^{2+}-\text{Mn}^{4+}$  and  $\text{Ni}^{3+}-\text{Mn}^{3+}$ ) having distinctly different electronic properties<sup>20,23,28,29</sup>.

In ref.<sup>8</sup>, the low temperature magnetic transition was identified to be glassy due to the presence of anti-site disorder (ASD) in the system. ASD leads to  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Ni}^{2+}$  and  $\text{Mn}^{4+}-\text{O}^{2-}-\text{Mn}^{4+}$  antiferromagnetic interactions resulting in magnetic frustration. Large magnetodielectric coupling<sup>1,8</sup>

was also observed near the room temperature in  $\text{La}_2\text{NiMnO}_6$  and was attributed to  $\text{Ni}^{2+}$  and  $\text{Mn}^{4+}$  cation ordering.

Based on the above mentioned literature, it becomes evident that ASD plays a major role in the magnetic, dielectric and magneto-dielectric properties. Thus, the understanding of ASD and the nature of magnetic interactions in ASD phase is important. The ASD has been suggested to give rise to antiferromagnetic interactions<sup>8</sup>, but there is no conclusive experimental verification so far. Ordered and disordered  $\text{La}_2\text{NiMnO}_6$  thin films were studied by Singh *et al.*, but their disordered sample exhibited a strongly lowered  $T_C$  compared to other studies<sup>23</sup>. The present study is aimed at eliminating all uncertainties regarding the role of ASD and valency of magnetic cations. This has been achieved by XAS, XMCD and magnetometry experiments performed on two monoclinic  $\text{La}_2\text{NiMnO}_6$  samples, but with a large difference in ASD.

## EXPERIMENTAL METHOD

$\text{La}_2\text{NiMnO}_6$  has been synthesized in its pure monoclinic phase using a sol-gel method, similar to Ref. 28. Stoichiometric amount of  $\text{La}_2\text{O}_3$ ,  $\text{Ni}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  and  $\text{MnCO}_3$  were dissolved in dilute nitric acid. Due to the hygroscopic nature of the rare earth oxide,  $\text{La}_2\text{O}_3$ , it was pre-heated at 900 °C for 12 hours to remove moisture from the precursor. Ethylene glycol and citric acid were added to the solution for chelation and gel formation, which ensured the completion of the reaction. The resulting solution was then heated at 170 °C to evaporate the solvents completely, giving a dark brown powder, which was subsequently heated at 450 °C for 6 hours. The obtained powder was again heated at 1350 °C in a flow of argon for 6 hours. Two different approaches were followed to cool the sample from this highest temperature in order to influence the extent of ordering between Mn and Ni sites by kinetically controlling the Mn/Ni ASD formation. In one case, the temperature of the sample was brought down in a controlled manner with a slow cooling rate of 1 °C/min. For the other sample, the furnace power supply was switched off to initiate the rapid cooling; average cooling rates in this case were  $\sim 14$  °C/min down to 1000 °C, 6 °C/min till 700 °C, and 3 °C/min till 300 °C. Our intention was to achieve a highly ordered sample with a slow cooling protocol and a considerably disordered sample with a rapid cooling. It is curious to note that exactly the opposite was achieved in reality, with first sample being disordered and the second ordered, as shall be shown later in the result section.

Crystal structure of the two  $\text{La}_2\text{NiMnO}_6$  samples were determined using powder X-ray diffrac-

tion (XRD) measurements with a Panalytical Philips diffractometer using Cu-K $\alpha$  radiation ( $\lambda = 1.54056 \text{ \AA}$ ). Rietveld refinements were performed to estimate structural parameters using the FULLPROF suite<sup>34</sup>. Field-cooled (FC) and zero field-cooled (ZFC) dc magnetization measurements were performed in the temperature range of 10 to 350 K in an applied field of 100 Oe using a Quantum Design SQUID magnetometer.

In order to characterise the valency of the transition metal cations, XAS measurements at the La  $M_{4,5}$ , Ni  $L_{2,3}$  and Mn  $L_{2,3}$  edges were performed at the I1011 beamline at MAX-lab, Sweden<sup>35</sup>. X-ray absorption spectra were recorded in the total electron yield (TEY) mode by recording the sample drain current as a function of the photon energy. The base pressure of the chamber was maintained at around  $7 \times 10^{-9}$  mbar. Sample surfaces were prepared by *in-situ* scraping of the samples with a diamond file prior to the XAS measurement. X-ray magnetic circular dichroism (XMCD) spectra were recorded at the 4-ID-C beamline, Advanced Photon Source (APS), ANL, USA. Each spectrum was simultaneously recorded in the more surface sensitive TEY mode and the more bulk-sensitive total fluorescence yield (TFY) mode, while applying a 5 kOe magnetic field and at a temperature of 150 K. All spectra were normalized by the photon flux.

## RESULTS AND DISCUSSIONS

In Fig. 1 (a) and (b), we show the recorded powder XRD data, together with the Rietveld refinement results, of the ordered and disordered samples, respectively. These results confirm the formation of both samples purely in monoclinic ( $P2_1/n$ ) phase without any rhombohedral ( $R\bar{3}$ ) phase as an impurity. The inset of Fig. 1 (a) exhibits a schematic illustration of monoclinic  $\text{La}_2\text{NiMnO}_6$ <sup>28</sup>. Ni and Mn are octahedrally coordinated with six oxygen atoms. The  $\text{NiO}_6$  and  $\text{MnO}_6$  corner-shared octahedra appear alternately in the fully-ordered unit cell, representing two sub lattices; anti site disorder represents a point defect with a Mn ion occupying a Ni site or vice versa. In absence of any vacancies, anti site disorder appears necessarily in pairs due to the interchange of positions of a pair of Ni and Mn ions. The Ni-Mn ordering related peak is expected to appear at  $2\theta \approx 20^\circ$  (see Fig. 1) with an intensity of 0.6% of the most intense peak at  $\sim 32^\circ$ ; this makes this feature masked by the background signal. Moreover, the maximum change expected in this extremely weak order-related signal is only about 17% between a fully-ordered and completely disordered structures due to very similar scattering cross-sections of x-rays by Mn and Ni ions. The expected change in this weak peak for the two samples, based on estimates of the extents of

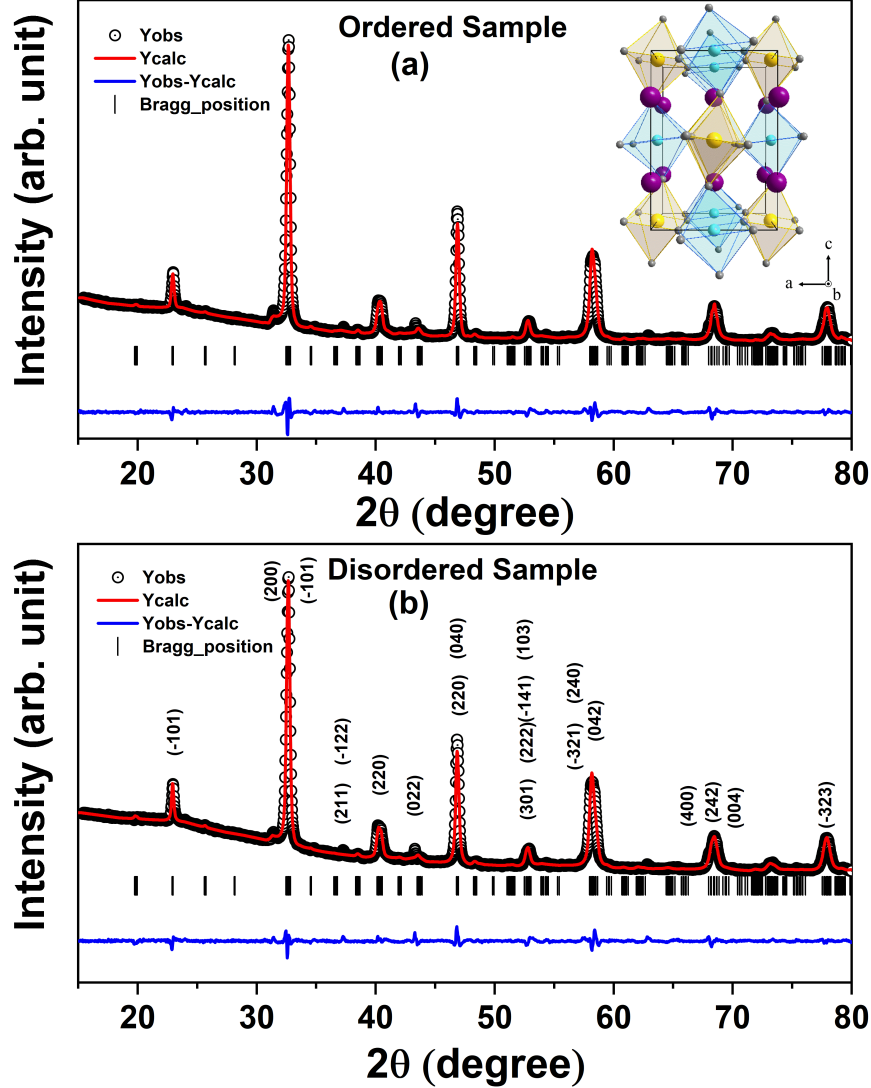


FIG. 1. Powder x-ray diffraction data with the corresponding Rietveld refinement and residual of experiment – fit of (a) Ordered  $\text{La}_2\text{NiMnO}_6$  and (b) Disordered  $\text{La}_2\text{NiMnO}_6$ . (See text). Inset of Fig. 1 (a) presents a schematic of the distribution of La (purple), Mn (cyan), Ni (yellow) and O (grey) atoms within the unit cell of monoclinic  $\text{La}_2\text{NiMnO}_6$ .

ASD from the saturation magnetizations, discussed later, is only about 7%. These considerations explain why Rietveld analysis is not sufficiently sensitive to probe the extent of such ASD in this system and consequently, has never been used for this purpose. The cell parameters obtained from the Rietveld analysis are given in Table I, indicating no significant variation in the structure.

Choudhury *et al.* recently showed that the valence states of Ni and Mn in a particular sample of  $\text{La}_2\text{NiMnO}_6$  are  $\text{Ni}^{2+}$  and  $\text{Mn}^{4+}$ , respectively<sup>8</sup>; however, any possible impact of a changing

TABLE I. Lattice parameters for ordered and disordered  $\text{La}_2\text{NiMnO}_6$  samples derived from our Rietveld refinement.

Sample	Unit Cell Parameters					
	a (Å)	b (Å)	c (Å)	$\alpha = \gamma$ (°)	$\beta$ (°)	cell volume (V) [ $\text{Å}^3$ ]
Ordered	$5.4636 \pm 0.5406 \times 10^{-3}$	$5.5120 \pm 0.4089 \times 10^{-3}$	$7.7550 \pm 0.3004 \times 10^{-3}$	90	$90.2881 \pm 0.3814 \times 10^{-2}$	233.5115
Disordered	$5.4615 \pm 0.5247 \times 10^{-3}$	$5.5119 \pm 0.4424 \times 10^{-3}$	$7.7512 \pm 0.3294 \times 10^{-3}$	90	$90.2334 \pm 0.5414 \times 10^{-2}$	233.3333

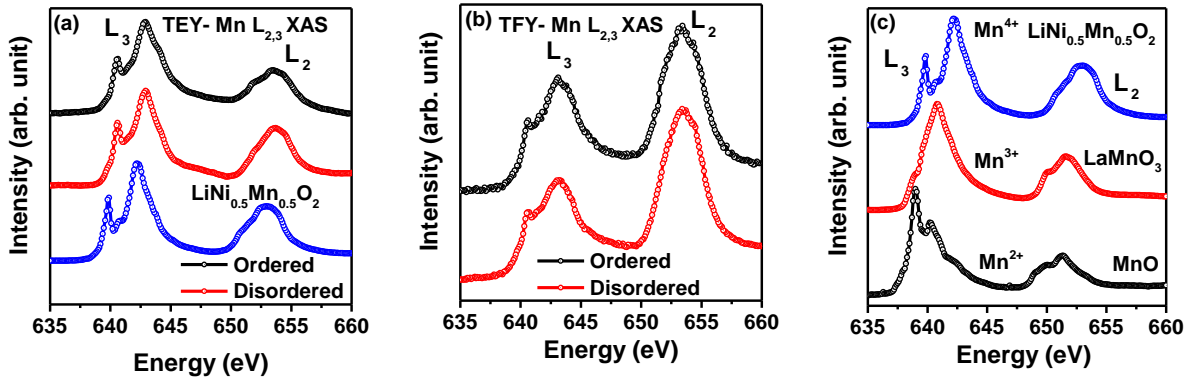


FIG. 2. XAS of Mn  $L_{2,3}$  edge of ordered and disordered  $\text{La}_2\text{NiMnO}_6$  recorded in the TEY (a) and TFY (b) modes. (a) also includes the spectrum of  $\text{LiNi}_{0.5}\text{Mn}_{0.5}\text{O}_2$  to illustrate a typical XAS of  $\text{Mn}^{4+}$  species in TEY mode. (c) XAS spectra of a few standard Mn-oxides samples, obtained in the TEY mode, to illustrate the distinctive spectral features of  $\text{Mn}^{2+}$ ,  $\text{Mn}^{3+}$  and  $\text{Mn}^{4+}$  species.

level of disorder on the valence states of these ions was not investigated in this earlier report. This is particularly significant in view of claim of correlation between valence state and the extent of disorder in the reported literature. Among the measurement techniques available for determining the valence state of a particular species, XAS is a very sensitive and direct method for this purpose. In soft X-ray absorption spectroscopy, the transition from  $2p^63d^n$  initial state to  $2p^53d^{n+1}$  configuration in the final state provides an extremely sensitive local probe, ideal to study the valence<sup>36</sup>, and spin<sup>37,38</sup> character in initial states and crystal field environment of the system.

Fig. 2 (a) and (b) display the normalized Mn  $L_{2,3}$  XAS spectra measured in TEY and TFY, respectively. Standard Mn  $L_{2,3}$  XAS for +2, +3 and +4 valency are shown in fig. 2 (c). Ignoring slight differences in the background signals arising from the two compounds with vastly different extent of ordering, the Mn  $L_{2,3}$  XAS spectra of the ordered and disordered  $\text{La}_2\text{NiMnO}_6$  do not dif-

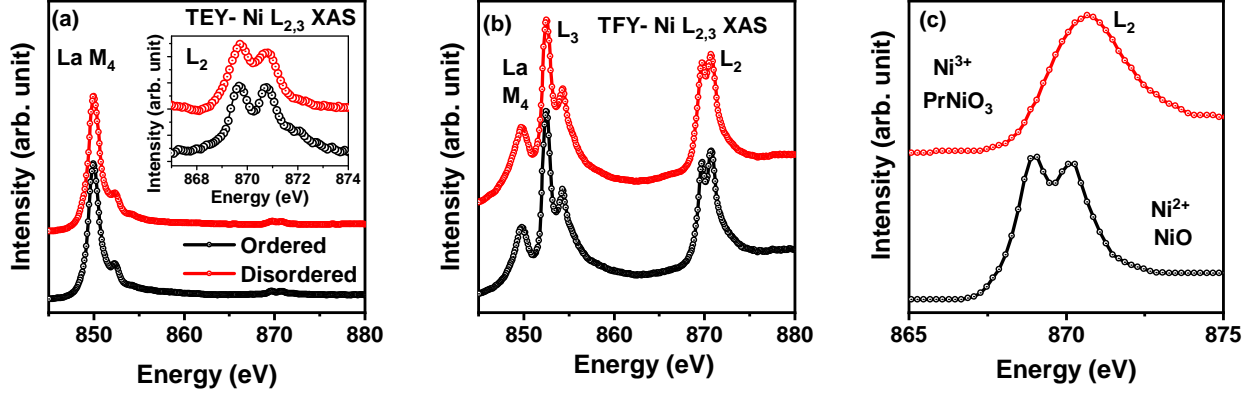


FIG. 3. XAS of Ni  $L_{2,3}$  edge of ordered and disordered  $\text{La}_2\text{NiMnO}_6$  recorded in the TEY (a) and TFY (b) modes. (c) XAS of NiO and  $\text{PrNiO}_3$ , illustrating characteristic spectral features of  $\text{Ni}^{2+}$  and  $\text{Ni}^{3+}$  states, respectively.

fer either in TEY or the TFY mode. Comparing with the spectral features of standard compounds, shown in fig. 2 (c), we find that the spectral features from both samples match quite well with that of  $\text{Mn}^{4+}$  in  $\text{LiNi}_{0.5}\text{Mn}_{0.5}\text{O}_2$  compared to  $\text{Mn}^{3+}$  in  $\text{LaMnO}_3$  and  $\text{Mn}^{2+}$  in  $\text{MnO}$ ; this is made further evident by the comparison of  $\text{Mn}^{4+}$  spectral features from  $\text{LiNi}_{0.5}\text{Mn}_{0.5}\text{O}_2$  reproduced in fig. 2 (a) for a direct comparison with those of ordered and disordered  $\text{La}_2\text{NiMnO}_6$ . It is to be noted that spectral features of  $\text{Mn}^{4+}$  species in  $\text{LiNi}_{0.5}\text{Mn}_{0.5}\text{O}_2$  are quite similar to reports of spectral features of  $\text{Mn}^{4+}$  species in other related oxide systems, such as  $\text{MnO}_2$  and  $\text{SrMnO}_4$ <sup>39</sup>. These comparisons suggest that Mn is in +4 valence state in both samples. Further, very similar Mn  $L_{2,3}$  peak positions in both the TEY and TFY spectra reveal that the valence state of Mn does not differ at the near-surface region compared to the bulk. The difference in the relative intensity for the  $L_3$  and  $L_2$  peaks in TFY spectra relative to the TEY spectra, with  $L_2$  intensities considerably enhanced for the TFY mode, are due to self-absorption and saturation effects<sup>40</sup>.

The Ni  $L_{2,3}$  edge XAS spectra in TEY and TFY are shown in fig. 3 (a) and (b), respectively. The Ni  $L_3$  edge is overlapped with the intense La  $M_5$  edge, which obscures the Ni spectral features. Therefore, we rely on the spectral features at  $L_2$ , (magnified in the inset of fig. 3 (a)) for our analysis. For the TFY mode, self absorption effects favor intensities of higher energy features relative to lower energy spectral features, making Ni  $L_2$  spectral features more clearly visible in the main frame of fig. 3 (b). Fig. 3 (c) shows  $L_{2,3}$  XAS spectra of  $\text{Ni}^{2+}$  in NiO and  $\text{Ni}^{3+}$  in  $\text{PrNiO}_3$ <sup>8</sup>. Line shapes of Ni  $L_2$  edge in fig. 3 (a) and (b) are very similar to that of NiO shown in



fig. 3 (c). Therefore, we argue from the Ni  $L_{2,3}$  XAS spectra that the oxidation states of Ni ions are +2 in both samples, which is consistent with the observation of the  $Mn^{4+}$  state from the Mn  $L_{2,3}$  XAS spectra. X-ray absorption spectroscopy thus establishes a constant valency for the Ni and Mn ions independent of the amount of disorder in the samples.

While the valence states at individual atomic Ni and Mn sites, and consequently the gross electronic properties of  $La_2NiMnO_6$ , appear to be insensitive to the extent of ASD present in these samples, we next show that magnetic properties are profoundly affected by the extent of this disorder and provide a microscopic understanding of the same, based on a combination of dc magnetic and XMCD measurements. Fig. 4 shows results of magnetization,  $M$ , as a function of applied field,  $H$ , at 2 K for the ordered and disordered  $La_2NiMnO_6$  samples. With enhanced disorder, a large decrease in the saturation magnetization can be clearly observed in the plot. The saturation magnetic moment for a perfectly ordered structure should be  $5 \mu_B/f.u.$ , since  $Ni^{2+}$  and  $Mn^{4+}$  contribute 2 and 3 unpaired electrons, respectively, the two atomic sites being ferromagnetically coupled arising from the ferromagnetic superexchange interaction between  $Ni^{2+} d^8$  and  $Mn^{4+} d^3$  configurations via fully-filled oxygen  $2p$  orbitals in octahedral symmetries<sup>33</sup>. A saturation moment of  $3.2 \mu_B/f.u.$  for the present sample suggests a more ordered state than reported in ref. 8 with a saturation moment of  $3.0 \mu_B/f.u.$  The impact of an ASD on the magnetic moment can be understood easily by assuming the interchange of one  $Ni^{2+}$  with one  $Mn^{4+}$ . In the ideally ordered case, each  $Ni^{2+}$  ion is surrounded by six  $Mn^{4+}$  ions, coupled ferromagnetically; likewise, each  $Mn^{4+}$  ion is coupled ferromagnetically to six  $Ni^{2+}$  ions surrounding it. If a nearest  $Ni^{2+}$ - $Mn^{4+}$  pair forms the ASD by interchanging positions of the two ions, we obtain around the defect  $Ni^{2+}$  site five  $Ni^{2+}$  and one  $Mn^{4+}$  and *vice versa* for the  $Mn^{4+}$  defect site with five  $Mn^{4+}$  and one  $Ni^{2+}$ . The antiferromagnetic super-exchange for  $Ni^{2+}$ - $O^{2-}$ - $Ni^{2+}$  and  $Mn^{4+}$ - $O^{2-}$ - $Mn^{4+}$  dominate these local defect sites, forcing the  $Ni^{2+}$  and  $Mn^{4+}$  involved in forming the ASD to be antiferromagnetically oriented with respect to the remaining ferromagnetically coupled lattice. Thus, each ASD converts a pair of  $Ni^{2+}$  and  $Mn^{4+}$  ions with a total moment of  $5 \mu_B$  coupled ferromagnetically to the rest of the system into a pair carrying the same  $5 \mu_B$ , but coupled antiferromagnetically, thereby reducing the magnetic moment of the sample by  $10 \mu_B$  for each ASD pair. Thus, a net magnetic moment of  $3.2 \mu_B/f.u.$ , with a reduction of  $1.8 \mu_B/f.u.$  from the fully ordered moment of  $5 \mu_B/f.u.$ , indicates the presence of  $\sim 18\%$  ASD. Similarly, the moment obtained for the disordered sample,  $1.2 \mu_B/f.u.$ , suggests a  $38\%$  ASD in this case. Noting that the maximum extent of ASD in this definition is  $50\%$  that leads to a zero net moment case, a  $38\%$  disorder indicates a very high

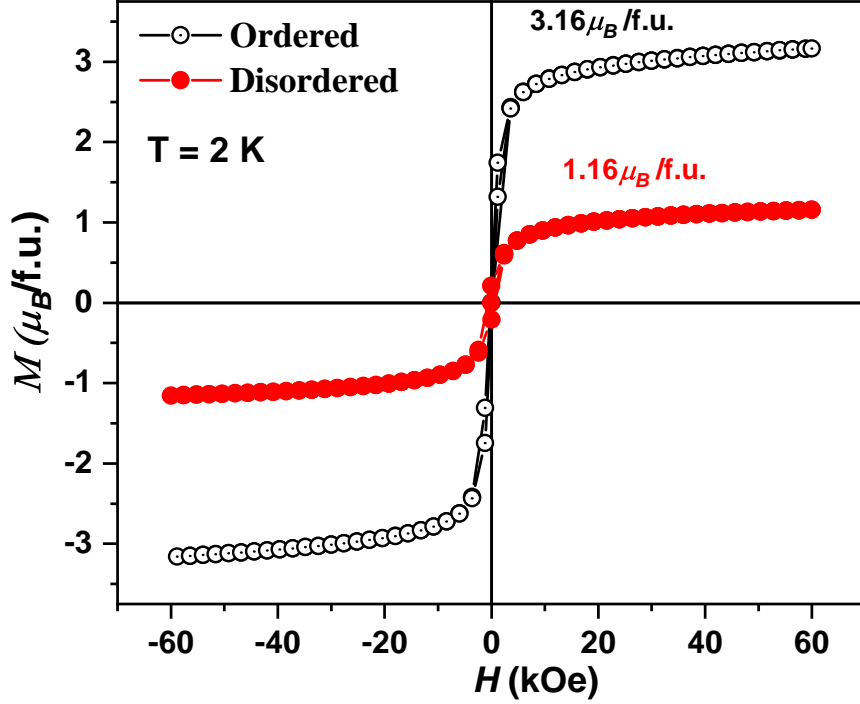


FIG. 4.  $M$  vs.  $H$  data of ordered (black open circle) and disordered (red closed circle)  $\text{La}_2\text{NiMnO}_6$  at  $T = 2$  K.

degree of disorder in this sample; in contrast, the ordered sample exhibits a fairly high degree of ordering ( $\sim 18\%$  disorder).

The dc magnetic susceptibility measurements at a field of 100 Oe and the inverse susceptibilities derived from these are shown in fig. 5 (a)- (d) for both samples. The ferromagnetic transition temperature ( $T_C \sim 266$  K) remains unchanged for both samples, suggesting that the strength of the primary interaction, responsible for the long-range magnetic ordering is insensitive to the extent of disorder. This is in accordance with the finding that the XAS measurements indicate that both sample contain  $\text{Mn}^{4+}$  and  $\text{Ni}^{2+}$  ions only, but is in contrast to most of the previous reports on this system<sup>20,23,28,29</sup>. This is strongly reminiscent of the case of  $\text{Sr}_2\text{FeMoO}_6$ , where also it has been shown<sup>41</sup> that samples with a very high degree of disorder exhibit magnetic transition temperatures almost identical to those of highly ordered samples, though the saturation magnetization can differ by as much as a factor of 4. The anomaly present at low temperatures (below 150 K) in both samples has been attributed to spin glass type behaviour<sup>8</sup>.

In the paramagnetic region, the magnetic susceptibility of the sample exhibits a Curie-Weiss

behaviour with the paramagnetic susceptibility ( $\chi = \frac{M}{H}$ ) given by:

$$\chi = \frac{C}{T - \theta} \quad (1)$$

where  $C$  is the Curie constant, and  $\theta$  is the Curie-Weiss temperature. The Curie constant,  $C$ , in the above equation is related to effective paramagnetic moment,  $\mu_{\text{eff}}$ , by

$$\mu_{\text{eff}} = \sqrt{\frac{3k_B C}{N\mu_B^2}} = 2.827\sqrt{C} \quad (2)$$

where,  $k_B$  is the Boltzmann constant,  $\mu_B$  is Bohr Magneton and  $N$  is the number of magnetic atoms per unit volume<sup>1,42,43</sup>. The inverse susceptibility, being proportional to  $(T - \theta)$ , appears as a straight line, when plotted as a function of the temperature, as shown in fig. 5 (c) and (d). The obtained Curie-Weiss temperature ( $\theta$ ), Curie constant ( $C$ ) and effective magnetic moment ( $\mu_{\text{eff}}$ ), extracted from these data, via a least-squared-error fitting approach, are given in Table II for both compounds. As expected for a ferromagnet, we find positive Curie-Weiss temperature ( $\theta$ ) values for both ordered and disordered  $\text{La}_2\text{NiMnO}_6$  samples. Almost identical values of  $\theta$  for the two samples suggest that the ferromagnetic interaction, between  $\text{Ni}^{2+}$  and  $\text{Mn}^{4+}$  sites, or in

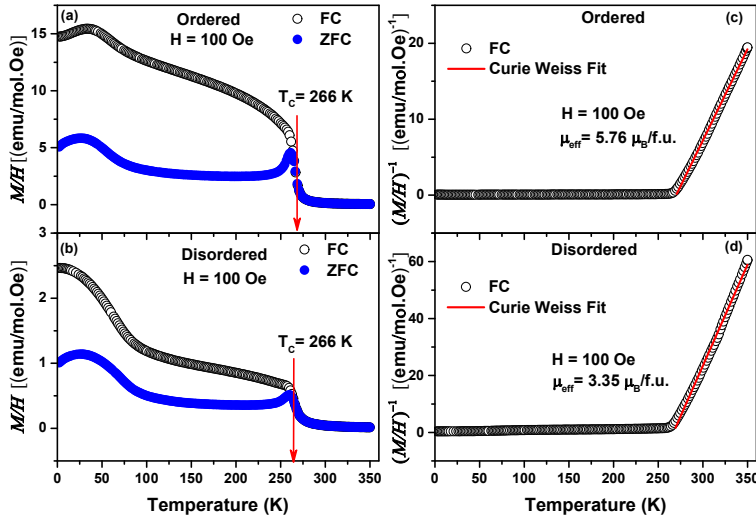


FIG. 5. (a)-(b) dc magnetic FC and ZFC measurements at a field of 100 Oe and their inverse susceptibilities (c)-(d) for ordered and disordered samples of  $\text{La}_2\text{NiMnO}_6$ , respectively.

TABLE II. Parameter calculated from Curie-Weiss fitting of ordered and disordered  $\text{La}_2\text{NiMnO}_6$

Sample	Curie-Weiss temperature ( $\theta$ ) (K)	Curie constant (C) ( $\text{emuKmol}^{-1} \text{Oe}^{-1}$ )	$\mu_{\text{eff}}$ ( $\mu_B/\text{f.u.}$ )
Order	270	4.16	5.76
Disorder	267	1.41	3.35

other words, the superexchange interaction between these sites is not affected by the presence of even extensive disorder, though evidently there is a strong reduction in the effective paramagnetic moment with an increasing disorder. Specifically, the ordered  $\text{La}_2\text{NiMnO}_6$  sample has an effective paramagnetic moment ( $\mu_{\text{eff}}$ ) of  $5.8 \mu_B/\text{f.u.}$ , while for the disordered sample, it is only  $3.4 \mu_B/\text{f.u.}$  The lowering of  $\mu_{\text{eff}}$  in the disordered sample indicates that increased ASD leads to increased antiferromagnetic interactions, in the form of strongly coupled  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Ni}^{2+}$  and  $\text{Mn}^{4+}-\text{O}^{2-}-\text{Mn}^{4+}$  arrangements.

The XAS data discussed above already establishes that the Mn and Ni valencies do not change with disorder, thereby providing a basis to understand the constancy of  $\theta$  and the magnetic ordering temperature,  $T_C$ , but those results do not provide any insight into why the effective paramagnetic moment (table II) and the saturation magnetization (fig. 4) drop so significantly with increasing disorder. We have already suggested that these reductions in the magnetic moment with an increasing ASD density is most likely to arise from the antiparallel orientation of the pair of  $\text{Ni}^{2+}$  and  $\text{Mn}^{4+}$  ions involved in this defect formation with respect to the ferromagnetically coupled magnetic moment of the ordered lattice, leading to a reduction of  $10 \mu_B$  for each ASD pair formed. This would imply a simultaneous reduction of the average magnetic moments of both  $\text{Mn}^{4+}$  and  $\text{Ni}^{2+}$  sublattices to the total moment, which is measured by the saturation magnetization (fig. 4).

To address this question, the element specific magnetic measurement, XMCD, was performed. The measured XMCD at the Mn and Ni  $L_{2,3}$  edges in the TEY mode, relatively less influenced by self-absorption effects, was measured at 150 K in a magnetic field of 50 kOe, as shown for both samples in figs. 6 (a) and (b), respectively. The small, leading peak around 850 eV in the Ni  $L_3$  edge XMCD fig. 6 (b) is an artifact arising from incomplete subtraction of the signal arising from nonmagnetic La. The polarity of the XMCD signal at both Ni and Mn  $L_{2,3}$  edges has the same sign for both samples. This means the majority of the  $\text{Ni}^{2+}$  and  $\text{Mn}^{4+}$  spin moments are aligned parallel for both samples. This result is consistent with the ferromagnetic behavior of  $\text{La}_2\text{NiMnO}_6$

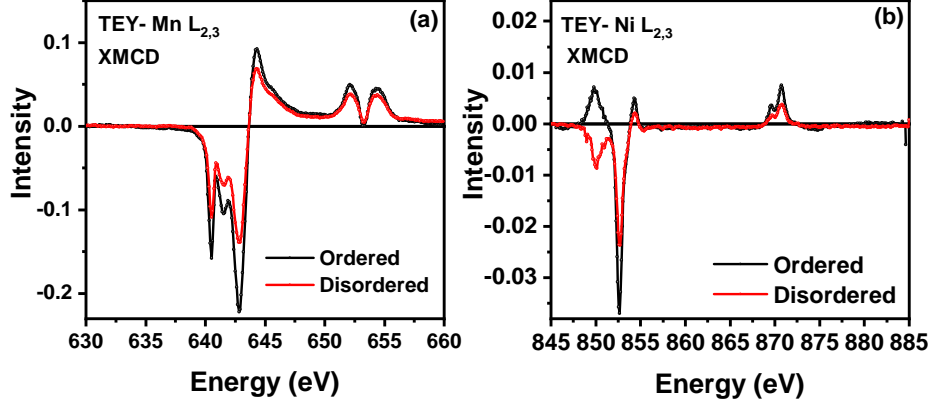


FIG. 6. (a) Mn  $L_{2,3}$  edge XMCD spectra (b) Ni  $L_{2,3}$  XMCD spectra for both ordered and disordered  $\text{La}_2\text{NiMnO}_6$  samples at TEY mode with an applied magnetic field 50 kOe at  $T=150$  K.

in both samples<sup>44–46</sup>. It is seen that the intensity of both Mn and Ni XMCD signals for the ordered sample is larger than those of the disordered  $\text{La}_2\text{NiMnO}_6$  sample, which corroborates the results from dc magnetic measurements.

It is known that XMCD signal can be quantitatively analyzed using well-known sum-rules<sup>47</sup> to provide estimates of site-specific magnetic moments. While such an analysis of results in Fig. 6(a) indicate an average contribution of 1.3 and 0.4  $\mu_B$  per  $\text{Mn}^{4+}$  ion for the ordered and the disordered samples, respectively, a similar analysis for the  $\text{Ni}^{2+}$  signal in Fig. 6(b) is not possible due to the overlapping La  $M_4$  signal (see Fig. 3). However, it is still possible to relate the extracted site-specific average magnetization of the  $\text{Mn}^{4+}$  sublattice from the XMCD results to the bulk magnetizations by noting that the total magnetization in these samples is contributed only by the  $\text{Mn}^{4+}$  ( $3d^3$ ) and  $\text{Ni}^{2+}$  ( $3d^8$ ) sites in the proportion of 3:2, with  $\text{La}^{3+}$  and  $\text{O}^{2-}$  being nonmagnetic. Thus, three-fifth of the total magnetization arises from  $\text{Mn}^{4+}$  and two-fifth from  $\text{Ni}^{2+}$ . Ref. 47 showed that the saturation magnetization of  $\text{La}_2\text{NiMnO}_6$  at 150 K is about 67% of its low temperature value. The low temperature saturation magnetization of the two samples here are 3.16 and 1.16  $\mu_B/\text{f.u.}$ , shown in Fig. 4. This suggests that the saturation magnetization of our samples, if measured at 150 K, would be 2.1 and 0.8  $\mu_B/\text{f.u.}$  Three-fifths of these values,  $\sim 1.3$  and 0.5  $\mu_B$ , as  $\text{Mn}^{4+}$  contributions to the total bulk magnetizations, are in good agreement with XMCD estimates of 1.3 and 0.4  $\mu_B/\text{Mn}^{4+}$  for ordered and disordered samples at 150 K, respectively. These observations lend support to our suggestion above that the ASD leads to antiferromagnetic interactions in  $\text{Mn}^{4+}-\text{O}^{2-}-\text{Mn}^{4+}$  and  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Ni}^{2+}$  bonds.

## CONCLUSION

In conclusion, we have synthesized two  $\text{La}_2\text{NiMnO}_6$  samples in the monoclinic ( $P2_1/n$ ) phase with strongly differing extents of anti-site disorder. Using X-ray absorption spectroscopy we have verified that the oxidation state of Ni is +2 and Mn is +4, independent of the amount of anti-site disorder. Our samples show ferromagnetic transition at  $\sim 266$  K due to  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Mn}^{4+}$  super-exchange interactions, also independent of the amount of anti-site disorder. XMCD measurements show similar extents of reductions in the average Ni and Mn moments with an increasing disorder, providing evidence that anti-site disorder leads to the introduction of antiferromagnetic interaction through  $\text{Ni}^{2+}-\text{O}^{2-}-\text{Ni}^{2+}$  and  $\text{Mn}^{4+}-\text{O}^{2-}-\text{Mn}^{4+}$  super-exchange.

## ACKNOWLEDGMENTS

The work is supported primarily by Indo-U.S. Joint Center for Rational Control of Functional Oxides under Indo-U.S. Science and Technology Forum. Work at the Advanced Photon Source, Argonne was supported by the U.S. Department of Energy, Office of Science under Grant No. DEAC02-06CH11357. D.D.S. thanks Jamsetji Tata Trust for support.

## REFERENCES

- \* sarma@iisc.ac.in; also at Jawaharlal Nehru Centre for Advanced Scientific Research, Bengaluru
- <sup>1</sup> N. Rogado, J. Li, A. Sleight, and M. Subramanian, *Advanced Materials* **17**, 2225 (2005).
- <sup>2</sup> M. Hashisaka, D. Kan, A. Masuno, M. Takano, Y. Shimakawa, T. Terashima, and K. Mibu, *Applied Physics Letters* **89**, 032504 (2006).
- <sup>3</sup> S. Zhou, L. Shi, H. Yang, and J. Zhao, *Applied Physics Letters* **91**, 172505 (2007).
- <sup>4</sup> P. Padhan, H. Z. Guo, P. LeClair, and A. Gupta, *Applied Physics Letters* **92**, 022909 (2008).
- <sup>5</sup> M. Kitamura, I. Ohkubo, M. Matsunami, K. Horiba, H. Kumigashira, Y. Matsumoto, H. Koinuma, and M. Oshima, *Applied Physics Letters* **94**, 262503 (2009).
- <sup>6</sup> S. M. Zhou, Y. Q. Guo, J. Y. Zhao, S. Y. Zhao, and L. Shi, *Applied Physics Letters* **96**, 262507 (2010).
- <sup>7</sup> M. Zhu, Y. Lin, E. W. C. Lo, Q. Wang, Z. Zhao, and W. Xie, *Applied Physics Letters* **100**, 062406 (2012).

- <sup>8</sup> D. Choudhury, P. Mandal, R. Mathieu, A. Hazarika, S. Rajan, A. Sundaresan, U. V. Waghmare, R. Knut, O. Karis, P. Nordblad, and D. D. Sarma, *Phys. Rev. Lett.* **108**, 127201 (2012).
- <sup>9</sup> Y. Guo, L. Shi, S. Zhou, J. Zhao, and W. Liu, *Applied Physics Letters* **102**, 222401 (2013).
- <sup>10</sup> D. Chakraborty, U. N. Nandi, D. Jana, M. G. Masud, and S. Giri, *Journal of Applied Physics* **118**, 035103 (2015).
- <sup>11</sup> P. Kumar, S. Ghara, B. Rajeswaran, D. Muthu, A. Sundaresan, and A. Sood, *Solid State Communications* **184**, 47 (2014).
- <sup>12</sup> M. P. Singh, C. Grygiel, W. C. Sheets, P. Boullay, M. Hervieu, W. Prellier, B. Mercey, C. Simon, and B. Raveau, *Applied Physics Letters* **91**, 012503 (2007).
- <sup>13</sup> X. Wang, Y. Sui, Y. Li, L. Li, X. Zhang, Y. Wang, Z. Liu, W. Su, and J. Tang, *Applied Physics Letters* **95**, 252502 (2009).
- <sup>14</sup> S. Zhao, L. Shi, S. Zhou, J. Zhao, H. Yang, and Y. Guo, *Journal of Applied Physics* **106**, 123901 (2009).
- <sup>15</sup> H. Z. Guo, J. Burgess, E. Ada, S. Street, A. Gupta, M. N. Iliev, A. J. Kellock, C. Magen, M. Varela, and S. J. Pennycook, *Phys. Rev. B* **77**, 174423 (2008).
- <sup>16</sup> H. Guo, A. Gupta, M. Varela, S. Pennycook, and J. Zhang, *Phys. Rev. B* **79**, 172402 (2009).
- <sup>17</sup> Y. Mao, J. Parsons, and J. S. McCloy, *Nanoscale* **5**, 4720 (2013).
- <sup>18</sup> R. Takahashi, I. Ohkubo, K. Yamauchi, M. Kitamura, Y. Sakurai, M. Oshima, T. Oguchi, Y. Cho, and M. Lippmaa, *Phys. Rev. B* **91**, 134107 (2015).
- <sup>19</sup> M. Ullah, S. A. Khan, G. Murtaza, R. Khenata, N. Ullah, and S. B. Omran, *Journal of Magnetism and Magnetic Materials* **377**, 197 (2015).
- <sup>20</sup> V. L. J. Joly, P. A. Joy, S. K. Date, and C. S. Gopinath, *Phys. Rev. B* **65**, 184416 (2002).
- <sup>21</sup> C. L. Bull, D. Gleeson, and K. S. Knight, *Journal of Physics: Condensed Matter* **15**, 4927 (2003).
- <sup>22</sup> M. N. Iliev, M. M. Gospodinov, M. P. Singh, J. Meen, K. D. Truong, P. Fournier, and S. Jandl, *Journal of Applied Physics* **106**, 023515 (2009).
- <sup>23</sup> M. P. Singh, K. D. Truong, S. Jandl, and P. Fournier, *Phys. Rev. B* **79**, 224421 (2009).
- <sup>24</sup> H. Guo, A. Gupta, M. Varela, S. Pennycook, and J. Zhang, *Phys. Rev. B* **79**, 172402 (2009).
- <sup>25</sup> J. B. Goodenough, A. Wold, R. J. Arnett, and N. Menyuk, *Phys. Rev.* **124**, 373 (1961).
- <sup>26</sup> G. Blasse, *Journal of Physics and Chemistry of Solids* **26**, 1969 (1965).
- <sup>27</sup> M. C. Sánchez, J. García, J. Blasco, G. Subías, and J. Perez-Cacho, *Phys. Rev. B* **65**, 144409 (2002).
- <sup>28</sup> R. I. Dass, J.-Q. Yan, and J. B. Goodenough, *Phys. Rev. B* **68**, 064415 (2003).

- <sup>29</sup> H. Z. Guo, J. Burgess, E. Ada, S. Street, A. Gupta, M. N. Iliev, A. J. Kellock, C. Magen, M. Varela, and S. J. Pennycook, *Phys. Rev. B* **77**, 174423 (2008).
- <sup>30</sup> K. Asai, H. Sekizawa, and S. Iida, *Journal of the Physical Society of Japan* **47**, 1054 (1979).
- <sup>31</sup> M. Sonobe and K. Asai, *Journal of the Physical Society of Japan* **61**, 4193 (1992).
- <sup>32</sup> J. Blasco, M. Sánchez, J. Pérez-Cacho, J. García, G. Subías, and J. Campo, *Journal of Physics and Chemistry of Solids* **63**, 781 (2002).
- <sup>33</sup> H. Das, U. V. Waghmare, T. Saha-Dasgupta, and D. D. Sarma, *Phys. Rev. Lett.* **100**, 186402 (2008).
- <sup>34</sup> J. Rodríguez-Carvajal, *Physica B: Condensed Matter* **192**, 55 (1993).
- <sup>35</sup> I. A. Kowalik, G. Öhrwall, B. N. Jensen, R. Sankari, E. Wallén, U. Johansson, O. Karis, and D. Arvanitis, *Journal of Physics: Conference Series* **211**, 012030 (2010).
- <sup>36</sup> C. Mitra, Z. Hu, P. Raychaudhuri, S. Wirth, S. I. Csiszar, H. H. Hsieh, H.-J. Lin, C. T. Chen, and L. H. Tjeng, *Phys. Rev. B* **67**, 092404 (2003).
- <sup>37</sup> S. Ray, A. Kumar, D. D. Sarma, R. Cimino, S. Turchini, S. Zennaro, and N. Zema, *Phys. Rev. Lett.* **87**, 097204 (2001).
- <sup>38</sup> F. Nolting, A. Scholl, J. Stohr, J. W. Seo, J. Fompeyrine, H. Siegwart, J.-P. Locquet, S. Anders, J. Luning, E. E. Fullerton, M. F. Toney, M. R. Scheinfein, and H. A. Padmore, *Nature* **405**, 767 (2000).
- <sup>39</sup> K. Horiba, H. Kawanaka, Y. Aiura, T. Saitoh, C. Satoh, Y. Kikuchi, M. Yokoyama, Y. Nishihara, R. Eguchi, Y. Senba, H. Ohashi, Y. Kitajima, and S. Shin, *Phys. Rev. B* **81**, 245127 (2010).
- <sup>40</sup> G. van der Laan and A. I. Figueroa, *Coordination Chemistry Reviews* **277**, 95 (2014).
- <sup>41</sup> D. Topwal, U. Manju, S. Ray, S. Raj, D. D. Sarma, S. R. Krishnakumar, M. Bertolo, S. La Rosa, and G. Cautero, *Journal of Chemical Sciences* **118**, 87 (2006).
- <sup>42</sup> C. Shi, Y. Hao, and Z. Hu, *Journal of Physics D: Applied Physics* **44**, 245405 (2011).
- <sup>43</sup> W. Z. Yang, X. Q. Liu, H. J. Zhao, Y. Q. Lin, and X. M. Chen, *Journal of Applied Physics* **112**, 064104 (2012).
- <sup>44</sup> J.-S. Kang, S. M. Lee, D. H. Kim, S. Kolesnik, B. Dabrowski, B.-G. Park, J.-Y. Kim, J. Lee, B. Kim, and B. I. Min, *Journal of Applied Physics* **107**, 09D721 (2010).
- <sup>45</sup> J. C. Rojas Sánchez, B. Nelson-Cheeseman, M. Granada, E. Arenholz, and L. B. Steren, *Phys. Rev. B* **85**, 094427 (2012).
- <sup>46</sup> J. Hoffman, I. C. Tung, B. B. Nelson-Cheeseman, M. Liu, J. W. Freeland, and A. Bhattacharya, *Phys. Rev. B* **88**, 144411 (2013).
- <sup>47</sup> B. T. Thole, P. Carra, F. Sette, and G. van der Laan, *Phys. Rev. Lett.* **68**, 1943 (1992).