

This is the accepted manuscript made available via CHORUS. The article has been published as:

Interplay between orbital-quantization effects and the Fulde-Ferrell-Larkin-Ovchinnikov instability in multiple-band layered superconductors

Kok Wee Song and Alexei E. Koshelev

Phys. Rev. B **97**, 224520 — Published 27 June 2018

DOI: [10.1103/PhysRevB.97.224520](https://doi.org/10.1103/PhysRevB.97.224520)

Interplay between orbital-quantization effects and the Fulde-Ferrell-Larkin-Ovchinnikov instability in multiple-band layered superconductors

Kok Wee Song and Alexei E. Koshelev
*Materials Science Division, Argonne National Laboratory,
9700 South Cass Avenue, Lemont, Illinois 60639, USA*
(Dated: June 6, 2018)

We explore superconducting instability for a clean two-band layered superconductor with deep and shallow bands in the magnetic field applied perpendicular to the layers. In the shallow band, the quasiclassical approximation is not applicable, and Landau quantization has to be accounted for exactly. The electronic spectrum of this band in the magnetic field is composed of the one-dimensional Landau-level minibands. With increasing magnetic field the system experiences series of Lifshitz transitions when the chemical potential enters and exits the minibands. These transitions profoundly influence the shape of the upper critical field at low temperatures. In addition, the Zeeman spin splitting may cause the nonuniform state with interlayer modulation of the superconducting order parameter (Fulde-Ferrell-Larkin-Ovchinnikov state). Typically, the quantization effects in the shallow band strongly promote the formation of this state. The uniform state remains favorable only in the exceptional resonance cases when the spin-splitting energy exactly matches the Landau-level spacing. Furthermore, for specific relations between electronic spectrum parameters, the alternating FFLO state may realize, in which the order parameter changes sign between the neighboring layers. For all above cases, the reentrant high-field superconducting states may emerge at low temperatures if the shallow band has significant contribution to the Cooper pairing.

I. INTRODUCTION

The nature of superconducting instability in the magnetic field is a long-standing fundamental problem. In clean type-II superconductors, the upper critical field H_{C2} and its temperature dependence are sensitive to the electronic band properties as well as to the gap structure which contains crucial information on how the correlated Cooper pairs are formed. The magnitude of H_{C2} is mostly determined by the suppression of superconductivity due to the quasiparticles orbital motion and the Zeeman spin splitting of the Fermi surface by the magnetic field. The problem of orbital H_{C2} for a single-band system was solved in the seminal papers¹ within the quasiclassical approximation which neglects the Landau quantization of the orbital motion. This approach works with high accuracy in common metals with large Fermi energies and describes very well most of known conventional superconductors. Nevertheless, the exact Landau quantization calculation was discussed in Refs. 2, and 3 shortly after the quasiclassical work and the topic was further elaborated in great details later⁴⁻⁹.

Landau-quantization effects are most relevant when the Fermi energy is comparable to the cyclotron frequency so that only a few lowest Landau levels are occupied. Such extreme quantum limit has not been viable in most of known superconducting materials. The situation changed with the recent discovery of the iron-based superconductors (FeSC). It is very common in FeSCs that some of the bands have very small Fermi energies and they can be driven through the Lifshitz transition by chemical dopings¹⁰⁻¹³ and, importantly, these materials usually remain superconducting after one of the bands is completely depleted. As the Fermi energy of the shallow band may be smaller than the pairing energy scale,

the proper treatment of this band requires revision of the conventional BCS approach. Such situation was first considered in the context of shape resonances in confined superconductors (thin films and nanowires)¹⁴⁻¹⁷ The influence of the shallow band on the superconducting transition temperature in multiple-band materials near Lifshitz transition has been considered in Ref.¹⁸ and, more recently, physics of FeSCs motivated detailed investigations of this problem¹⁹⁻²³. It was demonstrated that, in spite of low quasiparticle density, shallow bands may strongly influence the Cooper pairing. Another key property facilitating the extreme quantum limit near superconducting instability of FeSCs is that they are characterized by the very high upper critical fields, up to 100 tesla.

As the orbital upper critical field is inversely proportional to the Fermi energy, it is strongly affected by the shallow bands. Moreover, in the vicinity of the Lifshitz transition, the extreme quantum limit can be reached for these bands near H_{C2} meaning that the quasiclassical consideration cannot be used. It has been indeed demonstrated that the Landau quantization has a dramatic effect on superconducting instability in the magnetic field for two-dimensional materials near the Lifshitz transition²⁴. The most spectacular prediction is the emergence of the pronounced reentrant states at the magnetic field corresponding to the matching of the Landau levels with the chemical potential.

In addition to the orbital effect, shallow bands also promote the Zeeman spin splitting suppression of superconductivity. The relative role of the spin and orbital mechanisms is usually characterized by the Maki parameter α_M defined as $\sqrt{2}H_{C2}^O/H_{C2}^P$, where H_{C2}^O and H_{C2}^P are the orbital and spin upper critical fields respectively. In a clean isotropic single-band material with the free-

electron g -factor, the Maki parameter is proportional to the ratio of the superconducting gap Δ and the Fermi energy ϵ_F , $\alpha_M = \pi^2 \Delta / 4\epsilon_F$. In this case, unless the band is very shallow, α_M is very small meaning that the orbital effect strongly dominates. The Maki parameter is greatly enhanced in special cases of weak orbital effect such as quasi-one-dimensional materials and layered superconductors for magnetic field directed along the layers.

An important consequence of the strong Zeeman effect (i.e., large α_M) is the emergence of the nonuniform Fulde-Ferrell-Larkin-Ovchinnikov (FFLO) state in very clean materials^{25,26}. In this state, the order parameter is periodically modulated which allows for a gain in the Zeeman energy which may exceed the kinetic-energy loss due to the nonzero center-of-mass momentum pairing. Rich physics of the FFLO state has been extensively investigated in many subsequent theoretical studies within quasiclassical approximation^{27–36}. The FFLO instability may only realize in very pure materials with weak scattering of quasiparticles. That is why, even though the FFLO state was predicted more than half century ago, the experimental data consistent with this state have been reported only relatively recently in organic superconductors^{37,38} and, less convincingly, in the heavy-fermion compounds^{39,40}. The conditions for the FFLO instability with modulation along the magnetic field in *isotropic* material were studied by Gruenberg and Gunther²⁷ within the quasiclassical framework. They found that the nonuniform state appears only for very large Maki parameters, $\alpha_M > 1.8$, which is unlikely to realize in any single-band isotropic material. That is why most FFLO studies have been focused on quasi-low-dimensional materials with strongly reduced orbital effects.

The FFLO state may realize in the iron-based superconductors due to the presence of shallow bands and huge upper critical fields which are likely to be limited by the Zeeman effect. This motivated recent investigations of the conditions for the emergence of this state in multiple-band materials within the quasiclassical approach in different situations^{41–44}. However, in the presence of very shallow bands, this approach may be insufficient and quantization effects have to be accounted for.

In this paper, we investigate the superconducting instability for a two-band layered material in the magnetic field applied perpendicular to the layers. We consider the case of the material near the Lifshitz transition when one of the bands is very shallow. In this case, the Landau-quantization effects strongly influence the formation of the superconducting state. Even though our consideration is motivated by physics of iron-based superconductors, it is very general, and our goal is not to describe any particular compound but, instead, to develop a general understanding of how the orbital-quantization effects influence the onset of superconductivity in clean two-band layered materials. The major new feature in comparison with a pure two-dimensional case²⁴ is that, due to the

large Zeeman effect in the shallow band, this system is prone to the formation of the FFLO state with interlayer modulation of the order parameter. The quantum effects have a profound influence on this FFLO instability.

The interlayer tunneling lifts all the degenerate Landau levels to dispersive minibands along the out-of-plane momentum direction. As a consequence, the system experiences series of Lifshitz transitions with increasing the magnetic field corresponding to crossing of the chemical potential with the miniband edges. Every Landau-level miniband has two van Hove singularities at the reduced z -axis momentums $k_z = 0$ and π , at which the density of states (DoS) is enhanced. In special situations, when two such singular points for spin-up and spin-down bands simultaneously match the Fermi level, the pairing strongly enhanced. Two distinct cases of such resonance matching are possible. The first well-known case is realized when spin-splitting energy equal to the Landau-level spacing^{7,8}. In this case, the van Hove points of the same kind (either $k_z = 0$ or π) may match leading to the standard uniform superconducting state. The second case corresponds to matching of the opposite van Hove points, e. g., spin-down/ $k_z = 0$ and spin-up/ $k_z = \pi$ points, which may occur only for a certain relation between the electronic band parameter. In this situation, the *alternating* FFLO state may emerge, in which the superconducting order parameter changes sign between the neighboring layers. These matching effects may generate the high-field reentrant superconducting states which are somewhat less pronounced than for two-dimensional case²⁴ due to the DoS spreading by the interlayer tunneling.

On the other hand, the Landau-level spreading somewhat mitigates the Zeeman pair-breaking effect, since the dispersive spin-up and spin-down minibands can cross the Fermi level simultaneously within a finite energy range for arbitrary spin splitting. In such generic situation, the shallow band favors the formation of the FFLO state, in which the optimal modulation wave vector equals to the difference between the spin-up and spin-down Fermi momenta. Such FFLO instability leads to different kind of reentrant states with the field-dependent modulation wave vectors. In contrast to the reentrant states caused by the matching of the van Hove singularities, the latter states can extend over a broad magnetic-field range.

This paper is organized as follows. In section II, we introduce the microscopic Hamiltonian describing two-band layered superconductor in magnetic field and derive the corresponding linearized gap equations. In section III, we briefly discuss these equations for the transition temperature in zero magnetic field providing the reference for the further investigation of instability in finite magnetic field. In section IV, we derive the equations for the upper critical field H_{C2} and evaluate the pairing kernels in these equations. In section V, we discuss the dependences of the quantum pairing kernel on relevant parameters. In section VI, we present the typical

magnetic field versus temperature phase diagrams. We conclude the paper by section VII.

II. THE MODEL OF A TWO-BAND LAYERED SUPERCONDUCTOR

We will investigate the shallow band effects in layered superconductors using the simple tight-binding Hamiltonian with only the nearest-neighbor interlayer hopping term,

$$\begin{aligned} \mathcal{H} = & \sum_{j\alpha} \int d^2\mathbf{r} \left[c_{\alpha js}^\dagger(\mathbf{r}) (\varepsilon^\alpha(\mathbf{k}) \sigma_{ss'}^0 - \mu_z H \sigma_{ss'}^z) c_{\alpha js'}(\mathbf{r}) \right. \\ & - t_z^\alpha \exp \left[\frac{ie}{c} \int_{l_j} dz A_z \right] c_{\alpha js}^\dagger(\mathbf{r}) c_{\alpha, j+1, s}(\mathbf{r}) + h.c. \\ & \left. - \sum_\beta U_{\alpha\beta} c_{\alpha j\downarrow}^\dagger(\mathbf{r}) c_{\alpha j\uparrow}^\dagger(\mathbf{r}) c_{\beta j\downarrow}(\mathbf{r}) c_{\beta j\uparrow}(\mathbf{r}) \right], \end{aligned} \quad (1)$$

where $\mathbf{r} = (x, y)$ is the in-plane coordinate, j is the layer index, s represents spin, and $\alpha = e$ (h) represents the e -band (h -band). Furthermore, t_z^α is the (nearest) interlayer hopping energy, $\varepsilon^e(\mathbf{k}) = \hat{\mathbf{k}}^2/(2m_e)$ and $\varepsilon^h(\mathbf{k}) = -\hat{\mathbf{k}}^2/(2m_h) + \varepsilon_0$ are intralayer energy dispersions with the band masses m_h and m_e and the momentum operator $\hat{\mathbf{k}} = -i\nabla_{\mathbf{r}} - e\mathbf{A}/c$. In the model, we also consider the Zeeman spin splitting and assume, for simplicity, that the band electron's magnetic moment, μ_z , is the same in each band. In the second line of Eq. (1), $\int_{l_j} = \int_{ja_z}^{(j+1)a_z}$ is the line integration along the out-of-plane direction and a_z is the interlayer spacing (set to unity in the later calculation) and A_z is the z -component of the vector potential. In zero magnetic field, the three-dimensional energy dispersions are $\varepsilon^\alpha(\mathbf{k}, k_z) = \varepsilon^\alpha(\mathbf{k}) - 2t_z^\alpha \cos k_z$, see Fig. 1(a).

In this paper, we limit ourselves to the case of the magnetic field applied in the z direction. In this case, $A_z = 0$ with standard gauge choices and the magnetic phase factor in Eq. (1) tight-binding terms drops out. For definiteness, we consider the case when the hole band is shallow meaning that the chemical potential μ is located near its edge $\mu_h = \varepsilon_0 - \mu \ll \varepsilon_0$. We note that whether the shallow band is hole-like or electron-like does not have any influence on the results of this paper. The two Lifshitz transitions in this model occur at $\mu_h = \pm 2t_z^h$ [see Fig. 1(b)]⁴⁵. At $\mu_h = 2t_z^h$ the neck near $k_z = 0$ interrupts and $\mu_h = -2t_z^h$ the hole band got completely depleted.

To study the superconducting instabilities in the model Eq. (1), we follow the standard approach and write the linearized gap equation as

$$\Delta_{\mathbf{r},j}^\alpha = T \sum_{\omega_n} \sum_{\beta j'} U_{\alpha\beta} \int_{\mathbf{r}'} K_{\omega_n}^\beta(\mathbf{r}j, \mathbf{r}'j') \Delta_{\mathbf{r}',j'}^\beta, \quad (2)$$

where the gap function is defined as $\Delta_{\mathbf{r},j}^\alpha = \sum_\beta U_{\alpha\beta} \langle c_{\beta,j\downarrow}(\mathbf{r}) c_{\beta,j\uparrow}(\mathbf{r}) \rangle$ and we used the notation $\mathbf{r}_r =$

$\int d\mathbf{r}$, $\omega_n = 2\pi T(n + 1/2)$ are the Matsubara frequencies, and the kernel is

$$K_{\omega_n}^\alpha(\mathbf{r}j, \mathbf{r}'j') = G_{\omega_n,+}^\alpha(\mathbf{r}j, \mathbf{r}'j') G_{-\omega_n,-}^\alpha(\mathbf{r}'j', \mathbf{r}j), \quad (3)$$

where $G_{\omega_n,\pm}^\alpha(\mathbf{r}j, \mathbf{r}'j')$ is the one-particle Green's function in the normal phase and the subscripts $+$ or $-$ describe spin orientation. Without magnetic field, the normal Green's functions can be expanded into the plane-wave basis

$$G_{\omega_n,\pm}^\alpha(\mathbf{r}j, \mathbf{r}'j') = \sum_{\mathbf{k}k_z} \frac{e^{-i[\mathbf{k}\cdot\boldsymbol{\rho} + k_z(j-j')]} }{i\omega_n - \xi_{\mathbf{k}}^\alpha + 2t_z^\alpha \cos k_z}, \quad (4)$$

where $\xi_{\mathbf{k}}^\alpha = \varepsilon^\alpha(\mathbf{k}) - \mu$ and $\boldsymbol{\rho} = \mathbf{r} - \mathbf{r}'$. In the presence of out-of-plane magnetic fields, in the symmetric gauge $\mathbf{A} = \frac{H}{2}(-y, x, 0)$ the one-particle Green's function can be represented as

$$\begin{aligned} G_{\omega_n,\pm}^\alpha(\mathbf{r}j, \mathbf{r}'j') = & \exp \left(i \frac{[\mathbf{r} \times \mathbf{r}']_z}{2l^2} \right) \\ & \times \sum_{k_z} e^{-ik_z(j-j')} g_{\omega_n,\pm}^\alpha(\rho, k_z) \end{aligned} \quad (5)$$

where $l = \sqrt{c/(eH)}$ is the magnetic length and $\rho = |\boldsymbol{\rho}|$. We use the quasiclassical approximation for the Green's function of the deep e -band

$$g_{\omega_n,\pm}^e \approx \sum_{\mathbf{k}} \frac{e^{-i\mathbf{k}\cdot\boldsymbol{\rho}}}{i\omega_n \mp \mu_z H - \xi_{\mathbf{k}}^e + 2t_z^e \cos k_z}, \quad (6)$$

and expand the Green's function of the shallow h -band over the exact Landau-level basis^{9,46}

$$g_{\omega_n,\pm}^h = \frac{1}{2\pi l^2} \sum_{\ell=0} \frac{L_\ell(\frac{\rho^2}{2l^2}) \exp(-\frac{\rho^2}{4l^2})}{i\omega_n \mp \mu_z H + \mathcal{E}_\ell - \mu_h + 2t_z^h \cos k_z}, \quad (7)$$

where $\mu_h = \varepsilon_0 - \mu$, $\mathcal{E}_\ell = \omega_c(\ell + \frac{1}{2})$, $\omega_c = eH/m_h c$ is the cyclotron frequency, and $L_\ell(x)$ are the Laguerre polynomials.

We note that in the single-band case the chemical potential of the shallow band may depend on the magnetic field⁴⁷. However, in our case the deep band serves as the particle reservoir that stabilizes the chemical potential. This allows us to solve the gap function assuming fixed chemical potential, see also Ref.⁴⁸.

III. TRANSITION TEMPERATURE IN ZERO MAGNETIC FIELD (T_C)

For zero magnetic field, the superconducting order parameter is homogeneous $\Delta_{\mathbf{r}j}^\alpha = \Delta_0^\alpha$. This gives the linearized gap equation, which we represent as

$$\Delta_0^\alpha = \sum_\beta \Lambda_{\alpha\beta} \Lambda_{0,\beta}^{-1} \Delta_0^\beta, \quad (8)$$

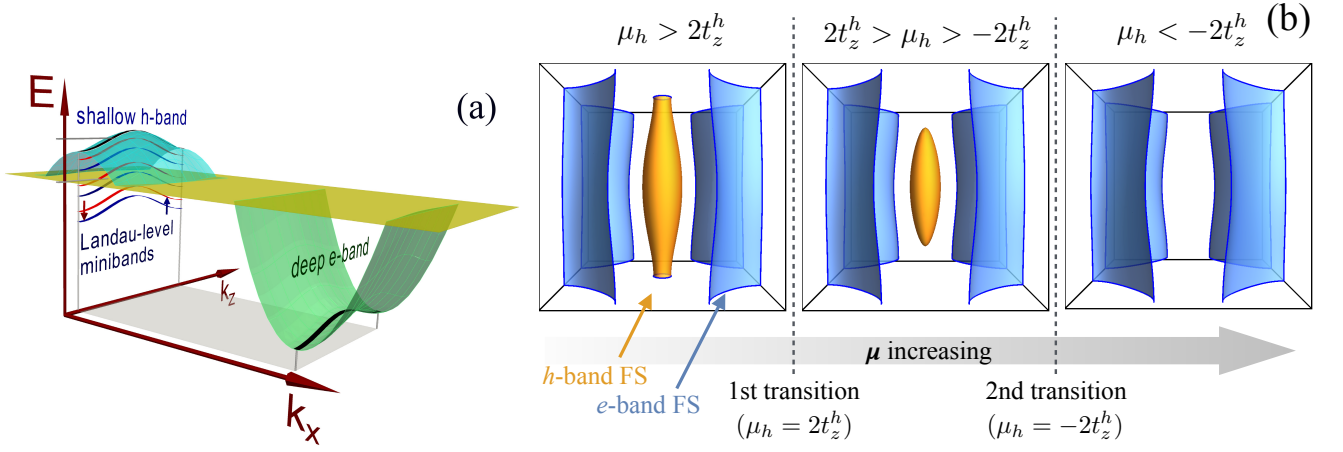


FIG. 1. (a) The illustration of electronic spectrum for a layered superconductor with deep and shallow bands. (b) The schematic diagram demonstrating the evolution of the Fermi surfaces of the quasi-2D model in Eq. (1) near the Lifshitz transitions. The first Lifshitz transition occurs at $\mu_h = 2t_z^h$, at which the neck at $k_z = 0$ interrupts and the FS of the h -band changes from open to closed. The second Lifshitz transition occurs at $\mu_h = -2t_z^h$, where the h -band becomes completely depleted.

where we have introduced the notations for the coupling matrix $\Lambda_{\alpha\beta} = U_{\alpha\beta}N_\beta$ with $N_\alpha = m_\alpha/(2\pi)$ is the densities of states per layer (for shallow band, N_h is the true density of states only in the regime of open Fermi surface, $\mu_h > 2t_z^h$), and

$$\Lambda_{0,\alpha}^{-1} \equiv N_\alpha^{-1} T \sum_{\omega_n=-\infty}^{\infty} \sum_{j'} \int_{\mathbf{r}'} K_{\omega_n}^\alpha(\mathbf{r}j, \mathbf{r}'j'). \quad (9)$$

The kernels are determined by the zero-field Green's function in Eq. (4) giving

$$\Lambda_{0,\alpha}^{-1} = N_\alpha^{-1} T \sum_{\omega_n} \sum_{\mathbf{k}k_z} [\omega_n^2 + (\xi_{\mathbf{k}}^\alpha - 2t_z \cos k_z)^2]^{-1},$$

see Appendix A1. We further integrate out the wave vectors in $\Lambda_{0,\alpha}^{-1}$ by using $\sum_{\mathbf{k}} = N_e \int_{-\Omega}^{\Omega} d\xi^e$ for e -band ($\sum_{\mathbf{k}} = N_h \int_{-\Omega}^{\mu_h} d\xi^h$ for h -band) and $\sum_{k_z} = \int_{-\pi}^{\pi} \frac{dk_z}{2\pi}$. Here, Ω is the energy cutoff and we have assumed that $\Omega \gg t_z, T_C, \mu_h$. We therefore obtain the following gap equation near T_C

$$[\hat{\Lambda}^{-1} - \hat{\Lambda}_0^{-1}] \begin{pmatrix} \Delta_0^h \\ \Delta_0^e \end{pmatrix} = 0, \quad (10)$$

where $\hat{\Lambda}_0^{-1} = \text{diag}[\Lambda_{0,h}^{-1}, \Lambda_{0,e}^{-1}]$ with

$$\Lambda_{0,e}^{-1} \approx \sum_{\omega_n > 0}^{\infty} \frac{2T_C}{\omega_n} \tan^{-1} \frac{\Omega}{\omega_n} \approx \ln \frac{A\Omega}{T_C}, \quad (11a)$$

$$\Lambda_{0,h}^{-1} \approx \frac{1}{2} \ln \frac{A\Omega}{T_C} + \Upsilon_C, \quad (11b)$$

$A = 2e^{\gamma_E}/\pi \approx 1.134$, and $\gamma_E \approx 0.5772$ is the Euler-Mascheroni constant. Here the parameter $\Upsilon_C = \Upsilon_{T_C}$ is the value of the temperature-dependent function

$$\Upsilon_T = \sum_{\omega_n > 0}^{\infty} \int_{-\pi}^{\pi} \frac{dk_z}{2\pi} \frac{2T}{\omega_n} \tan^{-1} \left[\frac{\mu_h - 2t_z^h \cos k_z}{\omega_n} \right] \quad (12)$$

at $T = T_C$. This parameter appears due to the cut off at the band edge for the shallow band. We can carry out k_z -integration and the Matsubara-frequency sum in Υ_T using the relation $\tan^{-1} \frac{1}{a} = -\int_0^\infty \frac{dx}{x} e^{-ax} \sin x$. This gives

$$\Upsilon_T = -\int_0^\infty \frac{ds}{\pi s} \ln \tanh(\pi T s) \sin(2\mu_h s) J_0(4t_z^h s), \quad (13)$$

where $J_0(x)$ is the Bessel's function. In the limit of low temperatures, $T \ll \mu_h$, this function diverges logarithmically, $\Upsilon_T \approx \frac{1}{2} \ln \left[A \left(\mu_h + \sqrt{\mu_h^2 - (2t_z^h)^2} \right) / (2T) \right]$.

The transition temperature T_C is determined by the condition of degeneracy of the matrix $\hat{W} \equiv \hat{\Lambda}^{-1} - \hat{\Lambda}_0^{-1}$, i. e., $\det[\hat{W}] = 0$. This equation determines $\Lambda_{0,e}$ as

$$\Lambda_{0,e}^{-1} = \frac{\Lambda_{ee} + \frac{\Lambda_{hh}}{2}}{\mathcal{D}_\Lambda} - \Upsilon_C + \delta_\Lambda \sqrt{\left(\frac{\Lambda_{ee} - \frac{\Lambda_{hh}}{2}}{\mathcal{D}_\Lambda} - \Upsilon_C \right)^2 + 2 \frac{\Lambda_{eh}\Lambda_{he}}{\mathcal{D}_\Lambda^2}} \quad (14)$$

with $\delta_\Lambda = -\text{sign}[(1 - \Upsilon_C \Lambda_{hh})\mathcal{D}_\Lambda]$ and $\mathcal{D}_\Lambda = \Lambda_{ee}\Lambda_{hh} - \Lambda_{eh}\Lambda_{he}$. This parameter directly determines T_C by Eq. (11a). In the following consideration, we will use the zero-field equation, Eq. (10), to eliminate the logarithmic divergencies from the gap equation at finite magnetic field.

IV. SUPERCONDUCTING INSTABILITY IN MAGNETIC FIELD

In the presence of magnetic field, the superconducting order parameter is nonuniform. Near the onset of the superconducting instabilities in the magnetic field,

the solutions for the linear problem in Eq. (2) are given by the Landau-level eigenfunctions. Typically, the *lowest Landau-level* eigenfunction yields the optimal H_{C2} , where the superconducting instability develops first⁴⁹. This solution has the following shape²⁷

$$\Delta_{\mathbf{r},j}^\alpha = \Delta_0^\alpha \exp\left(-\frac{r^2}{2l^2} + iQ_z j\right). \quad (15)$$

We have assumed the possibility of the layer-to-layer modulation in the order parameters with the wave vector Q_z .⁵⁰ Such modulation is the realization of the nonuniform FFLO state^{25,26}. Superconducting instability is determined by the condition that Eq. (15) provides a solution of the gap equation at least for one value of Q_z and then this optimal modulation wave vector realizes in the emerging superconducting state. The *ansatz* in Eq. (15) is the kernel eigenfunction in the magnetic field,

$$\sum_{j'} \int_{\mathbf{r}'} K_{\omega_n}^\alpha(\mathbf{r}j, \mathbf{r}'j') \Delta_{\mathbf{r}'j'}^\alpha = \pi N_\alpha \lambda_{\omega_n, Q_z}^\alpha \Delta_{\mathbf{r},j}^\alpha \quad (16)$$

with

$$\lambda_{\omega_n, Q_z}^\alpha = \frac{2}{N_\alpha} \int_0^\infty \rho d\rho \exp\left(-\frac{\rho^2}{2l^2}\right) \times \left\langle g_{\omega_n, +}^\alpha\left(\rho, k_z - \frac{Q_z}{2}\right) g_{-\omega_n, -}^\alpha\left(\rho, k_z + \frac{Q_z}{2}\right) \right\rangle_z. \quad (17)$$

Here and below we use notation $\langle F(k_z) \rangle_z \equiv \int_{-\pi}^\pi \frac{dk_z}{2\pi} F(k_z)$ for the averaging with respect to k_z . We omit the dependence of $\lambda_{\omega_n, Q_z}^\alpha$ on T , H , and the electronic parameters. As follows from the definitions of the Green's functions, Eqs. (6) and (7), $(\lambda_{\omega_n, Q_z}^\alpha)^* = \lambda_{-\omega_n, Q_z}^\alpha$. Next, we first discuss the kernel eigenvalue for the deep e -band and then for the shallow h -band.

For the deep e -band, the Landau quantization does not play a role. Using Eqs. (6) and (17), linearizing the band dispersion at Fermi level $[\varepsilon_{\mathbf{k}_F + \mathbf{q}}^e \approx \varepsilon_{\mathbf{k}_F}^e + \mathbf{v}_e \cdot \mathbf{q}]$, where $\mathbf{v}_e = \nabla_{\mathbf{k}} \varepsilon_{\mathbf{k}}^e|_{\mathbf{k}_F} = \mathbf{k}^F/m_e$ with the Fermi wave vector $\mathbf{k}^F = (k_x^F, k_y^F)$, we obtain the following quasiclassical result for the kernel eigenvalue

$$\lambda_{\omega_n, Q_z}^e = 2 \int_0^\infty ds \left\langle \exp\left[-\frac{s^2\left(\mu + 2t_z^e \cos k_z \cos \frac{Q_z}{2}\right)}{m_e l^2}\right] - 2s\zeta_\omega \left(\omega_n + i\mu_z H - 2it_z^e \sin k_z \sin \frac{Q_z}{2}\right) \right\rangle_z, \quad (18)$$

where $\zeta_\omega \equiv \text{sign}(\omega_n)$. The derivation details are described in the Appendix A 2 a.

For the shallow h -band, substituting the Green's function, Eq. (7), into the general presentation in Eq. (17),

and using relation $\int_0^\infty dx L_\ell(x) L_{\ell'}(x) e^{-2x} = \frac{(\ell + \ell')!}{2^{\ell + \ell' + 1} \ell! \ell'!}$, we derive

$$\lambda_{\omega_n, Q_z}^h = -\frac{1}{2\pi\omega_c} \quad (19)$$

$$\times \sum_{\ell\ell'} \left\langle \frac{(\ell + \ell')! / (2^{\ell + \ell'} \ell! \ell'!)}{(i\bar{\omega}_n + \ell + \frac{1}{2} - \tilde{\gamma}_z + \tilde{\mu}_h)(i\bar{\omega}_n - \ell' - \frac{1}{2} - \tilde{\gamma}_z + \tilde{\mu}_h)} \right\rangle_z,$$

where we introduced the following notations

$$\tilde{\mu}_h(k_z, Q_z) = \bar{\mu}_h - 2t_z^h \cos k_z \cos(Q_z/2), \quad (20a)$$

$$\tilde{\gamma}_z(k_z, Q_z) = \gamma_z - 2t_z^h \sin k_z \sin(Q_z/2). \quad (20b)$$

Here all “barred” normalized quantities are defined as $\bar{a} \equiv a/\omega_c$ (with $a = \omega_n, \mu_h, t_z$). Furthermore, $\gamma_z = \mu_z m_h c/e = gm_h/4m_0$ is the reduced spin-splitting parameter, where m_0 is the free-electron mass and g is the band-electrons g -factor.

Therefore, the gap equation, Eq. (2), in the presence of the magnetic field becomes

$$\hat{\Lambda}^{-1} \begin{bmatrix} \Delta_0^h \\ \Delta_0^e \end{bmatrix} = 2\pi T \text{Re} \sum_{\omega_n > 0}^\Omega \begin{bmatrix} \lambda_{\omega_n, Q_z}^h \Delta_0^h \\ \lambda_{\omega_n, Q_z}^e \Delta_0^e \end{bmatrix}. \quad (21)$$

The Matsubara-frequency sums, $\mathcal{S}_\alpha(H, T, Q_z) \equiv 2\pi T \sum_{\omega_n > 0}^\Omega \lambda_{\omega_n, Q_z}^\alpha$, are logarithmically-divergent and have to be cut at $\omega_n \sim \Omega$. Similarly to the two-dimensional case²⁴, we can regularize the gap equation using its zero-field counterpart, Eq. (10). Namely, we decompose $\mathcal{S}_\alpha(H, T, Q_z)$ as $\mathcal{S}_\alpha(H, T, Q_z) = [\mathcal{S}_\alpha(H, T, Q_z) - \mathcal{S}_\alpha(0, T, 0)] + [\mathcal{S}_\alpha(0, T, 0) - \mathcal{S}_\alpha(0, T_C, 0)] + \mathcal{S}_\alpha(0, T_C, 0)$ with $\mathcal{S}_\alpha(0, T_C, 0) \equiv \Lambda_{0,\alpha}^{-1}$ being the only log-diverging term. This leads to

$$\hat{W} \begin{bmatrix} \Delta_0^h \\ \Delta_0^e \end{bmatrix} + \begin{bmatrix} \mathcal{A}_1 \Delta_0^h \\ \mathcal{A}_2 \Delta_0^e \end{bmatrix} = \begin{bmatrix} \mathcal{J}_1 \Delta_0^h \\ \mathcal{J}_2 \Delta_0^e \end{bmatrix}. \quad (22)$$

Here $\mathcal{A}_\alpha(T) \equiv \mathcal{S}_\alpha(0, T_C, 0) - \mathcal{S}_\alpha(0, T, 0)$ are the temperature-dependent parts of the pairing eigenvalues, $\mathcal{A}_2(T) = \ln(T/T_C)$ and $\mathcal{A}_1(T) = \frac{1}{2} \ln(T/T_C) - \Upsilon_T + \Upsilon_C$, where the function $\Upsilon_T(T/\mu_h, t_z^h/\mu_h)$ is defined in Eq. (13). The field-dependent parts, $\mathcal{J}_\alpha(H, T, Q_z) \equiv \mathcal{S}_\alpha(H, T, Q_z) - \mathcal{S}_\alpha(0, T, 0)$, are

$$\mathcal{J}_1(H, T, Q_z) = 2\pi T \sum_{\omega_n > 0}^\infty \text{Re} \left(\lambda_{\omega_n, Q_z}^h - \frac{1}{2\omega_n} \right) - \Upsilon_T, \quad (23a)$$

$$\mathcal{J}_2(H, T, Q_z) = 2\pi T \sum_{\omega_n > 0}^\infty \text{Re} \left(\lambda_{\omega_n, Q_z}^e - \frac{1}{\omega_n} \right). \quad (23b)$$

Note that, by definition, $\mathcal{A}_\alpha(T_C) = 0$ and $\mathcal{J}_\alpha(0, T, 0) = 0$. Therefore, the UV cutoffs are explicitly removed and the Matsubara-frequency sums in the right-hand side in Eqs. (23a) and (23b) converge now in the limit of $\Omega \rightarrow \infty$. We can represent the functions \mathcal{J}_α in this limit as

$$\mathcal{J}_1(H, T, Q_z) = \frac{1}{4} \sum_{m=0}^{\infty} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell!} \left\langle \frac{\mathcal{T}(\ell + \tilde{\gamma}_z - \tilde{\mu}_h) + \mathcal{T}(m-\ell - \tilde{\gamma}_z - \tilde{\mu}_h) - 2\mathcal{T}(\frac{m}{2} - \tilde{\mu}_h)}{m+1-2\tilde{\mu}_h} \right\rangle_z$$

$$- \frac{1}{2} \left\langle \int_0^{1/2} dx \frac{\mathcal{T}(\frac{x-1}{2} - \tilde{\mu}_{h0})}{x-2\tilde{\mu}_{h0}} + \sum_{m=0}^{\infty} \int_{-1/2}^{1/2} dx \left[\frac{\mathcal{T}(\frac{m+x}{2} - \tilde{\mu}_{h0})}{m+1+x-2\tilde{\mu}_{h0}} - \frac{\mathcal{T}(\frac{m}{2} - \tilde{\mu}_h)}{m+1-2\tilde{\mu}_h} \right] \right\rangle_z, \quad (24a)$$

$$\mathcal{J}_2(H, T, Q_z) = 2 \int_0^{\infty} ds \ln \tanh \left(\frac{\pi T}{\omega_c^e} s \right) \langle \exp(-\tilde{\mu}_e s^2) [\tilde{\mu}_e s \cos(2\tilde{\gamma}_z^e s) + \tilde{\gamma}_z^e \sin(2\tilde{\gamma}_z^e s)] \rangle_z, \quad (24b)$$

where we introduced notations $\mathcal{T}(x) \equiv \tanh[\omega_c(x + \frac{1}{2})/2T]$, $\tilde{\mu}_{h0}(k_z) = \tilde{\mu}_h - 2\tilde{t}_z^h \cos k_z$. Furthermore, $\omega_c^e = eH/cm_e$ is the e -band cyclotron frequency, $\tilde{\mu}_e \equiv \tilde{\mu} + 2\tilde{t}_z^e \cos k_z \cos \frac{Q_z}{2}$, $\tilde{\gamma}_z^e \equiv \gamma_z - 2\tilde{t}_z^e \sin k_z \sin \frac{Q_z}{2}$, $\tilde{\mu} = \mu/\omega_c^e$, and $\tilde{t}_z^e = t_z^e/\omega_c^e$. We remind that the parameters $\tilde{\mu}_h$ and $\tilde{\gamma}_z$ also depend on k_z , see Eqs. (20a) and (20b). We describe derivation of $\mathcal{J}_1(H, T, Q_z)$ in the Appendix A 2 b. The double sum in Eq. (24a) collects the contributions to pairing coming from the quasiparticles located at the Landau levels ℓ and $m-\ell$. The quantum kernel eigenvalue \mathcal{J}_1 depends on five independent dimensionless parameters: the reduced magnetic field ω_c/μ_h , the reduced temperature T/μ_h , the modulation wave vector Q_z , the ratio t_z^h/μ_h , and the spin-splitting factor γ_z .

The H_{C2} problem is reduced to the solution of equation

$$\det \begin{bmatrix} W_{11} + \mathcal{A}_1 - \mathcal{J}_1 & W_{12} \\ W_{21} & W_{22} + \mathcal{A}_2 - \mathcal{J}_2 \end{bmatrix} = 0 \quad (25)$$

for a given T and Q_z , and we need to find the optimized Q_z in $H_{C2}(T, Q_z)$ for which the instability develops first. As the matrix \hat{W} is degenerate, this equation can be rewritten as

$$\prod_{\alpha=1,2} \left(1 + \frac{\mathcal{A}_\alpha(T) - \mathcal{J}_\alpha(H, T, Q_z)}{W_{\alpha\alpha}} \right) = 1. \quad (26)$$

This is our main equation for determination of the upper critical field in two-band layered superconductors. All information about the coupling matrix is contained in the two parameters, W_{11} and W_{22} . The analytical expressions for these parameters can be derived from Eq. (10), see also Ref. ²⁴,

$$W_{11} = \frac{\Lambda_{ee} - \frac{1}{2}\Lambda_{hh}}{2\mathcal{D}_\Lambda} - \frac{\Upsilon_C}{2} + \delta_W \frac{R}{2} \quad (27a)$$

$$W_{22} = -\frac{\Lambda_{ee} - \frac{1}{2}\Lambda_{hh}}{\mathcal{D}_\Lambda} - \Upsilon_C + \delta_W R \quad (27b)$$

with $\mathcal{D}_\Lambda = \Lambda_{ee}\Lambda_{hh} - \Lambda_{he}\Lambda_{eh}$, $\delta_W = \text{sign}[\mathcal{D}_\Lambda(1 - \Upsilon_C\Lambda_{hh})]$, and

$$R = \sqrt{\left(\frac{\Lambda_{ee} - \frac{1}{2}\Lambda_{hh}}{\mathcal{D}_\Lambda} - \Upsilon_C \right)^2 + 2 \frac{\Lambda_{he}\Lambda_{eh}}{\mathcal{D}_\Lambda^2}}. \quad (28)$$

As follows from Eq. (26) the weights with which the bands contribute to the pairing near the upper critical field scale as $1/|W_{\alpha\alpha}|$.

The behavior of the upper critical field is mostly determined by the shape of the kernel eigenvalues $\mathcal{J}_\alpha(H, T, Q_z)$. In general, larger values of \mathcal{J}_α correspond to stronger pairing strength. In the next section, we will explore in detail the quantum kernel eigenvalue \mathcal{J}_1 .

V. BEHAVIOR OF THE QUANTUM PAIRING KERNEL EIGENVALUE

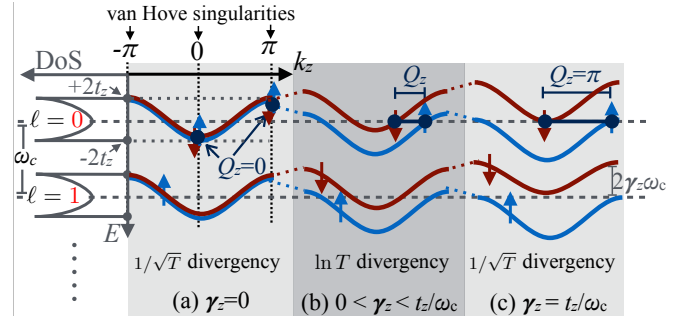


FIG. 2. The schematic diagram illustrating the k_z spectrum of the shallow h -band in the magnetic field in different situations. The dispersion along k_z -direction has two van Hove singular points at $k_z = 0, \pi$. If the spin-up and spin-down van Hove singular points match the Fermi level, the superconducting pairings lead to $1/\sqrt{T}$ -divergence in the pairing kernel eigenvalue \mathcal{J}_1 [cases (a) and (c)]. The matching condition for (a) is $\omega_c = (\mu_h \pm 2t_z)/(\ell + \frac{1}{2})$ and for (c) is $\omega_c = \mu_h/(\ell + \frac{1}{2})$. The pairing instabilities for cases (b) and (c) favor the formation of the FFLO states with non-zero Q_z .

The shape of magnetic field-temperature phase diagrams is determined by the behavior of the pairing kernel eigenvalues \mathcal{J}_α . While the quasiclassical kernel eigenvalue \mathcal{J}_2 is well studied and has monotonic dependence on the magnetic field for all temperatures, the quantum kernel eigenvalue \mathcal{J}_1 has rather complicated nonmonotonic dependence on the magnetic field which is very sensitive to the electronic-spectrum parameters μ_h and t_z^h as well as the spin-splitting factor γ_z . The electronic

spectrum of the shallow band in the magnetic field is composed of the Landau-level minibands with width $4t_z^h$ (see Fig. 2a). The system has series of Lifshitz transitions with increasing magnetic field when the chemical potential enters or exits a particular miniband. At low temperatures, the magnetic-field dependences of \mathcal{J}_1 have features at these transitions whenever the chemical potential crosses the van Hove points at the miniband edges. There are two such points for every miniband corresponding to two values of k_z , 0 and π . In addition, there are two minibands for every Landau level for two spin orientations. This gives *four* miniband-edge magnetic fields per Landau level, $H_{\ell,\sigma,\delta_t} = (cm_h/e)\omega_{\ell,\sigma,\delta_t}$, corresponding to cyclotron frequencies

$$\omega_{\ell,\sigma,\delta_t} = \frac{\mu_h + 2\delta_t t_h^h}{\ell + \frac{1}{2} + \sigma\gamma_z}, \quad (29)$$

where $\sigma = \pm 1$ (\uparrow/\downarrow) describes spin orientation and $\delta_t = 1$ and -1 corresponds to $k_z = \pi$ and 0 respectively. In addition, we have to consider the behavior of \mathcal{J}_1 for different modulation wave vectors Q_z . In general, as the larger \mathcal{J}_1 corresponds to stronger pairing strength, the shallow band favors the states which maximize \mathcal{J}_1 .

Before proceeding to the investigation of the magnetic field-temperature phase diagrams for two-band systems, it is very instructive to study the analytical properties of the function $\mathcal{J}_1(H, T, Q_z)$, particularly, in the low-temperature limit. We first focus on its singularities when the magnetic field crosses the typical values in Eq. (29) and on identifying the possible divergencies for $T \rightarrow 0$, since these features have important implications on the superconducting instabilities. Next, we consider the magnetic field dependences of \mathcal{J}_1 for representative cases. Furthermore, by studying the Q_z dependences of \mathcal{J}_1 for different Zeeman spin-splitting parameters, we identify possible parameter ranges for FFLO instabilities.

A. The low-temperature limit and its divergencies

In this subsection, we investigate the leading divergencies of the quantum kernel eigenvalues \mathcal{J}_α as $T \rightarrow 0$ for different cases. We review first the behavior of the quasiclassical kernel eigenvalue, \mathcal{J}_2 , Eq. (24b). For all magnetic fields, \mathcal{J}_2 has the same logarithmic divergency as \mathcal{A}_2 so that $\mathcal{J}_2 - \mathcal{A}_2$ approaches a finite value. In the typical situation of a moderate spin-splitting factor, $\gamma_z \ll \sqrt{\mu/\omega_c^e}$, it can be treated perturbatively. For the uniform case, $Q_z = 0$, we derive from Eq. (24b) the result for the zero-temperature limit of the full quasiclassical kernel eigenvalue

$$\mathcal{J}_2(H, T \rightarrow 0, 0) - \mathcal{A}_2(T \rightarrow 0) = -\frac{1}{2} \ln r_C^{(0)}, \quad (30)$$

$$r_C^{(0)} \approx \frac{e^{\gamma_E} \omega_c^e \mu + \sqrt{\mu^2 - (2t_z^e)^2}}{\pi^2 T_C^2} \left(1 + \frac{2\gamma_z^2 \omega_c^e}{\sqrt{\mu^2 - (2t_z^e)^2}} \right).$$

The parameter $r_C^{(0)}$ is just the ratio $H/H_{c2}^e(0)$, where $H_{c2}^e(0)$ is the upper critical field of the deep band at zero temperature. In the case of finite Q_z the parameter $r_C^{(0)}$ has to be replaced by the function $r_C(Q_z)$. The closed analytical result for $r_C(Q_z)$ is not available even for $\gamma_z = 0$. One can only derive an approximate result in the limits, $\gamma_z \ll \sqrt{\mu/\omega_c^e}$ and $t_z^e/\mu, t_z^e \sin(Q_z/2)/\sqrt{\omega_c^e \mu} \ll 1$

$$r_C(Q_z) \approx \frac{e^{\gamma_E} \omega_c^e \mu}{\pi^2 T_C^2} \left[1 + 2 \frac{\omega_c^e \gamma_z^2}{\mu} + 4 \frac{(t_z^e)^2}{\mu \omega_c^e} \sin^2 \frac{Q_z}{2} - \frac{(t_z^e)^2}{\mu^2} \cos^2 \frac{Q_z}{2} \right]. \quad (31)$$

Generally, the quasiclassical kernel eigenvalue $\mathcal{J}_2 - \mathcal{A}_2$ is a monotonically decreasing function of H at all temperatures and spin-splitting parameters meaning that the magnetic field *always* suppresses superconductivity. As expected, it has maximum at $Q_z = 0$ in the limit $\gamma_z \ll \sqrt{\mu/\omega_c^e}$ meaning that the deep band favors the uniform state.

The quantum kernel eigenvalue \mathcal{J}_1 typically behaves similarly to \mathcal{J}_2 , i. e., it has the same logarithmic divergency as \mathcal{A}_1 , $\mathcal{J}_1 \propto \ln(T/T_C)$ so that the total kernel eigenvalue $\mathcal{J}_1 - \mathcal{A}_1$ approaches a finite value in the zero-temperature limit. This zero temperature value, however, has singular contributions when the magnetic field crosses the typical values given by Eq. (29), corresponding to Lifshitz transitions for the Landau-level minibands. We discuss these singularities in the next subsection. In several exceptional resonant cases, when two miniband-edge fields with opposite spin orientations are identical, the Landau quantization leads to faster divergency $\mathcal{J}_1 \propto 1/\sqrt{T}$. In the case when these two fields originate from the van-Hove singular points of the same type (either $k_z = 0$ or π) the divergency occurs in the uniform channel $Q_z = 0$. On the other hand, if the two fields correspond to the opposite van-Hove points, the divergency takes place in the alternating channel $Q_z = \pi$. We discuss both these cases below. Another divergency appears within the field ranges where the chemical potential simultaneously crosses two minibands with opposite spin orientations. In this case, the total kernel eigenvalue $\mathcal{J}_1 - \mathcal{A}_1$ diverges logarithmically for $T \rightarrow 0$ at the optimal wave vector $Q_z = Q_{\text{op}}$ connecting the minibands' Fermi momenta, see Fig. 2(b). All these low- T divergencies may lead to the high-field superconducting states.

1. Square-root singularity of the pairing kernel at the miniband-edge fields

As discussed above, the system has series of the miniband Lifshitz transitions at the magnetic fields given by Eq. (29). In this subsection we discuss singularity of the pairing kernel eigenvalue $\mathcal{J}_1(H, T \rightarrow 0, Q_z)$ at these transition, when the cyclotron frequency ω_c crosses the miniband-edge value $\omega_{\ell_0,\sigma,\delta_t}$. We consider here only a general nondegenerate situation when the corresponding

transition magnetic field, $H_{\ell_0, \sigma, \delta_t}$, is separated from other typical fields. The derivation in Appendix B 1 gives the result for the singular contribution at zero temperature

$$\begin{aligned} & \mathcal{J}_1(\omega_c) - \mathcal{J}_1(\omega_{\ell_0, \sigma, \delta_t}) \\ & \approx -\frac{\delta_t}{2\pi} \sqrt{\frac{\mu_h + 2\delta_t t_z^h}{t_z^h}} \sqrt{\left|1 - \frac{\omega_c}{\omega_{\ell_0, \sigma, \delta_t}}\right|} \theta\left[\delta_t \left(1 - \frac{\omega_c}{\omega_{\ell_0, \sigma, \delta_t}}\right)\right] \\ & \times \mathcal{G}_{\ell_0} \left[\frac{\mu_h + 2\delta_t t_z^h \cos^2 \frac{Q_z}{2}}{\omega_c} \right] \end{aligned} \quad (32)$$

with $\theta(x)$ being the step function and

$$\mathcal{G}_\ell(x) \equiv \sum_{m=\ell}^{\infty} \frac{m!}{2^m (m-\ell)!} \frac{1}{m+1-2x}.$$

We see that the square-root singularity $\mathcal{J}_1(H) \propto \sqrt{|H - H_{\ell_0, \sigma, \delta_t}|}$ appears near the transition point when the chemical potential is inside the Landau-level miniband, i.e., $H \gtrsim H_{\ell_0, \sigma, -}$ or $H \lesssim H_{\ell_0, \sigma, +}$. It reflects the pairing enhancement caused by the square-root divergency of the density of state at the edge of one-dimensional miniband. Finite temperature smears this singularity.

2. Resonant cases for the uniform state ($Q_z = 0$)

In the uniform state, $Q_z = 0$, the resonant condition corresponds to the matching of the Zeeman spin-splitting energy, $2\gamma_z \omega_c$, and the Landau-level energy spacing, $j_z \omega_c$, giving $2\gamma_z = j_z$ with integer $j_z \geq 0$. The divergency occurs when the Fermi level matches the van Hove singular point at $k_z = 0$ or π corresponding to the magnetic field

$$\omega_c = \frac{\mu_h \mp 2t_z}{\ell_0 + (j_z + 1)/2}. \quad (33)$$

Fig. 2(a) illustrates the simplest case with $j_z = 0$. In this case we derive in Appendix B 2 the following asymptotic behavior for $T \ll \omega_c, t_z^h$

$$\mathcal{J}_1(H, T, 0) \sim C \frac{(2\ell_0 + j_z)!}{2^{2\ell_0 + j_z} (\ell_0 + j_z)! \ell_0!} \frac{\omega_c}{\sqrt{t_z^h T}}, \quad (34)$$

where $C = (2\sqrt{2} - 1)\zeta(\frac{3}{2})/(8\pi^{3/2}) \approx 0.1072$ and $\zeta(x)$ is the Riemann zeta function [$\zeta(\frac{3}{2}) \approx 2.6124$]. We can see that the \mathcal{J}_1 diverges as $\sim 1/\sqrt{T}$ manifesting the enhancement of pairing. The coefficient decreases with increasing interlayer hopping t_z^h and with increasing of the resonance order described by the integers ℓ_0 and j_z . We note that for any small deviations from the condition $(\ell_0 + \frac{1}{2}j_z + \frac{1}{2})\omega_c = \mu_h \pm 2t_z^h$, the total eigenvalue $\mathcal{J}_1 - \mathcal{A}_1$ approaches a finite limit at $T \rightarrow 0$. We can also note that this divergency is somewhat weaker than the $1/T$ divergency for the 2D case²⁴, due to the smearing of δ -function singularity in the density of states at the Landau

levels by the interlayer hopping. Such $1/\sqrt{T}$ -divergency in the uniform state for zero or resonant spin-splitting factor has also been reported in Refs. 2 and 9.

For the strongest resonance at $\ell_0 = 0$, $j_z = 0$, and $\omega_c = 2(\mu_h \mp 2t_z^h)$ for $k_z = 0/\pi$, we derived in Appendix B 2 the more accurate asymptotic for the total kernel eigenvalue

$$\begin{aligned} \mathcal{J}_1 - \mathcal{A}_1 & \approx C \frac{\omega_c}{\sqrt{t_z^h T}} + \mathcal{R}_\mp(\bar{t}_z^h) - \frac{1}{2} \ln \frac{\omega_c}{\pi T_C} - \Upsilon_C, \quad (35) \\ \mathcal{R}_\mp(\bar{t}_z^h) & = \frac{1}{2} \sum_{m=1}^{\infty} \left(\frac{1}{\sqrt{m(m \mp 8\bar{t}_z^h)}} - \frac{1}{m} \right). \end{aligned}$$

For $k_z = 0$ the functions $\mathcal{R}_-(\bar{t}_z^h)$ diverges for $\omega_c = 8t_z^h$. As $\omega_c = 2(\mu_h - 2t_z^h)$, meaning that this result is only valid for $\mu_h > 6t_z^h$.

We mention that the spin splitting is a fixed material's parameter and therefore the resonance cases, $2\gamma_z = j_z$, are exceptional. To some extent, the effective spin splitting can be tuned by tilting the magnetic field⁵¹. We note however, that in contrast to the two-dimensional case²⁴, in layered superconductors the in-plane magnetic field also influences the orbital motion of quasiparticles meaning that the problem of the upper critical field for this case requires separate consideration.

3. Resonant cases for alternating FFLO state ($Q_z = \pi$)

The resonance enhancement of pairing may also take place in the *alternating* FFLO state because in this case the modulation wave vector $Q_z = \pi$ couples the van Hove singular points at $k_z = 0$ and π . Such enhancement is a unique property of a layered superconductor with open Fermi surface and it only exists for specific relations between the band parameters μ_h and t_z^h . Writing the full quasiparticle energy in the magnetic field as $\xi_\pm^h(\ell, k_z) = \mu_h - \omega_c(\ell + \frac{1}{2} \pm \gamma_z) - 2t_z^h \cos k_z$, we can identify that the resonance conditions are realized when the spin-down (spin-up) energy at $k_z = 0$ at the Landau level ℓ_0 simultaneously matches with the spin-up (spin-down) energy at $k_z = \pi$ at the Landau level ℓ_π and with the chemical potential, i. e., $\xi_\mp^h(\ell_0, 0) = \xi_\pm^h(\ell_\pi, \pi) = 0$ [see the first-case example with $\ell_0 = \ell_\pi = 0$ in Fig. 2 (c)]. This gives the conditions

$$\omega_c = \frac{4t_z^h}{\ell_\pi - \ell_0 \pm 2\gamma_z} = \frac{2\mu_h}{\ell_0 + \ell_\pi + 1}, \quad (36a)$$

$$\mu_h = \frac{\omega_c}{2} (\ell_0 + \ell_\pi + 1) = \frac{2t_z^h (\ell_0 + \ell_\pi + 1)}{\ell_\pi - \ell_0 \pm 2\gamma_z}. \quad (36b)$$

To derive the low-temperature behavior of \mathcal{J}_1 , we substitute the conditions in Eqs. (36a) and (36b) into Eq. (24a) with $Q_z = \pi$. The derivation described in Appendix B 3 yields the low-temperature asymptotic for generic case of noninteger $2\gamma_z$

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{C (\ell_0 + \ell_\pi)!}{2^{2\ell_0 + \ell_\pi} \ell_0! \ell_\pi!} \frac{\omega_c}{\sqrt{T t_z^h}}. \quad (37)$$

where the numerical constant C is defined above, after Eq. (34). We note that this additional divergency is purely a consequence of the interplay between the Landau quantization and interlayer tunneling. In particular, such FFLO instability is absent in the 3D case with k_z^2 dispersion.

For the strongest resonance, $\ell_0 = \ell_\pi = 0$, $\mu_h = t_z^h/\gamma_z$ ($\gamma_z < 0.5$), and $\omega_c = 2\mu_h$, we derived the more accurate asymptotic

$$\mathcal{J}_1 - \mathcal{A}_1 \simeq \frac{C}{2} \frac{\omega_c}{\sqrt{T} t_z^h} - \frac{1}{2} \ln \frac{2\omega_c}{\pi T_c} - \Upsilon_C. \quad (38)$$

In the real systems such instability can be obtained by tuning the chemical potential μ_h by doping or pressure.

4. Logarithmic divergency at the optimal modulation wave vector

In the case when the chemical potential crosses two Landau-level branches with opposite spin orientations, the kernel eigenvalue also has logarithmic divergency at the wave vector connecting the crossing points, see Fig. 2(b). This divergency originates from the one-dimensional character of the electronic spectrum. The similar result was also found in the study of a three-dimensional model with parabolic Landau minibands⁹. For illustration, we consider such divergency for such branches belonging to the same Landau level with index ℓ_0 . In this case the diverging term in Eq. (24a) is the one with $m = 2\ell_0$ and $\ell = \ell_0$,

$$\mathcal{J}_{1,\ell_0} = \frac{\omega_c}{4} \frac{(2\ell_0)!}{2^{2\ell_0} (\ell_0!)^2} \times \int_{-\pi}^{\pi} \frac{dk_z}{2\pi} \sum_{\delta=\pm 1} \frac{\tanh\left[\frac{\omega_c(\ell_0 + \frac{1}{2} + \delta\gamma_z) - \mu_h + 2t_z^h \cos(k_z + \delta\frac{Q_z}{2})}{2T}\right]}{\omega_c(2\ell_0 + 1) - 2\left(\mu_h - 2t_z^h \cos k_z \cos \frac{Q_z}{2}\right)}.$$

For the optimal modulation wave vector $Q_z = Q_{\text{op}}$ shown in Fig. 2(b), we have the relations

$$\omega_c(\ell_0 + \frac{1}{2} + \delta\gamma_z) - \mu_h + 2t_z^h \cos\left(k_{z0} + \delta\frac{Q_{\text{op}}}{2}\right) = 0,$$

for $\delta = \pm 1$, where $k_{z0} \pm Q_{\text{op}}/2$ are the Fermi wave vectors for the two considered branches. These relations determine Q_{op} as

$$Q_{\text{op}} = \sum_{\delta=\pm 1} \delta \arccos\left[\frac{\mu_h - \omega_c(\ell_0 + \frac{1}{2} + \delta\gamma_z)}{2t_z^h}\right]. \quad (39)$$

In the limit $T \ll t_z^h$ the dominating contribution to $\mathcal{J}_{1,0}$ is coming from the regions near the Fermi momenta meaning that we can use expansion $k_z = k_{z0} + \tilde{k}$ with

$\tilde{k} \ll k_{z0}$ and approximate

$$\mathcal{J}_{1,\ell_0} \approx \frac{(2\ell_0)!}{32\pi 2^{2\ell_0} (\ell_0!)^2} \frac{\omega_c}{t_z^h \sin k_{z0} \cos \frac{Q_{\text{op}}}{2}} \times \sum_{\delta=\pm 1} \int_{-\pi}^{\pi} \frac{d\tilde{k}}{\tilde{k}} \tanh\left[\frac{t_z^h}{T} \sin\left(k_{z0} + \delta\frac{Q_{\text{op}}}{2}\right) \tilde{k}\right].$$

Evaluating the integral, we obtain

$$\mathcal{J}_{1,\ell_0} \approx \frac{(2\ell_0)!}{8\pi 2^{2\ell_0} (\ell_0!)^2} \frac{\omega_c}{t_z^h \sin k_{z0} \cos \frac{Q_{\text{op}}}{2}} \times \ln \left[\frac{t_z^h}{T} \sqrt{\left| \sin\left(k_{z0} - \frac{Q_{\text{op}}}{2}\right) \sin\left(k_{z0} + \frac{Q_{\text{op}}}{2}\right) \right|} \right]. \quad (40)$$

This logarithmic divergency for $T \rightarrow 0$ is similar to the well-known Peierls divergency of the electronic susceptibility for one-dimensional metals at the nesting wave vector which, in particular, leads to the charge-density-wave transition. In the simplest scenario when the chemical potential crosses only two minibands, the kernel eigenvalue diverges only at one wave vector. In more complicated cases with many minibands at the Fermi level, the divergency takes place at several wave vectors and one can expect competition between multiple ground states, similar to the situation considered in Ref.⁴².

B. Magnetic-field dependences of quantum kernel eigenvalue \mathcal{J}_1 for different cases

Now, we discuss the general behavior of the kernel eigenvalue \mathcal{J}_1 . In contrast to the monotonic behavior of the quasiclassical result, the low-temperature divergencies discussed in the section V A may lead to the emergence of strong peaks in \mathcal{J}_1 at the specific magnetic fields and modulating wave vectors Q_z which indicate the enhancement of pairing. The magnitude and location of these peaks are sensitive to the details of electronic band properties.

1. The uniform state: $Q_z = 0$

Figure 3 illustrates the effects of interlayer tunneling, temperature, and Zeeman spin-splitting in the *uniform state* ($Q_z = 0$). Without spin splitting, the interlayer tunneling broadens the Landau levels and splits a single divergent peak into two smaller peaks at low temperatures [see Fig. 3(a)]. The smaller peaks correspond to the matching between the chemical potential and the van Hove singularities in the spectrum at $k_z = 0$ and π , Eq. (33). Their values are estimated by Eq. (34). The shaded regions mark the field ranges for which the chemical potential is located within the broadened Landau levels, and their boundaries correspond to the crossing of the van Hove singularities.

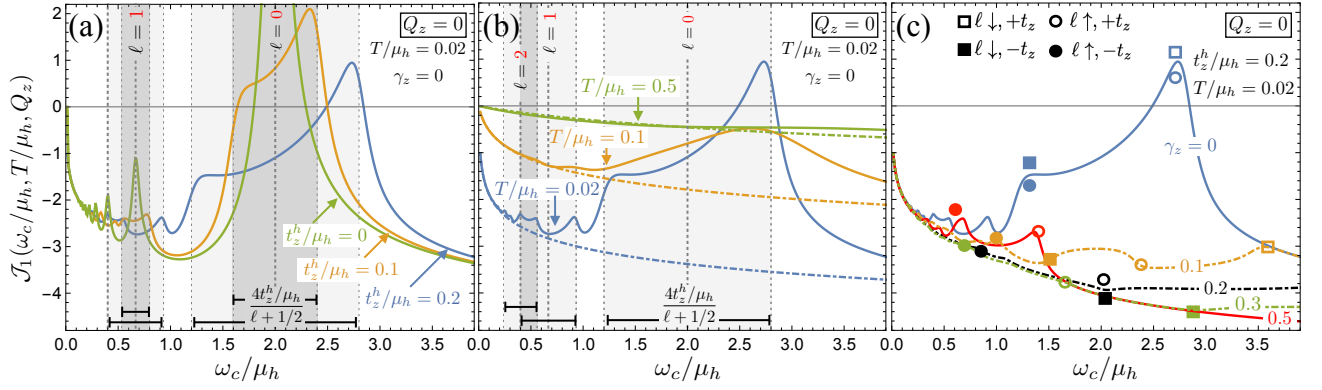


FIG. 3. The behavior of the kernel eigenvalue \mathcal{J}_1 in the uniform state, $Q_z = 0$, for different interlayer tunnelings t_z^h (a), temperatures (b), and spin-splitting factors γ_z (c). We can see that at low temperatures the function $\mathcal{J}_1(H)$ has pronounced peaks when the chemical potential matches Landau levels broadened by the interlayer tunneling. From plots in the panel (a) we can see that the interlayer tunneling splits a single 2D peak into two smaller peaks corresponding to the locations of the van Hove singularities in the spectrum at $k_z = 0$ and π , Eq. (33). Plots in the panel (b) show that thermal fluctuations smear the Landau levels and eventually wash out the quantum effects near $T \sim \omega_c/2$. The dot-dashed lines are the quasiclassical results. Plots in the panel (c) indicate that the uniform state is very sensitive to the Zeeman spin-splitting effects: the Landau peaks are rapidly suppressed at very small γ_z . Smaller peaks reappear when the resonant conditions are met ($2\gamma_z = j_z$). The symbols mark the miniband-edge magnetic fields, at which the chemical potential matches the van Hove points, Eq. (29).

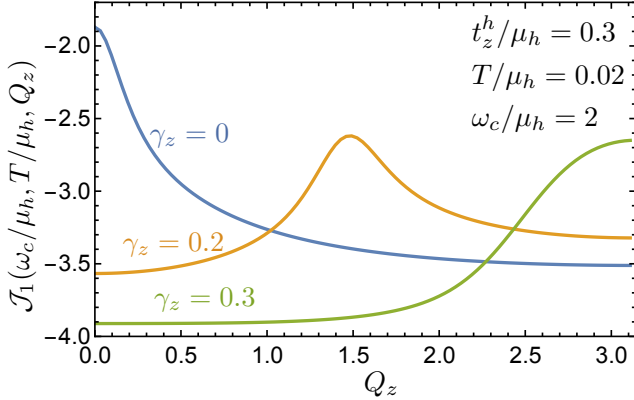


FIG. 4. The representative dependences of the pairing kernel eigenvalue on the modulation wave vector Q_z . In the resonance cases with integer $2\gamma_z$ the maximum of \mathcal{J}_1 is always realized at $Q_z = 0$ corresponding to the uniform state. The curve with $\gamma_z = 0.2$ illustrates the nonresonant case, when the chemical potential crosses both spin up and spin down zero Landau-level minibands, as illustrated in Fig. 2(b). The maximum is realized at the modulation vector connecting the Fermi momenta of these minibands. Finally, the curve with $\gamma_z = 0.3$ illustrates a special situation when the chemical potential matches two opposite van Hove points at $k_z = 0$ and π , see Fig. 2(c). In this case, the maximum is realized at $Q_z = \pi$ favoring the alternating FFLO state.

Figure 3(b) shows that the peaks are rapidly smeared by the thermal effects and disappear at $T \sim \omega_c/2$. In this figure, we compare the exact kernel eigenvalue with the quasiclassical results (dot-dashed lines), which are

calculated by using

$$\mathcal{J}_1^{qc}(H, T, Q_z) = 2 \int_0^\infty ds \left\langle \ln \tanh \left(\frac{\pi T}{\omega_c} s \right) \exp(-\tilde{\mu}_h s^2) \times [\tilde{\mu}_h s \cos(2\tilde{\gamma}_z s) + \tilde{\gamma}_z \sin(2\tilde{\gamma}_z s)] \right\rangle_z. \quad (41)$$

This quasiclassical approximation of \mathcal{J}_1 can be obtained from the quantum kernel in Eq. (24a) by assuming small-field limit⁵², $\omega_c \ll \mu_h$ with the temperature range, $\omega_c \ll T \ll \mu_h$. One can see that this approximation yields a monotonic behavior for the kernel eigenvalue in the magnetic field and gives a good approximation at low fields.

We can see in Fig. 3(c) that the divergent peaks are also rapidly suppressed by finite spin splitting γ_z meaning that the uniform state is highly susceptible to the Zeeman effect. The smaller peaks reappear if the resonant conditions are met (the solid red line for $\gamma_z = 0.5$). We also observe a noticeable enhancement of \mathcal{J}_1 in the field ranges where the chemical potential crosses both spin up and spin down minibands for the zero Landau level (e. g., in the range $1.5 < \omega_c/\mu_h < 2.4$ for $\gamma_z = 0.1$). We point, however, that in this range the maximal \mathcal{J}_1 is not at $Q_z = 0$. We discuss the Q_z dependences in the next subsection.

2. The FFLO modulated state: $Q_z \neq 0$

We now consider the behavior of the quantum kernel eigenvalue at finite modulation wave vectors Q_z . Figure 4 shows the dependences of \mathcal{J}_1 on Q_z for fixed electronic-spectrum parameters, fixed magnetic field and for three spin-splitting factors representing different cases. In the resonant cases with half-integer spin-splitting factors the

kernel eigenvalue always has the maximum at $Q_z = 0$, as illustrated by the curve with $\gamma_z = 0$. The finite- Q_z modulated states are not favorable in these cases, due to the absence of strong Zeeman pairbreaking at the Landau levels [see Fig. 2(a)], and the uniform state always dominates. Away from the uniform-state resonances, $2\gamma_z \neq j_z$, the Zeeman pairbreaking favors developing of the finite- Q_z states. The second curve with $\gamma_z = 0.2$ illustrates the situation when the chemical potential crosses both spin up and spin down zero Landau-level minibands. In this case, the maximum is realized at the modulation wave vector connecting the minibands Fermi momenta, see Fig. 2(b). This modulation vector varies with the magnetic field. The third curve with $\gamma_z = 0.3$ illustrates a special situation when the chemical potential matches two opposite van Hove points at $k_z = 0$ and π , see Fig. 2(c). Such matching is realized when the parameters satisfy relation given by Eqs. (36a) and (36b) (the plot is made for $\ell_0 = \ell_\pi = 0$). In this case, the maximum is realized at $Q_z = \pi$ favoring the alternating FFLO state.

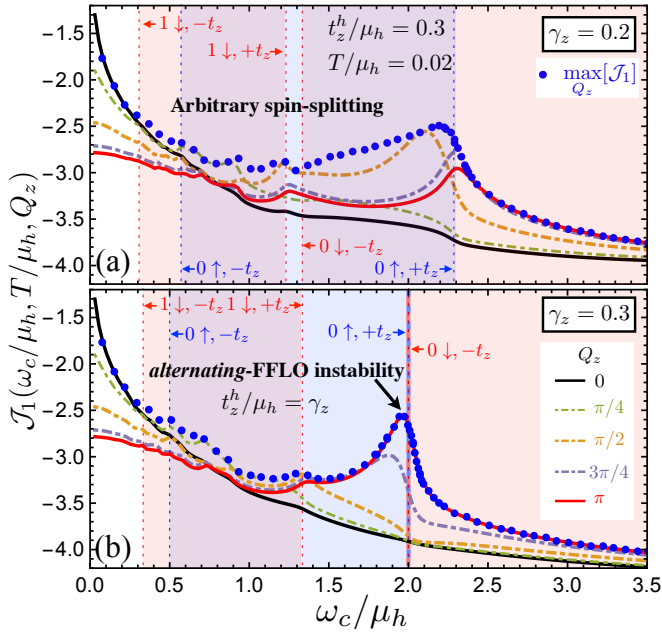


FIG. 5. The magnetic-field dependences of \mathcal{J}_1 for different modulation wave vectors Q_z for noninteger $2\gamma_z$. The parameters in the panel (a), $t_z/\mu_h = 0.3$, $\gamma_z = 0.2$, correspond to a general case without any resonances. In this case, states with different Q_z are favorable for different magnetic fields. The parameters in the panel (b), $t_z/\mu_h = \gamma_z = 0.3$, favor π -FFLO instability. As a consequence, a new diverging peak appears for $Q_z = \pi$ state at $\omega_c = 2\mu_h$. In both panels, we also show the magnetic-field dependence of the maximum value of \mathcal{J}_1 with respect to Q_z (blue circles).

Figure 5 illustrates the magnetic-field dependences of \mathcal{J}_1 for different Q_z in two situations with noninteger $2\gamma_z$. We also show the maximal \mathcal{J}_1 with respect to Q_z . The light blue and pink regions mark the crossing of the chemical potential with the mismatching spin-up and spin-

down Landau-level minibands. These regions are limited by the miniband-edge magnetic fields given by Eq. (29) with $\delta_t = \pm 1$ while ℓ and σ are fixed. The simultaneous crossing of both such bands at the chemical potential only occurs in the overlapping regions in which the pairing favors finite- Q_z states as illustrated in Fig. 2(b). Figure 5(a) corresponds to a general situation without any resonances. In this case, the states with different Q_z become favorable in different fields. In particular, for $Q_z = \pi/2$ the maximum at $\omega_c/\mu_h \approx 2.1$ corresponds to the condition for optimum modulation vector $Q_{op}(\omega_c) = Q_z$, Eq. (39). We can also see that the pairing strength is noticeably enhanced in the region $1.3 < \omega_c/\mu_h < 2.3$ when the chemical potential crosses zero-Landau level minibands for both spin orientations. The choice of parameters in Fig. 5(b) allows for $Q_z = \pi$ singularity, see Eq. (36b) and the illustration in Fig. 2(c). At $\omega_c/\mu_h = 2$ the chemical potential matches simultaneously two van Hove singular points: the spin-up energy at $k_z = 0$ and spin-down energy at $k_z = \pi$. This matching leads to the additional divergent peak at this point strongly favoring $Q_z = \pi$ instability and may lead the formation of the superconducting state with the alternating sign of the order parameter between the layers. In both cases, the optimal kernel eigenvalue (blue circles) significantly exceeds the one for the uniform state (black line) almost in the whole field range.

To obtain a better presentation for the range of parameters where the shallow band favors nonuniform states, we expand \mathcal{J}_1 with respect to small Q_z ,

$$\mathcal{J}_1(H, T, Q_z) \approx \mathcal{J}_1(H, T, 0) + \frac{1}{2} \mathcal{J}_1''(H, T, 0) Q_z^2. \quad (42)$$

If $\mathcal{J}_1''(H, T, 0)$ is positive then $Q_z = 0$ does not maximize \mathcal{J}_1 and the finite non-zero Q_z state is favorable. For better visual impression of the parameter range where the shallow band favors nonuniform states, we present in Fig. 6 the regions of positive (shaded) and negative (unshaded) $\mathcal{J}_1''(H, T, 0)$ in the magnetic field – spin splitting plane for representative parameter $t_z^h/\mu_h = 0.2$ and two values of temperature $T = 0.02\mu_h$ (a) and $0.2\mu_h$ (b). For comparison, we also show in Fig. 6(c) the same diagram for the quasiclassical kernel eigenvalue, Eq. (41). In the latter case an analytical analysis²⁷ suggests that the boundary should behave as $\omega_c/\mu_h \propto 1/\gamma_z^2$ while the exact fit gives $\omega_c/\mu_h \approx 1/(0.14 + 1.07\gamma_z)^2$. If the upper critical field with $Q_z = 0$ state falls into the shaded region, this means that the shallow band favors the nonuniform state, and the order parameter has a tendency to develop nonzero Q_z modulation in real space. We see that at low temperatures the shaded regions cover substantial part of the phase diagram except locations around the integer $2\gamma_z$. Especially surprising is that they extend to very low fields, down to $\omega_c/\mu_h \sim 0.1$. These low-field regions are eliminated at higher temperatures.

To avoid misunderstanding, we note that for two-band systems the nonuniform states do not automatically appear in the shaded regions, because the ground state

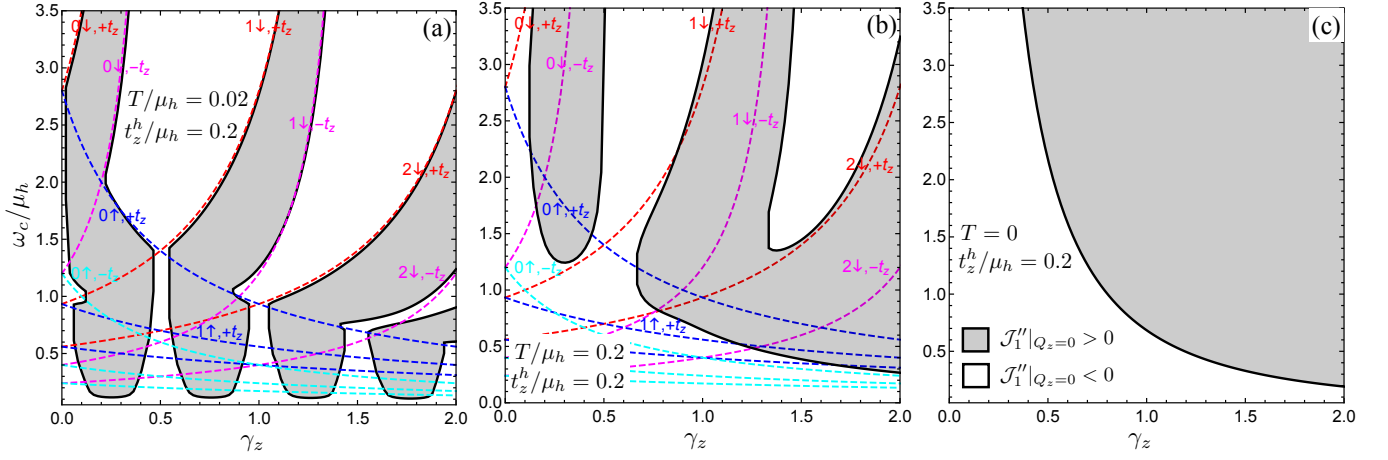


FIG. 6. These plots show positive and negative regions of the kernel-eigenvalue second derivative with respect to the modulation wave vector Q_z , $\mathcal{J}_1''(H, T, 0)$, in the spin-splitting–magnetic field plane. In the shaded regions with $\mathcal{J}_1''(H, T, 0) < 0$ the onset of the finite- Q_z FFLO states may be expected. The (a) and (b) diagrams are made using the exact kernel eigenvalue at $T = 0.02\mu_h$ and $0.2\mu_h$. The dashed lines trace the magnetic fields for which the van Hove singularities of the Landau-level minibands match the chemical potential exactly, Eq. (29). The label ‘ $+t_z$ ’ (‘ $-t_z$ ’) in the diagram marks the $k_z = \pi$ ($k_z = 0$) van Hove singular point. (c) The diagram for the quasiclassical pairing kernel at zero temperature, Eq. (41).

is determined by both bands and the deep band typically favors the uniform state, $\mathcal{J}_2''(H, T, 0) < 0$. The FFLO modulation may appear below certain temperature T_{FFLO} , at which the second derivative $\partial^2 H_{C2}/\partial Q_z^2$ changes sign. From the general equation for the upper critical field, Eq. (26), we can derive equation for this temperature, $T = T_{\text{FFLO}}$,

$$\frac{\mathcal{J}_1''(H, T, 0)}{W_{11} + \mathcal{A}_1(T) - \mathcal{J}_{1,0}(H, T)} + \frac{\mathcal{J}_2''(H, T, 0)}{W_{22} + \mathcal{A}_2(T) - \mathcal{J}_{2,0}(H, T)} = 0 \quad (43)$$

with $\mathcal{J}_{\alpha,0}(H, T) \equiv \mathcal{J}_\alpha(H, T, 0)$, in which we have to substitute $H \rightarrow H_{C2}(T)$ at $Q_z = 0$. This equation may have solution only if (i) $\mathcal{J}_1''(H, T, 0) > 0$ at low temperatures (i.e., the parameters are in the shaded region in Fig. 6(a) and (ii) the ratio W_{11}/W_{22} characterizing the relative weight of the shallow band is not too small.

VI. SUPERCONDUCTING INSTABILITIES AND PHASE DIAGRAMS

The exact shape of the H - T phase diagram of a layered multiple-band superconductor depends on many parameters: electronic spectra properties of the bands, spin-splitting factors, and structure of the coupling matrix. The most crucial factor is the quantum pairing kernel eigenvalue for the shallow band, \mathcal{J}_1 , whose shape at low temperatures is extremely sensitive to the electronic parameters of the shallow band, μ_h , t_z^h and γ_z , as we discussed in the previous section. With the finite interlayer tunneling, the k_z -dispersion in the Landau-quantization spectrum can lead to complex behavior of the superconducting state in the magnetic field.

In addition, the Zeeman spin-splitting in the shallow

band favors the formation of the FFLO states (see Figs. 2 and 5). As the Landau quantization strongly influences the Cooper pairing in the bands with relatively low Fermi energies, this brings a natural general question about the role of quantum effects in the FFLO instability, even in the common case of a single-band superconductor in the quasiclassical limit. Surprisingly this important topic has been never addressed before and we leave it to a separate paper. Here, we focus on the general behavior of the H - T phase diagrams for the two-band system where the shallow band is close to the ultra-quantum limit. We illustrate this behavior for several representative cases.

The most spectacular consequence of the Landau quantization is the emergence of the high-field superconducting states at the magnetic fields corresponding to matching of the chemical potential with the Landau levels. These states are most pronounced in the two-dimensional case and for the lowest Landau level²⁴. The interlayer tunneling smears the delta-function singularity in the density of states leading to suppression of the high-field superconductivity. To quantify these effects, we first calculate the transition temperatures in magnetic field, T_{C2} , in the resonance cases for which the kernel eigenvalue diverges as $\sim 1/\sqrt{T}$, see Sec. V A. For this we find solution of Eq. (26) assuming that $T_{C2} \ll T_C, t_z$.

First, we evaluate the transition temperature for the strongest resonance in the uniform state without Zeeman spin-splitting ($\gamma_z = 0$), $T_{C2}^{(0)}$, which is realized when the chemical potential matches the van Hove singular points at $k_z = 0, \pi$ at the magnetic fields $\omega_c = 2(\mu_h \mp 2t_z^h)$. In this case, substituting the low- T asymptotics of $\mathcal{J}_\alpha - \mathcal{A}_\alpha$

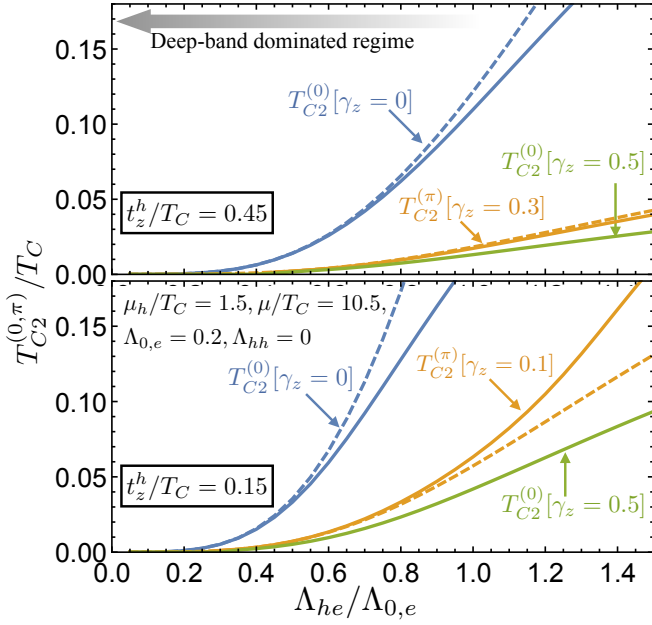


FIG. 7. The dependences of the transition temperatures T_{C2} on the interband coupling constant Λ_{he} for the superconducting states that are induced by the strongest $1/\sqrt{T}$ divergences at high magnetic field. The plots are made assuming fixed effective coupling constant $\Lambda_{0,e} = 0.2$. The blue (green) curve shows the dependences of uniform-state T_{C2} on the interband coupling $\Lambda_{he} = \Lambda_{eh}$ at the magnetic field $\omega_c = 2\mu_h + 4t_z$ ($\omega_c = \mu_h + 2t_z$) with $\gamma_z = 0$ ($\gamma_z = 0.5$), while the orange curve is for the alternating-state case at the magnetic field $\omega_c = 2\mu_h$ with $\gamma_z = 0.3$. The dashed lines are the approximate results given by Eqs. (44) and (45) (which are accurate only if $t_z \ll T_{C2}$) and the solid lines are calculated using the exact formula in Eq. (26). The upper and lower figures compare two different values of the interlayer hopping energy t_z^h .

given by Eqs. (30) and (35) into Eq. (26), we derive

$$T_{C2}^{(0)} = \frac{C^2 \omega_c^2}{t_z^h} \left[\frac{W_{11} \ln r_C^{(0)}}{2W_{22} + \ln r_C^{(0)}} - \mathcal{R}_\mp(\bar{t}_z^h) + \frac{1}{2} \ln \frac{\omega_c}{\pi T_C} + \Upsilon_C \right]^{-2} \quad (44)$$

This result allows us to understand better the typical sizes of the high-field reentrant regions. A similar result can be derived for the strongest alternating-state resonance with $Q_z = \pi$ realized when the parameters satisfy the relation $\mu_h = t_z^h / \gamma_z$. In this case the low-temperature asymptotics of $\mathcal{J}_1 - \mathcal{A}_1$ is given by Eq. (38) leading to the π -state transition temperature at $\omega_c = 2\mu_h$,

$$T_{C2}^{(\pi)} = \frac{C^2 \omega_c^2}{4t_z^h} \left[\frac{W_{11} \ln r_C^{(\pi)}}{2W_{22} + \ln r_C^{(\pi)}} + \frac{1}{2} \ln \frac{2\omega_c}{\pi T_C} + \Upsilon_C \right]^{-2} \quad (45)$$

with $r_C^{(\pi)} \equiv r_C(Q_z = \pi)$. Even though the overall scale of the above transition temperatures is given by ω_c^2 / t_z^h with the small numerical factor $C^2 \approx 0.0115$, their absolute values are very sensitive to the structure of the coupling matrix. The latter dependence is given by the first term

in the square brackets in Eqs. (44) and (45). In general, these transition temperatures are not vanishingly small only if the shallow band gives substantial contribution to pairing.

In particular, in the case when the deep band dominates pairing, $\Lambda_{ee} > \Lambda_{hh}, |\Lambda_{eh}|, |\Lambda_{he}|$, the constants $W_{\alpha\alpha}$ can be estimated as $W_{11} \approx \Lambda_{ee} / \mathcal{D}_\Lambda$ and $W_{22} \approx \Lambda_{eh} \Lambda_{he} / (\Lambda_{ee} \mathcal{D}_\Lambda)$ meaning that $|W_{22}| \ll |W_{11}|$. In addition, inequalities $\ln r_C \ll |W_{22}|$ and $W_{11} \ln r_C / W_{22} \approx \Lambda_{ee}^2 \ln r_C / \Lambda_{eh} \Lambda_{he} \gg \Upsilon_C, \ln(\mu_h / T_C)$ are typically satisfied, leading to the estimate $T_{C2}^{(0)} \approx (C^2 \omega_c^2 / t_z^h) \left[2\Lambda_{eh} \Lambda_{he} / (\Lambda_{ee}^2 \ln r_C^{(0)}) \right]^2$. In this case the transition temperature has the additional small factor which rapidly decreases with decreasing of the interband couplings constants, Λ_{eh} and Λ_{he} , and with increasing the deep-band coupling constant, Λ_{ee} . On the other hand, we see that $T_{C2}^{(0)}$ increases when the resonance field approaches the orbital field of the shallow band, $r_C^{(0)} \rightarrow 1$. In the interband-coupling scenario, $|\Lambda_{eh}|, |\Lambda_{he}| > \Lambda_{ee}, \Lambda_{hh}$, the ratio $W_{11} / W_{22} \approx 1/2$ meaning that there is no additional smallness caused by the coupling factor.

We illustrate the typical behavior of T_{C2} in Fig. 7, by plotting the transition temperatures for uniform and alternating states as function of the ratio $\Lambda_{h,e} / \Lambda_{0,e}$ which controls the shallow-band weight. The plots are made for fixed effective coupling constant $\Lambda_{0,e} = 0.2$ which fixes the zero-field transition temperature T_C . As expected, in all cases the transition temperatures rapidly decrease with decreasing of the shallow-band contribution to pairing. For comparison, we present the T_{C2} -dependences for two values of the interband hopping energy $t_z^h = 0.45T_C$ and $0.15T_C$. We see that T_{C2} 's are much higher for smaller t_z^h .

We also note that, in spite of the kernel low-temperature divergencies in the resonance cases, the two-band system not always becomes superconducting at the corresponding magnetic fields. Indeed, the above solutions for $T_{C2}^{(0)}$ and $T_{C2}^{(\pi)}$ are only valid if the arguments in the square parenthesis of Eqs. (44) and (45) are positive. When the interband coupling dominates, $\mathcal{D}_\Lambda < 0$ and the parameters $W_{\alpha\alpha}$ are negative. In this case $T_{C2}^{(\alpha)}$ may vanish if $\ln r_C^{(\alpha)} = 2|W_{22}|$. As $|W_{22}| \gg 1$ this may only realize if the resonance magnetic field is much larger than the deep-band orbital field, $r_C^{(\alpha)} \gg 1$, corresponding to the very large Fermi energy, $\mu > 100T_C$.

We now present numerically computed temperature-magnetic field phase diagrams for different typical situations. We first illustrate the influence of the interlayer tunneling on the reentrant high-field states in the resonant cases with integer $2\gamma_z$. Figure 8 shows the H - T diagrams for $\gamma_z = 0.5$, $\mu_h = 3T_C$, and different hopping energies t_z^h . The diagrams are made for the case of dominating interband coupling scenario ($\Lambda_{hh} = \Lambda_{ee} = 0$, $\Lambda_{he} = \Lambda_{eh} = 0.3$), for which the discussed reentrant effects are very pronounced. The vertical scale of the

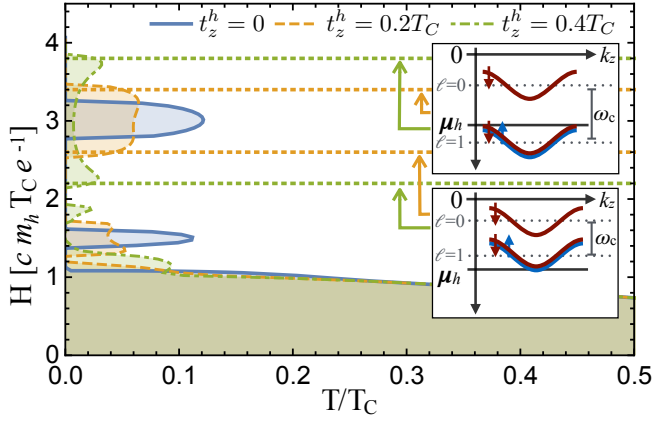


FIG. 8. The influence of the interlayer tunneling on the typical H - T diagram for the resonant case ($2\gamma_z = 1$) in the low- T regime. We used the following parameters: the coupling constants $\Lambda_{hh} = \Lambda_{ee} = 0$, $\Lambda_{he} = \Lambda_{eh} = 0.3$, the mass ratio is $m_e/m_h = 1$, $\varepsilon_0 = 12T_C$ and $\mu_h/T_C = 3$. The insets demonstrate the crossing of the van Hove singular points at the chemical potential.

magnetic field $cm_h T_C/e$ in the plot can be rewritten as $7.44T(m_h/m_0)(T_C/10K)$. Two reentrant states are realized for selected parameters, around the zeroth and first Landau levels. We can see that the interlayer tunneling smears these states. It splits the single peak in $T_{C2}(H)$ around the field $\omega_c = \mu_h(\ell + \frac{1}{2} + \frac{1}{2}j_z)^{-1}$ into the two peaks with maximums approximately located at $\omega_c = (\mu_h \pm 2t_z^h)(\ell + \frac{1}{2} + \frac{1}{2}j_z)^{-1}$ (in the plot $\ell=0, 1$ and $j_z = 1$). The latter fields correspond to the crossing of the Fermi level and the van Hove singular points of the shallow h -band given by Eq. (29), as illustrated by the insets. Since the increase of t_z^h reduces the low- T divergent peaks in $\mathcal{J}_1(H)$ dependence, Eq. (34), the reentrant T_{C2} are always smaller than in the two-dimensional case. We emphasize again that for the resonant cases, $2\gamma_z = j_z$, the FFLO state is not favorable and $Q_z = 0$ always gives the largest T_{C2} .

We now discuss the formation of the interlayer FFLO states due to spin splitting in the shallow band for a more general case of noninteger $2\gamma_z$. Figure 9 shows the representative H - T phase diagram for the spin-splitting factor $\gamma_z = 0.3$, the interlayer hopping energy $t_z = 0.45T_C$ and three values of the Fermi energy, $\mu_h = T_C$ (a), $1.25T_C$ (b) and $1.5T_C$ (c). We again consider the interband-coupling scenario with the same coupling constants as in the previous figure. We plot the H_{C2} lines with Q_z at the optimal values (Q_{op}) and the lines are color-coded by Q_{op} . For comparison we also show the $Q_z = 0$ transition lines.

In the case $\mu_h = T_C$, Fig. 9(a), the Zeeman spin-splitting in the Landau levels of the shallow h -band leads to the pairings that favor the FFLO modulation along the out-of-plane direction for $T < 0.18T_C$. The formation of this state leads to substantial enhancement of the upper critical field at low temperatures. The modula-

tion wave vector at the transition Q_{op} rapidly increases with decreasing temperature reaching 2.17 at $T \rightarrow 0$. At somewhat higher Fermi energy $\mu_h = 1.25T_C$, Fig. 9(b), the pairing at overlapping spin-up and spin-down zero-Landau-level minibands leads to the formation of the separated reentrant high-field state. This state also has z -axis modulation with the wave vector Q_{op} shown in the inset and its value is very close to the distance between spin-up and spin-down Fermi momenta given by Eq. (39). Note that the reentrant FFLO state occupies a quite extended field range corresponding to $1.5 < \omega_c/T_C < 2.75$, where the spin-up and spin-down zero-Landau-level minibands overlap.

As demonstrated in Sec. V A 3, a layered superconductor with shallow band may have special resonance situations leading to appearance of the *alternating* FFLO state. Namely, if μ_h satisfies the condition in Eq. (36b), \mathcal{J}_1 diverges for $T \rightarrow 0$ at the magnetic field that is given by Eq. (36a). This divergence typically gives rise to the FFLO modulation with $Q_z = \pi$. Figure 9(c) shows example of the H - T diagram for such situation with $\ell_0 = \ell_\pi = 0$ in Eqs. (36a) and (36b) corresponding to the strongest resonance. We can see that the small reentrant region indeed appears at the high magnetic field. However, only part of this region is occupied by the alternating state. In contrast to the uniform state, $T_{C2}(H)$ has only single maximum, as in the two-dimensional case. We see that, depending on parameters, the reentrant states can be either well-separated from or very close to the main superconducting region.

For better understanding of general trends, we plot in Fig. 10 the dependences of the low-temperature upper critical field on the shallow-band Fermi energy μ_h . The upper curve is made for the same parameters as in Fig. 9. We can see that this dependence has several salient features. The H_{C2} curve has a clear tendency to follow one of the miniband-edge field lines and it sharply turns away from this line close to crossing points with the second miniband-edge field line. As a consequence, the regions of multiple H_{C2} values corresponding to reentrant behavior appear below some of these crossing points. Near the crossing of $0\downarrow -t_z$ and $0\uparrow +t_z$ lines corresponding to the matching of the opposite van Hove singularities for the zero Landau level, the region of the alternating FFLO state is realized.

So far we only considered the purely interband-coupling scenario for which the quantum effects from the shallow band are quite pronounced. The behavior, however, is sensitive to the structure of the coupling-constants matrix reflecting the pairing mechanism. In addition to the interband-coupling case, Fig. 9 also shows the $H_{C2} - \mu_h$ dependences at low temperatures for two coupling-constant sets with finite Λ_{ee} . We can see that with increasing deep-band pairing weight, the upper critical field *decreases* and moves to the region of miniband-edge field lines for higher Landau levels, especially for ' $+t_z$ ' lines corresponding to larger-area cross section of the Fermi surface at $k_z = \pi$. Nevertheless, the main

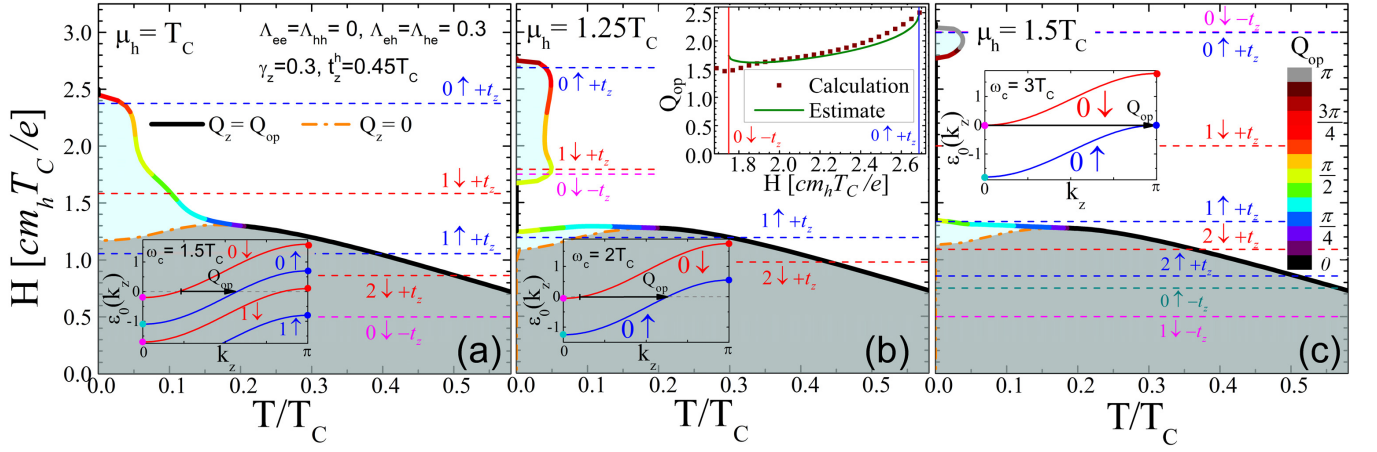


FIG. 9. The representative H - T phase diagrams for nonresonant spin-splitting factor $\gamma_z = 0.3$ and interband-coupling scenario (the coupling constants $\Lambda_{hh} = \Lambda_{ee} = 0$, $\Lambda_{he} = \Lambda_{eh} = 0.3$) computed for three Fermi energies. Other used parameters are: the interlayer hopping energies $t_z^h = t_z^e = 0.45T_C$, the mass ratio $m_e/m_h = 1$, and $\varepsilon_0 = 12T_C$. The boundaries are color-coded by the optimal-modulation wave vector Q_{op} . The orange dot-dashed line shows instability boundary for the uniform state $Q_z = 0$. The horizontal dashed lines are the magnetic fields that match the Fermi level of spin up/down electrons in the h -band with $k_z = 0, \pi$, see Eq. (29). (a) For $\mu_h = T_C$ we can see that the formation of the nonuniform FFLO state below $0.18T_C$ leads to significant enhancement of H_{C2} at low temperatures caused by the proximity to the lines $0 \uparrow, +t_z$ and $1 \downarrow, +t_z$. The inset in this and other plots demonstrate the Landau-level minibands near the chemical potential for selected magnetic fields and corresponding optimal modulation vectors. (b) For the larger Fermi energy $\mu_h = 1.25T_C$, the reentrant region appears located between the lines $0 \uparrow, +t_z$ and $0 \downarrow, -t_z$, where the chemical potential crosses the zero-Landau-level minibands for both spin orientations. The upper right inset in this plot shows the optimal modulated wave vector Q_{op} evaluated from Eq. (39) (green line) and the realized one (solid brown points). (c) The value of the Fermi energy $\mu_h = 1.5T_C$ in this plot satisfies the relation $\mu_h = t_z^h/\gamma_z$, which is required for realization of the π -FFLO state around the field $\omega_c = 2\mu_h$. Indeed, matching of the levels $0 \uparrow, +t_z$ and $0 \downarrow, -t_z$ at this field leads to the reentrant high-field state with $Q_{op} = \pi$.

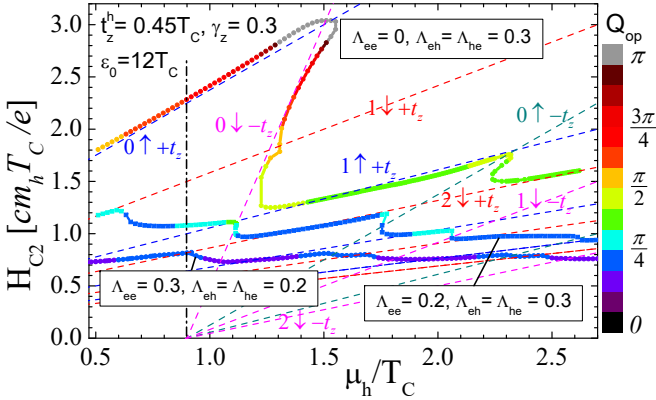


FIG. 10. The dependence of the upper critical field on the shallow-band Fermi energy μ_h for three different coupling-constants sets shown in the plot. Other parameters are the same as in Fig. 9. As in previous figures, we also show the miniband-edge field lines. The vertical dash-dot line marks the location of the first Lifshitz transition, see Fig. 1.

trends remain: the H_{C2} curves still tend to follow the miniband-edge field lines and the reentrant regions appear near the crossing points (at least, for the case $\Lambda_{ee} = 0.2$ and $\Lambda_{eh} = 0.3$). Note that the reentrance completely vanishes when the deep-band coupling is too strong (the lowest curve in Fig. 9). The ground state

at low temperature is modulated for all studied cases, but the optimal modulation wave vector Q_{op} progressively decreases with increasing the deep-band weight. The middle curve includes the crossing of $0 \downarrow, -t_z$ and $1 \uparrow, +t_z$ lines, where the shallow band strongly favors the alternating state. This state, however, is not formed due to the large weight of the deep band. The modulation wave vector is sharply enhanced when μ_h approaches the crossing-point value $1.125T_C$ but it only reaches ~ 1.1 at the maximum.

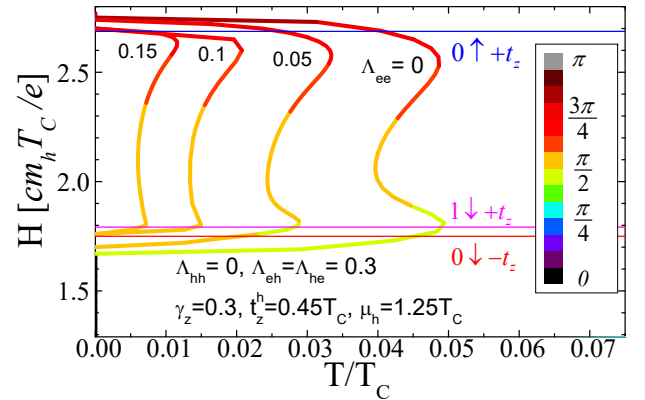


FIG. 11. Shrinking of the reentrant region with increasing deep-band coupling constant Λ_{ee} . All parameters except Λ_{ee} are the same as in Fig. 9(b).

The temperature range of reentrant states rapidly reduces with increasing deep-band coupling. We illustrate this trend in Fig. 11 in which we present the evolution of the reentrant region of Fig. 9(b) with increasing deep-band coupling constant Λ_{ee} . We can see that the size of this region rapidly shrinks with increasing Λ_{ee} . This counterintuitive behavior is again caused by the reduction of the shallow-band weight in the pairing. In the regime of dominating deep-band coupling, $\Lambda_{ee} > \Lambda_{eh}$, the reentrant region becomes practically invisible for these electronic-spectrum parameters.

We discuss in Appendix C the scenario in which superconductivity is dominated by the deep-band coupling with $\Lambda_{ee} > \Lambda_{he}$. The resulting H - T diagrams are not qualitatively different from the representative case in Figs. 8 and 9 but there are substantial quantitative differences. In the resonant case the sizes of reentrant regions are much smaller than for the interband-coupling case due to the strong reduction of the shallow-band contribution to the pairing, see also Fig. 7. In the nonresonant case, the reentrant behavior only appears either for smaller interlayer tunneling or smaller Fermi energy of the deep band in comparison with the parameters considered in this section. Nevertheless, the FFLO instability in the main superconducting region always appears at low temperatures.

VII. SUMMARY AND DISCUSSION

In summary, we have investigated the pairing instabilities of a clean two-band layered superconductor in the magnetic field oriented perpendicular to the layers. In this system, the interlayer tunneling lifts the degeneracies in all Landau levels and transforms them into the dispersive minibands along the out-of-plane momentum (k_z) with two van Hove singularities at $k_z=0$ and π . We explored the possible pairing instabilities as the Landau minibands cross the chemical potential in the vicinity of the first Lifshitz transition ($\mu_h \gtrsim 2t_z^h$ in Fig. 1).

Solving the linearized gap equation [Eq. (2)], we found that the Landau quantization leads to strong $1/\sqrt{T}$ divergencies in the shallow-band's pairing kernel if either the same [Eq. (33)] or opposite [Eqs. (36a-36b)] van Hove points match at the chemical potential. The former matching condition gives the *uniform* superconducting state and the latter one favors the *alternating* FFLO state with $Q_z=\pi$ modulation. For general Zeeman spin-splitting energy, the pairing kernel has $\ln T$ divergency in the pairing channel with the optimal wave vector Q_{op} [Eq. (39)] corresponding to the difference between the spin-up and spin-down Fermi momenta. These logarithmic divergencies are similar to the FFLO instabilities in quasi-one-dimensional superconductors^{40,53,54} and they strongly promote the formation of the FFLO states with $Q_z = Q_{\text{op}}$.

Furthermore, we studied the magnetic field v.s. temperature phase diagrams and found that the shallow-

band divergencies yield a complex reentrant behavior in the high-magnetic-field superconductivity. The properties of these reentrant states are highly sensitive to the shallow-band parameters, μ_h , t_z^h , γ_z , as well as to the coupling-matrix structure. In general, the interlayer tunneling smears the Landau-level densities of states which reduces the quantum effects in the resonant cases. Therefore, the reentrant transition temperatures are smaller than those in the two-dimensional monolayer²⁴. On the other hand, the interlayer tunneling enables the formation of the FFLO modulations which mitigate the Zeeman suppression in the reentrant states. As a result, the reentrant region is stretched to a wider magnetic-field range [see Fig. 9(a) and (b)]. Furthermore, we also found the reentrant *alternating*-FFLO states [see Fig. 9(c)] due to the interplay between the Landau quantization and interlayer tunneling. The similar *alternating*-FFLO state has been also suggested for the layered system in the magnetic field applied parallel to the layers.³⁴ The formation of these *alternating*-FFLO states is the consequence of the compensation between the Zeeman energy and the interlayer hopping energy.

In this study, we only performed the linear stability analysis and, strictly speaking, the computed phase lines describe instability of the normal state. These lines would correspond to true second-order phase transitions only if the coefficient for the quartic order-parameter term in the free energy is positive. Otherwise, superconducting state will emerge via a first-order transition. Such first-order scenario for the emergence of the FFLO state indeed realizes in quasi-two-dimensional materials with very strong Zeeman effect for the magnetic field perpendicular to conducting layers⁵⁵. This analysis, however, has been performed only for the quasiclassical regime and it does not take into account the effect we stress here, promotion of the FFLO instability by the Landau quantization. A full nonlinear consideration with proper accounting for the quantum effects remains to be done.

The described behavior can only be observed in very clean materials in which the scattering time τ satisfies the condition $\tau\omega_c \gg 1$. This condition implies that superconducting transition should take place in the region of noticeable quantum magnetic oscillations of magnetization and conductivity (de Haas-van Alphen and Shubnikov-de Haas effects). This is obviously the most stringent requirement for observation of the described anomalous behavior of the upper critical field. We expect that impurity scattering suppresses such behavior similar to the thermal noise. Indeed, in the interpretation of the quantum-oscillation phenomena scattering is frequently accounted for by introducing a fictitious temperature proportional to the scattering rate, so called Dingle temperature.

We only considered the simplest nearest-neighbor interlayer tunneling process. Additional strong pairing instability may arise if new van Hove singularities appear in the Landau band due to the complicated interlayer tunneling processes. Furthermore, for sufficiently

strong Zeeman splitting and/or small Fermi surfaces for all bands, the higher-Landau-level gap eigenfunction may be relevant⁵⁶. Influence of the quantization effects on this gap solution and modification of the reentrant behavior are another interesting topics for future study.

The quantum effects considered in this paper may be relevant to the high-magnetic-field behavior of several iron-based superconductors, in particular, for FeSe and LiFeAs single crystals. The simplest compound FeSe has the transition temperature $\sim 8\text{K}$ ⁵⁷ and the low-temperature upper critical field $\sim 17\text{T}$ ^{58,59}. The material can be made clean allowing for observation of quantum oscillations at fields $> 20\text{T}$ ⁵⁹⁻⁶¹. Its band structure is composed of hole and electron bands with rather small Fermi surfaces. In particular, Shubnikov-de Haas oscillations show that the smallest Fermi energy for the electron and hole bands are only 3.9 and 5.4 meV respectively⁵⁹ (the first energy corresponds to the ratio $\epsilon_F/\omega_c \sim 4$ at H_{c2}). Similar Fermi energies are also observed by ARPES^{60,62-64}. Moreover, the additional field-induced transition inside the superconducting state has been observed in this compound near 13 T by thermal conductivity measurement⁵⁸. The plausible intriguing interpretation of this transition is the onset of the FFLO modulation along the magnetic field⁴³. Such explanation is also consistent with the low-temperature upturn of the upper critical field. If this interpretation is correct, then this FFLO transition is likely influenced by quantum effects. Furthermore, the transition temperature in FeSe can be increased by pressure up to 20K at 25 kbar and the upper critical field increases above 35 T at 14 kbar. As a consequence, at high pressures, the superconducting transition in the magnetic field takes place in the region of pronounced quantum oscillations⁶⁵. As for the most shallow band $\epsilon_F/\omega_c \sim 2$ at H_{C2} in this region, it is clear that the quantum effects strongly influence the superconducting instability.

The 111 compound LiFeAs is one of the few stoichiometric iron-based superconductors with transition temperature $\sim 18\text{K}$ ⁶⁶ and zero-temperature c-axis $H_{C2} \sim 24\text{T}$ ^{67,68}. The quantum oscillations also have been reported for this material in Refs.^{69,70}. It has the hole-like shallow band located at the zone center with closed Fermi surface and tiny Fermi energy $\mu_h \sim 3\text{meV}$ ⁷⁰. It is important to note that this band actually has the largest superconducting gap¹² meaning strong participation in the formation of the superconducting state. In addition, this band can be completely depleted by small Co doping¹². The band with so small Fermi energy definitely should cause noticeable quantum effects near the upper critical field if the material can be made sufficiently clean. The quantitative predictions for a particular material require a detailed knowledge of the electronic spectrum, spin-splitting factors for all bands, and coupling matrix.

The high-field reentrant superconductivity has been reliably found at least in one material, Eu-doped Chevrel phases, $\text{Eu}_x\text{Sn}_{1-x}\text{Mo}_6\text{S}_8$ ⁷¹, where an isolated semi-elliptical superconducting region has been observed

in the H - T diagram for $T < 1\text{K}$ and a very wide magnetic field range, $4\text{T} < H < 22.5\text{T}$. The interpretation of this strong reentrance was based on the Jaccarino-Peter effect⁷², the compensation of the Zeeman spin splitting due to the interaction with the local magnetic moments of the *Eu* dopants. However such interpretation also required an assumption of the extremely weak orbital effect of the magnetic field (a huge Maki parameter $\alpha_M \approx 4.8$ was used in the theoretical fits). The reason for this assumption is not very clear, as the material is isotropic. We cannot, therefore, exclude that the quantization effects may also play role in the formation of the reentrant region.

The newly discovered Dirac/Weyl semimetals⁷³⁻⁷⁷ (see review⁷⁸) with very small and tunable Fermi energies are another interesting systems to search for the high-magnetic-field induced superconductivity. Of particular interests to this paper is the superconducting states that are found in some compounds under high pressure⁷⁹⁻⁸². It has been demonstrated in Ref. 83 that the orbital quantization in superconducting materials with such Dirac-like spectrum can also lead to the reentrant superconductivity in high magnetic fields. Furthermore, the similar reentrant behavior has also been found in the theoretical study on the Dirac-like surface states of a topological insulator⁸⁴. In contrast to the conventional quadratic electronic dispersion, the linearly-dispersive band yields nonuniform Landau-level spacing and it has been argued that this intriguing feature makes the quantum limit much easier to attain.⁸³ In addition to this feature, due to the small cyclotron effective mass near the Dirac point, the Landau quantization is more robust against disorders^{84,85}. So far, the above studies only considered the Landau-quantization effects in the uniform states. The possible enhancement of the FFLO instabilities in the three-dimensional Dirac/Weyl semimetal due to quantum effects is an interesting problem to be explored in future.

Finally, we note that the study in this paper only concentrated on the correlation effects in the BCS pairing channels. For real systems, other correlation effects in spin and charge channels are also likely to play an important role. Particularly, the Landau-level miniband is effectively a one-dimensional system, and the spin and charge fluctuations may have significant influence. Indeed, the strong competition between the pairing and density-wave instabilities may have dramatic effects and give rise to a new class of strongly correlated quantum states⁸⁶. The rich strongly-correlated phenomena due to the interplay between these fluctuations in quantum limit are certainly important problems for future consideration.

ACKNOWLEDGMENTS

The authors would like to thank Alexander Buzdin, Konstantin Matveev, Takasada Shibauchi, Luis Balicas,

Yakov Kopelevich and Alexander Gurevich for useful discussions. The work was supported by the US Department of Energy, Office of Science, Materials Sciences and Engineering Division. K.W.S. was supported by the Center for Emergent Superconductivity, an Energy Frontier Research Center funded by the US DOE, Office of Science, under Award No. DEAC0298CH1088.

Appendix A: Calculation of the kernel eigenvalues

In this appendix, we give details of the calculations of the kernels in zero and finite magnetic field.

1. Zero magnetic field

The kernels, Eq. (3) are composed by the zero-field Green's function, Eq. (4). The effective coupling constant $\Lambda_{0,\alpha}$, Eq. (9) is determined by

$$\Lambda_{0,\alpha}^{-1} = \frac{T}{N_\alpha} \sum_{\omega_n, j'} \sum_{\mathbf{k}\mathbf{k}'} \int_{k_z k'_z} \int_{\mathbf{r}'} e^{-i[(\mathbf{k}-\mathbf{k}') \cdot (\mathbf{r}-\mathbf{r}') + (k_z - k'_z)(j-j')]} \times \frac{1}{(i\omega_n - \xi_{\mathbf{k}}^\alpha + 2t_z \cos k_z)(i\omega_n + \xi_{\mathbf{k}'}^\alpha - 2t_z \cos k'_z)}.$$

Since the system is translationally invariant, it is straightforward to integrate out \mathbf{r}' and sum all j' . This yields

$$\Lambda_{0,\alpha}^{-1} = N_\alpha^{-1} T \sum_{\omega_n} \sum_{\mathbf{k}k_z} \frac{1}{\omega_n^2 + (\xi_{\mathbf{k}}^\alpha - 2t_z \cos k_z)^2}.$$

We further integrate out the (\mathbf{k}, k_z) by using $\sum_{\mathbf{k}} = N_e \int_{-\Omega}^{\Omega} d\xi^e$ for e -band ($\sum_{\mathbf{k}} = N_h \int_{-\Omega}^{\mu_h} d\xi^h$ for h -band) with $N_e = \frac{m_e}{2\pi}$ ($N_h = \frac{m_h}{2\pi}$) and $\sum_{k_z} = \int_{-\pi}^{\pi} \frac{dk_z}{2\pi}$. We therefore obtain

$$\Lambda_{0,e}^{-1} = \sum_{\omega_n} \int_{-\pi}^{\pi} \frac{dk_z}{2\pi} \left[\frac{T}{\omega_n} \tan^{-1} \frac{x}{\omega_n} \right]_{x=-\Omega}^{x=\Omega},$$

$$\Lambda_{0,h}^{-1} = \sum_{\omega_n} \int_{-\pi}^{\pi} \frac{dk_z}{2\pi} \left[\frac{T}{\omega_n} \tan^{-1} \frac{x}{\omega_n} \right]_{x=-\Omega}^{x=\mu_h - 2t_z \cos k_z}.$$

Note that we assumed $\Omega \gg t_z$. Further simplifying the above, we obtain Eqs. (11a) and (11b) in the main text.

2. Finite magnetic field

a. Deep band

For the deep e -band in which the Landau quantization does not play a role, we have the following quasiclassical

result for the kernel eigenvalue

$$\lambda_{\omega_n, Q_z}^e = \frac{2}{N_e} \sum_{\mathbf{k}\mathbf{k}'} \int_0^\infty \frac{\rho d\rho \exp \left[-i(\mathbf{k} - \mathbf{k}') \cdot \boldsymbol{\rho} - \frac{\rho^2}{2l^2} \right]}{[i\omega_n - \mu_z H - \xi_{\mathbf{k}}^e + 2t_z^e \cos(k_z - \frac{1}{2}Q_z)]} \times \frac{1}{[i\omega_n - \mu_z H + \xi_{\mathbf{k}'}^e - 2t_z^e \cos(k_z + \frac{1}{2}Q_z)]}. \quad (\text{A1})$$

Setting $\mathbf{k} \rightarrow \mathbf{k} - \frac{1}{2}\mathbf{q}$ and $\mathbf{k}' \rightarrow \mathbf{k} + \frac{1}{2}\mathbf{q}$, and keeping only the linear order in \mathbf{q} , we can approximate the dispersion near Fermi level as $\xi_{\mathbf{k}}^e \rightarrow \xi_{\mathbf{k}}^e - \frac{1}{2}\mathbf{v}^e \cdot \mathbf{q}$ and $\xi_{\mathbf{k}'}^e \rightarrow \xi_{\mathbf{k}}^e + \frac{1}{2}\mathbf{v}^e \cdot \mathbf{q}$. We now integrate out the \mathbf{k} in Eq. (A1) with the above approximation by using $\sum_{\mathbf{k}} = N_e \int_{-\infty}^{\infty} d\xi^e$. Extending the energy integration to a closed contour in the complex plane, this yields

$$\lambda_{\omega_n, Q_z}^e \approx -\pi i \sum_{k_z \mathbf{q}_0} \int_0^\infty \rho d\rho \exp \left[-i\mathbf{q} \cdot \boldsymbol{\rho} - \frac{\rho^2}{2l^2} \right] \left\{ i\omega_n - \mu_z H + \frac{1}{2}\mathbf{v}^e \cdot \mathbf{q} + t_z^e [\cos(k_z - \frac{1}{2}Q_z) - \cos(k_z + \frac{1}{2}Q_z)] \right\}^{-1}.$$

The absolute value of the momentum \mathbf{k} in the Fermi $\mathbf{v}^e(\mathbf{k})$ is approximately determined by $\xi_{\mathbf{k}}^e = t_z^e [\cos(k_z - \frac{1}{2}Q_z) + \cos(k_z + \frac{1}{2}Q_z)]$ giving

$$v_e^2 \approx \frac{2}{m_e} \left(\mu + 2t_z^e \cos k_z \cos \frac{Q_z}{2} \right). \quad (\text{A2})$$

Exponentiating the denominator as follows,

$$\lambda_{\omega_n, Q_z}^e \approx 2\pi \sum_{k_z \mathbf{q}_0} \int_0^\infty \rho d\rho \exp \left[-i\mathbf{q} \cdot \boldsymbol{\rho} - \frac{\rho^2}{2l^2} \right] \int_0^\infty ds \exp \left\{ 2\zeta_\omega s \times \left[\omega_n + i[\mu_z H - \frac{1}{2}\mathbf{v}^e \cdot \mathbf{q} - 2t_z^e \sin(k_z) \sin(\frac{1}{2}Q_z)] \right] \right\},$$

with $\zeta_\omega = \text{sign}(\omega_n)$, we integrate out \mathbf{q} , which gives

$$\lambda_{\omega_n, Q_z}^e \approx 2\pi \sum_{k_z} \int_0^\infty \rho d\rho \int_0^\infty ds \delta(\boldsymbol{\rho} + \zeta_\omega s \mathbf{v}^e) \exp \left[-\frac{\rho^2}{2l^2} \right] \times \exp \left\{ 2\zeta_\omega s \left[\omega_n + i[\mu_z H - 2t_z^e \sin(k_z) \sin(\frac{1}{2}Q_z)] \right] \right\}.$$

Finally, taking the ρ integral, we obtain the eigenvalue of the kernel

$$\lambda_{\omega_n, Q_z}^e = 2 \int_0^\infty ds \left\langle \exp \left[-2\zeta_\omega s (\omega_n + i\tilde{\gamma}_z^e) - \frac{v_e^2 s^2}{2l^2} \right] \right\rangle_z, \quad (\text{A3})$$

where $\tilde{\gamma}_z^e = \gamma_z - 2t_z^e \sin k_z \sin \frac{Q_z}{2}$. Substituting the Fermi velocity from Eq. (A2), we obtain Eq. (18).

b. Shallow band

In the case of shallow band, the quantum kernel eigenvalue \mathcal{J}_1 is defined by Eqs. (19) and (23a). The summation over the Matsubara frequencies in Eq. (19) can

be performed using the relation $T \sum_{\omega_n} \frac{1}{(i\omega_n + z)(i\omega_n - z')} = -\frac{1}{2} \left(\tanh \frac{z}{2T} + \tanh \frac{z'}{2T} \right) / (z + z')$, which gives

$$\pi T \sum_{\omega_n=-\infty}^{\infty} \lambda_{\omega_n}^h = \frac{1}{4} \sum_{m=0}^{M_\Omega} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell!} \times \left\langle \frac{\mathcal{T}(\ell + \tilde{\gamma}_z - \tilde{\mu}_h) + \mathcal{T}(m - \ell - \tilde{\gamma}_z - \tilde{\mu}_h)}{m + 1 - 2\tilde{\mu}_h} \right\rangle_z$$

where $\mathcal{T}(x) \equiv \tanh[\omega_c(x + 1/2)/2T]$ and the functions $\tilde{\mu}_h(k_z, Q_z)$ and $\tilde{\gamma}_z(k_z, Q_z)$ are defined by Eqs. (20a) and (20b) correspondingly. Here we introduced a new summation index $m = \ell + \ell'$ and cut off the diverging sum over m at $M_\Omega = 2\Omega/\omega_c$. The converging function \mathcal{J}_1 is obtained by subtracting the zero-field limit of this sum at $Q_z = 0$ which yields

$$\mathcal{J}_1 = \frac{1}{4} \sum_{m=0}^{M_\Omega} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell!} \left\langle \frac{\mathcal{T}(\ell + \tilde{\gamma}_z - \tilde{\mu}_h) + \mathcal{T}(m - \ell - \tilde{\gamma}_z - \tilde{\mu}_h)}{m + 1 - 2\tilde{\mu}_h} \right\rangle_z - \frac{1}{2} \int_0^{M_\Omega} dx \left\langle \frac{\mathcal{T}(\frac{x-1}{2} - \tilde{\mu}_{h0})}{x - 2\tilde{\mu}_{h0}} \right\rangle_z \quad (\text{A4})$$

with $\tilde{\mu}_{h0}(k_z) \equiv \tilde{\mu}_h(k_z, 0) = \bar{\mu}_h - 2t_z^h \cos k_z$. This quantity remains finite in the limit $\Omega \rightarrow \infty$. Note that the subtracted term can also be represented as

$$\begin{aligned} \frac{1}{2} \int_0^{M_\Omega} dx \left\langle \frac{\mathcal{T}(\frac{x-1}{2} - \tilde{\mu}_{h0})}{x - 2\tilde{\mu}_{h0}} \right\rangle_z &= \pi T \sum_{0 < \omega_n < \Omega} \frac{1}{\omega_n} + \Upsilon_T \\ &\approx \frac{1}{2} \ln \frac{A\Omega}{T} + \Upsilon_T. \end{aligned} \quad (\text{A5})$$

To derive presentation better suited for numerical evaluation, we split the integration over x as $\int_0^\infty dx F(x) = \int_0^{1/2} dx F(x) + \sum_{m=0}^\infty \int_{-1/2}^{1/2} dx F(m+1+x)$ and subtract the term $\left\langle \frac{\mathcal{T}(\frac{m}{2} - \tilde{\mu}_h)}{m+1-2\tilde{\mu}_h} \right\rangle_z$ from both m sums making them converging independently. This results in Eq. (24a) of the main text.

Appendix B: The low-temperature asymptotics of $\mathcal{J}_1(H, T, Q_z)$

In this section, we analyze the low-temperature behavior of the function $\mathcal{J}_1(H, T, Q_z)$. In most cases it behaves $\propto \ln(T)$ which gives the finite zero-temperature limit of the total kernel eigenvalue $\mathcal{J}_1 - \mathcal{A}_1$. This zero-temperature limiting value has square-root singularities when magnetic field crosses the miniband-edge fields, Eq. (29). In addition, in several resonance cases \mathcal{J}_1 diverges as $1/\sqrt{T}$. Such behavior may be realized only in the uniform state with $Q_z = 0$ or in the alternating FFLO state with $Q_z = \pi$ and for special values of the spin-splitting factor γ_z .

1. Derivation of the pairing kernel near the miniband-edge fields

In this appendix we derive the square-root contribution to the pairing kernel eigenvalue \mathcal{J}_1 , which appears when chemical potentials enters Landau level miniband at $H = H_{\ell, \sigma, \delta_t}$, see Eq. (32). The singular behavior is coming from the terms with $\ell = \ell_0$ for $\sigma = 1$ ($m - \ell = \ell_0$ for $\sigma = -1$) in the Landau-level sum, Eq. (A4). The corresponding singular term can be written as

$$r_{m, \ell_0, \sigma}(\omega_c) = \left\langle \frac{\tanh \left[\frac{\omega_c(\ell_0 - \sigma\gamma_z + \frac{1}{2}) - \mu_h + 2t_z^h \cos(k_z - \frac{1}{2}Q_z)}{2T} \right]}{m + 1 - 2 \left(\mu_h - 2t_z^h \cos k_z \cos \frac{Q_z}{2} \right) / \omega_c} \right\rangle_z.$$

At $T \rightarrow 0$ we can replace $\tanh(A/T)$ with the sign function $\text{sign}(A)$. For ω_c near $\omega_{\ell_0, \sigma, \delta_t}$, we use the presentation

$$\begin{aligned} \omega_c(\ell_0 - \sigma\gamma_z + \frac{1}{2}) - \mu_h + 2t_z^h \cos \left(k_z - \frac{Q_z}{2} \right) \\ = (\mu_h + 2\delta_t t_z^h) \left(\frac{\omega_c}{\omega_{\ell_0, \sigma, \delta_t}} - 1 \right) + 2t_z^h \left(\delta_t + \cos \left(k_z - \frac{Q_z}{2} \right) \right), \end{aligned}$$

which indicates that the main contribution to the difference $r_{m, \ell_0, \sigma}(\omega_c) - r_{m, \ell_0, \sigma}(\omega_{\ell_0, \sigma, \delta_t})$ comes from the miniband-edge region (i.e., near $k_z = \pi + \frac{Q_z}{2}$ for $\delta_t = 1$ and $k_z = \frac{Q_z}{2}$ for $\delta_t = -1$), where the quadratic expansion

of the cosine can be used. This allows us to evaluate

$$\begin{aligned} & r_{m,\ell_0,\sigma}(\omega_c) - r_{m,\ell_0,\sigma}(\omega_{\ell_0,\sigma,\delta_t}) \\ & \approx \frac{-2\delta_t/\pi}{m+1-2\left(\mu_h+2\delta_t t_z^h \cos^2 \frac{Q_z}{2}\right)/\omega_c} \\ & \times \sqrt{\frac{\mu_h+2\delta_t t_z^h}{t_z^h}} \sqrt{\left|1-\frac{\omega_c}{\omega_{\ell_0,\sigma,\delta_t}}\right|} \theta\left[\delta_t\left(1-\frac{\omega_c}{\omega_{\ell_0,\sigma,\delta_t}}\right)\right], \end{aligned}$$

where $\theta(x)$ is step function. We see that $r_{m,\ell_0,\sigma}(\omega_c)$ has a singular square-root behavior when ω_c approaches $\omega_{\ell_0,\sigma,\delta_t}$ from the side, at which the chemical potential is inside the miniband. Collecting the singular terms, we obtain the corresponding result for the kernel eigenvalue

$$\begin{aligned} & \mathcal{J}_1(\omega_c) - \mathcal{J}_1(\omega_{\ell_0,\sigma,\delta_t}) \\ & \approx \frac{1}{4} \sum_{m=\ell_0}^{\infty} \frac{m!}{2^m (m-\ell_0)! \ell_0!} [r_{m,\ell_0,\sigma}(\omega_c) - r_{m,\ell_0,\sigma}(\omega_{\ell_0,\sigma,\delta_t})]. \end{aligned}$$

Substituting the difference $r_{m,\ell_0,\sigma}(\omega_c) - r_{m,\ell_0,\sigma}(\omega_{\ell_0,\sigma,\delta_t})$ from the previous equation, we arrive at Eq. (32) of the main text.

2. Uniform state ($Q_z = 0$) and $2\gamma_z = j_z$

We analyze the low-temperature divergency of the function $\mathcal{J}_1(H, T, Q_z)$ in the uniform case when the spin-splitting energy matches the Landau level separation, i. e., $\gamma_z = j_z/2$. In this case a singular behavior takes place when the chemical potential matches the Landau level energy at $k_z = 0$ or π corresponding to the condition $(\ell_0 + \frac{1}{2}j_z + \frac{1}{2})\omega_c = \mu_h \mp 2t_z^h$. To extract the leading low- T divergence, we will use Eqs. (A4) and (A5). First, near $T = 0$, the second term of Eq. (A4) diverges as $\sim \ln T$. The dominating low- T divergent contribution is coming from the first term with $m = 2\ell_0 + j_z$ and $\ell = \ell_0$,

$$\mathcal{J}_1 \simeq \frac{\omega_c}{8t_z^h} \frac{(2\ell_0 + j_z)!}{2^{2\ell_0+j_z}(\ell_0 + j_z)! \ell_0!} \int_0^\pi \frac{dk_z}{\pi} \frac{\tanh \frac{t_z^h(\cos k_z \mp 1)}{T}}{\cos k_z \mp 1}. \quad (\text{B1})$$

Making the substitution $x = \frac{t_z^h}{T}(\cos k_z \mp 1)$, we obtain

$$\begin{aligned} & \mathcal{J}_1 \simeq \frac{\omega_c}{8\pi \sqrt{T t_z^h}} \frac{(2\ell_0 + j_z)!}{2^{2\ell_0+j_z}(\ell_0 + j_z)! \ell_0!} \\ & \times \int_0^{2t_z^h/T} dx \frac{\tanh x}{x^{3/2} \sqrt{2 - T x / t_z^h}}. \end{aligned} \quad (\text{B2})$$

In the limit $T \ll t_z^h$, using $\int_0^\infty dx x^{-3/2} \tanh x = \sqrt{2}(2\sqrt{2}-1)\zeta(3/2)/\sqrt{\pi}$, we obtain Eq. (34) in the main text.

We derive a more accurate asymptotics for the strongest resonance, $\ell_0 = 0$ and $j_z = 0$. Substituting $\omega_c = 2(\mu_h \mp 2t_z)$ for $k_z = 0/\pi$ and $Q_z = 0$ into the Eq. (A4), we obtain

$$\begin{aligned} \mathcal{J}_1 &= \frac{1}{2} \sum_{m=0}^{2\Omega/\omega_c} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell!} \left\langle \frac{\tanh \frac{\ell-2t_z^h(\pm 1 - \cos k_z)}{2T/\omega_c}}{m-4t_z^h(\pm 1 - \cos k_z)} \right\rangle_z \\ & - \frac{1}{2} \ln \frac{A\Omega}{T} - \Upsilon_T. \end{aligned} \quad (\text{B3})$$

At low temperatures we can replace $\tanh \rightarrow 1$ in all terms except $m = 0$. This gives,

$$\begin{aligned} \mathcal{J}_1 &\simeq \frac{1}{2} \left\langle \frac{\tanh \frac{t_z^h(1 \mp \cos k_z)}{T}}{4t_z^h(1 \mp \cos k_z)} + \sum_{m=1}^{\infty} \left[\frac{1}{m+4t_z^h(\cos k_z \mp 1)} - \frac{1}{m} \right] \right\rangle_z \\ & + \frac{1}{2} \left(\sum_{m=1}^{2\Omega/\omega_c} \frac{1}{m} - \ln \frac{A\Omega}{T} \right) - \Upsilon_T. \end{aligned}$$

Using $\lim_{N \rightarrow \infty} \left(\sum_{m=1}^N \frac{1}{m} - \ln N \right) = \gamma_E$ and performing averaging with respect to k_z , we finally obtain

$$\mathcal{J}_1 \approx \frac{C\omega_c}{\sqrt{T t_z^h}} + \mathcal{R}_\mp(t_z^h) - \frac{1}{2} \ln \frac{\omega_c}{\pi T} - \Upsilon_T, \quad (\text{B4})$$

$$\mathcal{R}_\mp(t_z^h) = \frac{1}{2} \sum_{m=1}^{\infty} \left(\frac{1}{\sqrt{m(m \mp 8t_z^h)}} - \frac{1}{m} \right).$$

where $C = (2\sqrt{2}-1)\zeta(\frac{3}{2})/(8\pi^{3/2}) \approx 0.1072$ and $\zeta(x)$ is the Riemann zeta function. Subtracting \mathcal{A}_1 gives Eq. (35) of the main text.

3. Alternating state ($Q_z = \pi$)

For the alternating case, $Q_z = \pi$, the resonance conditions are given by Eqs. (36a) and (36b) corresponding to $\bar{t}_z^h = \frac{1}{4}(\ell_\pi - \ell_0 \pm 2\gamma_z)$ and $\bar{\mu}_h = \frac{1}{2}(\ell_0 + \ell_\pi + 1)$. Substituting these relations into the first term of Eq. (A4) and using $\tilde{\mu}_h(k_z, \pi) = \bar{\mu}_h$, $\tilde{\gamma}_z(k_z, \pi) = \gamma_z - 2t_z^h \sin k_z$, we obtain

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{1}{4} \sum_{m=0}^{\infty} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell! (\ell_0 + \ell_\pi)} \times \left\langle \tanh \frac{2\ell - \ell_0 - \ell_\pi \pm 2\gamma_z + (\ell_\pi - \ell_0 \pm 2\gamma_z) \sin k_z}{4T/\omega_c} + \tanh \frac{2(m-\ell) - \ell_0 - \ell_\pi \mp 2\gamma_z - (\ell_\pi - \ell_0 \pm 2\gamma_z) \sin k_z}{4T/\omega_c} \right\rangle_z.$$

The singular term $m = \ell_0 + \ell_\pi$ requires resolution of a ‘zero over zero’ uncertainty which leads to

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{\omega_c}{8T} \sum_{\ell=0}^{\ell_0 + \ell_\pi} \frac{(\ell_0 + \ell_\pi)!}{2^{\ell_0 + \ell_\pi} (\ell_0 + \ell_\pi - \ell)! \ell!} \times \left\langle \text{sech}^2 \frac{\ell_0 + \ell_\pi - 2\ell \mp 2\gamma_z - (\ell_\pi - \ell_0 \pm 2\gamma_z) \sin k_z}{4T/\omega_c} \right\rangle_z.$$

The terms for which $|\ell_0 + \ell_\pi - 2\ell \pm 2\gamma_z| = |\ell_\pi - \ell_0 \pm 2\gamma_z|$ are divergent. This condition is always satisfied for $\ell = \ell_\pi$ and this term is

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{\omega_c}{16\pi T 2^{\ell_0 + \ell_\pi} \ell_0! \ell_\pi!} \int_{-\pi}^{\pi} dk_z \text{sech}^2 \frac{t_z^h (1 + \sin k_z)}{T}.$$

At low temperatures, $T \ll t_z^h$, the dominating contribution to the integral comes from the region near the inflection point $k_z = -\pi/2$ and the integration can be approximately evaluated using the substitution $k_z = -\pi/2 + \sqrt{2T/t_z^h} x$ giving

$$\begin{aligned} \int_{-\pi}^{\pi} dk_z \text{sech}^2 \frac{t_z^h (1 + \sin k_z)}{T} &\approx \sqrt{\frac{2T}{t_z^h}} \int_0^{\infty} \frac{dx}{\sqrt{x} \cosh^2 x} \\ &= \sqrt{\frac{2T}{t_z^h}} \frac{(2\sqrt{2} - 1)\zeta(\frac{3}{2})}{\sqrt{2\pi}}. \end{aligned}$$

Therefore, we obtain

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{C}{2} \frac{(\ell_0 + \ell_\pi)!}{2^{\ell_0 + \ell_\pi} \ell_0! \ell_\pi!} \frac{\omega_c}{\sqrt{T t_z^h}}, \quad (\text{B5})$$

where the constant C is defined after Eq. (B4). We also mention that in the exceptional cases when $2\gamma_z$ is integer, the term with $\ell = \ell_0 - 2\gamma_z$ also diverges and this gives additional diverging contribution

$$\mathcal{J}_1(H, T, \pi) \simeq \frac{C}{2} \frac{(\ell_0 + \ell_\pi)!}{2^{\ell_0 + \ell_\pi} (\ell_\pi + 2\gamma_z)! (\ell_0 - 2\gamma_z)!} \frac{\omega_c}{\sqrt{T t_z^h}}.$$

We again derive a more accurate asymptotic for the strongest resonance of this kind with $t_z^h/\mu_h = \gamma_z$ and $\omega_c = 2\mu_h$. Near the 1st Lifshitz transition, $\mu_h > 2t_z^h$ which implies that $\gamma_z < 0.5$. For these relations, the function \mathcal{J}_1 becomes

$$\begin{aligned} \mathcal{J}_1 &= \frac{1}{4} \sum_{m=0}^{M_\Omega} \sum_{\ell=0}^m \frac{m!}{2^m (m-\ell)! \ell! m} \left\langle \tanh \frac{\ell + \gamma_z (1 + \sin k_z)}{2T/\omega_c} \right. \\ &\quad \left. + \tanh \frac{m - \ell - \gamma_z (1 + \sin k_z)}{2T/\omega_c} \right\rangle_z - \frac{1}{2} \ln \frac{A\Omega}{T} - \Upsilon_T. \quad (\text{B6}) \end{aligned}$$

Note that the $m=0$ term again has ‘zero over zero’ uncertainty. All terms in the sum remain finite for $T \rightarrow 0$ except the $m = \ell = 0$ term. Therefore, we separate this diverging term from the sum and take the limit $T \rightarrow 0$ for the rest of the terms. This yields

$$\begin{aligned} \mathcal{J}_1 &\simeq \frac{\omega_c}{8T} \left\langle \text{sech}^2 \frac{\gamma_z (1 + \sin k_z)}{2T/\omega_c} \right\rangle_z \\ &\quad - \frac{1}{2} \sum_{m=1}^{\infty} \frac{1}{2^m m} + \frac{1}{2} \sum_{m=1}^{M_\Omega} \frac{1}{m} - \frac{1}{2} \ln \frac{A\Omega}{T} - \Upsilon_T \\ &\approx \frac{C}{2} \frac{\omega_c}{\sqrt{T t_z^h}} - \frac{1}{2} \ln \frac{2\omega_c}{\pi T} - \Upsilon_T. \quad (\text{B7}) \end{aligned}$$

This corresponds to Eq. (38) in the main text.

Appendix C: The phase diagrams for the deep-band dominating scenario

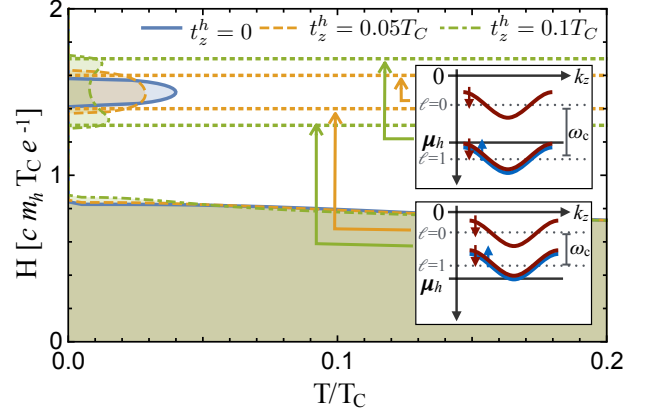


FIG. 12. The representative H - T diagram for the resonant case, $\gamma_z = 0.5$, within the deep-band coupling dominating scenario. We have used the coupling constants $\Lambda_{ee} = 0.3$, $\Lambda_{he} = \Lambda_{eh} = 0.2$, and $\Lambda_{hh} = 0$. Other parameters are $\mu_h = 1.5T_C$, $\mu = 10.5T_C$, and $m_e = m_h$. The interlayer hopping energies t_z^h are shown in the plot.

In the main text, we mostly presented results for the interband-coupling scenario ($\Lambda_{ee} = \Lambda_{hh} = 0$), for which the shallow band is essential for the formation of the superconducting state and the quantization effects caused by this band are very pronounced. In this appendix, we consider the phase diagrams for the alternative scenario

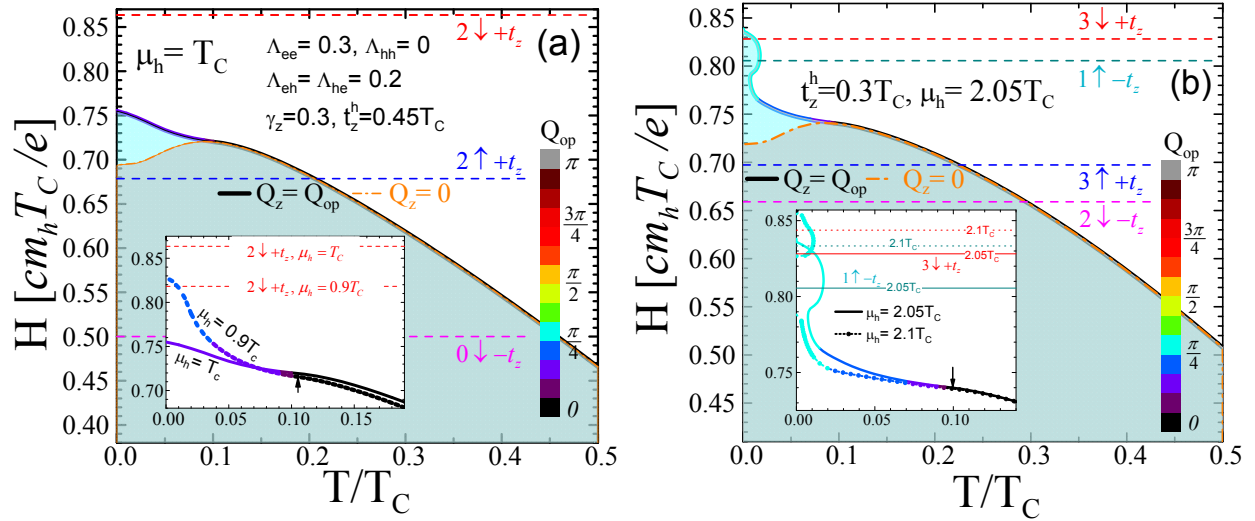


FIG. 13. The magnetic field-temperature phase diagrams for the non-resonant case, $\gamma_z = 0.3$, and dominating deep-band coupling, $\Lambda_{ee} = 0.3 > \Lambda_{eh} = \Lambda_{he} = 0.2$. (a) The diagram for the same spectrum parameters as in Fig. 9(a). The inset zooms into the low-temperature region for the same Fermi energy as in the main plot and for a smaller value, $\mu_h = 0.9T_C$. In the latter case, the H_{C2} line has a pronounced upturn at low temperatures caused by the proximity to the van Hove singularity. (b) The example of the H - T phase diagrams with reentrant regions for the same parameters as in the previous figure except smaller $t_z^h = 0.3T_C$ and different μ_h . The inset shows the low-temperature region for two values of μ_h for which the reentrant region is connected with and separated from the main domain.

when the deep band itself has strong pairing strength and the interband coupling induces superconductivity into the shallow band, i. e., $\Lambda_{ee} > \Lambda_{he}, \Lambda_{eh}, \Lambda_{hh}$. In such scenario, the Lifshitz transition weakly affects superconductivity as is indeed realized in several iron-based superconductors. On the other hand, the influence of the shallow band is only noticeable if it has substantial contribution to pairing, i. e., the interband coupling constants Λ_{he} and Λ_{eh} should be comparable with Λ_{ee} . Note that we focus in this paper on the scenario when there is no intraband pairing in the shallow band, $\Lambda_{hh} = 0$. Such pairing would further enhance shallow-band quantization effects. For illustration, we use the coupling constants $\Lambda_{ee} = 0.3$ and $\Lambda_{he} = \Lambda_{eh} = 0.2$ in this appendix. This corresponds to the ratio $\Lambda_{he}/\Lambda_{0,e} \sim 0.54$ in Fig. 7.

We consider the resonant case first. Figure 12 shows the representative H - T diagrams for $\gamma_z = 0.5$. The diagrams are presented for three values of the interlayer hopping energies t_z^h shown in the plot. We can see that the overall behavior is similar to the interband-coupling scenario shown in Fig. 8. The quantitative difference is that the size of the reentrant region is rather small even in the 2D case and it further diminishes with increasing the interlayer tunneling. Already for small interlayer hopping energy, $t_z^h = 0.1T_C$, the maximum T_{C2} drops below $0.02T_C$.

In a more generic nonresonant case (noninteger $2\gamma_z$), two features of the H - T diagrams have been emphasized in the main text: (i) the interlayer FFLO instability accompanied by the enhancement of the upper critical field at low temperatures and (ii) the emergence of reentrant states for the magnetic fields slightly below the crossings of two miniband-edge field lines. We find that the

FFLO instability in the main superconducting region is robust. For example, Fig. 13(a) shows the magnetic field-temperature phase diagram for the same electronic parameters as in Fig. 9(a) but for large pairing strength in the deep band (the same coupling constants $\Lambda_{ee} = 0.3$, $\Lambda_{he} = \Lambda_{eh} = 0.2$, and $\Lambda_{hh} = 0$). For these parameters, the shallow band induces the FFLO instability at $T \approx 0.1T_C$ accompanied by the upturn of the upper critical field at lower temperatures. This upturn is much smaller than the one for the interband-coupling scenario presented in Fig. 9(a). It is enhanced, however, when the miniband-edge field approaches the zero-temperature H_{C2} . This can be seen from the inset which also shows the low-temperature behavior of the H_{C2} line for the smaller Fermi energy $\mu_h = 0.9T_C$, where the H_{C2} line approaches the miniband-edge field “ $2\downarrow + t_z$ ” at $T \rightarrow 0$. Such enhancement is only observed for few special values of the Fermi energy, while the behavior illustrated in the main figure is typical. Another difference from the interband-coupling scenario is that the modulation wave vector remains rather small, $Q_{op} < 1$, much smaller than the optimal wave vector favored by the shallow band.

We find that in the dominating deep-band regime the reentrant behavior is not realized for that electronic parameters used in Fig. 9. Nevertheless, this behavior does appear for smaller interlayer hopping energy and/or smaller Fermi energy of the deep band. For example, Fig. 13(b) presents of the phase diagram for $t_z^h = 0.3T_C$ and $\mu_h = 2.05T_C$. In this case, the reentrant region connected with the main domain exists. As one can see from the inset, it separates at slightly larger μ_h . This region is caused by the closely located miniband-edge fields for $\ell = 3/\text{spin down}/k_z = \pi$ and $\ell = 1/\text{spin up}/k_z = 0$. Such

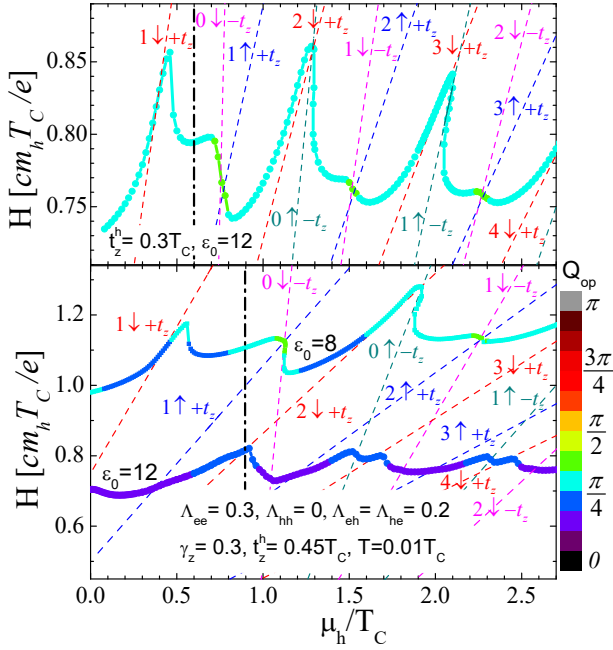


FIG. 14. The dependences of the upper critical field on the Fermi energy μ_h for the case of dominating deep-band pairing. The lower plots are computed for the interlayer hopping energy $t_z^h = 0.45T_C$ and two values of separation between the band edges $\varepsilon_0 = 8T_C$ and $12T_C$. The upper plot is computed for $t_z^h = 0.3T_C$ and $\varepsilon_0 = 12T_C$. The dashed lines show the miniband-edge fields defined by Eq. (29). The vertical dot-dashed lines mark locations of the first Lifshitz transition at zero magnetic field.

reentrance only exists within narrow range of the Fermi energies.

For better representation of the overall behavior, we show in Fig. 14 the dependences of the low-temperature upper critical field on the Fermi energy μ_h . The lower curve in the lower plot is made for parameters $t_z^h = 0.45T_C$ and $\varepsilon_0 = 12T_C$ (1st set). The same plot is also shown in Fig. 10. There are no reentrant regions for this parameter set. To illustrate the emergence of such regions and other general trends, we also present $H_{C2}(\mu_h)$ dependences for (i) smaller energy separation between the band edges $\varepsilon_0 = 8T_C$ (the upper curve in the lower plot, 2nd set) and (ii) smaller interlayer hopping energy $t_z^h = 0.3T_C$ (upper plot, 3rd set). Note that the parameter ε_0 controls the Fermi energy of the deep band $\mu = \varepsilon_0 - \mu_h$. In all cases the $H_{C2}(\mu_h)$ curves have pronounced oscillations and have a clear tendency to follow the miniband-edge field lines. As we already mentioned, for the 1st set $H_{C2}(\mu_h)$ is a single-valued function reconfirming the absence of the reentrant behavior. We see, however, that the $H_{C2}(\mu_h)$ line has the pronounced kinklike features near the crossing of the miniband-edge lines. For the Fermi energies at the maxima, the $H_{C2}(T)$ line has a pronounced low-temperature upturn, as illustrated in the inset of Fig. 13 for $\mu_h = 0.9T_C$. For the 2nd and 3rd sets multiple solutions for $H_{C2}(\mu_h)$ appear below some crossing points corresponding to existence of the reentrant behavior in these regions. For example, for the $t_z^h = 0.3T_C$ (upper plot) such regions are located near $\mu_h = 1.28$ and $2.1T_C$. We also see that for these sets a kinklike feature also exists below the first Lifshitz transition at $\mu_h = 0.9T_C$, in the region of closed Fermi surface, where the H_{C2} curve separates from the “ $1 \downarrow + t_z$ ” line. It is clear that the reentrant regions will become more pronounced with further decreasing of either t_z^h or ε_0 .

- ¹ E. Helfand and N. R. Werthamer, Phys. Rev. **147**, 288 (1966); N. R. Werthamer, E. Helfand, and P. C. Hohenberg, Phys. Rev. **147**, 295 (1966).
- ² L. Gunther and L. W. Gruenberg, Solid State Commun. **4**, 329 (1966); L. W. Gruenberg and L. Gunther, Phys. Rev. **176**, 606 (1968).
- ³ A. Rajagopal and R. Vasudevan, Phys. Lett. **23**, 539 (1966).
- ⁴ Z. Tešanović and M. Rasolt, Phys. Rev. B **39**, 2718 (1989); Z. Tešanović, M. Rasolt, and L. Xing, Phys. Rev. B **43**, 288 (1991).
- ⁵ C. Rieck, K. Scharnberg, and R. Klemm, Physica C **170**, 195 (1990).
- ⁶ A. H. MacDonald, H. Aker, and M. R. Norman, Phys. Rev. B **45**, 10147 (1992).
- ⁷ M. R. Norman, H. Aker, and A. H. MacDonald, in *Physical Phenomena at High Magnetic Fields*, edited by E. Manousakis, P. Schlottmann, P. Kumar, K. Bedell, and F. Mueller (Addison-Wesley, New York, 1992) p. 326.
- ⁸ T. Maniv, A. I. Rom, I. D. Vagner, and P. Wyder, Phys. Rev. B **46**, 8360 (1992).
- ⁹ T. Maniv, V. Zhuravlev, I. Vagner, and P. Wyder, Rev. Mod. Phys. **73**, 867 (2001).

- ¹⁰ C. Liu, T. Kondo, R. M. Fernandes, A. D. Palczewski, E. D. Mun, N. Ni, A. N. Thaler, A. Bostwick, E. Rotenberg, J. Schmalian, S. L. Bud'ko, P. C. Canfield, and A. Kaminski, Nat. Phys. **6**, 419 (2010).
- ¹¹ N. Xu, P. Richard, X. Shi, A. van Roekeghem, T. Qian, E. Razzoli, E. Rienks, G.-F. Chen, E. Ieki, K. Nakayama, T. Sato, T. Takahashi, M. Shi, and H. Ding, Phys. Rev. B **88**, 220508 (2013).
- ¹² H. Miao, T. Qian, X. Shi, P. Richard, T. K. Kim, M. Hoesch, L. Y. Xing, X. C. Wang, C. Q. Jin, J. P. Hu, and H. Ding, Nat. Commun. **6**, 6056 (2015).
- ¹³ X. Shi, Z.-Q. Han, X.-L. Peng, P. Richard, T. Qian, X.-X. Wu, M.-W. Qiu, S. C. Wang, J. P. Hu, Y.-J. Sun, and H. Ding, Nat. Commun. **8**, 14988 EP (2017).
- ¹⁴ J. M. Blatt and C. J. Thompson, Phys. Rev. Lett. **10**, 332 (1963); V. Kresin and B. Tavger, Zh. Eksp. Teor. Fiz. **50**, 1689 (1966), [Sov. Phys. JETP, **23**, 1124 (1966)].
- ¹⁵ A. A. Shanenko and M. D. Croitoru, Phys. Rev. B **73**, 012510 (2006); M. D. Croitoru, A. A. Shanenko, and F. M. Peeters, Phys. Rev. B **76**, 024511 (2007).
- ¹⁶ M. Cariglia, A. Vargas-Paredes, M. M. Doria, A. Bianconi, M. V. Milošević, and A. Perali, J. Supercon. Novel Magn. **29**, 3081 (2016).

- ¹⁷ D. Valentinis, D. van der Marel, and C. Berthod, Phys. Rev. B **94**, 054516 (2016).
- ¹⁸ D. Innocenti, N. Poccia, A. Ricci, A. Valletta, S. Caprara, A. Perali, and A. Bianconi, Phys. Rev. B **82**, 184528 (2010).
- ¹⁹ Y. Bang, New J. Phys. **16**, 023029 (2014).
- ²⁰ A. E. Koshelev and K. A. Matveev, Phys. Rev. B **90**, 140505 (2014).
- ²¹ X. Chen, S. Maiti, A. Linscheid, and P. J. Hirschfeld, Phys. Rev. B **92**, 224514 (2015).
- ²² D. Valentinis, D. van der Marel, and C. Berthod, Phys. Rev. B **94**, 024511 (2016).
- ²³ A. V. Chubukov, I. Eremin, and D. V. Efremov, Phys. Rev. B **93**, 174516 (2016).
- ²⁴ K. W. Song and A. E. Koshelev, Phys. Rev. B **95**, 174503 (2017).
- ²⁵ P. Fulde and R. A. Ferrell, Phys. Rev. **135**, A550 (1964).
- ²⁶ A. Larkin and Y. Ovchinnikov, Zh. Eksp. Teor. Fiz. **47**, 1136 (1964), [Sov. Phys. JETP, **20**, 762 (1965)].
- ²⁷ L. W. Gruenberg and L. Gunther, Phys. Rev. Lett. **16**, 996 (1966).
- ²⁸ S. Takada and T. Izuyama, Prog. Theor. Phys. **41**, 635 (1969).
- ²⁹ K. Machida and H. Nakanishi, Phys. Rev. B **30**, 122 (1984).
- ³⁰ H. Burkhardt and D. Rainer, Ann. Phys. **506**, 181 (1994).
- ³¹ H. Shimahara, Phys. Rev. B **50**, 12760 (1994); H. Shimahara and D. Rainer, J. Phys. Soc. Jpn. **66**, 3591 (1997); H. Shimahara, Phys. Rev. B **80**, 214512 (2009).
- ³² M. Houzet and A. Buzdin, Europhys. Lett. **50**, 375 (2000).
- ³³ M. Houzet and A. Buzdin, Phys. Rev. B **63**, 184521 (2001).
- ³⁴ A. Buzdin, S. Tollis, and J. Cayssol, Phys. Rev. Lett. **95**, 167003 (2005).
- ³⁵ V. H. Dao, D. Denisov, A. Buzdin, and J.-P. Brison, Phys. Rev. B **87**, 174509 (2013).
- ³⁶ M. D. Croitoru and A. I. Buzdin, Phys. Rev. B **89**, 224506 (2014).
- ³⁷ R. Beyer and J. Wosnitza, Low Temp. Phys. **39**, 225 (2013).
- ³⁸ C. C. Agosta, N. A. Fortune, S. T. Hannahs, S. Gu, L. Liang, J.-H. Park, and J. A. Schleuter, Phys. Rev. Lett. **118**, 267001 (2017).
- ³⁹ K. Kumagai, M. Saitoh, T. Oyaizu, Y. Furukawa, S. Takashima, M. Nohara, H. Takagi, and Y. Matsuda, Phys. Rev. Lett. **97**, 227002 (2006).
- ⁴⁰ Y. Matsuda and H. Shimahara, J. Phys. Soc. Jpn. **76**, 051005 (2007).
- ⁴¹ A. Gurevich, Phys. Rev. B **82**, 184504 (2010).
- ⁴² T. Mizushima, M. Takahashi, and K. Machida, J. Phys. Soc. Jpn. **83**, 023703 (2014); M. Takahashi, T. Mizushima, and K. Machida, Phys. Rev. B **89**, 064505 (2014).
- ⁴³ K. Adachi and R. Ikeda, J. Phys. Soc. Jpn. **84**, 064712 (2015).
- ⁴⁴ A. Ptok and D. Crivelli, J. Low Temp. Phys. **172**, 226 (2013); A. Ptok, Eur. Phys. J. B **87**, 2 (2014); J. Phys. Condens. Matter **27**, 482001 (2015); A. Ptok, K. J. Kapcia, P. Piekarz, and A. M. Oleś, New J. Phys. **19**, 063039 (2017).
- ⁴⁵ I. M. Lifshitz, Zh. Eksp. Teor. Fiz. **38**, 1569 (1960), [Sov. Phys. JETP **11**, 1130 (1960)].
- ⁴⁶ A. K. Rajagopal and J. C. Ryan, Phys. Rev. B **44**, 10280 (1991).
- ⁴⁷ I. D. Vagner, T. Maniv, and E. Ehrenfreund, Phys. Rev. Lett. **51**, 1700 (1983).
- ⁴⁸ M. A. Itskovsky, T. Maniv, and I. D. Vagner, Phys. Rev. B **61**, 14616 (2000).
- ⁴⁹ For strong Zeeman spin-splitting, the largest H_{C2} may be realized for *higher Landau-level* eigenfunction⁵⁶.
- ⁵⁰ To be accurate, the complex order parameter in Eq. (15) was suggested by Fulde and Ferrel²⁵. As demonstrated by Larkin and Ovchinnikov²⁶, for purely paramagnetic case the ground state below the transition is actually given by the order parameter with the amplitude modulation $\propto \cos(Q_z j)$. In the presence of orbital effects, both states may realize³³. We only investigate the instability location here, which is the same for both states.
- ⁵¹ J. Wosnitza, *Fermi surfaces of Low-Dimensional Organic Metals and Superconductors* (Springer, Berlin, 1996).
- ⁵² T. Champel and V. P. Mineev, Philos. Mag. B **81**, 55 (2001).
- ⁵³ Y. Suzumura and K. Ishino, Prog. Theor. Phys. **70**, 654 (1983).
- ⁵⁴ K. Machida and H. Nakanishi, Phys. Rev. B **30**, 122 (1984).
- ⁵⁵ V. Zhuravlev and T. Maniv, Phys. Rev. B **80**, 174520 (2009).
- ⁵⁶ A. I. Buzdin and J. P. Brison, Europhys. Lett. **35**, 707 (1996); A. Buzdin and J. Brison, Phys. Lett. A **218**, 359 (1996).
- ⁵⁷ S. Medvedev, T. M. McQueen, I. A. Troyan, T. Palasyuk, M. I. Erements, R. J. Cava, S. Naghavi, F. Casper, V. Ksenofontov, G. Wortmann, and C. Felser, Nat. Mater. **8**, 630 EP (2009).
- ⁵⁸ S. Kasahara, T. Watashige, T. Hanaguri, Y. Kohsaka, T. Yamashita, Y. Shimoyama, Y. Mizukami, R. Endo, H. Ikeda, K. Aoyama, T. Terashima, S. Uji, T. Wolf, H. von Löhneysen, T. Shibauchi, and Y. Matsuda, Proc. Natl. Acad. Sci. USA **111**, 16309 (2014).
- ⁵⁹ T. Terashima, N. Kikugawa, A. Kiswandhi, E.-S. Choi, J. S. Brooks, S. Kasahara, T. Watashige, H. Ikeda, T. Shibauchi, Y. Matsuda, T. Wolf, A. E. Böhmer, F. Hardy, C. Meingast, H. v. Löhneysen, M.-T. Suzuki, R. Arita, and S. Uji, Phys. Rev. B **90**, 144517 (2014).
- ⁶⁰ M. D. Watson, T. K. Kim, A. A. Haghighirad, N. R. Davies, A. McCollam, A. Narayanan, S. F. Blake, Y. L. Chen, S. Ghannadzadeh, A. J. Schofield, M. Hoesch, C. Meingast, T. Wolf, and A. I. Coldea, Phys. Rev. B **91**, 155106 (2015).
- ⁶¹ A. Audouard, F. Duc, L. Drigo, P. Toulemonde, S. Karlsson, P. Strobel, and A. Sulpice, Europhys. Lett. **109**, 27003 (2015).
- ⁶² T. Shimojima, Y. Suzuki, T. Sonobe, A. Nakamura, M. Sakano, J. Omachi, K. Yoshioka, M. Kuwata-Gonokami, K. Ono, H. Kumigashira, A. E. Böhmer, F. Hardy, T. Wolf, C. Meingast, H. v. Löhneysen, H. Ikeda, and K. Ishizaka, Phys. Rev. B **90**, 121111 (2014).
- ⁶³ K. Nakayama, Y. Miyata, G. N. Phan, T. Sato, Y. Tanabe, T. Urata, K. Tanigaki, and T. Takahashi, Phys. Rev. Lett. **113**, 237001 (2014).
- ⁶⁴ A. Fedorov, A. Yaresko, T. K. Kim, Y. Kushnirenko, E. Haubold, T. Wolf, M. Hoesch, A. Grüneis, B. Büchner, and S. V. Borisenko, Sci. Rep. **6**, 36834 (2016).
- ⁶⁵ T. Terashima, N. Kikugawa, A. Kiswandhi, D. Graf, E.-S. Choi, J. S. Brooks, S. Kasahara, T. Watashige, Y. Matsuda, T. Shibauchi, T. Wolf, A. E. Böhmer, F. Hardy, C. Meingast, H. v. Löhneysen, and S. Uji, Phys. Rev. B **93**, 094505 (2016).
- ⁶⁶ S. J. Zhang, X. C. Wang, R. Sammynaiken, J. S. Tse, L. X. Yang, Z. Li, Q. Q. Liu, S. Desgreniers, Y. Yao, H. Z. Liu, and C. Q. Jin, Phys. Rev. B **80**, 014506 (2009).

- ⁶⁷ K. Cho, H. Kim, M. A. Tanatar, Y. J. Song, Y. S. Kwon, W. A. Coniglio, C. C. Agosta, A. Gurevich, and R. Prozorov, *Phys. Rev. B* **83**, 060502 (2011).
- ⁶⁸ S. Khim, B. Lee, J. W. Kim, E. S. Choi, G. R. Stewart, and K. H. Kim, *Phys. Rev. B* **84**, 104502 (2011).
- ⁶⁹ C. Putzke, A. I. Coldea, I. Guillaumon, D. Vignolles, A. McCollam, D. LeBoeuf, M. D. Watson, I. I. Mazin, S. Kasahara, T. Terashima, T. Shibauchi, Y. Matsuda, and A. Carrington, *Phys. Rev. Lett.* **108**, 047002 (2012).
- ⁷⁰ B. Zeng, D. Watanabe, Q. R. Zhang, G. Li, T. Besara, T. Siegrist, L. Y. Xing, X. C. Wang, C. Q. Jin, P. Goswami, M. D. Johannes, and L. Balicas, *Phys. Rev. B* **88**, 144518 (2013).
- ⁷¹ H. W. Meul, C. Rossel, M. Decroux, Ø. Fischer, G. Remenyi, and A. Briggs, *Phys. Rev. Lett.* **53**, 497 (1984); C. Rossel, H. W. Meul, M. Decroux, Ø. Fischer, G. Remenyi, and A. Briggs, *J. Appl. Phys.* **57**, 3099 (1985).
- ⁷² V. Jaccarino and M. Peter, *Phys. Rev. Lett.* **9**, 290 (1962).
- ⁷³ H. Weng, C. Fang, Z. Fang, B. A. Bernevig, and X. Dai, *Phys. Rev. X* **5**, 011029 (2015).
- ⁷⁴ S.-M. Huang, S.-Y. Xu, I. Belopolski, C.-C. Lee, G. Chang, B. Wang, N. Alidoust, G. Bian, M. Neupane, C. Zhang, S. Jia, A. Bansil, H. Lin, and M. Z. Hasan, *Nat. Commun.* **6**, 7373 EP (2015).
- ⁷⁵ S.-Y. Xu, I. Belopolski, N. Alidoust, M. Neupane, G. Bian, C. Zhang, R. Sankar, G. Chang, Z. Yuan, C.-C. Lee, S.-M. Huang, H. Zheng, J. Ma, D. S. Sanchez, B. Wang, A. Bansil, F. Chou, P. P. Shibayev, H. Lin, S. Jia, and M. Z. Hasan, *Science* **349**, 613 (2015).
- ⁷⁶ B. Q. Lv, H. M. Weng, B. B. Fu, X. P. Wang, H. Miao, J. Ma, P. Richard, X. C. Huang, L. X. Zhao, G. F. Chen, Z. Fang, X. Dai, T. Qian, and H. Ding, *Phys. Rev. X* **5**, 031013 (2015).
- ⁷⁷ L. X. Yang, Z. K. Liu, Y. Sun, H. Peng, H. F. Yang, T. Zhang, B. Zhou, Y. Zhang, Y. F. Guo, M. Rahn, D. Prabhakaran, Z. Hussain, S. K. Mo, C. Felser, B. Yan, and Y. L. Chen, *Nat. Phys.* **11**, 728 EP (2015).
- ⁷⁸ N. P. Armitage, E. J. Mele, and A. Vishwanath, *Rev. Mod. Phys.* **90**, 015001 (2018).
- ⁷⁹ Y. Zhou, J. Wu, W. Ning, N. Li, Y. Du, X. Chen, R. Zhang, Z. Chi, X. Wang, X. Zhu, P. Lu, C. Ji, X. Wan, Z. Yang, J. Sun, W. Yang, M. Tian, Y. Zhang, and H.-K. Mao, *Proc. Natl. Acad. Sci. USA* **113**, 2904 (2016).
- ⁸⁰ Y. Liu, Y. J. Long, L. X. Zhao, S. M. Nie, S. J. Zhang, Y. X. Weng, M. L. Jin, W. M. Li, Q. Q. Liu, Y. W. Long, R. C. Yu, C. Z. Gu, F. Sun, W. G. Yang, H. K. Mao, X. L. Feng, Q. Li, W. T. Zheng, H. M. Weng, X. Dai, Z. Fang, G. F. Chen, and C. Q. Jin, *Sci. Rep.* **7**, 44367 EP (2017).
- ⁸¹ Y. Qi, W. Shi, P. G. Naumov, N. Kumar, W. Schnelle, O. Barkalov, C. Shekhar, H. Borrmann, C. Felser, B. Yan, and S. A. Medvedev, *Phys. Rev. B* **94**, 054517 (2016).
- ⁸² Y. Li, Y. Zhou, Z. Guo, F. Han, X. Chen, P. Lu, X. Wang, C. An, Y. Zhou, J. Xing, G. Du, X. Zhu, H. Yang, J. Sun, Z. Yang, W. Yang, H.-K. Mao, Y. Zhang, and H.-H. Wen, *npj Quantum Materials* **2**, 66 (2017).
- ⁸³ B. Rosenstein, B. Y. Shapiro, D. Li, and I. Shapiro, *Phys. Rev. B* **96**, 224517 (2017).
- ⁸⁴ V. Zhuravlev, W. Duan, and T. Maniv, *Europhys. Lett.* **120**, 27004 (2017).
- ⁸⁵ V. Zhuravlev, W. Duan, and T. Maniv, *Phys. Rev. B* **95**, 024502 (2017).
- ⁸⁶ V. M. Yakovenko, *Phys. Rev. B* **47**, 8851 (1993).