

This is the accepted manuscript made available via CHORUS. The article has been published as:

Fermi surface reconstruction and dimensional topology change in Nd-doped CeCoIn_5

J. Klotz, K. Götze, I. Sheikin, T. Förster, D. Graf, J.-H. Park, E. S. Choi, R. Hu, C. Petrovic, J. Wosnitza, and E. L. Green

Phys. Rev. B **98**, 081105 — Published 9 August 2018

DOI: [10.1103/PhysRevB.98.081105](https://doi.org/10.1103/PhysRevB.98.081105)

Fermi-Surface Reconstruction and Dimensional Topology Change in Nd-doped CeCoIn₅

J. Klotz,^{1,2} K. Götze,^{1,2,*} I. Sheikin,³ T. Förster,¹ D. Graf,⁴ J.-H. Park,⁴
E. S. Choi,⁴ R. Hu,⁵ C. Petrovic,⁵ J. Wosnitza,^{1,2} and E. L. Green^{1,†}

¹*Hochfeld-Magnetlabor Dresden (HLD-EMFL), Helmholtz-Zentrum Dresden-Rossendorf, 01328 Dresden, Germany*

²*Institut für Festkörper- und Materialphysik, Technische Universität Dresden, 01069 Dresden, Germany*

³*Laboratoire National des Champs Magnétiques Intenses (LNCMI-EMFL), CNRS, UGA, F-38042 Grenoble, France*

⁴*National High Magnetic Field Laboratory, Florida State University, Tallahassee, Florida 32310, USA*

⁵*Condensed Matter Physics and Materials Science Department,
Brookhaven National Laboratory, Upton, New York 11973, USA*

(Dated: July 30, 2018)

We performed low-temperature de Haas-van Alphen (dHvA) effect measurements on a Ce_{1-x}Nd_xCoIn₅ series, for $x = 0.02, 0.05, 0.1$, and 1 , down to $T = 40$ mK using torque magnetometry in magnetic fields up to 35 T. Our results indicate that a Fermi-surface (FS) reconstruction occurs from a quasi-two-dimensional (2D) topology for Nd-2% to a rather three-dimensional (3D) for Nd-5%, thus reducing the possibility of perfect FS nesting. The FS evolves further with increasing Nd content with no observed divergence of the effective mass between Nd-2% and 10%, consistent with the crossing of a spin density wave (SDW) type of quantum critical point (QCP). Our results elucidate the origin of the Q -phase observed at the 5% Nd-doping level¹.

Heavy-fermion systems have garnered attention over the past few decades due to their novel physical properties and exotic behavior, particularly when exposed to high magnetic fields²⁻⁵. Most notably CeCoIn₅, which has the highest critical temperature of all Ce-based heavy-fermion compounds ($T_c = 2.3$ K^{6,7}), exhibits a field-induced ordered phase from 10 T up to 11.4 T for $B \parallel a^8$, a superconducting state now referred to as the Q -phase. It was initially believed this high-field state was the realization of the long-sought-after Fulde-Ferrell Larkin-Ovchinnikov (FFLO) phase⁸⁻¹¹, however, further measurements revealed the presence of antiferromagnetic (AFM) order¹²⁻¹⁴. Many questions, however, still remain about the interactions appearing in this high-field superconducting state.

By substituting a portion of the Ce atoms in CeCoIn₅ with Nd, an atom where the $4f$ electrons do not hybridize with the conduction electrons, one can introduce SDW and, at higher Nd contents, AFM order^{1,15}. It was recently reported that by replacing 5% of the Ce atoms with Nd the high-field Q -phase could be stabilized at zero applied magnetic field, inciting intense research to explore the mechanism behind such unique properties^{1,16-18}. An enhancement of the nesting has been proposed¹, however, experimental proof has been insufficient, thus providing our motivation to explore how Nd alters the FS. Additionally, it has previously been suggested that a QCP may exist in these materials¹⁶, which may also be induced by increasing Nd doping¹⁵.

In this paper, we provide evidence for a drastic FS reconstruction between 2% and 5% Nd substitution. The reconstruction manifests itself in a sharp deviation of the α orbit from the expected $1/\cos\theta$ dependence normally associated with a quasi-2D cylindrical FS. This is at odds with assumptions made in current theoretical models¹⁹. Furthermore, this distorted FS may be described as more 3D in nature and any effects from possible FS nesting

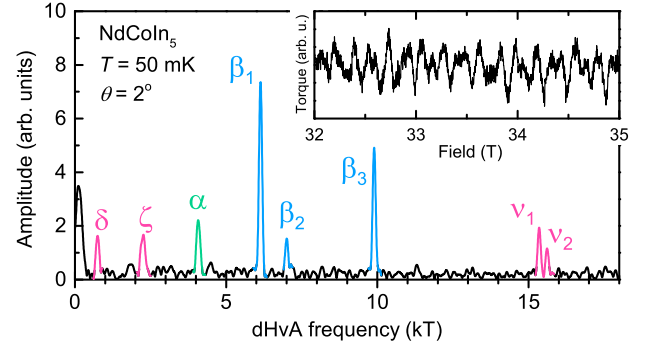


FIG. 1: Fourier transform of the quantum oscillations between 21-35 T measured on NdCoIn₅ at an angle $\theta = 2^\circ$ from [001] to [110]. Inset shows the torque signal at high magnetic fields after background subtraction.

suggested in prior works¹ may, therefore, be significantly reduced. The FSs continue to evolve for 5%, 10%, and 100% Nd substitution and are consistent with fully localized $4f$ electrons only at 100% substitution. The effective mass associated with the quasi-2D cylindrical band, previously found to play a key role in superconductivity^{20,21}, remains constant between 0 and 10% Nd substitution levels. Both the progressive change of the FSs with increasing substitution level and non-divergent effective carrier masses indicate the SDW-type nature of the QCP^{22,23}, consistent with thermodynamic measurements¹⁵.

High-quality single crystals of Ce_{1-x}Nd_xCoIn₅ with $x = 0.02, 0.05, 0.1$, and 1 (herein referred to as Nd-2%, 5%, 10%, and 100%) were grown and characterized as described elsewhere¹⁵. Torque magnetometry was performed at the Laboratoire National des Champs Magnétiques Intenses (LNCMI) in Grenoble, France, and the National High Magnetic Field Laboratory (NHMFL)

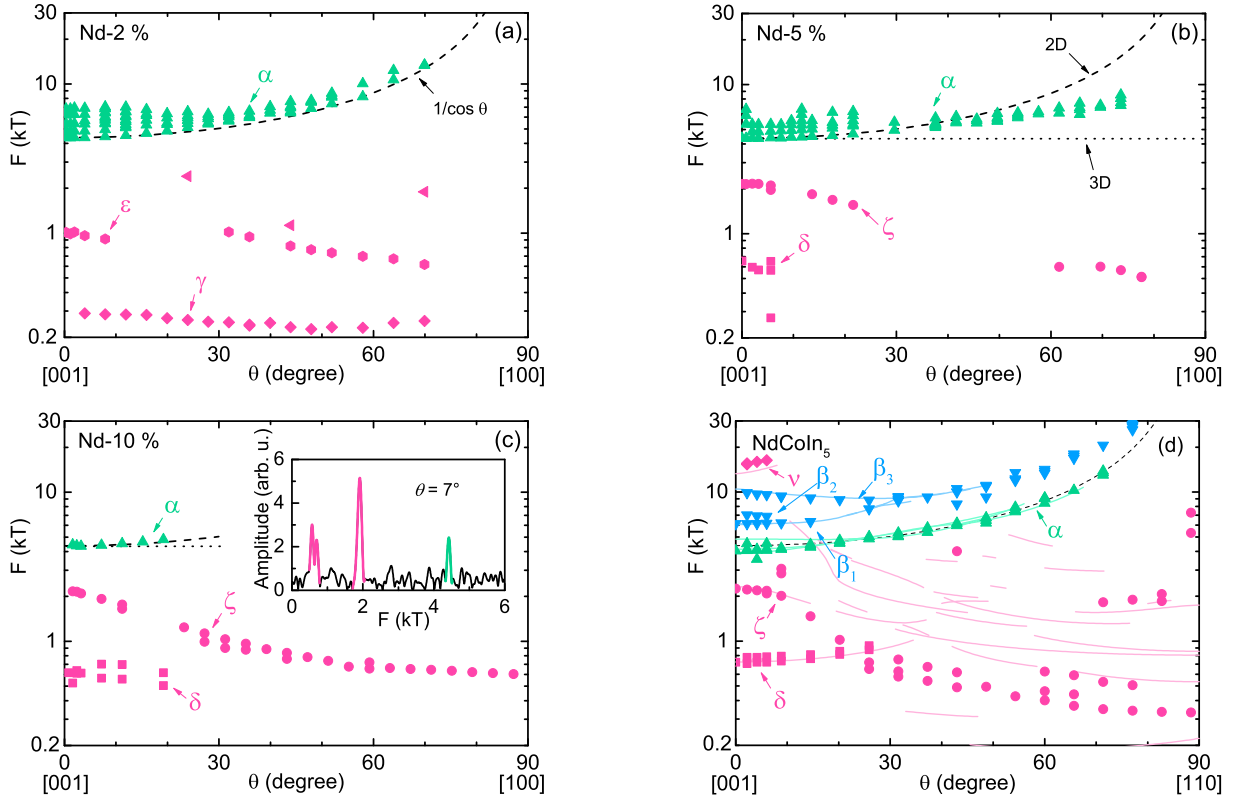


FIG. 2: Angular dependence of the dHvA frequencies for (a) Nd-2%, (b) 5%, (c) 10%, and (d) 100 %. The latter includes the results of the band-structure calculations, shown as lines. The labeling of the frequency branches has been defined so as to be consistent with prior works^{27,30}. Dashed lines denote $1/\cos \theta$ dependence arising from a 2D cylindrical FS, dotted from a 3D sphere. Inset in (c) depicts the FFT for $\theta = 7.2^\circ$.

in Tallahassee, USA, using a capacitive beam cantilever mounted on a rotator and placed in a top-loading $^3\text{He}/^4\text{He}$ dilution refrigerator. To accurately probe the lighter effective masses in NdCoIn_5 , a ^3He cryostat was utilized. Band-structure calculations for NdCoIn_5 were performed using the full-potential local-orbital (FPLO) minimum-basis code (version 9.01-35)²⁴ with a scalar-relativistic setting and the local density approximation of Ref.²⁵. Lattice parameters were taken from Ref.²⁶.

dHvA oscillations were detected using field-dependent torque magnetometry (21-35 T) for Nd-2%, 5%, 10%, and 100%, but could not be resolved for mid-range substitution levels (Nd-20% and 60%). Background magnetization was subtracted using a higher-order polynomial fit resulting in oscillations as shown for NdCoIn_5 in the inset of Fig. 1. A Fourier transform revealed several prominent frequencies well above the noise level (see Fig. 1). Angular dependence for the dHvA frequencies was explored, rotating from $B \parallel c$ ([001]) to $B \perp c$ ([100]), for Nd-2%, 5%, and 10% as shown in Figs. 2(a)-(c). Nd-100% was rotated towards [110] [see Fig. 2(d)]. In pure CeCoIn_5 , it has been shown that there is little difference in the dHvA frequencies between [100] and [110] due to the mostly isotropic FSs in the a - b plane^{27,28}. The same is assumed to be true for the isostructural compound NdCoIn_5 , backed by our calculations.

Numerous frequencies could be resolved for Nd-2%, as shown in Fig. 2(a), many of which correspond to those found in CeCoIn_5 ^{27,29}. The frequency labeled β by Settai *et al.*²⁸ could not be observed, possibly due to increased impurity scattering, which affects heavy-mass orbits stronger. Instead, we observe frequencies of 6.25 and 6.92 kT at $\theta = 3^\circ$, which were not reported for pure CeCoIn_5 ²⁷⁻³⁰. Since the frequencies between 4 and 8 kT, labeled α , follow roughly a $1/\cos \theta$ dependence, where θ is the angle between the applied magnetic field and the c direction (see drawing in Fig. 4), it is plausible that these frequencies arise from a strongly corrugated 2D cylindrical FS.

A drastic FS reconstruction occurs for 5% Nd doping [Fig. 2(b)]. The frequencies ϵ and γ in Nd-2% disappear and are replaced by δ and ζ in Nd-5%. Frequencies associated with the α orbits noticeably deviate from the expected $1/\cos \theta$ dependence seen in the 2% Nd-doping level indicating the 2D cylindrical FS has now warped into more of a quasi-3D structure. This is of particular interest because recent theoretical work exploring the reasoning behind the appearance of the Q -phase at zero applied magnetic field is based on the assumption that doping has a negligible effect on the FS¹⁹. Furthermore, it has been proposed that the Q vector appears at 0 T due to an enhanced FS nesting¹. However, since the cylindri-

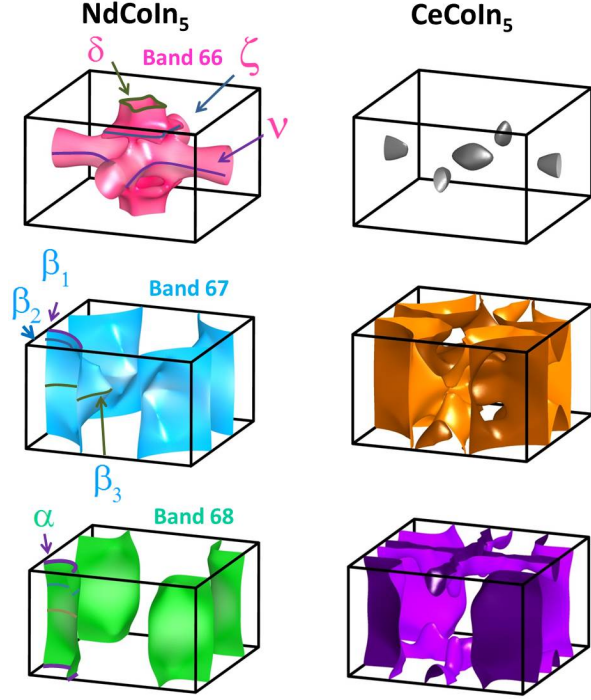


FIG. 3: Calculated FSs for NdCoIn₅ (left) and CeCoIn₅ (right). The black frames depict the first Brillouin zone. The solid lines on the FSs aid in the visualization of some extremal orbits for the magnetic field aligned along the c axis. For NdCoIn₅ (left) 66 is a hole band while 67 and 68 are electron bands.

cal FS is developing a more 3D structure, this scenario seems unlikely.

As the substitution level increases to 10%, the frequencies associated with the δ and ζ continue to evolve [Fig. 2(c)]. Few frequencies associated with the α band could be seen, all agreeing with frequencies found for Nd-2% and Nd-5%. Due to increased scattering provoked by doping-induced disorder, quantum oscillations could not be detected for further substitution levels (20% and 60%), but numerous frequencies appear for NdCoIn₅ as seen in Fig. 2(d). Furthermore, a well-defined 2D cylindrical FS, labeled α as before, reemerges as evidenced by the $1/\cos \theta$ behavior, but with a different FS cross section. In addition, a second corrugated 2D cylindrical FS labeled β is identified by a $1/\cos \theta$ dependence.

Band-structure calculations for NdCoIn₅, performed assuming localized, non-hybridizing $4f$ electrons, are in good agreement with experimental data [see Fig. 2d]. The topology of the FSs for NdCoIn₅ along with their corresponding frequencies are depicted in Figs. 2(d) and 3, herein referred to as band 66, band 67, and band 68 represented in the graphs as pink, blue, and green, respectively. A comparison between the FSs of CeCoIn₅ and NdCoIn₅ is shown in Fig. 3. As a note, the FS could only reasonably be calculated for NdCoIn₅ and CeCoIn₅, not for the substitution series because of the increased

complexity doping introduces to the calculation.

Effective masses were extracted by fitting the oscillation amplitudes, shown in Fig. 4, to the Lifshitz-Kosevich formula^{31,32}. In order to observe a sufficiently strong torque signal for as many frequency branches as possible, effective masses were measured at angles between 4 and 10° from the c axis for the different substitution levels. Effective masses for the observed frequencies in NdCoIn₅ are shown in Table I and are slightly larger than the calculated masses reflecting modest mass enhancements quantified by $\lambda = m^*/m_b - 1$ ³⁶. Effective masses for all other substitution levels are shown in Table II. It is evident that increasing the substitution level has little effect on the effective masses of existing orbits up to Nd-10%, while newly appearing orbits have a greatly reduced mass.

The effective mass for α_3 , the orbit associated with the 2D band at low doping level and the only branch that can be tracked up to Nd-10%, remains relatively unchanged with increasing substitution levels despite T_c rapidly decreasing ($T_c = 2.1, 2.0$, and 1.8 K for Nd-2%, 5%, and 10%, respectively)¹⁵. This behavior near QCPs was observed in the CeRh_{1-x}Co_xIn₅³⁷ and CeCo(In_{1-x}Cd_x)₅³⁸ series, but differs from the Ce_xLa_{1-x}CoIn₅³⁹ series and the pressure-induced QCP in CeRhIn₅⁴⁰. Consequently, our data indicate the presence of a SDW-type QCP^{22,23}, consistent with the experimental phase diagram¹⁵. The cylindrical FSs are generally assumed to be the heavy bands that possess the largest energy gap²⁰ and are theoretically considered to experience the interacting pairing potential relevant for superconductivity⁴¹. Therefore, since the band remains relatively heavy, most probably due to electronic correlations, Nd is likely altering the pairing potential. This is in agreement with the reduced jump in the specific heat upon entering the superconducting state¹⁵.

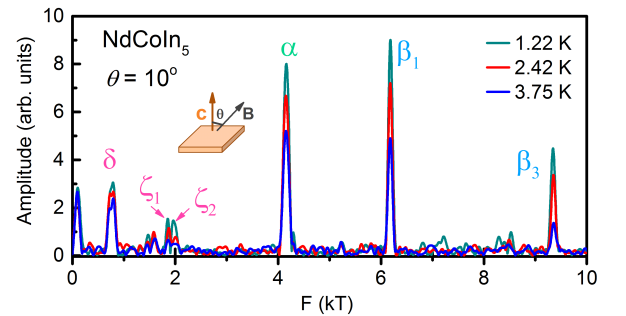


FIG. 4: Example of the temperature dependence of the observed frequencies in NdCoIn₅ measured between 21-35 T at an angle of $\theta = 10^\circ$ from [001] to [110].

In conclusion, the FS of Ce_{1-x}Nd_xCoIn₅ changes across the QCP associated with the appearance of long-range magnetic order at Nd-5% and continues to evolve with increasing x , consistent with a SDW-type QCP^{22,23}. Furthermore, between Nd-2% and Nd-5%, the FS moves away from two-dimensionality which is at odds with an

branch	Experiment		Calculation		λ
	F [kT]	m^* [m_e]	F [kT]	m_b [m_e]	$m^*/m_b - 1$
δ	0.79	0.53(8)	0.74	0.29	0.82
ζ_1	1.87	1.0(2)			
ζ_2	1.98	1.2(2)			
α	4.15	0.83(3)	4.12	0.73	0.13
β_1	6.17	1.06(3)	6.18	0.77	0.37
β_3	9.36	1.3(2)	9.42	0.86	0.55

TABLE I: Comparison of effective masses measured at an angle of 10° from [001] to [110] of NdCoIn₅ with calculations.

enhanced Fermi-nesting scenario given as an explanation for the Q -phase seen at zero applied magnetic field¹. Since effective masses are unaffected by altering Nd content up to 10% despite a decrease in T_c , it is plausible to conclude that Nd alters the electronic pairing potential. Our results provide the first information on the evolution of the FS topology under Nd perturbation and its influence on the emerging Q -phase in Nd-5%.

We acknowledge the support of HLD at HZDR and LNCMI at CNRS, members of the European Magnetic Field Laboratory (EMFL) and ANR-DFG grant Fermi-NES_t. A portion of this work was performed at the National High Magnetic Field Laboratory, which is supported by National Science Foundation Cooperative Agreement No. DMR-1157490 and the State of Florida. Work at Brookhaven is supported by the US DOE under Contract No. DE-SC0012704. C.P. acknowledges support by the Alexander von Humboldt Foundation. K.G. acknowledges support from the DFG within GRK 1621. We would like to thank A. Carrington, R.R. Urbano, G. Zwirnagl, C. Putzke, T. Murphy, and H. Rosner for fruitful discussions.

	CeCoIn ₅ ³⁰ $\theta = 0^\circ$		Nd-2% $\theta = 3^\circ$		Nd-5% $\theta = 2^\circ$		Nd-10% $\theta = 7^\circ$	
branch	F [kT]	m^* [m_e]	F [kT]	m^* [m_e]	F [kT]	m^* [m_e]	F [kT]	m^* [m_e]
γ			0.29	6.4(6)				
ϵ			0.99	20.3(15)				
δ_1					0.59	< 1	0.55	< 1
δ_2							0.68	< 1
ζ					2.16	< 1	1.9	< 1
α_1	5.46	14.5	5.44	10.3(5)	5.42	10.0(5)		
α_2	4.87	11.4	4.85	11.0(5)	4.84	10.5(8)		
α_3	4.37	9.3	4.39	6.7(2)	4.38	6.8(2)	4.41	7(1)
α_4			6.25	12.0(10)				
α_5			6.92	18.5(7)				

TABLE II: Effective masses for the various frequencies depicted in Figs. 3(a)-(c). Frequencies and effective masses associated with CeCoIn₅ were taken from Ref.³⁰. m^* associated with α remains relatively stable with increased Nd-doping.

- * Present address: Department of Physics, University of Warwick, Coventry CV4 7AL, UK
[†] e.green@hazdr.de
- ¹ S. Raymond, S. M. Ramos, D. Aoki, G. Knebel, V. P. Mineev, and G. Lapertot, *J. Phys. Soc. Jpn.* **83**, 013707 (2014).
 - ² I. Kouroudis, D. Weber, M. Yoshizawa, B. Lüthi, L. Puech, P. Haen, J. Flouquet, G. Bruls, U. Welp, J. J. M. Franse, A. Menovsky, E. Bucher, and J. Hufnagl, *Phys. Rev. Lett.* **58**, 820 (1987).
 - ³ D. M. Edwards and A. C. M. Green, *Z. Phys. B* **103**, 243 (1997).
 - ⁴ H. von Löhneysen, *J. Phys.: Condens. Matter* **8**, 9689 (1996).
 - ⁵ D. K. Singh, A. Thamizhavel, J. W. Lynn, S. Dhar, J. Rodriguez-Rivera, and T. Herman, *Sci. Rep.* **1**, 117 (2011).
 - ⁶ C. Petrovic, P. G. Pagliuso, M. F. Hundley, R. Movshovich, J. L. Sarrao, J. D. Thompson, Z. Fisk, and P. Monthoux, *J. Phys.: Condens. Matter* **13**, L337 (2001).
 - ⁷ S. Ikeda, H. Shishido, M. Nakashima, R. Settai, D. Aoki, Y. Haga, H. Harima, Y. Aoki, T. Namiki, H. Sato, and Y. Ōnuki, *J. Phys. Soc. Jpn.* **70**, 2248 (2001).
 - ⁸ A. Bianchi, R. Movshovich, C. Capan, P. G. Pagliuso, and J. L. Sarrao, *Phys. Rev. Lett.* **91**, 187004 (2003).
 - ⁹ P. Fulde and R. A. Ferrell, *Phys. Rev.* **135**, A550 (1964).
 - ¹⁰ A. I. Larkin and Yu. N. Ovchinnikov, *Zh. Eksp. Teor. Fiz.* **47**, 1136 (1964). [*Sov. Phys. JETP* **20**, 762 (1965)].
 - ¹¹ H. A. Radovan, N. A. Fortune, T. P. Murphy, S. T. Hannahs, E. C. Palm, S. W. Tozer, and D. Hall, *Nature* **425**, 51 (2003).
 - ¹² V. F. Mitrović, M. Horvatić, C. Berthier, G. Knebel, G. Lapertot, and J. Flouquet, *Phys. Rev. Lett.* **97**, 117002 (2006).
 - ¹³ B.-L. Young, R. R. Urbano, N. J. Curro, J. D. Thompson, J. L. Sarrao, A. B. Vorontsov, and M. J. Graf, *Phys. Rev. Lett.* **98**, 036402 (2007).
 - ¹⁴ M. Kenzelmann, Th. Strässle, C. Niedermayer, M. Sigrist, B. Padmanabhan, M. Zolliker, A. D. Bianchi, R. Movshovich, E. D. Bauer, J. L. Sarrao, and J. D. Thompson, *Science* **321**, 5896 (2008).
 - ¹⁵ R. Hu, Y. Lee, J. Hudis, V. F. Mitrovic, and C. Petrovic, *Phys. Rev. B* **77**, 165129 (2008).
 - ¹⁶ D. G. Mazzone, S. Raymond, J. L. Gavilano, E. Ressouche, C. Niedermayer, J. O. Birk, B. Ouladdiaf, G. Bastien, G. Knebel, D. Aoki, G. Lapertot, and M. Kenzelmann, *Sci. Adv.* **3**, e1602055 (2017).
 - ¹⁷ D. G. Mazzone, S. Raymond, J. L. Gavilano, P. Steffens, A. Schneidewind, G. Lapertot, and M. Kenzelmann, *Phys. Rev. Lett.* **119**, 187002 (2017).
 - ¹⁸ D. G. Mazzone, R. Yadav, M. Bartkowiak, J. L. Gavilano, S. Raymond, E. Ressouche, G. Lapertot, and M. Kenzelmann, *Sci. Reports* **8**, 1295 (2018).
 - ¹⁹ J. H. J. Martiny, M. N. Gastiasoro, I. Vekhter, and B. M. Anderson, *Phys. Rev. B* **92**, 224510 (2015).
 - ²⁰ M. P. Allan, F. Massee, D. K. Morr, J. Van Dyke, R. W. Rost, A. P. Mackenzie, C. Petrovic, and J. C. Davis, *Nat. Phys.* **9**, 468 (2013).
 - ²¹ K. Götze, J. Klotz, D. Gnida, H. Harima, D. Aoki, A. Demuer, S. Elgazzar, J. Wosnitza, D. Kaczorowski, and I. Sheikin, *Phys. Rev. B* **92**, 115141 (2015).
 - ²² Q. Si and F. Steglich, *Science* **329**, 1161 (2010).
 - ²³ P. Gegenwart, Q. Si, and F. Steglich, *Nat. Phys.* **4**, 186 (2008).
 - ²⁴ K. Koepernik and H. Eschrig, *Phys. Rev. B* **59**, 1743 (1999).
 - ²⁵ J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
 - ²⁶ J. Hudis, R. Hu, C. L. Broholm, V. F. Mitrovic, and C. Petrovic, *J. Magn. Magn. Mater.* **307**, 301 (2006).
 - ²⁷ D. Hall, E. C. Palm, T. P. Murphy, S. W. Tozer, Z. Fisk, U. Alver, R. G. Goodrich, J. L. Sarrao, P. G. Pagliuso, and T. Ebihara, *Phys. Rev. B* **64**, 212508 (2001).
 - ²⁸ R. Settai, H. Shishido, S. Ikeda, Y. Murakawa, M. Nakashima, D. Aoki, Y. Haga, H. Harima and Y. Ōnuki, *J. Phys.: Condens. Matter* **13**, L627 (2001).
 - ²⁹ H. Shishido, T. Ueda, S. Hashimoto, T. Kubo, R. Settai, H. Harima, and Y. Ōnuki, *J. Phys.: Condens. Matter* **15**, L499 (2003).
 - ³⁰ A. Polyakov, O. Ignatchik, B. Bergk, K. Götze, A. D. Bianchi, S. Blackburn, B. Prévost, G. Seyfarth, M. Côté, D. Hurt, C. Capan, Z. Fisk, R. G. Goodrich, I. Sheikin, Manuel Richter, and J. Wosnitza, *Phys. Rev. B* **85**, 245119 (2012).
 - ³¹ D. Shoenberg, *Magnetic Oscillations in Metals* (Cambridge University Press, Cambridge, UK, 1984).
 - ³² See Supplemental Material at [URL] for discussions of the energy bands from the band structure calculations, a detailed description of how the effective mass was extracted, and the possible reasons behind the discrepancy between the Sommerfeld coefficients extracted from prior specific heat measurements and the effective masses found in this work. These include Refs. ^{33–35}.
 - ³³ G. Zwicknagl, *Rep. Prog. Phys.* **79**, 124501 (2016).
 - ³⁴ P. Thalmeier and G. Zwicknagl, in *Handbook on the Physics and Chemistry of Rare Earths*, Vol. 34, edited by K. A. Gschneidner, Jr., J.-C. Bünzli, and V. Pecharsky (Elsevier, North Holland, 2004) pp. 135–287.
 - ³⁵ A. McCollam, S. R. Julian, P. M. C. Rourke, D. Aoki, and J. Flouquet, *Phys. Rev. Lett.* **94**, 186401 (2005).
 - ³⁶ FPLO typically results in lower effective masses than are observed experimentally, as is the case here, because it does not take many-body interactions into account.
 - ³⁷ S. K. Goh, J. Paglione, M. Sutherland, E. C. T. O’Farrell, C. Bergemann, T. A. Sayles, and M. B. Maple, *Phys. Rev. Lett.* **101**, 056402 (2008).
 - ³⁸ C. Capan, Y.-J. Jo, L. Balicas, R. G. Goodrich, J. F. DiTusa, I. Vekhter, T. P. Murphy, A. D. Bianchi, L. D. Pham, J. Y. Cho, J. Y. Chan, D. P. Young, and Z. Fisk, *Phys. Rev. B* **82**, 035112 (2010).
 - ³⁹ N. Harrison, U. Alver, R. G. Goodrich, I. Vekhter, J. L. Sarrao, P. G. Pagliuso, N. O. Moreno, L. Balicas, Z. Fisk, D. Hall, Robin T. Macaluso, and J. Y. Chan, *Phys. Rev. Lett.* **93**, 186405 (2004).
 - ⁴⁰ H. Shishido, R. Settai, H. Harima, and Y. Ōnuki, *J. Phys. Soc. Jpn.* **74**, 1103 (2005).
 - ⁴¹ J. S. Van Dyke, F. Massee, M. P. Allan, J. C. Séamus Davis, C. Petrovic, and D. K. Morr, *Proc. Natl. Acad. Sci. U.S.A.* **111**, 11663 (2014).