

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Kagome bands disguised in a coloring-triangle lattice

Shunhong Zhang, Meng Kang, Huaqing Huang, Wei Jiang, Xiaojuan Ni, Lei Kang, Shunping Zhang, Hongxing Xu, Zheng Liu, and Feng Liu

Phys. Rev. B **99**, 100404 — Published 18 March 2019

DOI: [10.1103/PhysRevB.99.100404](https://doi.org/10.1103/PhysRevB.99.100404)

## Kagome Bands Disguised in a Coloring-Triangle Lattice

Shunhong Zhang<sup>1,2</sup>, Meng Kang<sup>2,3</sup>, Huaqing Huang<sup>2</sup>, Wei Jiang<sup>2</sup>, Xiaojuan Ni<sup>2</sup>, Lei Kang<sup>4</sup>, Shunping Zhang<sup>3</sup>, Hongxing Xu<sup>3</sup>, Zheng Liu<sup>1,5</sup> and Feng Liu<sup>2,5</sup>

<sup>1</sup>*Institute for Advanced Study, Tsinghua University, Beijing 100084, China*

<sup>2</sup>*Department of Materials Science and Engineering, University of Utah, Salt Lake City, Utah 84112, USA*

<sup>3</sup>*School of Physics and Technology, Center for Nanoscience and Nanotechnology, and Key Laboratory of Artificial Micro- and Nano-structures of Ministry of Education, Wuhan University, Wuhan 430072, China*

<sup>4</sup>*Beijing Computational Science Research Center, Beijing 100193, China*

<sup>5</sup>*Collaborative Innovation Center of Quantum Matter, Beijing 100084, China*

### Abstract


The Kagome bands hosting exotic quantum phases are generally and understandably pertained only to a Kagome lattice. This has severely hampered the research of Kagome physics due to the lack of real Kagome-lattice materials. Interestingly we discover that a coloring-triangle (CT) lattice, named after color-triangle tiling, hosts also Kagome bands. We demonstrate first theoretically the equivalency between the Kagome and CT lattice, and then computationally in photonic (waveguide lattice) and electronic (Au overlayer on electride Ca<sub>2</sub>N surface) systems by respective finite-element and first-principles calculations. The theory can be generalized to even distorted Kagome and CT lattices to exhibit *ideal* Kagome bands. Our findings open a new avenue to explore the alluding Kagome physics.

Two-dimensional (2D) lattice band models have been intensively studied in the context of band structure and band topology because Bloch electrons in such models give rise to exotic quantum effects. In general, a given band structure, such as the so-called Kagome band as displayed in FIG. 1(a) and 1(b), is pertained *only* to a given type of lattice, namely the Kagome lattice [FIG. 1(c)] [1]. On the other hand, two Hermitian Hamiltonians are equivalent to each other by a unitary transformation, producing identical eigen spectra. However, this equivalency has rarely been demonstrated between two different types of lattice models which could both be physically accessible. In this Rapid Communication, surprisingly, we discover that a kind of triangular lattice, which we called coloring-triangle (CT) lattice, has the identical Kagome band as that of a Kagome lattice. We will first prove mathematically the equivalence between these two lattices, which is of fundamental interest to further our study of 2D lattice models, and then demonstrate the construction of CT lattice in real photonic and electronic materials, which has significant implications to advance the field of materials discovery for Kagome physics.

Kagome lattice is one of the most interesting lattices mainly because it exhibits two exotic quantum phenomena. First, spin frustration in a Kagome lattice with  $d$ -electrons leads to quantum-spin-liquid (QSL) phase [2]. Secondly, the Kagome band, arising from a Kagome lattice with single-orbital hopping, consists of two Dirac bands and one flat band [1]; the former, as in graphene [3,4], supports massless Dirac Fermions and integer quantum Hall effects [5]; the latter accommodates strongly-correlated topological states such as fractional quantum Hall effect [6-8]. Unfortunately, real materials having a Kagome lattice are very difficult to find. So far, only a handful materials have been identified to support QSL phase. In fact, the field of QSL has been staggering for a while because Herbertsmithite was the only promising materials candidate for QSL [9], until recent discovery of several other candidates, such as Zn-Barlowite [10,11] and YbMgGaO<sub>4</sub> (with a triangular lattice) [12]. We have seen that each spin lattice model plays an important role in advancing

the field, to provide a blueprint to guide the exploration and discovery of realistic materials with desired magnetic properties. On the other hand, a number of 2D materials possessing the geometry of Kagome lattice has been theoretically studied to realize Kagome bands [13-16]. However, to date experimental confirmation of Kagome bands has only been achieved in artificial photonic lattices [17], but remains allusive for real electronic materials. In this regard, our discovery of another 2D lattice, i.e., the CT lattice to also host Kagome band will significantly expand our search for the alluding flat-band materials.

The Kagome lattice is featured with the corner-sharing equilateral triangles, subject to the highest wallpaper symmetry group,  $P6mm$ . In contrast, the CT lattice we discover here has a lower wallpaper symmetry (plane group  $P3_1m$ ). Its geometry can be mapped onto a triangle tiling by filling the triangles with different edges using distinct colors [FIG. 1(d)], which is the reason we term it as CT lattice. Geometrically, this pattern can be labeled as “121213”, belonging to one class of the popular wallpaper tiling patterns made by coloring triangles (See FIG. S1 for nomenclature of triangle tiling [18]). Physically, it means that one modifies a triangular lattice by selectively blocking some nearest-neighbor (NN) hoppings in a  $\sqrt{3}\times\sqrt{3}$  supercell of a triangular lattice [see FIG. 2(b) and the discussion below]. Below we first prove that the CT lattice is equivalent to the renowned Kagome lattice mathematically by a unitary transformation and line graph construction [19-21].

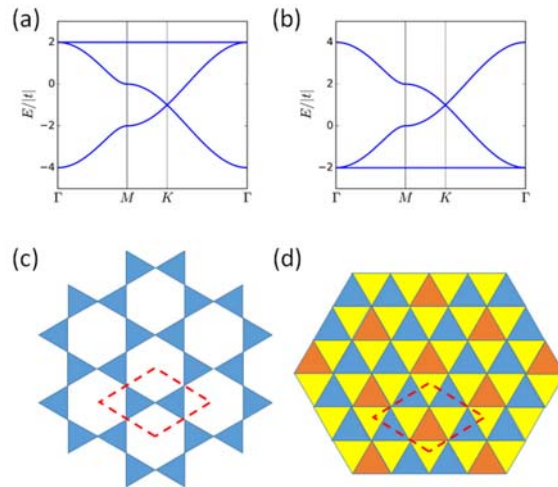

**FIG. 1** Kagome bands along high-symmetry k paths, with (a) flat band on top and (b) flat band at bottom. The location of the flat band depends on the sign of hopping integral. (c) The Kagome lattice. (d) The CT lattice. The dashed red rhombus in (c) and (d) denotes the three-site unit cell.

We begin with the simplest triangular lattice of single-orbital hopping (the one has mirror symmetry with respect to the lattice plane, such as s,  $p_z$  or  $d_z^2$ ). In this minimal model, each unit cell only contains one orbital and the TB Hamiltonian in second quantization form reads

$$H = \sum_{\langle i,j \rangle} t_{ij} c_i^\dagger c_j + h.c., \quad (1)$$

where  $c_i^\dagger$  and  $c_j$  are the electron creation and annihilation operator at site  $i$  and  $j$  respectively with  $t_{ij}$  being the hopping integral. The summation runs only over all the NN sites. The triangular lattice can be patterned by altering the hoppings, which in turn forms interesting electronic bands. For example, in a previously studied dice or  $\mathcal{T}_3$  lattice [22], a patterned removal of one-third of NN hoppings leads to emergence of localized electronic wave functions and hence flat bands. In fact, the Kagome lattice shown in FIG. 1(c) can be realized by blocking the hoppings around one lattice site in a  $2 \times 2$  supercell of triangular lattice, as illustrated in FIG. 2(a). In analogy, here we propose another patterning scheme by blocking the hoppings around the center of a triangle in a  $\sqrt{3} \times \sqrt{3}$  supercell of a triangular lattice, as illustrated in FIG. 2(b). This results in the CT lattice, which physically can be realized by introducing a 2D periodic potential to make  $t_2=0$  [FIG. 2(b)]. It can be shown that the NN hoppings in the CT lattice in FIG. 2(b) can be mapped to a trichromatic triangle tiling in FIG. 1(d) if one colors the triangles according to the hoppings along edges (bonds): blue for triangles with three unperturbed bonds ( $t_1$ ), orange for triangles with three removed bonds ( $t_2=0$ ), and yellow for the triangles with two  $t_1$  and one  $t_2$  bonds.

One can prove that the effective TB Hamiltonian associated with the new CT lattice is equivalent to that of the conventional Kagome lattice. The three-band TB

Hamiltonian of conventional Kagome lattice can be expressed in the  $k$ -space by a traceless matrix [1,6]

$$H^K(\vec{k}) = \begin{bmatrix} 0 & 2t_1 \cos(\vec{k} \cdot \vec{v}_3 / 2) & 2t_1 \cos(\vec{k} \cdot \vec{v}_1 / 2) \\ 2t_1 \cos(\vec{k} \cdot \vec{v}_3 / 2) & 0 & 2t_1 \cos(\vec{k} \cdot \vec{v}_2 / 2) \\ 2t_1 \cos(\vec{k} \cdot \vec{v}_1 / 2) & 2t_1 \cos(\vec{k} \cdot \vec{v}_2 / 2) & 0 \end{bmatrix}, \quad (2)$$

here  $\vec{v}_3 = -(\vec{v}_1 + \vec{v}_2)$  is introduced for convenience. Diagonalization of this Hamiltonian gives rise to the Kagome bands, which can be expressed as

$$E_0 = -2t_1; E_{\pm}(\vec{k}) = -t_1 \pm t_1 \sqrt{8 \cos(\vec{k} \cdot \vec{v}_1 / 2) \cos(\vec{k} \cdot \vec{v}_2 / 2) \cos(\vec{k} \cdot \vec{v}_3 / 2) + 1}. \quad (3)$$

Correspondingly, the TB Hamiltonian of CT lattice can also be constructed in  $k$ -space as

$$H^{CT}(\vec{k}) = \begin{bmatrix} 0 & t_1 [e^{i\vec{k} \cdot \frac{\vec{v}_1 - \vec{v}_3}{3}} + e^{i\vec{k} \cdot \frac{\vec{v}_3 - \vec{v}_2}{3}}] & t_1 [e^{-i\vec{k} \cdot \frac{\vec{v}_2 - \vec{v}_1}{3}} + e^{-i\vec{k} \cdot \frac{\vec{v}_1 - \vec{v}_3}{3}}] \\ t_1 [e^{-i\vec{k} \cdot \frac{\vec{v}_2 - \vec{v}_1}{3}} + e^{-i\vec{k} \cdot \frac{\vec{v}_3 - \vec{v}_2}{3}}] & 0 & t_1 [e^{i\vec{k} \cdot \frac{\vec{v}_2 - \vec{v}_1}{3}} + e^{i\vec{k} \cdot \frac{\vec{v}_1 - \vec{v}_3}{3}}] \\ t_1 [e^{i\vec{k} \cdot \frac{\vec{v}_3 - \vec{v}_2}{3}} + e^{i\vec{k} \cdot \frac{\vec{v}_2 - \vec{v}_1}{3}}] & t_1 [e^{-i\vec{k} \cdot \frac{\vec{v}_2 - \vec{v}_1}{3}} + e^{-i\vec{k} \cdot \frac{\vec{v}_1 - \vec{v}_3}{3}}] & 0 \end{bmatrix}. \quad (4)$$


A band structure identical to Eq. (3) can be obtained by diagonalizing Eq. (4). In fact, one can demonstrate that Eq. (4) is unitary transformable to (2) by using the following simple transformation matrix

$$U = \begin{bmatrix} e^{-i\vec{k} \cdot \vec{v}_1 / 6} & 0 & 0 \\ 0 & e^{-i\vec{k} \cdot \vec{v}_2 / 6} & 0 \\ 0 & 0 & e^{-i\vec{k} \cdot \vec{v}_3 / 6} \end{bmatrix}. \quad (5)$$

Thus, the CT lattice is inherently equivalent to the Kagome lattice. The physical connection between the  $U$  matrix elements and the movement of lattice sites is elucidated in FIG. S2 [18]. One can further generalize our theory to a series of distorted lattices in between the Kagome and CT lattice. In Eq. (5) we derived a transformation matrix with the diagonal elements containing a phase factor  $\phi_l = \exp(-i\vec{k} \cdot \vec{v}_l / 6)$  ( $l=1, 2, 3$ ). This means that the unitary transformation represents a geometric operation between the Kagome and CT lattice by rotating the two triangles

inside the three-site unit cell about their center by an angle of  $\theta=30^\circ$ . In such a rotation operation (note that it is not a pure rotation because the size/shape of triangle also has to change slightly to fit the lattice), each site  $l$  in the Kagome lattice moves by a vector of  $-\vec{v}_l/6$  (which is the origin of the phase factor). Then, one can immediately see that another unitary matrix with a smaller rotation angle ( $0 < \theta < 30^\circ$ ) will also produce the same Kagome band, except now  $\phi_l = \exp(-i\sqrt{3} \tan \theta \vec{k} \cdot \vec{v}_l / 6)$  (FIG. S2). In principle, Eq. (5) can be extended to a more generic mathematic form by replacing the  $\vec{v}_l$  ( $l=1, 2, 3$ ) vectors with  $\vec{r}_l$  which represents displacement of  $l$ -th lattice site (within the unit cell) from the original position of the Kagome lattice. However, the hypothesis that all hopping integrals are equal is only physically plausible if all NN bonds have the same norm. This constraint then limits the possible deformations of the lattice to the CT-like pattern. This is very interesting because usually lattice distortion will inevitably modify band structure. In contrast we prove mathematically that for the types of distortion here the band stays intact as they represent a unitary lattice transformation. In fact, two previous calculations have indeed shown the Kagome bands from such distorted lattices [15,16].

Furthermore, an elegant mathematical theory of line graph has been shown by Mielke that Kagome lattice is in fact a line graph of hexagonal lattice which defines the condition for the existence of flat band. Correspondingly, we found that the CT lattice as well as those distorted lattices in between the Kagome and CT lattice are also line graphs of hexagonal lattice as they should be, albeit with a different construction [illustrated in Fig. 2(c) and (d)] [18]. Consequently, all the exotic topological characteristics presented in Kagome bands can also be achieved in the CT lattice. If one includes a non-vanishing  $t_2$  and spin-orbit coupling **or many-body interaction** [23] in the CT lattice, it provides an extra degree of freedom to tune the band as shown in Fig. 2(e) and (f) [18].

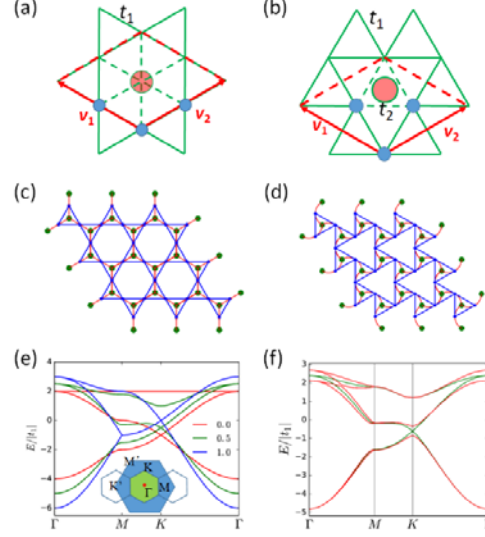


**FIG. 2** Illustration of (a) Kagome lattice and (b) CT lattice formed by patterning a triangular lattice. The red arrows denote the patterned unit cell basis vectors. (c) Line graph of a Kagome lattice (blue) constructed from a parent hexagonal graph (lattice, green dots) with straight edges (red). (d) Line graph of a CT lattice (blue) constructed from a parent hexagonal graph (green dots) with curved edges (red). (e) Band variation in a  $\sqrt{3} \times \sqrt{3}$  supercell of triangular lattice with one third of the NN hoppings tuned from  $t_2=0$  to  $t_2=t_1$  (bands corresponding to three typical  $t_2/t_1$  ratios, namely, 0, 0.5 and 1, are presented). Note that for the  $t_2=0$  case the three bands are just folded from a single band of perfect triangular lattice. The inset shows the first Brillouin zone of the supercell (green) folded from that of the unit cell of triangular lattice (blue). (f) The Kagome bands realized in the CT lattice for  $t_2 = t_1/4$ , without (green) and with (red) SOC ( $\lambda = 0.01t_1$ ).

All the discussions above in electronic systems are readily transferrable to describe the dynamics of photonic systems [18,24]. Considering that there is a significant body of literature implementing flat band models in dielectric waveguide array [17], we first discuss how to realize a photonic CT lattice. We start by constructing a 2D photonic triangular lattice using silica (the refractive index  $n_0 = 1.45$ ) as the bulk dielectric medium. The cylindrical waveguides distributed on the



triangle lattice sites can be technically realized by the femtosecond direct-writing method [25]. Each waveguide supports one single mode, which is placed at a distance of 15  $\mu\text{m}$  from each other to only allow for NN hopping, as determined by the interaction strength between adjacent waveguides. We set  $\Delta n = 2.17 \times 10^{-3}$ , the diameter of waveguide is 4  $\mu\text{m}$ , and the wavelength is 633 nm. Band structure was calculated using mode analysis in full-wave numerical simulation software COMSOL 52a based on finite element method [26,27].

By removing a waveguide to block the hopping around it, one obtains the photonic Kagome lattice [FIG. 3(a)]. The spacing is tuned to make NNN hopping negligible, so that an ideal photonic Kagome band is obtained [FIG. 3(c)]. Each band is degenerate because of the high symmetry of waveguide. To create a photonic CT lattice, the hopping term  $t_2$  can be blocked by introducing air holes [28] which decrease the overlap of evanescent wave [FIG. 3(b)]. When the air hole enlarges, the hopping term  $t_2$  decreases. However, if it is too large, the symmetry of the field distribution will be broken and band will split (FIG. S3 [18]). Therefore, the air hole has to be delicately designed to match field distribution so that  $t_2$  can be reduced as much as possible while preserving the symmetry. After some attempts, we found a desired shape and size of air hole [FIG. 3(b)] to achieve the ideal Kagome bands with a nearly flat band in the photonic CT lattice [FIG. 3(d)]. We note that the air hole can be replaced by a high refractive index waveguide [18], and hopping can be more delicately tuned by designing a chain of additional waveguides [18,29].

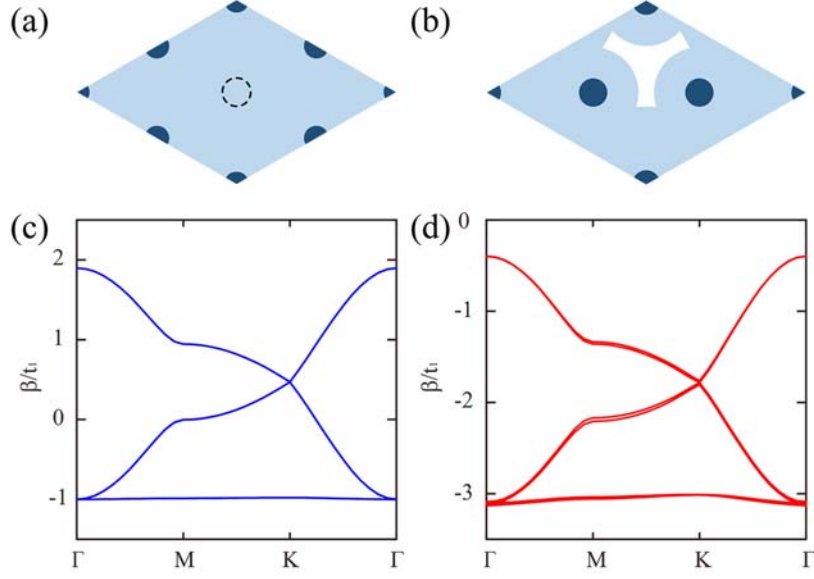

**FIG. 3** Unit cell of photonic (a) Kagome and (b) CT lattice formed by weakly coupled waveguide arrays (dark blue circles). The silica medium is colored light blue, and the air holes in the CT lattice are colored white. (c) and (d) Band structure corresponding to the photonic Kagome and CT lattice, respectively.

We expect that the photonic CT lattice we proposed above can be readily achieved experimentally in comparison with the photonic Kagome lattice [30] to confirm our prediction. On the other hand, realization of electronic materials of CT lattice is more challenging. Nevertheless, below we demonstrate such a possibility based on an approach of patterning the nearly-free 2D electron gas (2DEG). It has been theoretically proposed [31] that patterning 2DEG with a uniform triangular potential lattice can produce massless Dirac Fermions. If one further tunes the triangular potential lattice based on the hopping texture of CT lattice, in principle Kagome bands should be present. Experimentally, scanning tunneling microscopy (STM) affords delicate manipulations of atoms or molecules on clean crystal surface, making patterning of surface electron gas practical [32]. In the search of nearly-free 2DEG in realistic materials, we pay attention to electrified, a class of materials featured by the concept of “anionic excess electrons”. In particular, we select


monolayer  $\text{Ca}_2\text{N}$ , an experimentally already realized layered electride [33-36], as a candidate to materialize our patterning scheme.

Previous experimental and theoretical studies have shown the feasibility of Au to form a long-range ordered monolayer on different compound surfaces, which potentially realizes exotic electronic states [37-39]. In  $\text{Ca}_2\text{N}$  the two layers of inter-penetrating Ca triangular lattice form a honeycomb lattice, and according to our first principles calculations [40-43] (Computational details can be found in [18]), the energetically favorable site for Au adsorption is the hollow site of the hexagons (on top of N atoms), as shown in FIG. 4(a).

In FIG. 4(b) we plot the 2D contour of charge density, before and after the deposition of an Au monolayer. One can clearly see the top triangular lattice of Ca is patterned when the Au lattice is introduced, exhibiting a texture resembling our proposed CT lattice. The band structure of the Au patterned  $\text{Ca}_2\text{N}$  system in FIG. 4(c) displays a Dirac point at the first Brillouin zone corner, which we will show later is indeed a set of Kagome bands originated from the CT lattice of Ca-s orbitals. The orbital composition of each band is denoted by the size of the circles. Due to the unique electride nature of  $\text{Ca}_2\text{N}$ , the bands near the Fermi level are occupied by electrons that are loosely bound to Ca ions, while the projected bands only count the charge in spheres around the ions but cannot fully capture the delocalized charge spreading out in real space. Therefore, Fig. 4(c) can only be viewed as a qualitative assignment of electronic bands into several mainfolds according to the chemical species. However, by doing an electron counting, one can easily confirm that all N- $p$ -orbital dominated bands are mainly distributed in an energy window  $\sim 2$  eV below the Fermi level. On the other hand, it is clearly seen that the Au- $5d6s$  bands are buried deep below the Fermi level. Considering the electronic configuration of Au atom ( $5d^{10}6s^1$ ), one can conclude that each Au atom accommodates one extra electron from the underneath  $\text{Ca}_2\text{N}$  layer. Bader charge analysis confirms that  $\sim 0.97$  electron is transferred from the  $\text{Ca}_2\text{N}$  monolayer to each Au atom, forming a triangular lattice of  $\text{Au}^-$  anions. The negative charge of  $\text{Au}^-$  anions is beneficial for its uniform distribution

because the Coulomb repulsion can help prevent them from clustering on the  $\text{Ca}_2\text{N}$  surface similar to other surface overlayers [39].

Thus, the patterned system holds a nominal chemical formula  $[\text{Ca}_2\text{N}]^+_3[\text{e}^-]_2[\text{Au}^-]$ . The two excess anionic electrons with the smallest binding energy fill the highest occupied band, making the physics near the Fermi energy dominated by the Kagome-like bands. They are separated from other occupied bands in energy, enabling us to study the low-energy physics by projecting them onto a subspace spanned by the Ca-s orbitals. Here we use the maximally localized Wannier Functions (MLWFs) [44] as the basis instead of atomic s-orbitals of Ca so as to include possible hybridization with other electronic states. FIG. 4(d) shows that the bands formed by the MLWF basis well reproduce the salient features of DFT bands, indicating the existence of two sets of Kagome-bands arising from the two layers of patterned Ca-s triangular lattice, one on top right below the Au atoms and the other at the bottom farther away from Au [18].

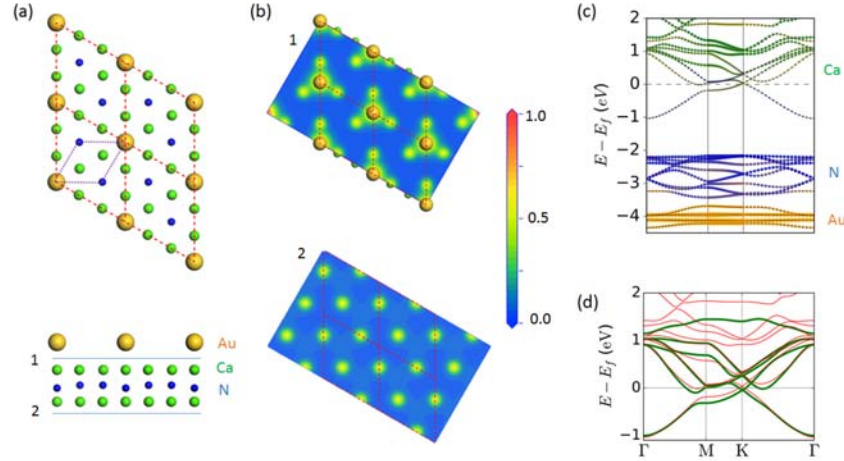

**FIG. 4** (a) Top and side view of a triangular Au lattice deposited on the surface of  $\text{Ca}_2\text{N}$  monolayer. The blue and red rhombus denotes the unit cell and  $\sqrt{3} \times \sqrt{3}$  supercell of the pristine  $\text{Ca}_2\text{N}$  monolayer, respectively. (b) Charge density distribution in the plane 1 shown in the side view of (a), without and with the Au lattice patterning. (c) Electronic band structure of the Au-patterned  $\text{Ca}_2\text{N}$  monolayer, with band

composition displayed in different colors. (d) The DFT band structure near the Fermi level (red) and the interpolated bands from MLWFs with Ca-s characteristics (green).

Considering the relativistic effect of Au, SOC may have a pronounced effect on the Ca-s dominated Kagome bands. In FIG. S4(a) [18], we plot the DFT band structure including SOC, where a gap of 106 meV at K is observed. However, a small electron pocket along the  $\Gamma$ -M path makes the bands not globally but only gapped at certain k-points as in the topological electride  $\text{Y}_2\text{C}$  [45]. We find that by applying an in-plane biaxial strain, the electron pocket shrinks and finally disappears. The band evolution under a tensile strain is traced in FIG. S4(b) [18]. The global gap emerges in a slightly strained structure ( $<2\%$ ) and increases up to 40 meV as the strain is further raised to 8% [18]. We note that in-plane strain is a practical technique to tune the electronic structure and properties of 2D layered materials [46], and more importantly, lattice engineering of  $\text{Ca}_2\text{N}$  has already been achieved in a recent experiment [47]. We further confirm the nontrivial band topology of the Au-decorated  $\text{Ca}_2\text{N}$  from first principles calculations [48] and TB modeling [49] of the CT lattice with SOC [18].

Based on the above analysis, we summarize the roles of the Au triangular lattice in forming the topologically nontrivial Kagome-like bands in the Au- $\text{Ca}_2\text{N}$  system. (1) It provides a triangular periodic potential which patterns the nearly-free 2DEG of the  $\text{Ca}_2\text{N}$  surface to create a CT lattice as our theoretical model predicts. (2) The stoichiometry ( $\text{Ca}_6\text{N}_3\text{Au}$ ) and the electronic configuration of Au ( $d^{10}s^1$ ) tune the Fermi level right at the Dirac points of the Kagome-like bands. (3) The Au overlayer introduces strong SOC that opens a relatively large nontrivial band gap at the Dirac points. We have also tried the patterning procedure by using Ag or Cu instead of Au, which leads to a similar effect but with weaker SOC. The discovery of more and more new electride materials holding anionic electrons [50,51], especially the experimentally synthesized layered electrides such as  $\text{Y}_2\text{C}$  [45,52], provides a unique material platform to achieve the novel patterning procedure. The emergent 2D molecular crystals and metal-organic frameworks can serve as another category of

candidates to materialize the proposed CT lattice model.

In summary, we have rigorously proved the equivalency of a CT lattice to the conventional Kagome lattice. Furthermore, we demonstrate the possibility to realize the CT lattice in both photonic and electronic systems. Well-developed femtosecond direct-writing method enables fabricating artificial photonic lattice with designer geometry and can be implemented to realize the photonic CT lattice. We suggest that layered electrides might provide a useful materials platform for patterning 2DEG, in order to realize a range of 2D lattices, including the new CT lattice we propose here. It is worth mentioning that the idea of CT lattice may be generalized to Kagome magnetic [53] or cold-atom [54] systems.

### **Acknowledgements**

Work at Tsinghua was supported by the Tsinghua University Initiative Scientific Research Program and the NSFC under Grant No. 11774196. Work at Utah was supported by grants from US-DOE (Grant No. DEFG02-04ER46148). Shunhong Zhang is supported by the National Postdoctoral Program for Innovative Talents of China (BX201600091) and the Funding from China Postdoctoral Science Foundation (2017M610858). Meng Kang, Shunping Zhang and Hongxing Xu thank the financial support from the National Key Basic Research Program (Grant No. 2015CB932400) and the National Natural Science Foundation of China (Grant No. 11674256). Meng Kang acknowledges the Wuhan University graduate student oversea exchange program. Numerical simulations of photonic lattice were performed on supercomputers at Wuhan University. First principles calculations were performed on the Tianhe-II supercomputer provided by The National Supercomputer Center in Guangzhou, China. Paratera tech Co. Ltd. is also sincerely acknowledged for the continuous technical support on high-performance computation.

To whom correspondence may be addressed: H. Xu ([hxxu@whu.edu.cn](mailto:hxxu@whu.edu.cn)), Z. L. ([zheng-liu@tsinghua.edu.cn](mailto:zheng-liu@tsinghua.edu.cn)), and F. L. ([fliu@eng.utah.edu](mailto:fliu@eng.utah.edu)).

### **References**

- [1] K. Ohgushi, S. Murakami, and N. Nagaosa, Phys. Rev. B **62**, R6065 (2000).
- [2] L. Balents, Nature **464**, 199 (2010).
- [3] Y. Zhang, Y.-W. Tan, H. L. Stormer, and P. Kim, Nature **438**, 201 (2005).
- [4] C. L. Kane and E. J. Mele, Phys. Rev. Lett. **95**, 226801 (2005).
- [5] H. M. Guo and M. Franz, Phys. Rev. B **80**, 113102 (2009).
- [6] Z. Liu, F. Liu, and Y.-S. Wu, Chin. Phys. B **23**, 077308 (2014).
- [7] Z. Liu, Z.-F. Wang, J.-W. Mei, Y.-S. Wu, and F. Liu, Phys. Rev. Lett. **110**, 106804 (2013).
- [8] E. Tang, J.-W. Mei, and X.-G. Wen, Phys. Rev. Lett. **106**, 236802 (2011).
- [9] M. R. Norman, Rev. Mod. Phys. **88**, 041002 (2016).
- [10] Z. Liu, X. Zou, J.-W. Mei, and F. Liu, Phys. Rev. B **92**, 220102 (2015).
- [11] Z. Feng, Z. Li, X. Meng, W. Yi, Y. Wei, J. Zhang, Y.-c. Wang, W. Jiang, Z. Liu, S. Li, F. Liu, J. Luo, S. Li, G.-q. Zheng, Z. Meng, J.-W. Mei, and Y. Shi, Chin. Phys. Lett. **34**, 077502 (2017).
- [12] Y. Shen, Y.-D. Li, H. Wo, Y. Li, S. Shen, B. Pan, Q. Wang, H. C. Walker, P. Steffens, M. Boehm, Y. Hao, D. L. Quintero-Castro, L. W. Harriger, M. D. Frontzek, L. Hao, S. Meng, Q. Zhang, G. Chen, and J. Zhao, Nature **540**, 559 (2016).
- [13] Z. F. Wang, N. Su, and F. Liu, Nano Lett. **13**, 2842 (2013).
- [14] B. Zhao, J. Zhang, W. Feng, Y. Yao, and Z. Yang, Phys. Rev. B **90**, 201403 (2014).
- [15] X. Li, J. Zhou, Q. Wang, Y. Kawazoe, and P. Jena, J. Phys. Chem. Lett. **4**, 259 (2013).
- [16] S. Kim, W. H. Han, I.-H. Lee, and K. J. Chang, Sci. Rep. **7**, 7279 (2017).
- [17] D. Leykam, A. Andreanov, and S. Flach, Adv. Phys. X **3**, 1473052 (2018).
- [18] See Supplementary Materials for details.
- [19] A. Mielke, J. Phys. A **24**, 3311 (1991).
- [20] A. Mielke, J. Phys. A **24**, L73 (1991).
- [21] A. Mielke, J. Phys. A **25**, 4335 (1992).
- [22] B. Sutherland, Phys. Rev. B **34**, 5208 (1986).
- [23] W. Zhu, S.-S. Gong, T.-S. Zeng, L. Fu, and D. N. Sheng, Phys. Rev. Lett. **117**, 096402 (2016).
- [24] T. Ozawa, H. M. Price, A. Amo, N. Goldman, M. Hafezi, L. Lu, M. Rechtsman, D. Schuster, J. Simon, O. Zilberberg, and I. Carusotto, in *ArXiv e-prints* (2018).
- [25] S. Alexander and N. Stefan, J. Phys. B **43**, 163001 (2010).
- [26] J.-M. Jin, *The finite element method in electromagnetics* (John Wiley & Sons, 2015).
- [27] I. Andonegui and A. J. Garcia-Adeva, Opt. Express **21**, 4072 (2013).
- [28] X. Ren, L. Feng, Z. Lin, and J. Feng, Opt. Lett. **38**, 1416 (2013).
- [29] G. G. Pyrialakos, N. S. Nye, N. V. Kantartzis, and D. N. Christodoulides, Phys. Rev. Lett. **119**, 113901 (2017).
- [30] Y. Zong, S. Xia, L. Tang, D. Song, Y. Hu, Y. Pei, J. Su, Y. Li, and Z. Chen, Opt. Express **24**, 8877 (2016).
- [31] C.-H. Park and S. G. Louie, Nano Lett. **9**, 1793 (2009).
- [32] M. R. Slot, T. S. Gardenier, P. H. Jacobse, G. C. P. van Miert, S. N. Kempkes, S. J. M. Zevenhuizen, C. M. Smith, D. Vanmaekelbergh, and I. Swart, Nat. Phys. **13**, 672 (2017).
- [33] K. Lee, S. W. Kim, Y. Toda, S. Matsuishi, and H. Hosono, Nature **494**, 336 (2013).
- [34] D. L. Druffel, K. L. Kuntz, A. H. Woome, F. M. Alcorn, J. Hu, C. L. Donley, and S. C. Warren, J. Am. Chem. Soc. **138**, 16089 (2016).
- [35] J. S. Oh, C.-J. Kang, Y. J. Kim, S. Sinn, M. Han, Y. J. Chang, B.-G. Park, S. W. Kim, B. I. Min, H.-D. Kim, and T. W. Noh, J. Am. Chem. Soc. **138**, 2496 (2016).

- [36] S. Zhao, Z. Li, and J. Yang, *J. Am. Chem. Soc.* **136**, 13313 (2014).
- [37] Z. F. Wang, K.-H. Jin, and F. Liu, *Nat. Commun.* **7**, 12746 (2016).
- [38] F.-C. Chuang, C.-H. Hsu, H.-L. Chou, C. P. Crisostomo, Z.-Q. Huang, S.-Y. Wu, C.-C. Kuo, W.-C. V. Yeh, H. Lin, and A. Bansil, *Phys. Rev. B* **93**, 035429 (2016).
- [39] M. Zhou, W. Ming, Z. Liu, Z. Wang, P. Li, and F. Liu, *Proc. Natl. Acad. Sci.* **111**, 14378 (2014).
- [40] H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).
- [41] P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994).
- [42] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- [43] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [44] N. Marzari, A. A. Mostofi, J. R. Yates, I. Souza, and D. Vanderbilt, *Rev. Mod. Phys.* **84**, 1419 (2012).
- [45] H. Huang, K.-H. Jin, S. Zhang, and F. Liu, *Nano Lett.* **18**, 1972 (2018).
- [46] C. Si, Z. Sun, and F. Liu, *Nanoscale* **8**, 3207 (2016).
- [47] S. Kim, S. Song, J. Park, H. S. Yu, S. Cho, D. Kim, J. Baik, D.-H. Choe, K. J. Chang, Y. H. Lee, S. W. Kim, and H. Yang, *Nano Lett.* **17**, 3363 (2017).
- [48] Y. Yao, L. Kleinman, A. H. MacDonald, J. Sinova, T. Jungwirth, D.-s. Wang, E. Wang, and Q. Niu, *Phys. Rev. Lett.* **92**, 037204 (2004).
- [49] Y. Yang, Z. Xu, L. Sheng, B. Wang, D. Y. Xing, and D. N. Sheng, *Phys. Rev. Lett.* **107**, 066602 (2011).
- [50] Y. Zhang, H. Wang, Y. Wang, L. Zhang, and Y. Ma, *Phys. Rev. X* **7**, 011017 (2017).
- [51] W. Ming, M. Yoon, M.-H. Du, K. Lee, and S. W. Kim, *J. Am. Chem. Soc.* **138**, 15336 (2016).
- [52] K. Horiba, R. Yukawa, T. Mitsuhashi, M. Kitamura, T. Inoshita, N. Hamada, S. Otani, N. Ohashi, S. Maki, J.-i. Yamaura, H. Hosono, Y. Murakami, and H. Kumigashira, *Phys. Rev. B* **96**, 045101 (2017).
- [53] R. Chisnell, J. S. Helton, D. E. Freedman, D. K. Singh, R. I. Bewley, D. G. Nocera, and Y. S. Lee, *Phys. Rev. Lett.* **115**, 147201 (2015).
- [54] N. Goldman, I. Satija, P. Nikolic, A. Bermudez, M. A. Martin-Delgado, M. Lewenstein, and I. B. Spielman, *Phys. Rev. Lett.* **105**, 255302 (2010).