



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Low-Photon-Number Optical Switching with a Single Quantum Dot Coupled to a Photonic Crystal Cavity

Ranojoy Bose, Deepak Sridharan, Hyochul Kim, Glenn S. Solomon, and Edo Waks

Phys. Rev. Lett. **108**, 227402 — Published 30 May 2012

DOI: [10.1103/PhysRevLett.108.227402](https://doi.org/10.1103/PhysRevLett.108.227402)

Low photon number optical switching with a single quantum dot coupled to a photonic crystal cavity

Deepak Sridharan,¹ Ranojoy Bose,¹ Hyochul Kim,¹ Glenn S. Solomon,² and Edo Waks^{1,2,*}

*¹Department of Electrical and Computer Engineering, IREAP,
University of Maryland, College Park, Maryland 20742, USA*

*²Joint Quantum Institute, National Institute of Standards and Technology,
and University of Maryland, Gaithersburg, Maryland 20899, USA*

Abstract

We demonstrate fast nonlinear optical switching between two laser pulses with as few as 140 photons of pulse energy by utilizing strong coupling between a single quantum dot (QD) and a photonic crystal cavity. The cavity-QD coupling is modified by a detuned pump pulse, resulting in a modulation of the scattered and transmitted amplitude of a time synchronized probe pulse that is resonant with the QD. The temporal switching response is measured to be as fast as 120 ps, demonstrating the ability to perform optical switching on picosecond timescales.

Nonlinear optical interactions are essential for a broad range of photonics applications. Such interactions enable all-optical switching, which plays a key role in increasing information bandwidth in telecommunications systems and could potentially reduce power consumption in computer processors [1]. Currently, there is also great interest in achieving optical switching at low photon numbers for applications in quantum information processing and quantum networking [2–4]. However, the majority of nonlinear optical processes rely on weak nonlinearities from a large ensemble of atomic systems and thus require high optical energies [5].

One promising method for reducing optical switching energies is to exploit the strong atom-light interactions between a quantum dot (QD) and a photonic crystal cavity. These interactions can enable the strong coupling regime where the cavity and QD mix to form new dressed polariton states, resulting in a modification of both the QD emission spectrum [6] and cavity spectrum [7–11]. In the strong coupling regime the cavity-QD system can exhibit a large nonlinear optical response at low optical powers [12–16]. Controlling these nonlinearities on fast timescales could enable all-optical switching at extremely low energies.

Here we demonstrate that interaction between a single QD and a cavity in the strong coupling regime can be optically modulated on picosecond timescales to enable all-optical switching at extremely low energies. We study the specific example of a photonic crystal defect cavity coupled to an indium arsenide (InAs) QD. The response of the strongly coupled system is modulated by a picosecond pump laser pulse that induces a large nonlinear response, resulting in an observed modification of the transmission and scattering amplitude of a second incident probe pulse. The pump energy required to perform optical switching is measured to be as low as 140 photons. Switching response times as short as 120 ps are also reported, which are ultimately limited by bandwidth constraints imposed on the pump and probe pulses by the cavity-QD coupling strength. We implement this approach in a planar photonic crystal cavity-waveguide structure that is compatible with large scale integration for development of complex devices on-a-chip.

Fig. 1a shows a scanning electron micrograph (SEM) of the device, which is composed of a gallium arsenide (GaAs) photonic crystal cavity coupled to a row defect waveguide. The initial wafer for device fabrication consisted of a 160 nm GaAs membrane with an InAs QD layer grown at the center (with QD density of approximately $10 \mu\text{m}^{-2}$), on a $1 \mu\text{m}$ thick

sacrificial layer of aluminum gallium arsenide ($\text{Al}_{0.78}\text{Ga}_{0.22}\text{As}$). Photonic crystal structures were defined using electron-beam lithography, followed by inductively coupled plasma dry etching and selective wet etching of the sacrificial AlGaAs layer. Details of the device design have been previously reported [11].

The pump and probe pulse are injected via grating couplers [17] into the waveguide. The probe pulse is collected either directly from the cavity (direct cavity scatter) or from the output coupler (transmitted waveguide signal) by spatial filtering. Fig. 1b shows the cavity photoluminescence (PL) spectrum, attained by exciting the cavity with a 780 nm pump laser. The PL exhibits an emission peak for the cavity mode, along with additional emission peaks for several coupled QDs. The QD used for all measurements reported in this letter is labeled in the figure. By fitting the cavity mode to a Lorentzian, we determine the cavity energy decay rate to be $\kappa/2\pi = 29.0 \pm 0.2$ GHz ($Q=11900$) (all error bounds quoted in this paper are based on a 90% confidence bound for the nonlinear regression). The cavity-waveguide coupling rate is determined to be $\kappa_{||}/2\pi = 2.9 \pm 0.1$ GHz by measuring the waveguide transmission at a temperature of 51 K when the QD is well detuned from the cavity mode [11]. The fraction of power coupled to the cavity from the waveguide is given by $1 - (1 - r_0)^2 = 0.36$ where $r_0 = 2\kappa_{||}/\kappa = 0.2$. Thus, the in-plane coupling rate reported here offers a good tradeoff between high cavity Q for strong coupling and efficient cavity excitation through the waveguide. The coupling efficiency of the grating couplers is also measured by observing the Stark shift on the detuned QD as a function of incident pump power, as describe in Ref. [16]. From these measurements we determine the coupling efficiency into the waveguide from the out-of-plane direction to be $\eta = 0.008$. Full details of the measurement of the cavity-waveguide coupling rate and input coupling efficiency for the device used in this work are provided in supplementary material.

Fig. 1c shows the resonant cavity scattering spectrum as a function of temperature when the waveguide is excited by a broadband LED that serves as a white light source. Light is collected directly from the cavity mode and is measured via a grating spectrometer with resolution of $23 \mu\text{eV}$. As the temperature is increased, the QD identified in Fig. 1b red-shifts and becomes resonant with the cavity. As the QD is tuned across the cavity mode the scattering spectrum exhibits an anti-crossing due strong coupling between the two systems [7–10]. Fig. 1d shows the measured scattering spectrum taken at 39 K when the QD is resonant with the cavity, which exhibits a doublet representing the two polariton modes. The solid line in

Fig. 1d is a theoretical fit assuming a Jaynes-Cummings interaction model [11, 18]. From the theoretical fit we determine the cavity-QD coupling strength to be $g/2\pi = 13.4 \pm 0.2$ GHz, and the QD linewidth to be $\gamma_{qd}/2\pi = 5.8 \pm 0.5$ GHz. The fact that $g > \kappa/4$ ensures that the system is operating in the strong coupling regime.

The nonlinearity of the device is first studied under continuous wave excitation by injecting a second pump field from a narrowband tunable external cavity diode into the input grating along with the broadband LED. The pump field is detuned from the cavity resonance by 35 GHz. Fig. 2 plots the resulting scattering spectrum, taken when the QD is resonant with the cavity, for both 0.1 μ W (panel a) and 14.5 μ W (panel b) pump power, measured after the focusing lens. The dashed red line shows the scattering spectrum when only the pump is present. At 14.5 μ W of pump power indirect emission from the cavity polaritons is observed due to inelastic scattering of the pump laser, an effect that has been previously reported in a number of works [19–22]. The blue curve shows the elastic scattering spectrum of the broadband LED when injected with the pump, where we have subtracted the inelastic scattering contribution. At 0.1 μ W the pump field is weak and does not affect the cavity scatter, which exhibits a dip at the bare QD resonant frequency. As the pump power is increased to 14.5 μ W, the position of the dip induced by the QD is red shifted due to the optical Stark effect [16, 23–25]. In addition, the contrast of the dip is partially reduced due to saturation of the QD by the strong pump field. These effects combine to enable the pump field to optically modify the cavity scatter and waveguide transmission, providing the possibility for all-optical switching. We note that the contrast of the dip in Figure 2 is reduced as compared to Figure 1d. This reduction in contrast occurs because the sample is excited with a large LED power in order to minimize the relative contribution of inelastic photons from the pump. The large LED power partially saturates the QD resulting in a degraded contrast. In addition, it is also noted that in panel b the dip in the inelastic scattering contribution does not line up with the dip of the elastic scattering spectrum. This behavior is fully expected and is consistent with the predicted behavior of a two-level system strongly coupled to a cavity. Additional discussion on this point is included in the supplementary material.

The measured elastic scattering spectra can be compared to theoretical predictions based on numerical solution of the master equation [26]. The details for these calculations are provided in the supplement. All calculations are performed using an open source quantum

optics toolbox [27]. The calculated spectra are plotted in Fig. 2c for several different values of the pump power, defined as the power incident on the grating coupler. At low powers, the spectrum exhibits a doublet feature consistent with the measured spectrum shown in Fig. 2a. As the pump power is increased, the elastic scattering spectrum becomes asymmetric due to Stark shift of the QD, consistent the measured spectrum in Fig. 2b. In addition, the contrast of the dip is reduced due to QD saturation. At even higher powers the linewidth of the lower polariton, which becomes increasingly QD-like with larger Stark shift, experiences power induced broadening [16, 22] that may further serve to modify the scattering spectrum by reducing the atomic cooperativity [8].

In order to dynamically modify the cavity spectrum on fast timescales the sample is excited with a pump and probe laser pulse generated from two synchronized Ti:Sapphire lasers. The pump laser has a pulse duration of 140 ps. The probe laser, whose initial pulse duration is 5ps, is filtered down to a bandwidth of 0.02 nm (7 GHz) using a Fabry-Perot cavity, resulting in a 45 ps exponential pulse. The bandwidth of the probe laser is chosen to be approximately one quarter of the spectral width of the dip induced by the QD in the cavity scattering spectrum, which is equal to $2g$ in the strong coupling regime. The pump pulse is synchronized to the probe by a piezo feedback in the laser cavity, and the delay between the two pulse is controlled electronically by a phase-locked loop in the synchronization circuit. The wavelength of the pump and probe fields are selected such that when the QD is resonant with the cavity mode, the probe is resonant with the bare QD frequency while the pump wavelength is resonant with the lower polariton. The average pump power is set to $1 \mu\text{W}$, while the probe power is set to 40 nW to ensure that it is in the linear response regime of the cavity-QD system. Temperature tuning is used to tune the QD through the probe field center frequency. The pump and probe fields are collected either directly from the cavity or from the output coupler, and are separated by a grating spectrometer.

Fig. 3a shows the probe scattering intensity collected directly from the cavity as a function of temperature when the delay between pump and probe is set to either 0 ns (simultaneous excitation) or 4 ns. The 4 ns delay is chosen because it is much larger than all the decay times of the cavity-QD system. In this case, the pulses excite the cavity at different times and therefore do not interact. The probe scattering is suppressed when resonant with the QD (42 K) due to cavity-QD interactions. We note that the temperature where resonance is achieved is slightly different than that of Fig. 1c because of a gradual red-shift of the

cavity resonance frequency observed over the course of the measurement process. When the pump and probe arrive simultaneously at the cavity (zero ns delay), a significant increase of the cavity scatter is observed at the same temperature. The switching contrast in the scattering spectrum, defined as $\eta_s = (I_{\max}^S - I_{\min}^T)/I_{\max}^S$ where I_{\max}^S and I_{\min}^T are the probe scattering intensities at zero and 4 ns delays respectively taken at 42 K sample temperature, is calculated to be 0.44.

In Fig. 3a the scattering spectrum is also plotted for the case where only a control pulse is injected (blue diamonds). In this case there is still some optical energy at the QD frequency, which is mostly dominated by the spectral overlap between the signal and control. In contrast to the continuous wave measurements shown in Fig. 2b, inelastic scattering of pump photons contributes very little in the pulsed measurements. We attribute this difference to the fact that the measured inelastic scattering energy is proportional to the average control power while Stark shift and saturation are proportional to peak control power. In pulsed operation, we can achieve a high peak power with a relatively low average power, which significantly reduces the inelastic scattering contribution.

In addition to cavity scattering intensity, the waveguide transmission intensity can also be measured by collecting the probe field from the output coupler. The results of this measurement are shown in Fig. 3b. At the output coupler the spectrum exhibits the conjugate effect. At 0 ns delay the transmission exhibits an anti-resonance, while at 4 ns a double anti-resonance can be observed. This double anti-resonance is consistent with the continuous wave measurement of the waveguide transmission spectrum, as described in the supplementary material. The switching contrast in transmission is calculated to be $\eta_t = (I_{\max}^T - I_{\min}^S)/I_{\max}^T = 0.13$, where I_{\max}^T and I_{\min}^S are the probe transmitted intensities at zero and 4 ns delays respectively taken at 43 K sample temperature, which is significantly lower than η_s . This reduction results from the fact that η_t is limited by the bare cavity transmission contrast denoted $\Delta T = 1 - (1 - r_0)^2$, where $r_0 = 2\kappa_{\parallel}/\kappa$. Using the values of $\kappa_{\parallel}/2\pi = 2.9$ GHz and $\kappa/2\pi = 29$ GHz measured under continuous wave excitation we determine that $\Delta T = 0.36$. In the supplementary material it is shown that $\eta_t \leq \Delta T$ with equality attained in the limit $C = 2g^2/\gamma_{qd}\kappa \gg 1$, where C is the atomic cooperativity. A relationship between η_t , η_s and ΔT is also derived and used to calculate ΔT , which is shown to be consistent with the value measured under continuous wave excitation when the bandwidth of the probe pulse is properly taken into account.

To measure the switching time of the system, the sample temperature is fixed at the strong coupling point and the cavity scatter is measured as a function of delay between pump and probe. The measurement results are shown in Fig. 4. The scatter exhibits a sharp peak near 0 ns delay. The temporal response of the system is asymmetric due to the fact that the probe pulse is filtered by a Fabry-Perot cavity and is therefore an asymmetric exponential pulse. The pump pulse shape was also measured using a high speed detector and found to be asymmetric. We fit the scattering intensity to a double-sided exponential of the form $S(\tau) = A[\exp(\tau/t_r)\Phi(-\tau) + \exp(-\tau/t_f)\Phi(\tau)]$ where $\Phi(\tau)$ is a unit step function, A is a normalization constant, and t_r (t_f) is the rise (fall) time of the response. The optimal fit is attained for $t_r = 47 \pm 10$ ps and $t_f = 127 \pm 19$ ps. The switching time, defined by the full width half maximum width, is $\Delta\tau = 120 \pm 15$ ps. This switching time is limited by the pulse duration of the pump and probe. Using a faster pump-probe excitation would reduce this time, but would also decrease the switching contrast because the bandwidth of the probe would be increased relative to the spectral width of the transmission dip shown Fig. 1d. In the strong coupling regime the bandwidth of the transmission dip is approximately equal to $2g$. The probe pulse must be longer than $g^{-1} = 12$ ps (assuming a transform limited gaussian pulse shape) to fit within this bandwidth, which sets the fundamental limit for the switching response time.

Fig. 5a plots the relative change in probe scattering intensity, defined as $\beta = (I_{\max}^S - I)/(I_{\max}^S - I_{\min}^T)$ where I is the scattering intensity and I_{\max}^S and I_{\min}^T are previously defined, as a function of the pump strength. The bottom axis indicates the pump strength in units of photons per pulse propagating in the waveguide mode, calculated using $E = P_{inc}\eta/\hbar\omega_p R$ where $R = 76.3$ MHz is the laser repetition rate, $\eta = 0.008$ is the grating coupler efficiency, and ω_p is the frequency of the pump pulse. The top axis indicates the pump strength in units of average pump power incident on the grating coupler, denoted P_{inc} . Measurements in Fig. 5a are shown for three different values of $\Delta = \omega_p - \omega_{qd}$, where the probe is always set to be resonant with the bare QD frequency ω_{qd} . For each curve, as the pump pulse energy is increased, the device makes a smooth transition from $\beta = 1$ to an asymptotic value of $\beta = 0$ at high pump energies. The pulse energy required to achieve switching increases with increased detuning, which is expected because fewer pump photons couple to the cavity mode.

The lines in Fig. 5a plot the theoretically predicted switching curve obtained by numer-

ical integration of the master equation. A single fitting parameter is introduced into the simulation to relate the simulated driving amplitude of the cavity to the pump pulse energy. This fitting parameter accounts for variations in the pump pulse duration, which was found to change substantially depending on the laser cavity alignment, as well as potential imperfect alignment of pump field to the grating coupler. A detailed description of these numerical calculations is provided in the supplement. The calculated solutions exhibit very good agreement with the experimental measurements. In addition to the switching curves, two horizontal lines are plotted which represent the 3 dB and 10 dB change in β . We define the pulse energy where these lines and the theoretical switching curves intersect as the 3dB and 10dB switching energies of the device, denoted E_{3dB} and E_{10dB} respectively. For $\Delta = 11.4$ GHz we attain $E_{3dB} = 140$ and $E_{10dB} = 440$ photons respectively. The ability to perform optical switching at these low photon numbers is a striking demonstration of the large nonlinearities that can be achieved using cavity-QD interactions in the strong coupling regime. Fig. 5b plots the measured value E_{3db} as a function of Δ , along with the numerically calculated values from the master equation. Numerical calculations are performed using a single fitting parameter to relate the simulated driving amplitude to the pump pulse energy for all detunings. Both experiment and theory indicate that when $\Delta < g$ the nonlinearity is not a strong function of the pump detuning. This behavior is explained by the fact that in this regime Δ is less than the modified spontaneous emission rate of the QD, which ultimately limits the nonlinearity of the system.

In conclusion, we have demonstrated fast optical switching at ultra-low energies by utilizing strong coupling between a QD and photonic crystal cavity. In our current device only 36% of the pump energy from the waveguide couples to the cavity mode. By using better device designs this coupling efficiency could be significantly improved [29] to further reduce the switching energy. Ultimately, the minimum energy required to perform switching is given by the steady state energy stored in the cavity which is estimated from coupled-mode theory [28] to be $E_{cav} = 2r_0/(\kappa\tau_c)E_{switch} = 2$ photons. This limit could be achieved by pulse shaping of the pump field to match the cavity lifetime in order to enable nonlinearities near the single photon level, which are of great importance in quantum optics and quantum information.

D. Sridharan and R. Bose contributed equally to this work. The authors would like to acknowledge support from a DARPA Defense Science Office grant (Grant W31P4Q0910013),

the Physics Frontier Center at the Joint Quantum Institute, the Office of Naval Research Applied Electromagnetics Center, the Army Research Office MURI on hybrid quantum interactions (grant number W911NF09104), and a National Science Foundation CAREER award (grant number ECCS - 0846494).

* Electronic address: edowaks@umd.edu

- [1] D. A. B. Miller, *Nat. Photonics* **4**, 3 (2010).
- [2] I. L. Chuang and Y. Yamamoto, *Phys. Rev. A* **52**, 3489 (1995).
- [3] K. Nemoto and W. J. Munro, *Phys. Rev. Lett.* **93**, 250502 (2004).
- [4] P. van Loock, T. D. Ladd, K. Sanaka, F. Yamaguchi, K. Nemoto, W. J. Munro, and Y. Yamamoto, *Phys. Rev. Lett.* **96**, 240501 (2006).
- [5] K. Hinton, G. Raskutti, P. M. Farrell, and R. S. Tucker, *IEEE J. Sel. Topics Quantum Electron.* **14**, 938 (2008).
- [6] T. Yoshie, A. Scherer, J. Hendrickson, G. Khitrova, H. M. Gibbs, G. Rupper, C. Ell, O. B. Shchekin, and D. G. Deppe, *Nature* **432**, 200 (2004).
- [7] S. Hughes and H. Kamada, *Phys. Rev. B* **70**, 195313 (2004).
- [8] E. Waks and J. Vuckovic, *Phys. Rev. Lett.* **96**, 153601 (2006).
- [9] D. Englund, A. Faraon, I. Fushman, N. Stoltz, P. Petroff, and J. Vuckovic, *Nature* **450**, 857 (2007).
- [10] J.-T. Shen and S. Fan, *Phys. Rev. A* **79**, 023837 (2009).
- [11] R. Bose, D. Sridharan, G. S. Solomon, and E. Waks, *Opt. Express* **19**, 5398 (2011).
- [12] E. Waks and J. Vuckovic, *Phys. Rev. A* **73**, 041803 (2006).
- [13] A. Aufferes-Garnier, C. Simon, J. M. Gerard, and J. P. Poizat, *Phys. Rev. A* **75**, 053823 (2007).
- [14] K. Srinivasan and O. Painter, *Nature* **450**, 862 (2007).
- [15] I. Fushman, D. Englund, A. Faraon, N. Stoltz, P. Petroff, and J. Vuckovic, *Science* **320**, 769 (2008).
- [16] R. Bose, D. Sridharan, G. S. Solomon, and E. Waks, *App. Phys. Lett.* **98**, 121109 (2011).
- [17] A. Faraon, I. Fushman, D. Englund, N. Stoltz, P. Petroff, and J. Vuckovic, *Opt. Express* **16**, 12154 (2008).

- [18] E. Waks and D. Sridharan, *Phys. Rev. A* **82**, 043845 (2010).
- [19] M. Winger, T. Volz, G. Tarel, S. Portolan, A. Badolato, K. J. Hennessy, E. L. Hu, A. Beveratos, J. Finley, V. Savona, et al., *Phys. Rev. Lett.* **103**, 207403 (2009).
- [20] S. Ates, S. M. Ulrich, A. Ulhaq, S. Reitzenstein, A. Löffler, S. Hofling, A. Forchel, and P. Michler, *Nat. Photonics* **3**, 724 (2009).
- [21] D. Englund, A. Majumdar, A. Faraon, M. Toishi, N. Stoltz, P. Petroff, and J. Vuckovic, *Phys. Rev. Lett.* **104**, 73904 (2010).
- [22] A. Majumdar, A. Faraon, E. D. Kim, D. Englund, H. Kim, P. Petroff, and J. Vucckaronkovic, *Phys. Rev. B* **82**, 045306 (2010).
- [23] X. Xu, B. Sun, P. R. Berman, D. G. Steel, A. S. Bracker, D. Gammon, and L. J. Sham, *Science* **317**, 929 (2007).
- [24] G. Jundt, L. Robledo, A. Hgele, S. Flt, and A. Imamo?lu, *Phys. Rev. Lett.* **100**, 177401 (2008).
- [25] A. Muller, W. Fang, J. Lawall, and G. S. Solomon, *Physical Review Letters* **101**, 027401 (2008).
- [26] D. Walls and J. Milburn, *Quantum Optics* (Springer, 2010).
- [27] M. T. Sze, *J. of Opt. B: Quantum Semiclassical Opt.* **1**, 424 (1999).
- [28] K. Nozaki, T. Tanabe, A. Shinya, S. Matsuo, T. Sato, H. Taniyama, and M. Notomi, *Nat. Photonics* **4**, 477 (2010).
- [29] Y. Huo, S. Sandhu, J. Pan, N. Stuhmann, M. L. Povinelli, J. M. Kahn, J. S. Harris, M. M. Fejer, and S. Fan, *Opt. Lett.* **36**, 1482 (2011).

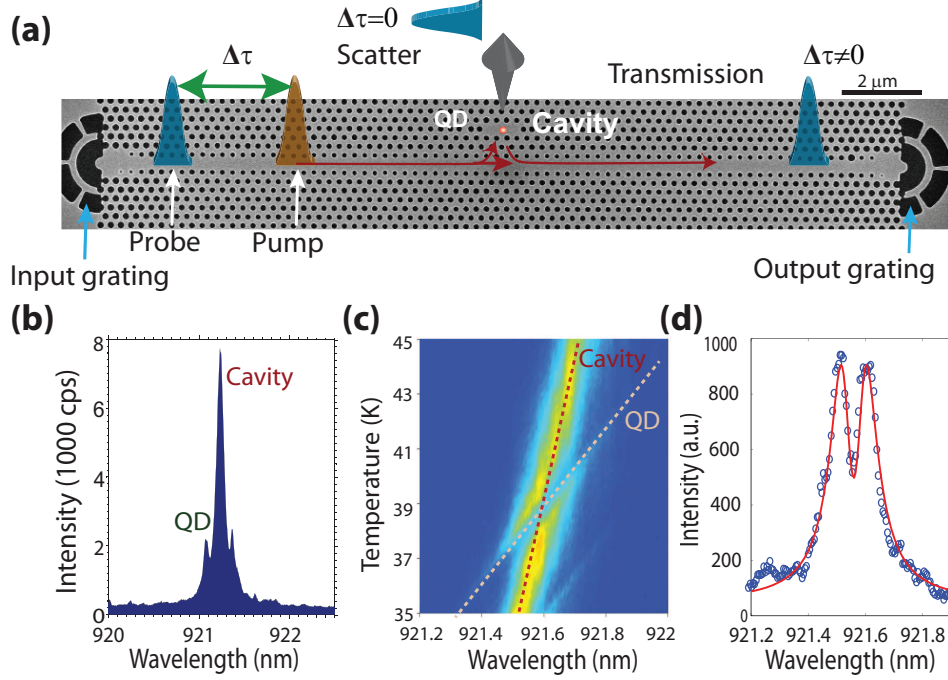


FIG. 1: (Color online) (a) SEM image showing fabricated device, and illustrating pump-probe measurements. (b) Low power PL measurement of cavity. (c) Cavity scatter under broadband LED excitation as a function of temperature. Dotted lines indicate the temperature dependence of QD and cavity. (d) Scattering spectrum taken at 39 K when the QD is resonant with the cavity.

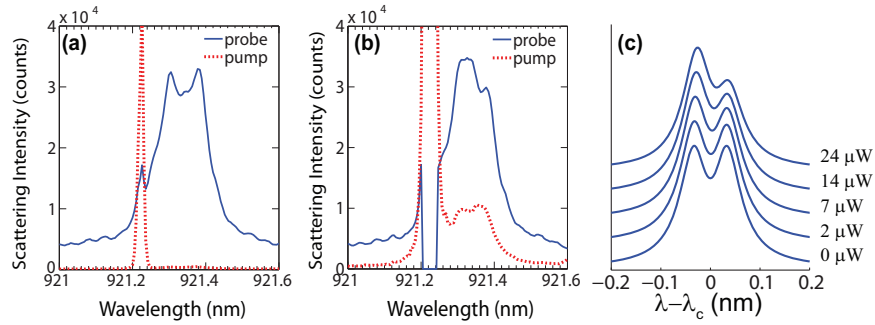


FIG. 2: (Color online) Cavity scattering spectrum for (a) $0.1 \mu\text{W}$ and (b) $14.5 \mu\text{W}$ pump field powers. The dashed red line shows the cavity scattering spectrum with only the pump field (no signal). The solid blue line shows the scattering spectrum of the probe, with pump scatter subtracted. (c) Theoretical scattering spectrum as function of incident pump power before the grating.

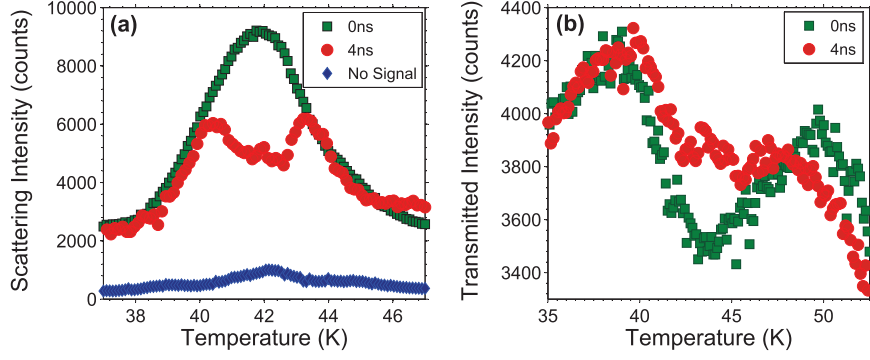


FIG. 3: (Color online) Probe scattering intensity as a function of sample temperature for delays of 0 ns (green squares) and 4 ns (red circles) (a) collected from the cavity and (b) collected from the output coupler. Scattering spectrum with pump only indicated as blue diamonds in panel a.

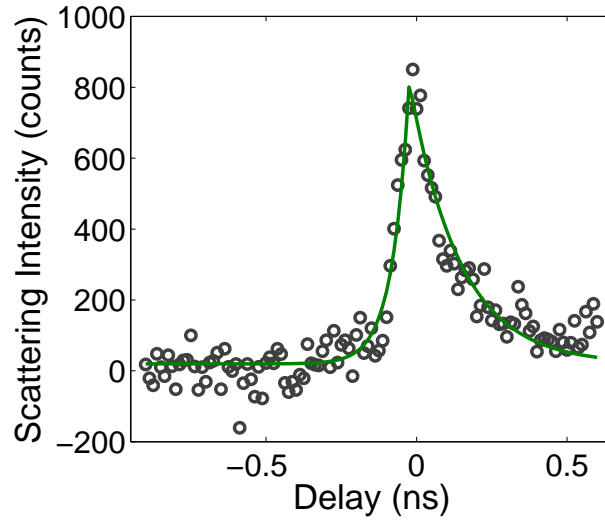


FIG. 4: (Color online) Cavity probe scattering intensity as a function of pump-probe delay. Solid line represents theoretical fit.

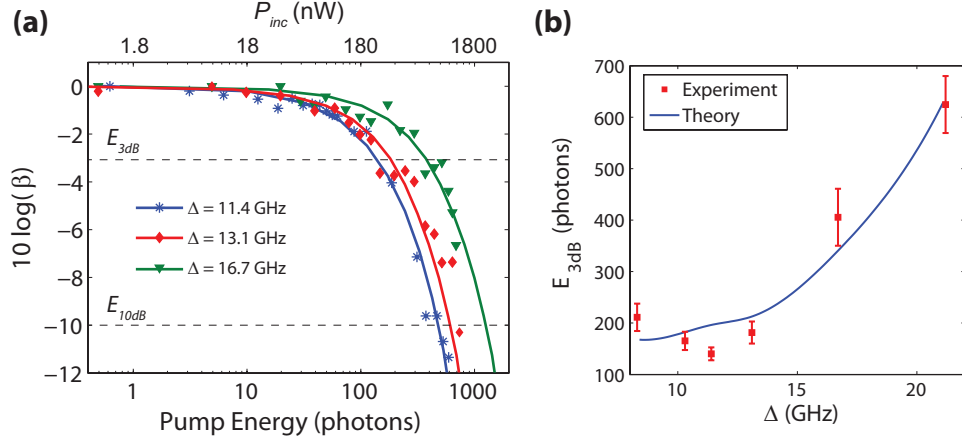


FIG. 5: (Color online) (a) Switching contrast as a function of pump pulse energy (in the waveguide) for three different values of $\Delta = \omega_p - \omega_{qd}$. Solid lines indicate the numerically calculated values. (b) Plot of E_{3dB} as a function of Δ . Solid line represents numerically calculated values.