



This is the accepted manuscript made available via CHORUS, the article has been published as:

## Revealed Architectures of Adsorbed Polymer Chains at Solid-Polymer Melt Interfaces

Peter Gin, Naisheng Jiang, Chen Liang, Takashi Taniguchi, Bulent Akgun, Sushil K. Satija, Maya K. Endoh, and Tadanori Koga

Phys. Rev. Lett. **109**, 265501 — Published 26 December 2012

DOI: [10.1103/PhysRevLett.109.265501](https://doi.org/10.1103/PhysRevLett.109.265501)

# Revealed architectures of adsorbed polymer chains at the solid-polymer melt interfaces

Peter Gin<sup>1</sup>, Naisheng Jiang<sup>1</sup>, Chen Liang<sup>1</sup>, Takashi Taniguchi<sup>2</sup>, Bulent Akgun<sup>3,4</sup>, Sushil Satija<sup>3</sup>,  
Maya K. Endoh<sup>1,\*</sup>, Tadanori Koga<sup>1,5,\*</sup>

<sup>1</sup>Department of Materials Science & Engineering, Stony Brook University, Stony Brook, NY  
11794-2275

<sup>2</sup>Graduate School of Engineering, Department of Chemical Engineering, Kyoto University  
Katsura-Campus, Nishikyo-ku, Kyoto 615-8510, Japan

<sup>3</sup>Center for Neutron Research, National Institute of Standards and Technology,  
Gaithersburg, Maryland 20899, USA

<sup>4</sup>Department of Materials Science and Engineering, University of Maryland, College Park, MD  
20742, USA

<sup>5</sup>Department of Chemistry, Stony Brook University, Stony Brook, New York 11794-3400

\*To whom correspondence should be addressed. E-mail: tkoga@notes.cc.sunysb.edu (T.K.);  
mkoga@notes.cc.sunysb.edu (M.K.E.)

## **ABSTRACT**

We report the chain conformations of polymer molecules accommodated at the solid-polymer melt interfaces in equilibrium. Polystyrene “Guiselin” brushes (adsorbed layers) with different molecular weights were prepared on Si substrates and characterized by using x-ray and neutron reflectivity. The results are intriguing to show that the adsorbed layers are composed of the two different nano-architectures: flattened chains that constitute the inner higher density region of the adsorbed layers and loosely adsorbed polymer chains that form the outer bulk-like density region. In addition, we found that the lone flattened chains, which are uncovered by the additional prolonged solvent leaching (~120 days), are reversibly densified with increasing temperature up to 150 °C. By generalizing the chain conformations of bulks, we postulate that the change in probabilities of the local chain conformations (i.e., trans- and gauche-states) of polymer molecules is the origin of this densification process.

**PACS numbers:** 61.05.cm, 68.35.bm, 68.43.-h

Solid-polymer melt (SPM) interfaces play crucial roles in a multidisciplinary field of nanotechnology at the confluence of physics, chemistry, biology, and engineering. One of the fundamental, but unsolved questions is the equilibrium conformations of polymer chains accommodated at the SPM interfaces. It is known that polymer chains adsorb even onto weakly attractive surfaces [1], forming three types of segment sequences, “trains” (adsorbed segments), “loops” (sequences of free segments connecting successive trains), and “tails” (non-adsorbed chain ends) [2]. The lattice mean-field model by Schuetjens and Fler [3-5] and lattice Monte Carlo simulations [6] by Bitsanis and ten Brinke arrived at the strong conclusion that the chain conformational features of homopolymer melts at the SPM interfaces are independent of chain intramolecular architectures, molecular weights, and strength of surface-segment interactions. Unfortunately, the experimental situations to gain the chain statistics of adsorbed polymer chains separately from those of unadsorbed chains still remain challenging. Recently though, several research groups utilized the approach proposed by Guiselin [7], which combines prolonged thermal annealing (to equilibrate the melt against the wall) and subsequent solvent leaching (to remove non-adsorbed chains)[8-15], uncovering the formation of a polymer adsorbed layer (i.e., a “Guiselin” brush) with several nanometer thick on the substrate surfaces. In particular, Durning et al. [8] and Fujii et al. [10] showed that the thickness of the equilibrated adsorbed layers increased with increasing molecular weights, which is in sharp contrast to the above theoretical predication. Thus, a molecular scale description of the real chain conformations, currently lacking, is crucial to provide insight into the mechanism of polymer adsorption from the melts and to bridge the gap between the theoretical and experimental viewpoints. Furthermore, since there is now growing evidence that the effects of the adsorbed layers at the SPM interfaces result in the long-range perturbations on various properties of supported polymer thin films [15-18], a better understanding of the chain conformations would also be a key for the development of new polymer nanostructures and nanoscale devices.

In this Letter, by combining in-situ x-ray reflectivity (XR) and neutron reflectivity (NR), we report the novel nanoscale architectures of adsorbed polymer chains established at the SPM

interfaces. Polystyrene (PS) adsorbed layers with different molecular weights were prepared on cleaned silicon (Si) substrates as model systems since the equilibrium layer preparation protocol based on the Guiselin's approach has been well established [10, 14]. The results show that the equilibrium PS adsorbed layers have the two different density regions in the direction normal to the surface: the nearly identical inner higher density region ( $2.8 \pm 0.5$  nm in thickness) regardless of molecular weights and the outer bulk-like density region whose thickness increases with increasing molecular weights. Based on the picture developed by Granick and coworkers for polymer adsorption from a dilute solution [19-22], we conjecture that polymer molecules arriving first on the surface are adsorbed with a flat conformation, forming the inner high-density region, while late arriving ones, which find less free surface areas and are hence adsorbed more loosely, form the outer bulk-like density region. In addition, we found that the further prolonged leaching process (up to 150 days) allows us to preferentially remove the outer bulk-like density layer, uncovering the lone flattened higher density layer. Intriguingly, the lone higher density layer is further densified with increasing temperature up to 150°C and the phenomenon is reversible as a function of temperature. By generalizing the chain conformations of bulks, we found that this unusual densification process is correlated to the change in the probabilities of the local chain conformations (i.e., trans- and gauche-states) of the adsorbed polymer molecules. Our finding suggests that the increase in the flexibility of the chains associated with the increase in the fraction of gauche conformers may be the origin of the reversible densification process.

Five different weight-average molar masses ( $M_w$ ) of polystyrene (PS) ( $M_w=123, 170, 290, 650, 2,000$  kDa) with narrow polydispersities ( $M_w/M_n=1.02-1.05$ , where  $M_n$  is the number-average molar mass) were obtained from Polymer Laboratories Inc. (Amherst, MA) [23]. We reproduced the established protocol for PS adsorbed layers [10, 14] on cleaned hydrogen-passivated silicon (H-Si) substrates [24]. Spun cast PS films (approximately 50 nm in thickness) prepared from toluene (Sigma-Aldrich, ACS reagent, > 99.5%) solutions [23] were annealed at 150 °C for 48 h in an oil free vacuum below  $10^{-3}$  Torr to promote adsorption [14] and to ensure equilibrium [15]. The films were then solvent leached at minimum of 5 times (each leach was for approximately

10 min) in baths of fresh toluene at room temperature [25]. The residual layers were dried in a vacuum oven to remove any excess solvent trapped in the films and characterized at room temperature by using AutoEL-II ellipsometry (Rudolf Research) [23]. Furthermore, high temperature XR experiments at the X10B beamline of the National Synchrotron Light Source, Brookhaven National Laboratory, were performed under vacuum by using a custom-built vacuum furnace with Kapton windows. The specular reflectivity was measured as a function of the scattering vector in the perpendicular direction,  $q_z = (4\pi\sin\theta)/\lambda$ , where  $\theta$  is the incident angle and  $\lambda$  is the x-ray wavelength ( $\lambda = 0.087$  nm, which is equivalent to the x-ray energy of 14.2 keV). The XR data was fitted by using a standard multilayer fitting routine for a dispersion value ( $\delta$  in the x-ray refractive index in conjunction with a Fourier method, a powerful tool to obtain detailed structures for low x-ray contrast polymer multilayers [26, 27]. Note that  $\delta$  is proportional to the density of a film [28] and the  $\delta$  value of the bulk PS is  $\delta_{\text{bulk}} = 1.14 \times 10^{-6}$ . To ensure the equilibrium of the layers at given temperatures, we stabilized for 1 h prior to XR measurements. Details of the neutron reflectivity experiments are described in supplementary information [28].

Figure 1 shows a representative time growth curve of the adsorbed PS ( $M_w = 170$  kDa) layer thickness ( $h$ ) measured by ellipsometry. Napolitano et al. introduced a new criterion to define the equilibrium of polymer chain conformations prepared on solid substrates via the ratio  $t^*$  between the annealing time and the adsorption time [14]. The adsorption time ( $\tau_{\text{ad}}$ ) was estimated to be  $\tau_{\text{ad}} \sim 0.6$  h based on the best-fit of the proposed function ( $h \sim \alpha(1 - \exp[-t / \tau_{\text{ad}}])$ ;  $\alpha$  is a constant) to the experimental growth curve. Therefore the ratio  $t^*$  is determined to be  $48\text{h}/0.6\text{h} = 80$  such that our annealing condition has met the criterion for equilibrium identified as  $t^* \gg 1$  [14]. We found that the  $\tau_{\text{ad}}$  values for all the adsorbed layers with different  $M_w$  are less than 24 h. We also confirmed that the equilibrium adsorbed PS layers are relatively smooth and homogenous, free of noticeable voids or defects based on scanning probe microscopy experiments (data not shown). Moreover, the equilibrium thickness ( $h_{\text{eq}}$ ) of the adsorbed layers at  $t^* \gg 1$  showed a linear relationship with the radius of polymer gyration ( $R_g$ ) [28], reflecting random-walk statistics of

polymer chains [8, 10]. The observed relationship of  $h_{\text{eq}} = 0.78R_g$  ( $R_g = \sqrt{N/6} \times a$ , where  $N$  and  $a$  are the degree of polymerization and segment length, respectively) is in good agreement with the previous results for the PS adsorbed layers onto H-Si substrates [10]. Hence, the present results demonstrate that we have achieved equilibrium melts against the solid surface and effectively revealed the adsorbed structures by vitrification of the polymer and subsequent “quick” rinsing (when compared with the prolonged desorption experiments to be discussed later) with the good solvent.

Figure 2 shows a representative XR profile for the equilibrium adsorbed PS ( $M_w = 123$  kDa) layer (circles). The XR and the corresponding Fourier transformation (FT) were fit simultaneously using a dispersion model [28]. Based upon the FT profile [28], a four layer model (silicon substrate, native oxide, and two different density PS layers) was chosen. The thickness of the SiO<sub>2</sub> layer was determined to be about 1.0 nm from a XR measurement on a bare H-Si substrate. The best fit (the solid line in Fig. 2) could be obtained with the density profile of the two polymer layers shown in the inset. The best-fitting results gave us the thickness of  $2.8 \pm 0.2$  nm and  $\delta$  of  $1.4 \pm 0.1 \times 10^{-6}$  for the bottom PS layer next to the SiO<sub>2</sub> layer, while  $\delta$  of the top layer ( $4.4 \pm 0.2$  nm in thickness) remains bulk-like ( $\delta_{\text{bulk}} = 1.14 \times 10^{-6}$ ). Moreover, we found that all the adsorbed layers with different  $M_w$  show similar architectures composed of the nearly identical inner higher density region ( $\delta = 1.4 \pm 0.1 \times 10^{-6}$  and  $2.8 \pm 0.5$  nm in thickness) regardless of  $M_w$  and the outer bulk-like density region whose thickness increases with increasing  $M_w$  [28].

It is interesting to address that the XR results are reminiscent of the picture developed by Granick and coworkers for polymer adsorption from a dilute solution: polymer molecules arriving first on the surface are adsorbed with a flat conformation, while late arriving ones, which find less free surface areas, adsorb more loosely with fewer adsorbed sites [19-22]. In fact, Napolitano and Wübbernhorst pointed out that polymer adsorption from the melts can also be explained by the same concept, while they have not clarified the inner architectures of the adsorbed layers [14]. It is therefore reasonable to suppose that the early-arriving polymer chains lie flat on the substrate, forming the inner high-density region, and the late-coming chains adsorb

loosely onto the substrate, developing the outer bulk-like density region (the inset of Fig. 3). As shown in the inset of Fig. 1, we also found that  $h_{\text{eq}}$  remains nearly constant with increasing temperature up to 150 °C, which is consistent with the previous results on the adsorbed PS layer using capacitive dilatometry [11]. Thus, it is clear that the outer loosely adsorbed polymer chains have the nearly zero thermal expansion.

Next, we reveal the inherent architecture of the flattened chains. For this purpose, it is desirable to uncover the inner high-density region by preferentially removing the outer bulk-like density region. This was successfully achieved by utilizing the large difference in the desorption energy, which is proportional to the number of segment-surface contacts, between the outer loosely adsorbed chains and the flattened chains [29, 30]. We immersed the equilibrium adsorbed layers in a bath of fresh toluene at room temperature for up to 5 months. Note that the experiments were carried out in the continually replenished solvent to facilitate the desorption kinetics [31]. The resultant layers after the given desorption times were dried in a vacuum oven to remove any excess solvent and then characterized by using XR. Figure 3 shows representative desorption kinetics for the adsorbed PS layer ( $M_w = 170$  kDa). From the figure we can see that the thickness of the adsorbed layer decreases with increasing desorption time and reaches the final thickness of  $3.5 \pm 0.2$  nm after 120 days. The XR results demonstrate that the thickness of the final desorbed layer are in good agreement with that of the inner high-density region of the equilibrium adsorbed layer before the desorption experiments [28]. Therefore, we conclude that the prolonged desorption process enables us to unveil the flattened high-density region.

We further provide new insight into the equilibrium conformations of the flattened chains. Figure 4 shows (a) representative XR curves for the lone flattened high-density layer ( $M_w = 290$  kDa) and (b) the temperature dependence of the thickness ( $h_{\text{flat}}$ ) that corresponds to the loop size of the flattened chains, as schematically shown in the inset. Hence it is clear that  $h_{\text{flat}}$  decreases with increasing temperature up to 150 °C and we confirmed that the temperature dependence of  $h_{\text{flat}}$  is reversible. This film contraction is in sharp contrast to the nearly zero thermal expansion of the flattened chains in the equilibrium adsorbed layer before the desorption experiments and



could be explained by the resultant empty spaces (i.e., more free volume) after removing the outer loosely adsorbed polymer chains. Density variations of the flattened layer may be difficult to determine for XR due to the macroscopic textured structures of the flattened layer [28]. Instead, NR, which is a more sensitive technique for determining density change of polymer thin films if one uses deuterated polystyrene (d-PS), was used. Recent preliminary NR investigations for the d-PS ( $M_w=676$  kDa,  $M_w/M_n=1.15$ , Polymer Source) flattened layer reveal film contraction and the corresponding increase in the density of the flattened polymer chains upon contraction: The scattering length density ( $SLD$ ) values of the flattened polymer chains are estimated to be  $7.4\pm 0.1 \times 10^{-4} \text{ nm}^{-2}$  at  $25^\circ\text{C}$  and  $7.8\pm 0.1 \times 10^{-4} \text{ nm}^{-2}$  at  $130^\circ\text{C}$ , respectively, both of which are larger than the  $SLD$  value of bulk d-PS ( $SLD_{bulk} = 6.0 \times 10^{-4} \text{ nm}^{-2}$ ) [28]. Hence, the important conclusion that the high temperature conditions further densify the flattened chains in equilibrium is drawn. A series of subsequent XR experiments have reproduced the same temperature dependence of  $h_{\text{flat}}$  with different  $M_w$  [28]. Using the self-consistent field theory, Schuetjens and Fler [4] have shown that the average loop size of isolated long polymer chains (with  $N \geq 50$ ) adsorbed on an attractive surface does not depend on chain length. To our best knowledge, this is the first experimental evidence to validate the generality of the equilibrium chain conformations at the solid-polymer melt interfaces regardless of chain length. However, it should be also emphasized that the theory cannot explain the densification of the loop.

In order to understand the origin of the densification process occurring within a few nanometers in space, we focus on the local conformations of a polymer chain. For this purpose, we assume that each loop of the flattened chains is composed of  $N_l$  segments with backbone bond angles all equal to  $\theta$  (the inset of Fig 4(b)), and that the temperature dependence of  $R_g$  of the loop ( $R_g^{loop}$ ) is given in the same way as the bulk [32]:

$$R_g^{loop} = \left[ N_l a^2 \frac{(1 - \cos \theta)(1 + \langle \cos \phi \rangle)}{(1 + \cos \theta)(1 - \langle \cos \phi \rangle)} \right]^{1/2} \quad (1)$$

$$\langle \cos \phi \rangle = \frac{1 - \exp(-\Delta E / k_B T)}{1 + 2 \exp(-\Delta E / k_B T)}, \quad (2)$$

where  $\Delta E$  is the energy gap between two conformational states (i.e., trans-and gauche-states) and  $k_B$  is the Boltzmann constant. From eq. (1), it is clear that the temperature dependence of  $R_g^{loop}$  is directed by the term  $(1 + \langle \cos \phi \rangle) / (1 - \langle \cos \phi \rangle)$ . Fig. 4 (b) also plots the calculated values of  $((1 + \langle \cos \phi \rangle) / (1 - \langle \cos \phi \rangle))^{1/2}$  (the dotted line) with the literature value of  $\Delta E = 5.0$  kJ/mol for PS [33]. Although this is a crude approximation without considerations of the effects of excluded volume and surface-segment interactions on the conformations of the flattened chains, we can see the reasonable correlation between  $h_{flat}$  and  $((1 + \langle \cos \phi \rangle) / (1 - \langle \cos \phi \rangle))^{1/2}$  as a function of temperature. We hence postulate that the increase in the fraction of gauche conformers at high temperatures [34], which has not been considered in the theory [3-6], leads to the more collapsed conformations of the flattened chains [35]. Further experiments are in progress to seek the generality of the equilibrium conformations of the flattened chains with various surface-segment interactions and intramolecular architectures.

In summary, we have revealed that polymer adsorption from the melts originate in piecemeal deposition with differential spreading dictated by the still-uncovered surface area, as for polymer adsorption from a dilute solution [19-22]. The piecemeal deposition results in the two different chain conformations at the SPM interface regardless of chain length, as opposed to the prevailing view [1] that chain conformations are selected such that free energy is minimized. We also found that the additional prolonged ( $\sim 120$  days) solvent leaching allows us to expose the flattened high-density region to the air interface. Moreover, the in-situ x-ray and neutron reflectivity measurements elucidate the reversible densification process of the flattened chains at higher temperatures irrespective of chain length. By generalizing the chain conformations of bulks, we postulate that the local conformations (i.e., trans-and gauche-states) of a polymer chain play a vital role in this unusual densification process. It is known that polymer adsorption occurs at a nanoparticle (curvature) surface filled in polymer melts as well [36-38] and the adsorbed layer is significantly thinner around nanoparticle surfaces than at chemically similar flat substrate surfaces [39]. We are currently working on the geometric effects on the architectures of flexible polymer chains, ultimately leading to a better understanding of the thermodynamics at the SPM

interfaces.

T.K. acknowledges the financial support from NSF Grant No. CMMI-084626. Use of the National Synchrotron Light Source was supported by the U.S. DOE under Contract No. DE-AC02-98CH10886.

## References

- [1] G. J. Fleer *et al.*, *Polymers at Interfaces* (Chapman and Hall, London, 1993).
- [2] P. G. de Gennes, *Scaling Concepts in Polymer Physics* (Cornell University Press, Ithaca, 1979).
- [3] M. H. M. Schuetjens, and G. J. Fleer, *J. Phys. Chem.* **83**, 1619 (1979).
- [4] M. H. M. Schuetjens, and G. J. Fleer, *J. Phys. Chem.* **84**, 178 (1980).
- [5] M. H. M. Schuetjens, and G. J. Fleer, *Macromolecules* **18**, 1882 (1985).
- [6] I. A. Bitsanis, and G. J. ten Brinke, *J. Chem. Phys.* **99**, 3100 (1993).
- [7] O. Guiselin, *Europhys. Lett.* **17**, 225 (1992).
- [8] C. J. Durning *et al.*, *Macromolecules* **32**, 6772 (1999).
- [9] S. Napolitano, V. Lupascu, and M. Wubbenhorst, *Macromolecules* **41**, 1061 (2008).
- [10] Y. Fujii *et al.*, *Macromolecules* **42**, 7418 (2009).
- [11] S. Napolitano *et al.*, *ACS Nano* **4**, 841 (2010).
- [12] C. Rotella *et al.*, *Macromolecules* **43**, 8686 (2010).
- [13] C. Rotella, M. Wubbenhorst, and S. Napolitano, *Soft Matter* **7**, 5260 (2011).
- [14] S. Napolitano, and M. Wubbenhorst, *Nat. Comm.* **2** (2011).
- [15] T. Koga *et al.*, *Phys. Rev. Lett.* **107**, 225901 (2011).
- [16] X.-W. Hu, and S. Granick, *Science* **258**, 1339 (1992).
- [17] W. J. Orts *et al.*, *Phys. Rev. Lett.* **71**, 867 (1993).
- [18] X. Zheng *et al.*, *Phys. Rev. Lett.* **79**, 241 (1997).
- [19] H. E. Johnson, and S. Granick, *Science* **255**, 966 (1992).
- [20] H. M. Schneider, P. Frantz, and S. Granick, *Langmuir* **12**, 994 (1996).
- [21] I. Soga, and S. Granick, *Langmuir* **14**, 4266 (1998).
- [22] J. F. Douglas, H. E. Johnson, and S. Granick, *Science* **262**, 2010 (1993).

- [23] Certain commercial equipment, instruments, or materials (or suppliers) are identified in this paper to foster understanding. Such identification does not imply recommendation or endorsement by the National Institute of Standards and Technology, nor does it imply that the materials or equipment identified are necessarily the best available for the purpose.
- [24] K. Shin *et al.*, *Macromolecules* **34**, 4993 (2001). In this literature, it was reported that a SiO<sub>2</sub> layer of about 1 nm in thickness is reproduced even just after hydrofluoric acid etching due to atmospheric oxygen and moisture.
- [25] Fujii *et al.* [10] proved that the sticking energy for PS chains adsorbed on H-Si substrates is high enough such that the equilibrated adsorbed structures at the SPM interface can be preserved even after the similar leaching process.
- [26] O. H. Seeck *et al.*, *Appl. Phys. Lett.* **76**, 2713 (2000).
- [27] T. Koga *et al.*, *Appl. Phys. Lett.* **83**, 4309 (2003).
- [28] See supplementary information for the details of the dispersion value, the FT analysis, the fitting results for all the adsorbed layers, the temperature dependence of the flattened layers for different molecular weights, the surface image of the flattened layer, and neutron reflectivity results on the flattened layer.
- [29] B. O'Shaughnessy, and D. Vavylonis, *Phys. Rev. Lett.* **90** (2003).
- [30] B. O'Shaughnessy, and D. Vavylonis, *Eur. Phys. J. E.* **11**, 213 (2003).
- [31] M. Santore, *Curr. Opin. Colloid In.* **10**, 176 (2005).
- [32] H. Yamakawa, (Harper & Row, Publishers, NY, 1971).
- [33] R. J. Young, and P. A. Lovell, *Introduction to polymers* (CRC press, FL, 2011).
- [34] H.-S. Shin *et al.*, *Langmuir* **18**, 5953 (2002).

- [35] The magnitude of the increase of the density is nicely correlated with that of the decrease of the thickness, implying that the total mass of the polymer is conserved. Hence, this densification is mainly due to the collapse of the polymer chains in the direction perpendicular to the substrate.
- [36] B. Metin, and F. D. Blum, *Journal of Chemical Physics* **125** (2006).
- [37] R. B. Bogoslovov *et al.*, *Macromolecules* **41**, 1289 (2008).
- [38] D. Brown *et al.*, *Macromolecules* **41**, 1499 (2008).
- [39] S. E. Harton *et al.*, *Macromolecules* **43**, 3415 (2010).

## Figure Captions

- Figure 1** Time evolution of the adsorbed PS ( $M_w = 170$  kDa) layer thickness during annealing at 150 °C. The solid line corresponds to the proposed function described in the text. In the inset, the temperature dependence of the thickness of the equilibrium adsorbed PS ( $M_w = 170$  kDa) layer is shown.
- Figure 2** Observed XR profiles for the equilibrium adsorbed PS ( $M_w = 123$  kDa) layer (circles). The black line corresponds to the best-fit based on the density profile against the distance ( $z$ ) from the SiO<sub>2</sub> surface shown in the inset. The dispersion values were converted into the density of the film relative to the bulk by using the measured dispersion value of the bulk.
- Figure 3** Desorption kinetics of the equilibrium adsorbed PS ( $M_w = 170$  kDa) layer during the toluene leaching. The inset shows the schematic view of the two different chain conformations.
- Figure 4** (a) Representative XR profiles for the flattened layer ( $M_w = 290$  kDa) at the three temperatures and (b) temperature dependence of  $h_{\text{flat}}$  along with the calculated values of the  $\left(\frac{1 + \langle \cos \phi \rangle}{1 - \langle \cos \phi \rangle}\right)^{1/2}$  term in eq. (1) (the dotted line) for PS. The inset shows the schematic conformation of the flattened chains.

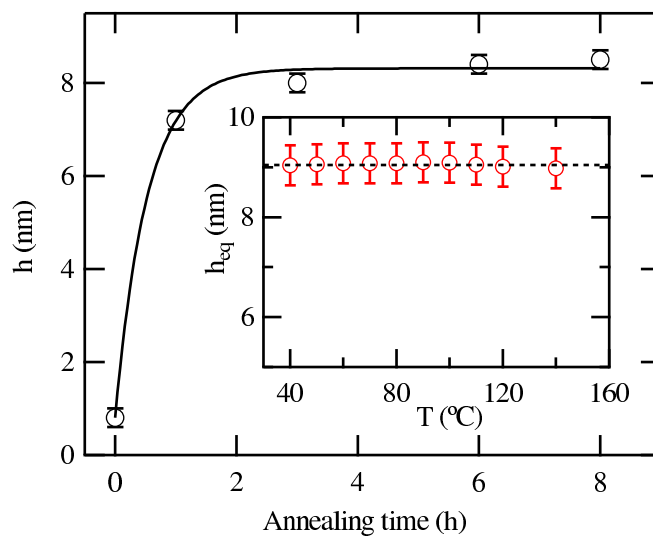


Figure 1 LU13991 14NOV2012



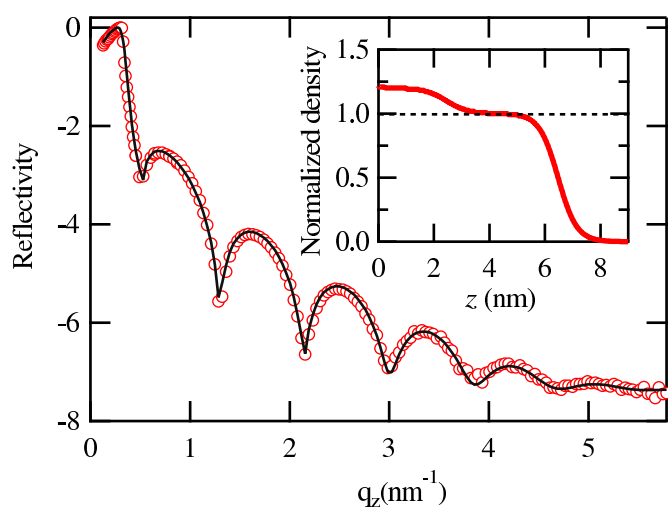


Figure 2

LU13991

14NOV2012

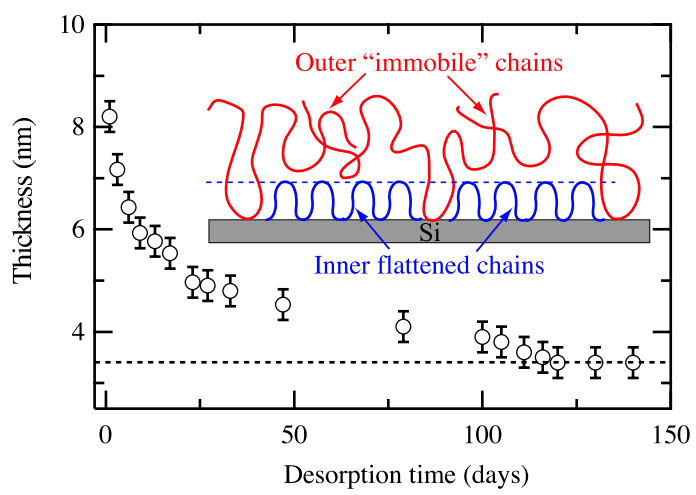


Figure 3

LU13991

14NOV2012

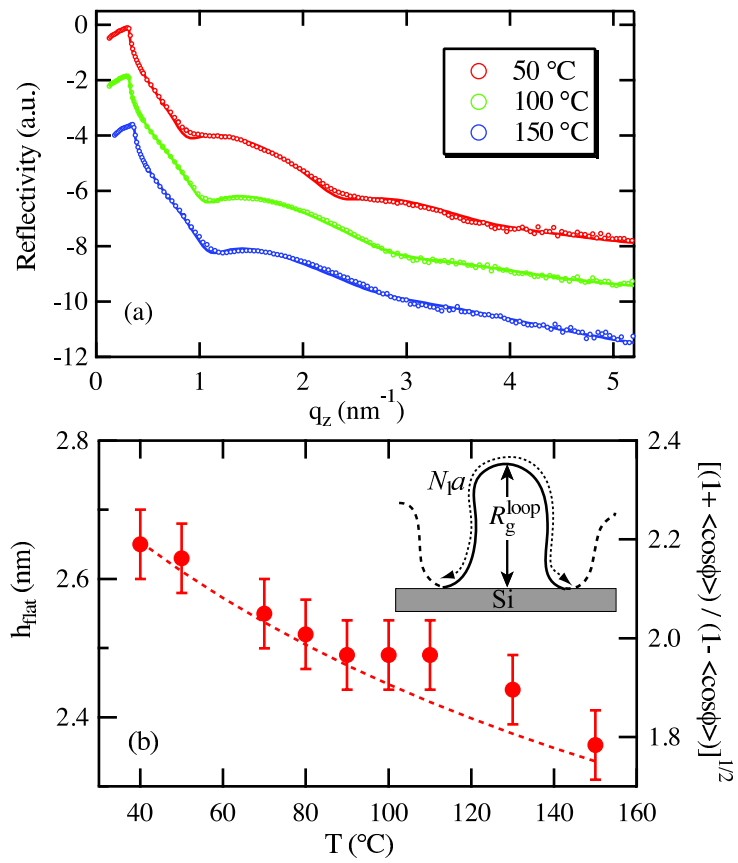


Figure 4

LU13991

14NOV2012