



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Measurement of Two Low-Temperature Energy Gaps in the Electronic Structure of Antiferromagnetic USb_2 Using Ultrafast Optical Spectroscopy

J. Qi, T. Durakiewicz, S. A. Trugman, J.-X. Zhu, P. S. Riseborough, R. Baumbach, E. D. Bauer, K. Gofryk, J.-Q. Meng, J. J. Joyce, A. J. Taylor, and R. P. Prasankumar

Phys. Rev. Lett. **111**, 057402 — Published 1 August 2013

DOI: [10.1103/PhysRevLett.111.057402](https://doi.org/10.1103/PhysRevLett.111.057402)

Measurement of two low-temperature energy gaps in the electronic structure of antiferromagnetic USb₂ using ultrafast optical spectroscopy

J. Qi,¹ T. Durakiewicz,¹ S. A. Trugman,¹ J.-X. Zhu,¹ P. S. Riseborough,² R. Baumbach,¹ E. D. Bauer,¹ K. Gofryk,¹ J.-Q. Meng,¹ J. J. Joyce,¹ A. J. Taylor,¹ and R. P. Prasankumar¹

¹*Los Alamos National Laboratory, Los Alamos, NM 87545, USA*

²*Temple University, Philadelphia, PA 19121, USA*

Ultrafast optical spectroscopy is used to study the antiferromagnetic f -electron system USb₂. We observe the opening of two charge gaps at low temperatures ($\lesssim 45$ K), arising from renormalization of the electronic structure. Analysis of our data indicates that one gap is due to hybridization between localized f -electron and conduction electron bands, while band renormalization involving magnons leads to the emergence of the second gap. These experiments thus enable us to shed light on the complex electronic structure emerging at the Fermi surface in f -electron systems.

PACS numbers: 78.47.+p, 75.50.Ee, 71.27.+a

Exotic phenomena, such as unconventional superconductivity, the heavy fermion state, or the elusive "hidden order" phase of URu₂Si₂, can emerge from many-body interactions in f -electron systems [1–5]. These phenomena, governed by strong electronic correlation and complex interactions between the electronic and bosonic degrees of freedom, are often associated with the dual nature (localized vs. itinerant) of the f -electrons. The itinerant response is usually related to the nature of the Fermi surface, where very small band renormalization effects often escape experimental detection due to lack of resolution. However, these minute changes in the Fermi surface cannot be ignored, as they can dramatically modify the properties of f -electron materials, leading to exotic phenomena mentioned above. A deeper understanding of such phenomena depends on a detailed knowledge of the electronic structure near the Fermi surface in f -electron systems.

Antiferromagnetic USb₂ ($T_N \sim 203$ K) [6, 7] is an excellent candidate for exploring these issues, as it is a moderately correlated electron system with a quasi-2D electronic structure exhibiting characteristics of both localized and itinerant $5f$ electrons [8–13]. Moreover, previous angle-resolved photoemission spectroscopy (ARPES) studies [13, 14] produced the first measurements of the self-energy in $5f$ electron systems and a model of boson-mediated band renormalization [15]. However, they could only explore the region near the center of the Brillouin zone ($k = 0$) and could not specify the nature of the boson involved. This directly motivated our search for new physical properties (e.g., the opening of a gap or changes in the quasiparticle (QP) effective mass) arising from boson-mediated many-body interactions, to understand the band structure of USb₂ over all k -space.

Optical spectroscopy measurements at GHz and THz frequencies have already shown complex low energy features linked to magnetic excitations in different uranium systems [16–20]. In the time domain, ultrafast optical spectroscopy (UOS) has also been quite successful

in providing such information, offering insight into the physics of strongly correlated materials [21] such as superconductors (SCs) [22–24] and heavy fermions (HFs) [25, 26]. In particular, by measuring the temperature (T)-dependent QP dynamics and analyzing the data with the Rothwarf-Taylor (RT) model [27, 28], one can extract small changes in the electronic structure, even away from the Brillouin zone center. Even more insight could potentially be gained by combining UOS with other techniques such as ARPES and specific heat measurements to obtain a more complete picture of the electronic structure in f -electron systems.

Here, we present the first ultrafast time-resolved differential reflectivity $\Delta R(t)/R$ measurements on USb₂ at a center wavelength of 830 nm (1.5 eV) using an 80 MHz Ti:sapphire femtosecond laser oscillator (see supplementary information (SI) for experimental details), taken from room temperature down to 6 K. Guided by ARPES and specific heat data, we reveal multiple gaps opening in the density of states (DOS), associated with emergent QP states at/near the Fermi level. We also observe coherent phonon oscillations, previously unobserved in metallic uranium systems, the analysis of which not only illustrates the temperature evolution of the gap structures, but also demonstrates that *magnons* can be involved in band renormalization.

Figure 1 shows the measured $\Delta R/R$ signals at (a) low and (b) high temperatures. Upon photoexcitation, the $\Delta R/R$ signal changes nearly instantaneously due to a rise in the temperature of the Fermi surface, as excited carriers rapidly equilibrate via electron-electron scattering [25]. This initial change reverses sign when the temperature crosses T_N . This is consistent with the reconstruction of the Fermi surface at T_N , as previously seen in dHvA measurements [9, 12]. At longer delays, after equilibration of the photoexcited carriers, the $\Delta R/R$ signals exhibit a damped ultrafast oscillation superimposed on a non-oscillating background decay.

We first focus on the non-oscillatory relaxation for

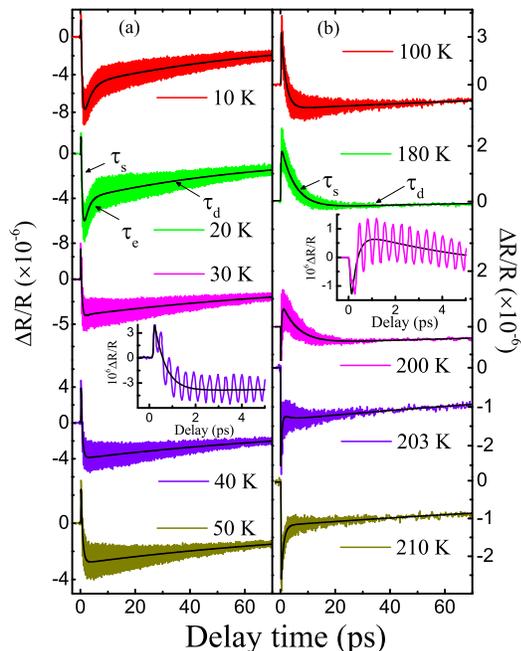


FIG. 1. Temperature-dependent $\Delta R/R$ data for USB_2 . The solid lines show the extracted non-oscillatory background decay. The insets show the dynamics at short timescales for two temperatures (40 K and 200 K). The arrows indicate the corresponding decay processes.

$T \lesssim T_N$, since it does not significantly change in the paramagnetic state. Below $\sim T_N$, this relaxation can be fitted with three exponential decays convoluted with a Gaussian laser pulse $G(t)$ (FWHM $\simeq 55$ fs): $\Delta R/R = [A_s e^{-t/\tau_s} + A_e e^{-t/\tau_e} + A_d e^{-t/\tau_d} + A_0] \otimes G(t)$, ($A_s > 0$, $A_e < 0$, $A_d < 0$). Here, A_e and τ_e represent a relaxation process that only appears below a critical temperature of $T^\dagger \sim 32$ K, and τ_s and τ_d are the time constants of the initial fast decay and very slow relaxation, respectively (Fig. 1). The subscripts “s”, “e”, and “d” were chosen to represent the components associated with “spin”/“magnetic”, “electronic”, and “heat diffusion” contributions, respectively, as will be made more clear below.

We find that τ_d has a timescale of at least a few hundred picoseconds (ps) at all temperatures, which is likely due to thermal diffusion, as in similar measurements on other strongly correlated systems [25, 29]. Here, we focus on the other two decay processes that occur on shorter timescales ($t \lesssim 10$ ps). We clearly observe from Figure 2 that: (a) τ_s increases continuously with T , and shows a sharp upturn at T_N (nearly diverging there); (b) As T decreases through a temperature T^* ($\simeq 45$ K), A_s strongly increases, while τ_s decreases significantly (inset to Fig. 2(b)); (c) A_e and τ_e , which appear below T^\dagger , increase rapidly as T decreases. Similar behaviour has been observed in superconductors [23, 24] and HF compounds [25, 30], and was attributed to the opening of a gap (Δ) in the DOS. However, the detailed mechanism behind

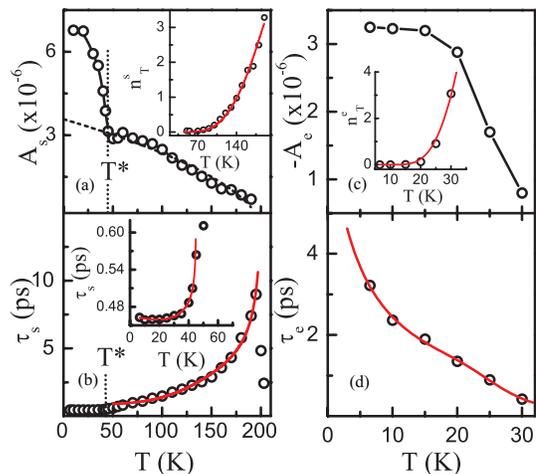


FIG. 2. T -dependence of amplitudes A_j and excited quasiparticle densities n_T^j ($j = s, e$), corresponding to the relaxation times τ_s ((a) and (b)) and τ_e ((c) and (d)), respectively. The red solid lines are best fits to the data using the RT model. The dashed line in (a) is an amplitude fit using a BCS-like T -dependence to obtain the value of $A_s(T = 0)$ for fitting $\tau_s(T > T^*)$ [24].

the gap opening demands separate analysis for different systems.

QP relaxation in a system with a narrow gap, such as superconductors and HFs, can be approximated by the RT model [27]. Here, the recovery process is governed by the decay of electrons with energies larger than the gap, via the emission of high frequency bosons that can subsequently re-excite electron-hole pairs. The RT model has been applied to many materials [24, 25, 28], using the equations

$$n_T(T) = A(0)/A(T) - 1, \quad (1)$$

$$\tau^{-1}(T) \propto [\delta(\beta n_T + 1)^{-1} + 2n_T](\Delta + \alpha T \Delta^4), \quad (2)$$

where $n_T(T)$ is the density of thermally excited QPs, and α , β and δ are fitting parameters. In these equations, we employ the standard form of n_T : $n_T \propto (T\Delta)^p e^{-\Delta/T}$ [25], where the choice of p ($0 < p < 1$) depends on the shape of the DOS.

We can use the RT model to gain more insight into the processes characterized by τ_s and τ_e . To model these processes, we use $p = 0.5$, which represents the DOS with a shape similar to that of BCS superconductors, as previously used for heavy fermion systems (Fig. 2) [25]. We can then fit τ_e (Fig. 2(c,d)) using a T -independent constant gap Δ_e , with a value of 11.8 meV. Modeling τ_s is more complicated, as the sharp change across T^* necessitates that we fit the data differently above and below T^* . At higher temperatures ($T > T^*$), we can fit τ_s using a BCS-like T -dependence for the gap: $\Delta_s \simeq 46.1(1 - T/T_N)^{0.5}$ (meV). However, at lower temperatures ($T \lesssim T^*$), τ_s can be fit with neither a BCS-like T -dependent gap nor a constant gap. There-

fore, we assume a gap with a simple T -dependent form: $\Delta_s^* = \Delta_s^*(0)(1 - T/T^*)^\eta$, where η is also a fitting parameter. With this assumption, we find that $\tau_s(T \lesssim T^*)$ can be reproduced well using $\Delta_s^* \simeq 12.8(1 - T/T^*)^{0.05}$ (meV). The excellent agreement between the experimental results and the curve fits confirms our initial expectation of a gap opening. We note that the number and functional form of the gaps used to fit our data was the simplest possible choice; efforts to fit our data with only one gap, or with two T -independent gaps, were unsuccessful (please see SI for more detail).

The quasi-divergence of τ_s at the Néel temperature suggests a QP gap opening (measured by Δ_s) due to the onset of magnetic order. In USb_2 , this magnetic order contains contributions from both spin and orbital polarization. Simultaneously, conditions for a possible Fermi surface nesting appear because of parallel boundaries existing between hole and electron pockets in this system [9, 11, 12, 31]. This is similar to the previous observation of a spin density wave gap in the itinerant antiferromagnetic actinide UNiGa_5 [30].

More interestingly, our analysis indicates that two additional gaps open up at lower temperatures (Δ_s^* and Δ_e), which we focus on below. Previous ultrafast optical studies on HFs [25] have shown that such small gaps are typically due to hybridization between the localized $5f$ electrons and the conduction electrons. However, such hybridization alone cannot explain the extremely narrow band below the Fermi level and the kink-like structures observed in previous ARPES studies on USb_2 [13–15] (Fig. 3(c)). Ref. [15] shows that electron-boson mediated processes also contribute to these features, where the bosons participate in interband electron scattering. Therefore, we need to consider both of these potential contributions in discussing the origin of Δ_s^* and Δ_e .

We have performed a theoretical analysis of the electronic structure that incorporates both hybridization between f electron bands and conduction bands as well as boson-mediated processes. To illustrate this, the calculated results along the Γ -X direction are shown in Figures 3(a) and (b). In our calculations, the non-interacting or bare bands are obtained from local density approximation calculations, and boson-mediated band hybridization is introduced via interband scattering [15]. Fig. 3 clearly shows that boson-mediated band renormalization can lead to multiple gaps and/or kink-like structures away from zone-center at/near the Fermi level. More specifically, our calculations produce indirect charge gaps at the Fermi level with a magnitude of ~ 10 -15 meV for both hole- and electron-like bands.

These predicted values agree well with current experimental findings. Previously, it was not possible to compare the calculation to the original ARPES data over the full Brillouin zone [13–15], since the features away from zone center were very hard to discern due to the rapidly decreasing signal intensity for high k values. Here, we

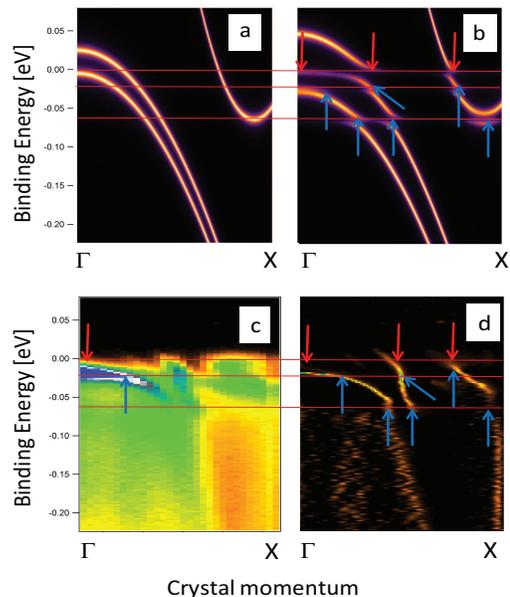


FIG. 3. Multiple gaps and kinks revealed by ARPES measurements on USb_2 at 12 K. Panels (a) and (b) show the calculated bare bands and the renormalized bands when including boson-mediated band renormalization [32], respectively. Panel (c) shows the original ARPES data [13, 15], including the single gap-and-kink structure. Panel (d) shows data from (c) reduced with the 2D curvature method [33]. Multiple gap structures are marked with red arrows, with their energy scales indicated by red horizontal lines. Blue arrows mark kinks in the dispersion due to band renormalization.

use a recent data reduction method involving the 2D Fermi surface curvature [33] to identify those features (Fig. 3(d)), allowing us to show that the complex multi-gap structure predicted by theory indeed agrees well with the ARPES data. Thus, we propose that boson-mediated many-body interactions play a prominent role in band renormalization at/near the Fermi surface and contribute to the low- T gap openings observed here. However, understanding the nature of the QP states associated with the band gaps Δ_s^* and Δ_e , as well as the type of boson involved, requires further evaluation.

We gain more insight on these issues by carefully considering the oscillations in the $\Delta R/R$ signal. It is generally accepted that these terahertz frequency oscillations, due to coherent optical phonons, are initiated either via the displacive excitation of coherent phonons [34] or a photoexcitation-induced Raman process [35]. A Fourier transform (FT) of the oscillation reveals only one frequency component (Figure 4(a)). This allows us to fit this signal with the expression $(\Delta R/R)_{osc} = Ae^{-\Gamma t} \sin(2\pi\nu t + \phi)$, where Γ and ν are the damping rate and frequency, respectively (Fig. 4(a)). The fitted T -dependence of ν and Γ is shown in Figure 4 (c,d), and clearly demonstrates that both parameters depend almost linearly on temperature above T^* (~ 45 K) but exhibit more complicated behaviour for $T \lesssim T^*$.

The T -dependence of ν and Γ is typically explained by the anharmonic effect [36–38]. This effect usually includes contributions from lattice thermal expansion (Grüneisen law) and anharmonic phonon-phonon coupling. We can thus model the experimentally measured ν and Γ , including these contributions, using [36–38]

$$\omega(T) = \omega_0 + \Delta\omega^{(1)}(T) + A_1[1 + 2n(\omega_0)], \quad (3)$$

$$\Gamma(T) = A_2[1 + 2n(\omega_0)], \quad (4)$$

where $\omega = 2\pi\nu$, $n(\omega) = [e^{\hbar\omega/k_B T} - 1]^{-1}$, and the shift $\Delta\omega^{(1)}$ from thermal expansion is given by $\Delta\omega^{(1)}(T) = \omega_0 [e^{-\gamma \int_0^T (\alpha_c + 2\alpha_a) dT'} - 1]$. Thermal expansion factors α_i ($i = a, c$) are obtained from Ref. [39]. Fig. 4 (c,d) demonstrates that the above model can explain the T -dependent behaviour of ν and Γ above T^* . However, it fails to capture the phonon softening in ν (relative to the model prediction) and the wiggle structure in Γ , which both appear below T^* .

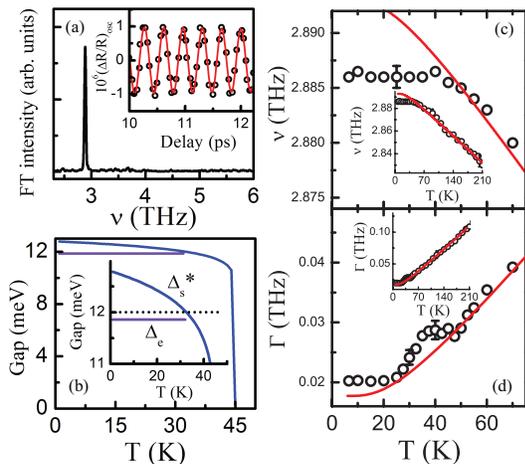


FIG. 4. (a) FT spectrum (main panel) of the extracted oscillation $(\Delta R/R)_{osc}$ and its fit (red line) at 60 K (inset). (b) Temperature evolution of the gaps Δ_e and Δ_s^* compared with the phonon energy (dotted line) for $T < T^*$. (c) The T -dependence of the oscillation frequency ν and (d) the damping rate Γ . The red solid curves are fits to the data using the anharmonic effect model.

Conventional magnon-phonon coupling cannot contribute to the large phonon softening below T^* , since there is no obvious change of $\nu(T)$ across T_N (see SI for more detail). However, it is clear that this softening happens at the same temperature (T^*) where the gap Δ_s^* opens, suggesting that both phenomena are closely related. We first note that Δ_s^* should be spin-related, since it is derived from τ_s , which diverges when the QP gap opens at T_N . This is further supported by the fact that a low energy spin excitation appears below T^* in specific heat measurements (see SI). These observations indicate that magnons participate in the boson-mediated

band renormalization below T^* , leading to the opening of Δ_s^* . This band renormalization increases the effective mass of the bands at the Fermi level with respect to the bare band structure, increasing their DOS. This in turn increases the density of QPs near the Fermi surface, which enhances the screening of atomic forces, leading to the phonon softening seen in our experiments. The observed phonon softening thus provides further evidence for boson (*magnon*)-mediated band renormalization [40].

At T^\dagger (~ 30 K), the gap Δ_e opens, which is associated with an additional band renormalization at the Fermi level, and in principle could influence phonon softening. However, we did not observe any clear change in $\nu(T)$ around T^\dagger (Fig. 4(c)). This implies that any enhancement of the DOS associated with Δ_e does not lead to an observable phonon frequency change, indicating that boson-mediated band renormalization is not the origin of Δ_e . Instead, this gap is likely due to f - d hybridization, as in other HF materials. This is supported by the fact that Δ_e is constant below T^\dagger , consistent with previous findings [25]. In contrast, Δ_s^* , which deviates from a constant T dependence, has a more complex origin (i.e. boson-mediated band renormalization). More importantly, this reveals that the QP states at/near the Fermi level associated with Δ_s^* and Δ_e are quite different.

The damping rate Γ of a coherent phonon with energy $E_{ph} (= h\nu)$ will be strongly enhanced upon a gap (Δ) opening if $E_{ph} > \Delta$, due to increased coupling between the phononic and electronic degrees of freedom. In contrast, Γ will be unaffected for $E_{ph} < \Delta$ [41, 42]. Here, there are two gaps, Δ_s^* and Δ_e , which successively open as T decreases. From Fig. 4(b), we can see that: (1) for $T < T^\dagger$, E_{ph} is always larger than Δ_e ; (2) for $T \gtrsim T^\dagger$, E_{ph} is greater than Δ_s^* . Thus, as shown in Fig. 4(d), the damping rate Γ below T^* should be always greater than that resulting from only considering the anharmonic effect, since E_{ph} is always greater than one of the two gaps. In addition, since Δ_s^* gradually increases as T decreases, E_{ph} is smaller than Δ_s^* below $\sim T^\dagger$. Therefore, the damping associated with Δ_s^* decreases as T decreases from T^* to T^\dagger (~ 30 K). Based on these considerations, the dependence of Γ on T is qualitatively expected to show the behaviour in Fig. 4(d). Clearly, T -dependent phonon damping can intuitively reflect the temperature evolution of the gap structure(s) in strongly correlated systems.

In conclusion, we used ultrafast optical spectroscopy to shed light on the detailed electronic structure of USb_2 . T -dependent QP relaxation revealed the opening of three gaps at different temperatures, T^\dagger , T^* , and T_N . The magnitudes of these gaps agree well with previous ARPES results and boson-mediated band renormalization calculations. Strong phonon energy renormalization below T^* also indicates that magnons are the bosons involved in band renormalization, which greatly increases the QP effective mass at the Fermi level. Overall, these

findings significantly enhance our understanding of the complex emergent states in USb_2 , as well as in other f -electron systems.

This work was performed under the auspices of the Department of Energy, Office of Basic Energy Sciences, Division of Material Sciences. Los Alamos National Laboratory, an affirmative action equal opportunity employer, is operated by Los Alamos National Security, LLC, for the National Nuclear Security administration of the U.S. Department of Energy under contract no. DE-AC52-06NA25396.

-
- [1] N. D. Mathur, F. M. Grosche, S. R. Julian, I. R. Walker, D. M. Freye, R. K. W. Haselwimmer, and G. G. Lonzarich, *Nature* **394**, 39 (1998)
- [2] P. Chandra, P. Coleman, J. A. Mydosh, and V. Tripathi, *Nature* **417**, 831 (2002).
- [3] N. J. Curro, T. Caldwell, E. D. Bauer, L. A. Morales, M. J. Graf, Y. Bang, A. V. Balatsky, J. D. Thompson, and J. L. Sarrao, *Nature* **434**, 622 (2005).
- [4] Y. -F. Yang, Z. Fisk, H. Lee, J. D. Thompson, and D. Pines, *Nature* **454**, 611 (2008).
- [5] S. V. Dordevic, D. N. Basov, N. R. Dilley, E. D. Bauer, and M. B. Maple, *Phys. Rev. Lett.* **86**, 684 (2001).
- [6] W. Trzebiatowski and R. Troc, *Bull. Acad. Pol. Sci. Ser. Sci. Chim.* **11**, 661 (1963).
- [7] A. Henkie and Z. Kletowski, *Acta Phys. Pol. A* **42**, 405 (1972).
- [8] R. Wawryk, *Philos. Mag.* **86**, 1775 (2006).
- [9] D. Aoki, P. Wisniewski, K. Miyake, N. Watanabe, Y. Inada, R. Settai, E. Yamamoto, Y. Haga, and Y. Onuki, *Philos. Mag. B* **80**, 1517 (2000).
- [10] P. Wisniewski, D. Aoki, N. Watanabe, R. Settai, Y. Haga, E. Yamamoto, and Y. Onuki, *J. Phys. Soc. Jpn.*, **70**, 278 (2001).
- [11] D. Aoki, P. Wisniewski, K. Miyake, R. Settai, Y. Inada, K. Sugiyama, E. Yamamoto, Y. Haga, and Y. Onuki, *Physica B: Condens. Matter* **281**, 761 (2000).
- [12] D. Aoki, P. Wisniewski, K. Miyake, N. Watanabe, Y. Inada, R. Settai, E. Yamamoto, Y. Haga, and Y. Onuki, *J. Phys. Soc. Jpn.* **68**, 2182 (1999).
- [13] T. Durakiewicz *et al.*, *Europhys. Lett.* **84**, 37003 (2008).
- [14] E. Guziewicz *et al.*, *Phys. Rev. B* **69**, 045102 (2004).
- [15] X. Yang *et al.*, *Phil. Mag.* **89**, 1893 (2009).
- [16] S. Donovan, A. Schwartz, and G. Gruner, *Phys. Rev. Lett.* **79**, 1401 (1997).
- [17] M. Dressel, N. Kasper, K. Petukhov, B. Gorshunov, G. Gruner, M. Huth, and H. Adrian, *Phys. Rev. Lett.* **88**, 186404 (2002).
- [18] M. Dressel, N. Kasper, K. Petukhov, D. N. Peligrad, B. Gorshunov, M. Jourdan, M. Huth, and H. Adrian, *Phys. Rev. B* **66**, 035110 (2002).
- [19] M. Scheffler, M. Dressel, M. Jourdan, and H. Adrian, *Nature* **438**, 1135 (2005).
- [20] M. Scheffler, M. Dressel, and M. Jourdan, *Eur. Phys. J. B* **74**, 331-338 (2010).
- [21] D. N. Basov, R. D. Averitt, D. van der Marel, M. Dressel, and K. Haule, *Rev. Mod. Phys.* **83**, 471 (2011); and references therein.
- [22] S. G. Han, Z. V. Vardeny, K. S. Wong, and O. G. Symko, *Phys. Rev. Lett.* **65**, 2708 (1990).
- [23] V. V. Kabanov, J. Demsar, B. Podobnik, and D. Mihailovic, *Phys. Rev. B* **59**, 1497 (1999).
- [24] Elbert E. M. Chia *et al.*, *Phys. Rev. Lett.* **99**, 147008 (2007).
- [25] J. Demsar, J. L. Sarrao, and A. J. Taylor, *J. Phys. Condens. Matter* **19**, R281 (2006); and references therein.
- [26] D. Talbayev *et al.*, *Phys. Rev. Lett.* **104**, 227002 (2010).
- [27] A. Rothwarf and B. N. Taylor, *Phys. Rev. Lett.* **19**, 27 (1967).
- [28] V. V. Kabanov, J. Demsar, and D. Mihailovic, *Phys. Rev. Lett.* **95**, 147002 (2005).
- [29] J. Qi, L. Yan, H. D. Zhou, J.-X. Zhu, S. A. Trugman, A. J. Taylor, Q. X. Jia, and R. P. Prasankumar, *Appl. Phys. Lett.* **101**, 122904 (2012).
- [30] Elbert E. M. Chia *et al.*, *Phys. Rev. B* **74**, 140409 (2006).
- [31] S. Lebegue, P. M. Oppeneer, and O. Eriksson, *Phys. Rev. B* **73**, 045119 (2006).
- [32] dHvA and ARPES experiments show that the Fermi surface is composed of two hole-like sheets around zone-center $(0, 0)$, and at least one electron-like sheet located near (π, π) . Thus, we simplify our calculations by considering the interband scattering processes between three bands.
- [33] P. Zhang, P. Richard, T. Qian, Y.-M. Xu, X. Dai, and H. Ding, *Rev. Sci. Instr.* **82**, 43712 (2011).
- [34] H.J. Zeiger, J. Vidal, T. K. Cheng, E. P. Ippen, G. Dresselhaus, and M. S. Dresselhaus, *Phys. Rev. B* **45**, 768 (1992).
- [35] R. Merlin, *Solid State Commun.* **102**, 207 (1997).
- [36] J. Menendez and M. Cardona, *Phys. Rev. B* **29**, 2051 (1984).
- [37] M. Balkanski, R. F. Wallis, and E. Haro, *Phys. Rev. B* **28**, 1928 (1983).
- [38] H. Tang and I. P. Herman, *Phys. Rev. B* **43**, 2299 (1991).
- [39] Z. Henkie, R. Maslanka, P. Wisniewski, R. Fabrowski, P. Markowski, J. Franse, and M. van Sprang, *J. Alloys and Compounds* **181**, 267 (1992).
- [40] The details of possible coupling of the spin component to the itinerant electrons remain unknown and need to be investigated further.
- [41] R. Zeyher and G. Zwirgagl, *Z. Phys. B* **78**, 175 (1990).
- [42] W. Albrecht, Th. Kruse, and H. Kurz, *Phys. Rev. Lett.* **69**, 1451 (1992).