

This is the accepted manuscript made available via CHORUS. The article has been published as:

# Reduction of Dissipative Nonlinear Conductivity of Superconductors by Static and Microwave Magnetic Fields

A. Gurevich

Phys. Rev. Lett. **113**, 087001 — Published 18 August 2014

DOI: [10.1103/PhysRevLett.113.087001](https://doi.org/10.1103/PhysRevLett.113.087001)

# Reduction of dissipative nonlinear conductivity of superconductors by static and microwave magnetic fields.

A. Gurevich

*Department of Physics and Center for Accelerator Science,  
Old Dominion University, 4600 Elkhorn Avenue Norfolk, VA 23529*

A theory of dissipative nonlinear conductivity,  $\sigma_1(\omega, H)$ , of s-wave superconductors under strong electromagnetic fields at low temperatures is proposed. Closed-form expressions for  $\sigma_1(H)$  and the surface resistance  $R_s(\omega, H)$  are obtained in the nonequilibrium dirty limit for which  $\sigma_1(H)$  has a significant minimum as a function of a low-frequency ( $\hbar\omega \ll k_B T$ ) magnetic field  $H$ . The calculated microwave suppression of  $R_s(H)$  is in good agreement with recent experiments on alloyed Nb resonator cavities. It is shown that superimposed dc and ac fields,  $H = H_0 + H_a \cos \omega t$ , can be used to reduce ac dissipation in thin film nanostructures by tuning  $\sigma_1(H_0)$  with the dc field.

PACS numbers: 74.25.-q, 74.25.Ha, 74.25.Op, 74.78.Na

One of the hallmarks of superconductivity is that static magnetic fields  $H$  induce screening currents which break Cooper pairs and reduce the transition temperature  $T_c$  [1]. This manifests itself in the nonlinear Meissner effect [2] and intermodulation [3] which have been observed on high- $T_c$  cuprates [4, 5]. Behavior of a superconductor becomes far more complex under the alternating field  $H = H_a \cos \omega t$  which not only induces pairbreaking currents, but also drives the quasiparticles out of equilibrium, particularly if the frequency  $\omega$  exceeds the superconducting gap  $\Delta$  [6]. Microwave absorption can produce nonequilibrium states with higher  $T_c$  and the critical current  $I_c$  as has been observed on thin films and tunnel junctions [7, 8]. The effect of nonequilibrium Andreev states on the Josephson current-phase relation and  $I_c$  in superconducting weak links and hybride nanostructures has recently attracted much interest [9–11].

At low temperatures  $T \ll T_c$  and frequencies  $\omega \ll \Delta$ , the small density of quasiparticles affects neither  $T_c$  nor the dynamics of superconducting condensate, yet the effects of oscillating superflow and nonequilibrium quasiparticle states on dissipative kinetic coefficients cause a strong field dependence of the surface resistance  $R_s(H)$ . Usually  $R_s$  increases with the amplitude of the radio-frequency (rf) field [4, 5], consistent with the expected enhancement of dissipation by pairbreaking currents, electron overheating, penetration of vortices, etc. A remarkable departure from this conventional scenario is the puzzling reduction of  $R_s$  by the rf field, which has been observed on many superconductors. For instance,  $R_s$  measured on the Nb resonator cavities at 2K and 1-2 GHz typically decreases by 10-20 % at  $H \simeq 20 - 30$  mT and then increases at higher fields [12, 13]. Moreover, the Nb resonators alloyed with Ti [14] or N [15] impurities can exhibit even stronger microwave suppression of  $R_s$  (by  $\simeq 50 - 70\%$  at 2K) which extends to the fields  $H \simeq 90 - 100$  mT at which the density of screening currents  $J \simeq H/\lambda$  reaches  $\simeq 50\%$  of the pairbreaking limit  $J_d \simeq H_c/\lambda$ , where  $H_c$  is the thermodynamic critical field, and  $\lambda$  is the London penetration depth (see Fig. 1). Re-

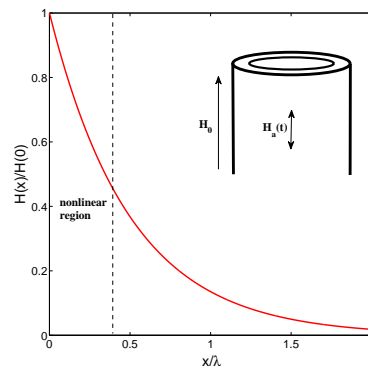


FIG. 1: Penetration of a parallel rf field into a superconductor. The dashed line depicts a layer where the current pairbreaking is essential. Inset shows a thin film ( $d < \lambda$ ) deposited onto a cylindrical substrate in a superimposed dc and rf fields.

duction of  $R_s$  by dc or microwave fields has also been observed on thin films [16–18]. The behavior of  $\sigma_1(H)$  at  $T \ll T_c$  is related to the fundamental limits of dissipation which controls decoherence in Josephson qubits [19] or performance of resonator cavities for particle accelerators [12] or microresonators [20].

In this work a theory of nonlinear conductivity and the microwave suppression of  $R_s$  in dirty s-wave superconductors is proposed. Here the electromagnetic response at weak fields is described by the local ohmic relation  $\mathbf{J}(\mathbf{r}, \omega) = [\sigma_1(\omega) - i\sigma_2(\omega)]\mathbf{E}(\mathbf{r}, \omega)$ , where  $\sigma_2 = 1/\mu_0\lambda^2\omega$ , and  $\sigma_1$  is the quasiparticle conductivity [21]

$$\sigma_1 = (2\sigma_n\Delta/T) \ln(CT/\omega)e^{-\Delta/T}, \quad T \ll T_c, \quad (1)$$

where  $\sigma_n$  is the normal state conductivity,  $C = 4e^{-\gamma} \approx 9/4$ ,  $\gamma = 0.577$ , and  $e = 2.78$ . The logarithmic term in Eq. (1) comes from the convolution of the BCS density of states  $\sigma_1 \propto \int N(\epsilon)N(\epsilon + \omega)e^{-\epsilon/T}d\epsilon$  which diverges at  $\omega = 0$  and  $N(\epsilon) = N_0\epsilon(\epsilon^2 - \Delta^2)^{-1/2}$  [21], so smearing the gap singularities in  $N(\epsilon)$  decreases  $\sigma_1$  at  $\omega \ll T$ .

The broadening of the gap peaks in  $N(\epsilon)$  and the re-

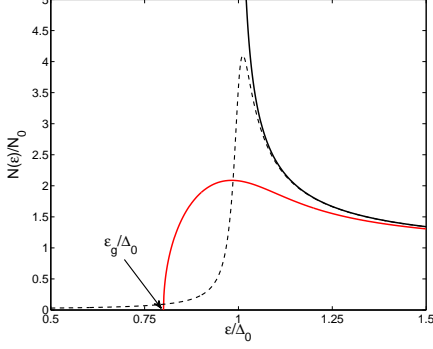


FIG. 2: The effect of current on the density of states calculated from Eqs. (6)-(8) at  $s = 0.2$ . The dashed line shows  $N(\epsilon) = N_0 \text{Re}[(\epsilon - i\gamma)/\sqrt{(\epsilon - i\gamma)^2 - \Delta_0^2}]$  at  $\gamma = 0.02\Delta_0$ .

duction of a quasiparticle gap  $\epsilon_g$  can be caused by current [1] or by magnetic impurities [22] which break the time reversal symmetry of pairing electrons. Particularly, the effect of dc current on  $N(\epsilon)$  shown in Fig. 2 was observed by tunneling spectroscopy [23], in full agreement with the theory [24]. Under strong rf current,  $N(\epsilon, t)$  oscillates between two solid curves in Fig. 2, so the peak in  $\langle N(\epsilon) \rangle$  averaged over the rf period is smeared out within the energy region  $\epsilon_g < \epsilon \lesssim \Delta$  of width  $\delta\epsilon = \Delta - \epsilon_g \sim (J/J_d)^{4/3}\Delta$  at  $J \ll J_d$  [23, 24]. This picture gives insight into one of mechanisms of microwave reduction of  $\sigma_1$ : as the current-induced width  $\delta\epsilon$  exceeds  $\omega$ , the energy cutoff in the logarithmic term in Eq. (1) changes from  $\omega$  to  $\delta\epsilon$ . Hence,  $\sigma_1 \propto \ln[(J_d/J)^{4/3}T/T_c]$  decreases with  $J$  if  $J > (\omega/\Delta)^{3/4}J_d$  and  $\omega \ll T$ , so that the decrease of  $\epsilon_g$  in the Boltzmann factor  $e^{-\epsilon_g/T}$  has a smaller effect on  $\sigma_1(H)$  at  $J < (T/\Delta)^{3/4}J_d$  since  $\delta\epsilon < T$ . For instance,  $\omega/T \sim 2 \cdot 10^{-2}$  at 1 GHz at 2K.

A theory of  $\sigma_1(H)$  must address both the pairbreaking and nonequilibrium effects caused by microwaves. Most of the previous works have focused on nonequilibrium states caused by absorption of photons by quasiparticles while neglecting the effect of rf superflow on  $N(\epsilon)$  at weak fields  $H \ll (\omega/\Delta)^{3/4}H_c$  and  $\omega \gtrsim T$  [7, 8]. Here  $\sigma_1(H)$  can be described by the linear response theory [21] but with a nonequilibrium quasiparticle distribution function  $f(\epsilon, H)$  calculated from a kinetic equation. Using this approach, it was shown recently that  $\sigma_1(H)$  can decrease with  $H_a$  as the quasi-particle population spreads to higher energies  $\epsilon \gtrsim T$  [18], similar to the mechanism of stimulated superconductivity [25]. This result was used to explain the reduction of  $\sigma_1$  with  $H_a$  observed on Al films at 5.3GHz at 350 mK [18]. Here I consider a fundamentally different mechanism of microwave suppression of  $\sigma_1(H)$  at strong, low-frequency fields with  $\omega \ll T$  and  $H > (\omega/\Delta)^{3/4}H_c$  for which the effect is due to the time-dependent  $N(\epsilon, t)$  and a nonequilibrium distribution function controlled by oscillating superflow. In this

case the Mattis-Bardeen theory is no longer applicable and  $\sigma_1(H)$  is to be re-derived using the Keldysh technique of nonequilibrium Green functions [6]. It is what was done in this work where the nonlinear conductivity  $\sigma_1(H)$  was calculated for two cases: 1. A weak ac field superimposed onto the dc field  $H(t) = H_0 + H_a \cos \omega t$ , where the dc superflow can be used to tune  $\sigma_1(H_0)$ ; 2. Parallel rf field  $H(t) = H_a \cos \omega t$ , as shown in Fig. 1.

In a type-II superconductor ( $\lambda \gg \xi$ ) considered here the rf field with  $\omega \ll T$  does not generate new quasiparticles while  $H(x, t)$  varies slowly over the coherence length  $\xi$ . In this case the dependence of  $\mathbf{J}(\mathbf{r}, t)$  on the vector potential  $\mathbf{A}(\mathbf{r}, t)$  is local but nonlinear and time-dispersive. It can be expressed in terms of nonequilibrium matrix Green functions  $\check{G}(t, t', \mathbf{r})$  which satisfy the time-dependent Usadel equation coupled with kinetic equations taking into account scattering of quasiparticles on phonons [6, 9, 26]. The nonlinear conductivity  $\sigma_1 = 2\langle \mathbf{J}\mathbf{E} \rangle / E_a^2$  is calculated in the Supplemental material [27] by averaging the dissipated power over the rf period of slowly oscillating superflow at  $\omega \ll T$  and  $(H/H_c)^2 \ll 1$ . Here  $\mathbf{E} = -\partial_t \mathbf{A} = \mathbf{E}_a \sin \omega t$  is the electric field,  $\check{G}[\epsilon, Q(t)]$  depends on the local current density  $\mathbf{J}(\mathbf{r}, t) = -\phi_0 \mathbf{Q}(\mathbf{r}, t) / 2\pi\mu_0\lambda^2$ , where  $\mathbf{Q} = \nabla\chi + 2\pi\mathbf{A}/\phi_0$ ,  $\phi_0$  is the flux quantum,  $\chi$  is the phase of the order parameter,  $\Delta(y) = \Delta e^{iQ(t)y}$ . The normal and anomalous Green functions are parameterized by  $G^R = \cosh(u + iv)$  and  $F^R = e^{iQy} \sinh(u + iv)$ , where  $u$  and  $v$  satisfy the quasi-static Usadel equation [6, 9]:

$$\epsilon + is \cosh(u + iv) = \Delta \coth(u + iv), \quad (2)$$

$$s(t) = DQ^2/2 = e^{-2x/\lambda} \beta(t) \Delta_0. \quad (3)$$

Here  $\beta(x, t) = (H/2H_c)^2 = (J/2J_d)^2 \ll 1$ ,  $D$  is the electron diffusivity,  $H_c = \phi_0/2^{3/2}\pi\mu_0\lambda\xi$ ,  $\xi = (D/\Delta_0)^{1/2}$ , and  $\Delta_0 = \Delta(T=0, Q=0)$ . A correction to  $Q$  due to the nonlinear Meissner effect [2] is disregarded.

The rf conductivity for the weak rf field superimposed onto the dc field is given by [27]

$$\sigma_1(H_0) = \frac{2\sigma_n}{\omega} \left(1 - e^{-\omega/T}\right) \int_{\epsilon_g}^{\infty} e^{-\epsilon/T} M(\epsilon, \omega, s) d\epsilon, \quad (4)$$

$$M(\epsilon, \omega, s) = \cos v_\epsilon \cos v_{\epsilon+\omega} \cosh(u_\epsilon + u_{\epsilon+\omega}), \quad (5)$$

where the spectral function  $M(\epsilon, \omega, s)$  incorporates the effect of dc superflow on  $N(\epsilon, Q)$  and the coherence factors. Here  $u_\epsilon$  and  $v_\epsilon$  are defined by the real and imaginary parts of Eq. (2) which yields the cubic equation  $\sinh^3 2u + [(\epsilon^2 - \Delta^2)/s^2 + 1] \sinh 2u - 2\epsilon\Delta/s^2 = 0$  with the following Cardano solution:

$$\sinh 2u = [(r + \epsilon\Delta s)^{1/3} - (r - \epsilon\Delta s)^{1/3}]/s, \quad (6)$$

$$r = [\epsilon^2\Delta^2s^2 + (\epsilon^2 + s^2 - \Delta^2)^3/27]^{1/2}, \quad (7)$$

$$\sin v = [-\Delta + (\Delta^2 - s^2 \sinh^2 2u)^{1/2}]/2s \cosh u \quad (8)$$

The quasiparticle density of states and the gap energy  $\epsilon_g$  at which  $N(\epsilon)$  vanishes (see Fig. 2), are given by

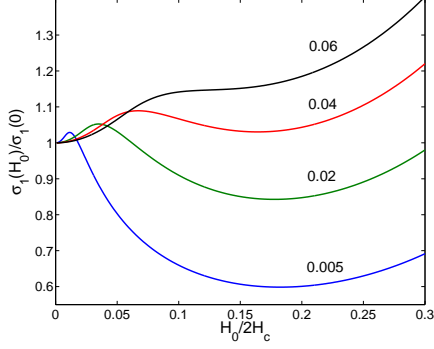


FIG. 3: Linear conductivity  $\sigma_1(H_0)$  calculated from Eqs. (4)-(9) for  $\omega/\Delta_0$ : 0.005, 0.02, 0.04, 0.06, and  $T/\Delta_0 = 0.1$ .

$N(\epsilon) = N_0 \cosh u \cos v$ , and [24]:

$$\epsilon_g^{2/3} = \Delta^2/3 - s^2/3, \quad \Delta = \Delta_0 - \pi s/4, \quad (9)$$

where  $\Delta$  is obtained from the BCS gap equation at  $T = 0$  in the first order in  $s$  [27]. Here  $\epsilon_g(H_0)$  decreases with  $H_0$  but remains finite ( $\epsilon_g \simeq 0.3\Delta_0$ ) even at the maximum superheating field  $H_{sh} \approx 0.84H_c$  for the Meissner state [28]. Shown in Fig. 3 is the linear rf conductivity  $\sigma_1(H_0)$  biased by a dc superflow calculated from Eqs. (4)-(9). At  $H_0 = 0$  and  $H_a \ll (\omega/\Delta)^{3/4}H_c$ , Eqs. (4)-(9) reproduce Eq. (1), but at higher field  $\sigma_1(H_0)$  has a minimum which becomes more pronounced as  $\omega$  decreases. This behavior is due to interplay of the current-induced broadening of the gap peak in  $N(\epsilon, s)$  and the reduction of  $\epsilon_g$  shown in Fig. 2. As a result,  $\sigma_1$  becomes dependent on  $H_0$  if  $H_0 > (\omega/\Delta)^{3/4}H_c$  and reaches minimum at  $H_0 \sim (T/T_c)^{3/4}H_c \ll H_c$ . The field region  $(\omega/\Delta_0)^{3/4}H_c < H_0 < (T/\Delta_0)^{3/4}H_c$  where  $\sigma_1(H_0)$  decreases with  $H_0$  shrinks as  $\omega$  increases and disappears at  $\omega > T$ , as shown in Fig. 3.

Calculation of the nonlinear conductivity  $\sigma_1(H_a)$  at a strong rf field  $H(t) = H_a \cos \omega t$  requires taking temporal oscillations of  $N(\epsilon, t)$  and  $f(\epsilon, t)$  into account. Here  $\sigma_1(H_a) = 2\langle \mathbf{J}\mathbf{E} \rangle / E_a^2$  is defined as before by averaging the power over the rf period [27]:

$$\sigma_1(H_a) = \frac{2\sigma_n}{\pi} \int_0^{\pi/\omega} dt \int_{\epsilon_g(t)}^\infty [f(\epsilon, s) - f(\epsilon + \omega, s)] M d\epsilon, \quad (10)$$

where  $M[\epsilon, \omega, s(t)]$  is given by Eq. (5). Solving the kinetic equation for  $f(\epsilon, s)$  with time-dependent parameters and the electron-phonon collision integral [6] is a very complicated problem, so I only consider here the case of  $\min(\tau_r^{-1}, \tau_s^{-1}) \ll \omega \ll T$  for which the rf period is shorter than either the recombination time  $\tau_r$  and the scattering time  $\tau_s$  of quasiparticles on phonons [29]

$$\tau_r = \tau_1(T_c/T)^{1/2}e^{\Delta/T}, \quad \tau_s = \tau_2(T_c/T)^{7/2}, \quad (11)$$

where  $\tau_1$  and  $\tau_2$  are materials constants. Taking  $\Delta = 1.9T_c$ ,  $T_c = 9.2\text{K}$ ,  $\tau_1 \simeq 3 \cdot 10^{-12}\text{ s}$  and  $\tau_2 \simeq 8 \cdot 10^{-11}\text{ s}$  for

Nb [29], yields  $\tau_r \sim 0.4 \mu\text{s}$  and  $\tau_s \simeq 1.7 \cdot 10^{-8}\text{ s}$  at 2K. The condition  $\tau_s^{-1} < \omega < T$  that the quasiparticle density does not change during the rf period, can be satisfied in a frequency range, (0.06 – 44 GHz) relevant to many experiments [12, 19, 20].

The distribution function  $f(\epsilon, t)$  can be obtained from the following consideration. As  $s(t)$  increases,  $N(\epsilon, s)$  extends to lower energies as shown in Fig. 2, but because the quasiparticles do not scatter during the rf period if  $\omega\tau_s \gg 1$ , the probability to occupy the energy state  $\epsilon$  moved from the state  $\tilde{\epsilon}$  at  $s = 0$  does not change. The relation between  $\tilde{\epsilon}$  and  $\epsilon$  follows from the conservation of states:  $\int_{\epsilon_g}^\epsilon N(\epsilon, s) d\epsilon = \int_{\Delta_0}^{\tilde{\epsilon}} N(\epsilon, 0) d\epsilon = N_0(\tilde{\epsilon}^2 - \Delta_0^2)^{1/2}$ , giving  $\tilde{\epsilon}^2 = \Delta_0^2 + [\int_{\epsilon_g}^\epsilon \cosh u \cos v d\epsilon]^2$ . The function  $f(\tilde{\epsilon})$  ensures that the quasiparticle density  $n_{qp} = \int f(\tilde{\epsilon}) N(\epsilon, s) d\epsilon = \int_0^\infty f[\tilde{\epsilon}(\psi)] d\psi$  does not change during the rf period, where  $\psi = \int_{\epsilon_g}^\epsilon N(\epsilon, s) d\epsilon$ . Then the condition  $f(\epsilon, s) = \exp(-\tilde{\epsilon}/T)$  at  $s(t) = 0$  yields

$$f = \exp\left[-\frac{1}{T}(\Delta_0^2 + [\int_{\epsilon_g}^\epsilon \cosh v_\epsilon \cosh u_\epsilon d\epsilon]^2)^{1/2}\right] \quad (12)$$

The quasiparticle temperature  $T$  at  $\omega\tau_s \gg 1$  is defined by the stationary power balance,  $R_s H_a^2/2 = h(T_i - T_0) = Y(T - T_i)$ . Here  $T_i$  is the lattice temperature,  $T_0$  is the ambient temperature,  $h = \kappa h_K/(dh_K + \kappa)$  accounts for heat transfer due to thermal conductivity  $\kappa$  and the Kapitza interface conductance  $h_K$  across a film of thickness  $d$ , and  $Y(T)$  quantifies the energy transfer rate from quasi-particle to phonons [30]. For weak overheating, the heat transfer may be linearized in  $T - T_0 \ll T_0$ :

$$T - T_0 = \frac{\alpha T_0}{R_{s0}} \left(\frac{H_a}{H_c}\right)^2 R_s(H_a, T), \quad (13)$$

$$\alpha = \frac{R_{s0} B_c^2}{2\mu_0^2 T_0} \left(\frac{1}{Y} + \frac{d}{\kappa} + \frac{1}{h_K}\right), \quad (14)$$

where  $Y$ ,  $h$  and  $R_{s0} = R_s(T_0)$  are taken at  $T = T_0$  and  $H_a = 0$ . The surface resistance  $R_s(T, H_a)$  is calculated by integrating the local power  $R_s H_a^2/2 = (\mu_0 \omega \lambda H_a)^2 \int_0^\infty e^{-2x/\lambda} \sigma_1(\beta) dx$ . Changing here to integration over  $\beta = \beta_0 e^{-2x/\lambda}$  defined by Eq. (3) yields

$$R_s = \frac{\mu_0^2 \omega^2 \lambda^3}{2\beta_0} \int_0^{\beta_0} \sigma_1(\beta) d\beta. \quad (15)$$

Equations (10) and (12)-(15) determine self-consistently  $R_s(H_a, T)$  and  $T(H_a)$ . Shown in Fig. 4a is  $\sigma_1(H_a)$  calculated from Eqs. (10)-(14) for different values of  $\alpha$ . The field dependence of  $\sigma_1(H_a)$  is similar to that of  $\sigma_1(H_0)$  in Fig. 3: in both cases the current-induced smearing of  $N(\epsilon)$  reduces  $\sigma_1(H)$ , but the mechanisms of the increase of  $\sigma_1(H)$  at higher fields are different. For a weak rf field superimposed onto the dc field, the increase of  $\sigma_1(H_0)$  results from the reduction of  $\epsilon_g(H)$ , while the increase

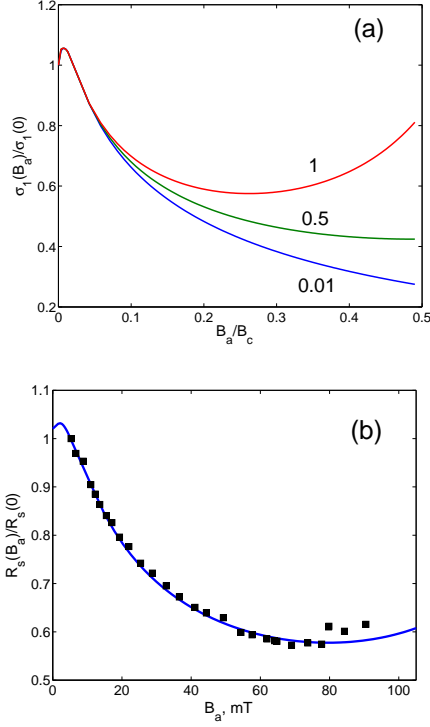


FIG. 4: (a)  $\sigma_1(B_a)$  calculated from Eqs. (10)-(15) at  $T/\Delta_0 = 0.1$ ,  $\omega/\Delta_0 = 0.0025$  and  $\alpha = 0.01, 0.5$ , and  $1$ . (b)  $R_s(B_a)$  calculated for  $\alpha = 0.91$ ,  $T_0 = 2$  K,  $\Delta_0 = 17.5$  K and  $B_c = 200$  mT. The dots show the experimental data for the Nb cavity at 1.75 GHz [14]. The quench at  $B_a \approx 90$  mT  $\approx 0.5B_c$  is likely due to penetration of vortices at surface defects.

of  $\sigma_1(H_a)$  in Fig. 4a is due to overheating: the condition that the density of quasiparticles does not change during the rf cycle greatly enhances the microwave reduction of  $\sigma_1(H_a)$ . If  $\omega \ll [\tau_s^{-1}(T), \tau_r^{-1}(T)]$  the minimum in  $\sigma_1(H_a)$  is controlled by the field reduction of  $\epsilon_g(H_a)$  as  $f(\epsilon) \rightarrow \exp(-\epsilon/T)$  in Eq. (10).

Shown in Fig. 4b is  $R_s(B_a)$  calculated from Eqs. (10) and (12)-(15) to fit the experimental data of Ref. [14] with only one adjustable parameter  $\alpha = 0.91$  for which the overheating  $T - T_0 \approx 0.17$  K calculated from Eq. (13) is indeed weak even at  $B_a = 80$  mT,  $R_s(B_a)/R_{s0} = 0.6$  and  $T_0 = 2$  K. This theory describes well the microwave suppression of  $R_s$  observed on Ti-alloyed Nb cavities [14]. For  $R_s = 20$  n $\Omega$ ,  $\kappa = 10$  W/mK,  $h_K = 5$  kW/m<sup>2</sup>K at 2 K and  $d = 3$  mm [14], the phonon heat transfer in Eq. (14) can only account for  $\alpha \approx 0.06$ . The larger value of  $\alpha = 0.91$  used to fit  $R_s(H_a)$  in Fig. 4b indicates a significant role of electron overheating [27, 30].

The parameters  $Y(T)$ ,  $\tau_s$  and  $\tau_r$  are not only controlled by the scattering and recombination of quasiparticles [29, 30], but also by the smearing of the gap peak in  $N(\epsilon)$  due to inhomogeneities, inelastic scattering or impurities [22, 31], which can make  $Y$  very sample-dependent. Interplay of the subgap states and current pairbreaking

can bring about competing mechanisms of nonlinearity of  $R_s(H_a)$ , since the subgap states can cause both a finite  $\tau_r$  at  $T \rightarrow 0$  [32] and a residual conductivity [33]. In any case, the microwave suppression of  $R(H_a)$  is more pronounced for sharper gap peaks in  $N(\epsilon)$  at  $H_a = 0$ , so that  $\tau_s$  and  $\tau_r$  are not much reduced and the current-induced broadening of  $N(\epsilon)$  takes over at comparatively low fields (see Fig. 2). This conclusion is consistent with the observed variability of the field-induced reduction of  $R_s(H_a)$  [12–15] and the tunneling measurements [14] which revealed fewer subgap states in  $N(\epsilon)$  for the Nb resonators exhibiting the significant minimum in  $R_s(H_a)$  shown in Fig. 4b. A dc field applied parallel to a thin film can be used to tune  $\sigma_1(H_0)$  and separate current pairbreaking from nonequilibrium effects [16, 34].

In conclusion, a theory of nonlinear conductivity of dirty superconductors at low temperatures and strong rf electromagnetic field is developed. The theory explains the effect of the field-induced suppression of surface resistance, in excellent agreement with recent experiments.

This work was supported by DOE HEP under the grant No. DE-SC0010081.

- 
- [1] J. Bardeen, Rev. Mod. Phys. **34**, 667 (1962).
  - [2] D. Xu, S. K. Yip and J. A. Sauls, Phys. Rev. B **51**, 16233 (1995); M. R. Li, P. J. Hirschfeld, and P. Wölfle, Phys. Rev. Lett. **81**, 5640 (1998); Phys. Rev. B **61**, 648 (2000).
  - [3] T. Dahm and D. J. Scalapino, J. Appl. Phys. **81**, 2002 (1997); Phys. Rev. B **60**, 13125 (1999).
  - [4] M. A. Hein, "Microwave properties of superconductors", NATO ASI Series, v.375, 21-53 (2002).
  - [5] D.E. Oates, J. Supercond. Novel Magn. **20**, 3 (2007).
  - [6] N. B. Kopnin, *Theory of Nonequilibrium Superconductivity*, University Press, Oxford (2001).
  - [7] J.E. Mooij, in *Nonequilibrium Superconductivity, Phonons and Kapitza Boundaries*, edited by K.E. Gray (Plenum, New York, 1981) p.191.
  - [8] V.M. Dmitriev, V.N. Gubankov, and F.Y. Nad', in *Nonequilibrium Superconductivity*, edited by D.N. Langenberg and A.I. Larkin (North Holland, Amsterdam 1986), p. 163.
  - [9] W. Belzig, F. K. Wilhelm, C. Bruder, G. Schön, A. D. Zaikin, Superlatt. & Microstruct. **25**, 1251 (1999).
  - [10] F. S. Bergeret, P. Virtanen, T. T. Heikkilä, and J. C. Cuevas, Phys. Rev. Lett. **105**, 117001 (2010); F. S. Bergeret, P. Virtanen, A. Ozaeta, T. T. Heikkilä, and J. C. Cuevas, Phys. Rev. B **84**, 224517 (2011).
  - [11] F. Kos, S. E. Nigg, and L. I. Glazman, Phys. Rev. B **87**, 174521 (2013).
  - [12] H. Padamsee, *RF Superconductivity: Science, Technology and Applications* (Wiley-VCH Verlag GmbH and Co. KGaA, Weinheim, 2009).
  - [13] A. Gurevich, Rev. Accel. Sci. Technol. **5**, 119 (2012).
  - [14] P. Dhakal, G. Ciovati, G. R. Myneni, K. E. Gray, N. Groll, P. Maheshwari, D. M. McRae, R. Pike, T. Proslir, F. Stevie, R. P. Walsh, Q. Yang, and J. Zasadzinski, Phys. Rev. ST-AB **16**, 042001 (2013).

- [15] A. Grassellino, A. Romanenko, D. Sergatskov, O. Melnychuk, Y. Trenikhina, A. Crawford, A. Rowe, M. Wong, T. Khabiboulline, and F. Barkov, *Supercond. Sci. Technol.* **26**, 102001 (2013).
- [16] S. Sridhar and J. E. Mercerau, *Phys. Rev. B* **34**, 203 (1986).
- [17] M. A. Hein, D. E. Oates, P. J. Hirst, R. G. Humphreys, A. V. Velichko, *Appl. Phys. Lett.* **80**, 1007 (2002).
- [18] P. J. de Visser, D. J. Goldie, P. Diener, S. Withington, J.J.A. Baselmans, and T. M. Klapwijk, *Phys. Rev. Lett.* **112**, 047004 (2014).
- [19] M. Reagor, H. Paik, G. Catelani, L. Sun, C. Axline, E. Holland, I.M. Pop, N.A. Masluk, T. Brecht, L. Frunzio, M.H. Devoret, L. Glazman, and R.J. Schoelkopf, *Appl. Phys. Lett.* **102**, 192604 (2013).
- [20] J. Zmuidzinas, *Annu. Rev. Cond. Mat. Phys.* **3**, 169 (2012).
- [21] D. C. Mattis and J. Bardeen, *Phys. Rev.* **111**, 412 (1958); C. B. Nam, *Phys. Rev.* **156**, 470, 487 (1967).
- [22] Ya. V. Fominov, M. Houzet, and L. I. Glazman, *Phys. Rev. B* **84**, 224517 (2011); M. Kharitonov, T. Proslie, A. Glatz, and M.J. Pellin, *Phys. Rev. B* **85**, 024514 (2012).
- [23] A. Anthore, H. Pothier, and D. Esteve, *Phys. Rev. Lett.* **90**, 127001 (2003).
- [24] P. Fulde, *Phys. Rev.* **137**, A783 (1965).
- [25] B. I. Ivlev, S. G. Lisitsyn, and G. M. Eliashberg, *J. Low Temp. Phys.* **10**, 449 (1973).
- [26] A. I. Larkin and Yu. N. Ovchinnikov, *In Nonequilibrium Superconductivity*, edited by D.N. Langenberg and A.I. Larkin (North Holland, Amsterdam 1986), p. 493.
- [27] See supplemental material.
- [28] F. Pei-Jen Lin and A. Gurevich, *Phys. Rev. B* **85**, 054513 (2012).
- [29] S. B. Kaplan, C. C. Chi, D. N. Langenberg, J. J. Chang, S. Jafarey, and D. J. Scalapino *Phys. Rev. B* **14**, 4854 (1976).
- [30] A.V. Timofeev, C. Pascual García, N. B. Kopnin, A. M. Savin, M. Meschke, F. Giazotto, and J. P. Pekola *Phys. Rev. Lett.* **102**, 017003 (2009).
- [31] A.I. Larkin and Yu.N. Ovchinnikov, *JETP* **34**, 1144 (1972); D.A. Browne, K. Levin and K.A. Muttalib, *Phys. Rev. Lett.* **58**, 156 (1987); T.P. Deveraux and D. Belitz, *Phys. Rev. B* **44**, 4587 (1999); J.S. Meyer and B.D. Simons, *Phys. Rev. B* **64**, 134516 (2001).
- [32] R. Barends, J. J. A. Baselmans, S. J. C. Yates, J. R. Gao, J. N. Hovenier, and T. M. Klapwijk, *Phys. Rev. Lett.* **100**, 257002 (2008).
- [33] E. F. C. Driessen, P. C. J. J. Coumou, R. R. Tromp, P. J. de Visser, and T. M. Klapwijk, *Phys. Rev. Lett.* **109**, 107003 (2012).
- [34] N. Groll, A. Gurevich, and I. Chiorescu, *Phys. Rev. B* **81**, 020504(R) (2010).