



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Electron Spin Coherence of Shallow Donors in Natural and Isotopically Enriched Germanium

A. J. Sigillito, R. M. Jock, A. M. Tyryshkin, J. W. Beeman, E. E. Haller, K. M. Itoh, and S. A. Lyon

Phys. Rev. Lett. **115**, 247601 — Published 7 December 2015

DOI: [10.1103/PhysRevLett.115.247601](https://doi.org/10.1103/PhysRevLett.115.247601)

Electron spin coherence of shallow donors in natural and isotopically enriched germanium

A. J. Sigillito,^{1,*} R. M. Jock,¹ A. M. Tyryshkin,¹ J. W. Beeman,² E. E. Haller,^{3,2} K. M. Itoh,⁴ and S. A. Lyon¹

¹*Department of Electrical Engineering, Princeton University, Princeton, New Jersey 08544, USA*

²*Materials Sciences Division, Lawrence Berkeley National Laboratory, Berkeley, California 94720, USA*

³*Department of Materials Science and Engineering,*

University of California, Berkeley, California 94720, USA

⁴*School of Fundamental Science and Technology, Keio University,*

3-14-1 Hiyoshi, Kohoku-ku, Yokohama 223-8522, Japan

(Dated: November 9, 2015)

Germanium is a widely used material for electronic and optoelectronic devices and recently it has become an important material for spintronics and quantum computing applications. Donor spins in silicon have been shown to support very long coherence times (T_2) when the host material is isotopically enriched to remove any magnetic nuclei. Germanium also has non-magnetic isotopes so it is expected to support long T_2 s while offering some new properties. Compared to Si, Ge has a strong spin-orbit coupling, large electron wavefunction, high mobility, and highly anisotropic conduction band valleys which will all give rise to new physics. In this Letter, the first pulsed electron spin resonance (ESR) measurements of T_2 and the spin-lattice relaxation (T_1) times for ^{75}As and ^{31}P donors in natural and isotopically enriched germanium are presented. We compare samples with various levels of isotopic enrichment and find that spectral diffusion due to ^{73}Ge nuclear spins limits the coherence in samples with significant amounts of ^{73}Ge . For the most highly enriched samples, we find that T_1 limits T_2 to $T_2 = 2T_1$. We report an anisotropy in T_1 and the ensemble linewidths for magnetic fields oriented along different crystal axes but do not resolve any angular dependence to the spectral-diffusion-limited T_2 in samples with ^{73}Ge .

Germanium was the original material for transistors, and is now being developed for the latest semiconductor electronics [1]. Recently, it has become a key material for spintronics [2–4] and quantum computing [5–7] devices. Compared to silicon, donor electrons in Ge have higher mobility (~ 3 times) [1], larger wavefunctions (6.5 nm compared to 2.5 nm), [8, 9], stronger spin-orbit coupling [10], and highly anisotropic conduction band valleys [6]. Much of silicon’s success in the quantum computing community has hinged on the attainability of long coherence times (T_2) exceeding seconds when Si is isotopically enriched to have no magnetic nuclei [11–14]. Germanium also has non-magnetic isotopes so it has been expected to support long coherence times. In this Letter, we report the first electron spin coherence measurements for donor electron spins in Ge. We find that spectral diffusion due to ^{73}Ge limits T_2 in natural Ge samples whereas the spin-lattice relaxation time, T_1 , limits T_2 in isotopically enriched Ge. The longest T_2 we measured is $T_2 = 2T_1 = 1.2$ ms at 350 mK in a magnetic field (B_0) of 0.44 T. The low-temperature T_1 fits the temperature dependence theorized by Roth [15] and Hasegawa [16] which also predicts $T_1 \propto B_0^{-4}$. This suggests that considerably longer coherence times are possible at lower fields.

While T_2 for donors in Ge is shorter than the times demonstrated for Si, Ge-based qubits have some important advantages. For example the larger electron wavefunctions relax the lithographic requirements for exchange coupling two donors which is important for most donor-based quantum computing schemes [17]. This is

advantageous considering Ge is compatible with most of the same nanofabrication techniques as silicon and single-donor devices are achievable [18]. Another useful feature of Ge is the large spin-orbit coupling and shallow donor depth which leads to a very large spin-orbit Stark shift in Ge (nearly 5 orders of magnitude larger than in silicon) [6] meaning that Ge based qubits are extremely tuneable. This will be important for gated quantum devices [17].

Despite these features, the spin coherence of donor electrons in Ge has remained mostly unstudied. The first experiments were conducted over fifty years ago by Feher, Wilson, and Gere [8, 19], but their measurements were limited to continuous wave (CW) ESR spectroscopy. They estimated T_1 for ^{75}As and ^{31}P donors based on power saturation measurements, but experimental errors were large. These experiments are difficult because wavefunction overlap occurs for densities as low as 10^{15} donors/cm³ such that only lightly doped samples with correspondingly weak signals are useful for isolated donor experiments. Some limited experiments on Sb [20, 21] and ^{31}P [22] donors in highly strained Ge were also reported. More recently, pulsed nuclear magnetic resonance studies were conducted on ^{73}Ge nuclear spins [23–25] which found that the ^{73}Ge nuclear spin coherence in germanium can be > 100 ms.

The samples discussed in this Letter include commercially available, natural Ge doped either 10^{15} As/cm³ or 10^{12} P/cm³. ^{73}Ge is the only naturally occurring isotope of Ge (7.75% abundance) with a nuclear spin and is thus expected to be a limiting factor in the donor spin coherence at low temperatures. Three isotopically enriched

samples were prepared at Lawrence Berkeley National Laboratory. The first is a piece of neutron transmutation doped ^{74}Ge described in Ref.[26, 27]. This sample is uniformly doped with ^{75}As to a density of 3×10^{15} donors/cm 3 and contains a residual 3.8% ^{73}Ge . The other two samples are 96% ^{70}Ge crystal (0.1% ^{73}Ge) and a 99.99% ^{70}Ge crystal (0.01% ^{73}Ge). They have ^{31}P concentrations of $\sim 10^{12}$ donors/cm 3 and $\sim 10^{11}$ donors/cm 3 , respectively and are described in [26, 28]. The crystallographic orientation of the samples was determined using X-ray diffraction. The sample details are summarized in Table I.

The experiments down to 1.65 K were performed in a pumped He cryostat (H.S. Martin), and lower temperature data were obtained in a ^3He cryostat (Janis Research). All data were taken at X-band (9.65 GHz) in a Bruker dielectric resonator (MD5). The ESR spectra were measured via echo-detected field sweeps using a standard Hahn-echo pulse sequence ($\pi/2 - \tau - \pi - \tau - \text{echo}$). Typical spectra are shown in Fig. 1(a) for phosphorus donors in the 0.1% ^{73}Ge :P sample and in Fig. 1(b) for arsenic donors in the 3.8% ^{73}Ge :As sample. From these plots we extract a hyperfine coupling constant of 3.55 mT for ^{75}As and 2.04 mT for ^{31}P .

The ESR linewidth depends strongly on the sample orientation and the abundance of ^{73}Ge present in the sample, as noted by Wilson [8]. With B_0 oriented along one of the $\langle 001 \rangle$ directions, the linewidth is narrowest and is limited primarily by hyperfine interactions with ^{73}Ge . At this orientation the line broadening from spin-orbit strain effects is suppressed by valley symmetry about the $\langle 001 \rangle$ as explained in Refs.[8, 15, 16]). To give a sense of the strain-induced line broadening for B_0 away from $[001]$ equivalent directions, Fig.1(c) shows the angular dependence of the linewidth for select samples rotated in the $(1\bar{1}0)$ plane relative to the $[001]$ axis. There is also an isotopic dependence of the linewidth away from the $\langle 001 \rangle$ direction and we presume this is due to isotopic strain [30]. The strong dependence of the linewidth on field orientation conveniently allows for accurate *in situ* orientation of the crystals. Unless otherwise noted, all data presented in this manuscript assumes B_0 is oriented along a $\langle 001 \rangle$ axis.

One can predict the effect of ^{73}Ge on the ESR linewidth through the hyperfine interaction using a second moment calculation [31], which gives $\Delta B \propto f^{1/2}$, where ΔB is the linewidth, and f is the percent abundance of ^{73}Ge . The measured ESR linewidths for samples of various isotopic enrichment with $B_0 \parallel \langle 001 \rangle$ is shown in Fig. 1(d). The point at $f = 0.8\%$ was taken from Wilson [8]. The solid curve in Fig. 1(d) gives the expected $f^{1/2}$ dependence for broadening of the line due to ^{73}Ge hyperfine interactions for ^{75}As . The solid curve fits the data well, implying that ^{73}Ge is indeed the dominant mechanism for line broadening in this orientation. The linewidth can be interpreted as an ensemble dephasing

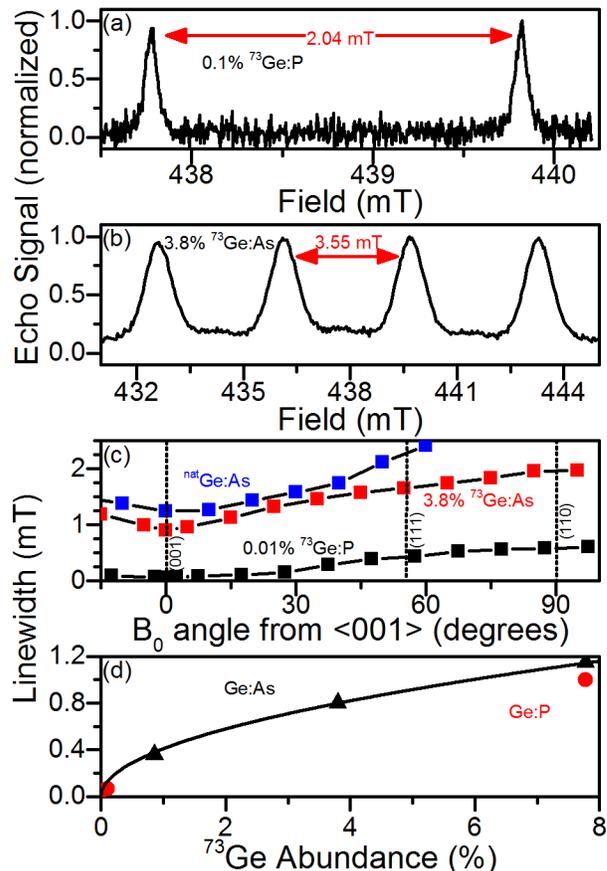


FIG. 1. (a) Echo-detected field sweep spectra for (a) 0.1% ^{73}Ge :P and (b) 3.8% ^{73}Ge :As with $B_0 \parallel \langle 001 \rangle$. (c) Plot of ESR linewidths as a function of field orientation for ^{nat}Ge :As (blue), 3.8% ^{73}Ge :As (red) and 0.01% ^{73}Ge :P (black). The solid lines serve only as guides to the eye. (d) Linewidth for $B_0 \parallel \langle 001 \rangle$ as a function of ^{73}Ge isotopic abundance. The Ge:As data appear as black triangles whereas the Ge:P data appear as red circles. The solid line shows the expected $f^{1/2}$ dependence for broadening due to ^{73}Ge hyperfine interactions. The ESR linewidth at 0.8% is taken from Ref. [8]. Data were taken at 1.8 K and 9.65 GHz.

time, T_2^* , which is also shown in Table I.

T_1 was measured using an inversion-recovery pulse sequence ($\pi - t - \pi/2 - \tau - \pi - \tau - \text{echo}$). The values of T_1 are plotted in Fig. 2 for ^{31}P (a) and ^{75}As (b) donors. The same two mechanisms limit T_1 for all of the samples. At higher temperatures, T_1 is limited by a highly temperature (T) dependent process. The theory of Roth and Hasegawa [15, 16] predicted a T^{-7} Raman process to dominate at these temperatures but this dependence does not fit our data well. An Orbach process does fit the data as shown in Fig. 2. The Orbach process is of the form $T_1 \propto a \times \exp(-\frac{E_{v.o.}}{kT})$, where a is a prefactor that can be calculated using Ref. [32], $E_{v.o.}$ is the valley-orbit splitting, and k is the Boltzmann constant. The valley-orbit splittings extracted from the T_1 fits in Fig. 2 agree well with the values measured by Ramdas (2.8 meV for

TABLE I. Sample Details

Sample Name	[⁷⁰ Ge]	[⁷² Ge]	[⁷³ Ge]	[⁷⁴ Ge]	[⁷⁶ Ge]	Doping (cm ⁻³)	[001] Linewidth (mT)	T_2^* (ns)
<i>nat</i> Ge:As*	20.57%	27.45%	7.75%	36.50%	7.73%	1×10^{15} As	1.2	11
<i>nat</i> Ge:P*	20.57%	27.45%	7.75%	36.50%	7.73%	$\sim 10^{12}$ P	1.1	13
3.8% ⁷³ Ge:As	0.1%	0.9%	3.8%	92.6%	2.6%	3×10^{15} As	0.8	17
0.1% ⁷³ Ge:P	96.3%	2.1%	0.1%	1.2%	0.3%	$\sim 10^{12}$ P	0.069	211
0.01% ⁷³ Ge:P	99.99%	-	0.01%	-	-	$\sim 10^{11}$ P	0.051	284
Nuclear Spin	0	0	9/2	0	0	-	-	-

*Percent abundances for the natural germanium samples were taken from Ref. [29]

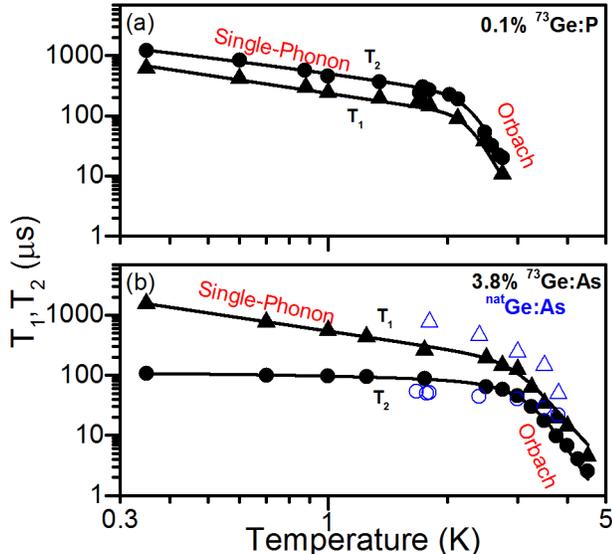


FIG. 2. Temperature dependence of T_1 (triangle) and T_2 (circle) for natural (open symbols) and isotopically-enriched (solid symbols) Ge with $B_0 \parallel \langle 001 \rangle$. The solid lines are fits for (a) phosphorus donors (0.1% ⁷³Ge:P) and (b) arsenic donors (3.8% ⁷³Ge:As), assuming two relaxation processes: a single-phonon (T^{-1}) process and an Orbach ($a \times \exp(\frac{E_{v,p}}{kT})$) process. For the T_2 fits, both T_1 and an additional (temperature independent) spectral diffusion mechanism due to ⁷³Ge were taken into account. Note that for the 0.1% ⁷³Ge:P sample, $T_2 = 2T_1$ down to the lowest temperatures.

³¹P and 4.2 meV for ⁷⁵As [33]). Likewise, the values of a extracted from our fits agree with the values calculated using Castner's theory [32] to within a factor of 2.

At lower temperatures, a single-phonon process with a T^{-1} dependence appears to dominate. This relaxation process is a result of the multivalley structure of germanium. In the unperturbed ground state, there are four degenerate valleys located along the $\langle 111 \rangle$ equivalent crystallographic axes. Each valley has an axially symmetric g-tensor, \vec{g}_i but the effective g-tensor, \vec{g}_{eff} , is given as a weighted average over all four valleys. In the electron ground state, each valley has equal amplitude, and, by symmetry, \vec{g}_{eff} is isotropic [15]. When strain is applied, valley energies shift relative to each other, leading to val-

ley repopulation and a change in \vec{g}_{eff} . The strain from phonons near the Larmor frequency modulates \vec{g}_{eff} , effectively mixing the spin up and down states. This gives a T_1 as calculated by Roth [15] and Hasegawa [16] which agrees well with our experimental data. The calculated estimates for T_1 at 350 mK are within 10% for Ge:As and 30% for Ge:P. The theory predicts that T_1 due to this single-phonon process should scale with the square of the \vec{g}_i anisotropy. The valley anisotropy of Ge was measured to be 3 orders of magnitude larger than in Si [8], implying that the single-phonon process should be 6 orders of magnitude stronger in germanium. This accounts for the short T_1 times observed for donors in germanium as compared with silicon.

An interesting property of the single-phonon spin-lattice relaxation mechanism is an anisotropy in T_1 predicted by the Roth-Hasegawa theory[15, 16]. The 3.8% ⁷³Ge:As crystal was rotated in the $(1\bar{1}0)$ plane at 1.8 K, and the resulting T_1 is plotted in Fig.3. The theory predicts that, for rotation in this plane, the spin-lattice relaxation is given by:

$$\frac{1}{T_1} = \alpha B_0^4 T (\cos^4(\theta) + \frac{1}{2} \sin^4(\theta)) \quad (1)$$

where α is a scaling factor which can be calculated following Hasegawa[16], and θ is the field orientation relative to $\langle 001 \rangle$. Hasegawa calculated $\alpha = 7.2 \times 10^4 K^{-1} s^{-1} T^{-4}$ for arsenic in Ge, but a fit to the data reveals $\alpha = 4.1 \times 10^4 K^{-1} s^{-1} T^{-4}$. We observe that for B_0 oriented along a $\langle 111 \rangle$ axis, T_1 becomes 3 times longer than along $\langle 001 \rangle$.

We note that T_1 for donors in highly enriched samples is shorter than it is for donors in the natural material as seen in Fig. 2(b). This effect is still under investigation, but one possible mechanism is the presence of isotopic strain in the natural germanium[30]. Wilson [8] demonstrated the use of large strains to partially lift the valley degeneracy, thus disrupting the single-phonon relaxation mechanism. Modelling the effects of strain can be complex, as strain not only modulates α , but can also modify the form of Eq.(1). Nevertheless, controlled strain may be beneficial for future quantum devices based on germanium.

We also measured the electron spin coherence time,

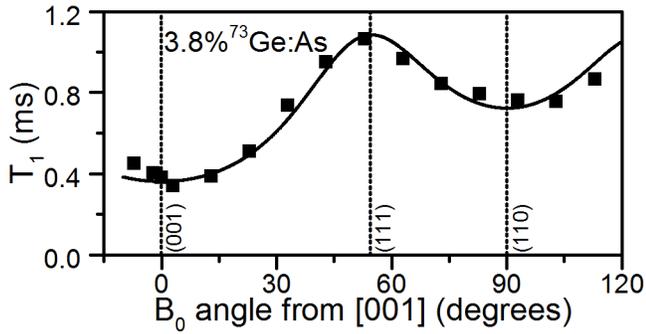


FIG. 3. Angular dependence of T_1 for the 3.8% $^{73}\text{Ge}:\text{As}$ sample rotated in the $(\bar{1}10)$ plane at 1.8 K. The curve is a fit using Eq.(1) assuming $\alpha = 4.1 \times 10^4 \text{ K}^{-1} \text{ s}^{-1} \text{ T}^{-4}$.

T_2 , for each of the samples using the standard Hahn-echo pulse sequence. The decay curves at 1.8 K for $B_0 \parallel \langle 001 \rangle$ are shown in Fig. 4(a) for Ge:P and in Fig. 4(b) for Ge:As. These decays are fit to an exponential decay of the form $Ae^{-(2\tau/T_2)^n}$, where A scales the amplitude, τ is the delay between the $\pi/2$ and π pulses in the Hahn echo sequence, and n is a fitting parameter that depends on the decoherence mechanism. The 0.1% $^{73}\text{Ge}:\text{P}$ sample decays with $n=1$ over the measured temperature range. For this sample it was found that $T_2 = 2T_1$ (representing the absolute T_1 limit [34]) down to 350 mK temperatures, meaning that decoherence due to ^{73}Ge is negligibly small with this level of isotopic enrichment at these temperatures. For samples with $f \geq 3.8\%$, we find that n varies from 1 at high temperatures to 2.1 at low temperatures. This is a characteristic of ^{73}Ge spectral diffusion limiting the coherence. At 1.8 K, the $^{nat}\text{Ge}:\text{As}$, $^{nat}\text{Ge}:\text{P}$, and 3.8% $^{73}\text{Ge}:\text{As}$ samples decay with this form.

The temperature dependence of T_2 is also plotted in Fig. 2 and fit to $1/T_2 = 1/(2T_1) + 1/T_{SD}$, where T_{SD} is the (temperature independent) spectral-diffusion-limited coherence time. For the natural germanium samples, T_{SD} limits the coherence to 57 μs whereas the 3.8% $^{73}\text{Ge}:\text{As}$ sample is limited to 113 μs . From similar work in silicon [35, 36], one might expect an orientation dependence to T_{SD} . We measured the orientation dependence of T_{SD} for the 3.8% $^{73}\text{Ge}:\text{As}$ sample at 1.8 K and fit the decays with a curve of the form $Ae^{-(2\tau/(2T_1))}e^{-(2\tau/T_{SD})^n}$ to separate the T_1 component from T_{SD} [37]. No angular dependence of T_{SD} could be resolved.

While coherence times of over one millisecond for isotopically enriched material open the possibility of using donor electrons in Ge for quantum computing devices, these coherence times are much shorter than those for donors in isotopically enriched silicon (seconds) [12, 13]. To extend the Ge donor coherence, one must either overcome the T_1 limit or use nuclear spins which may support longer coherence times. There are several promising techniques to extend the T_1 limit. One approach is to take advantage of the T_1 anisotropy, which will al-

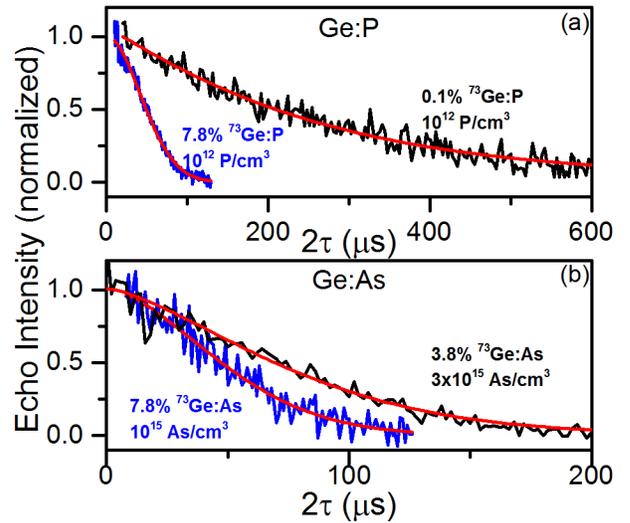


FIG. 4. Two-pulse Hahn echo decay curves for natural (blue) and isotopically enriched (black) germanium doped with phosphorus(a) and arsenic(b) donors. Data were taken at 1.8 K and 9.65 GHz. The solid curves are fits to the data using $\exp[-(\frac{2\tau}{T_2})^n]$.

low for up to a factor of 3 increase in T_1 when devices are oriented with $B_0 \parallel \langle 111 \rangle$, but this T_1 enhancement comes at the expense of a shorter ensemble T_2^* . A simple alternative is to operate devices at lower temperatures, since $T_1 \propto T^{-1}$. Perhaps the most effective technique is to operate devices at lower frequencies since theory predicts $T_1 \propto B_0^{-4}$. More complicated strategies are also available. In particular, one can apply a large strain, as demonstrated by Wilson [8] which shifts the valley energy levels, thus suppressing valley repopulation and the associated relaxation mechanisms. Another recent proposal suggests patterning Ge in a periodic structure to open a phononic bandgap at the Larmor frequency[38]. Such a structure would suppress the single phonon process.

In summary, we have measured the ESR linewidths, coherence times, and spin-lattice relaxation times for donors in natural and isotopically enriched germanium at X-band microwave frequencies. We find that the linewidths are primarily broadened by hyperfine interactions with ^{73}Ge spins when B_0 is oriented along the $[001]$ axis and by strain in other orientations. We find that donor electron spin coherence is limited by spectral diffusion due to hyperfine interactions with ^{73}Ge nuclei for the ^{nat}Ge ($T_{SD} = 57 \mu\text{s}$) and 3.8% $^{73}\text{Ge}:\text{As}$ ($T_{SD} = 113 \mu\text{s}$) samples, thus T_{SD} scales approximately as $1/f$ which is similar to silicon[36]. For the more highly enriched 0.1% $^{73}\text{Ge}:\text{P}$ sample, T_2 was limited to $2T_1$ down to 350 mK, the lowest temperature we have measured ($T_2 = 1.2 \text{ ms}$ for $B_0 \parallel \langle 001 \rangle$). We observe a large anisotropy in T_1 , which is explained by the theory of Roth and Hasegawa[15, 16], with the longest T_1 occurring for $B_0 \parallel \langle 111 \rangle$. It is predicted that at lower magnetic

fields T_1 and thus T_2 should become substantially longer.

Work at Princeton was supported by the NSF through the Materials World Network and MRSEC Programs (Grant No. DMR-1107606 and DMR-01420541), and the ARO (Grant No. W911NF-13-1-0179). The work at Keio has been supported by the Core-to-Core Program by JSPS, and the Grants-in-Aid for Scientific Research, and Project for Developing Innovation Systems by MEXT.

* asigilli@princeton.edu

- [1] M. L. Lee, E. A. Fitzgerald, M. T. Bulsara, M. T. Currie, and A. Lochtefeld, *Journal of Applied Physics* **97**, 011101 (2005).
- [2] P. Li, J. Li, L. Qing, H. Dery, and I. Appelbaum, *Phys. Rev. Lett.* **111**, 257204 (2013).
- [3] S. Dushenko, M. Koike, Y. Ando, T. Shinjo, M. Myronov, and M. Shiraishi, *Phys. Rev. Lett.* **114**, 196602 (2015).
- [4] C. Shen, T. Trypiniotis, K. Y. Lee, S. N. Holmes, R. Mansell, M. Husain, V. Shah, X. V. Li, H. Kurebayashi, I. Farrer, C. H. de Groot, D. R. Leadley, G. Bell, E. H. C. Parker, T. Whall, D. A. Ritchie, and C. H. W. Barnes, *Applied Physics Letters* **97**, 162104 (2010).
- [5] R. Vrijen, E. Yablonovitch, K. Wang, H. W. Jang, A. Balandin, V. Roychowdhury, T. Mor, and D. DiVincenzo, *Phys. Rev. A* **62**, 012306 (2000).
- [6] R. Rahman, S. H. Park, T. B. Boykin, G. Klimeck, S. Rogge, and L. C. L. Hollenberg, *Phys. Rev. B* **80**, 155301 (2009).
- [7] W. M. Witzel, R. Rahman, and M. S. Carroll, *Phys. Rev. B* **85**, 205312 (2012).
- [8] D. K. Wilson, *Phys. Rev.* **134**, A265 (1964).
- [9] G. Feher, *Phys. Rev.* **114**, 1219 (1959).
- [10] L. Liu, *Phys. Rev.* **126**, 1317 (1962).
- [11] J. J. L. Morton, D. R. McCamey, M. A. Eriksson, and S. A. Lyon, *Nature* **479**, 345 (2011).
- [12] A. M. Tyryshkin, S. Tojo, J. J. L. Morton, H. Riemann, N. V. Abrosimov, P. Becker, H.-J. Pohl, T. Schenkel, M. L. W. Thewalt, K. M. Itoh, and S. A. Lyon, *Nat Mater* **11**, 143 (2012).
- [13] G. Wolfowicz, A. M. Tyryshkin, R. E. George, H. Riemann, N. V. Abrosimov, P. Becker, H.-J. Pohl, M. L. W. Thewalt, S. A. Lyon, and J. J. L. Morton, *Nat Nano* **8**, 561 (2013).
- [14] K. M. Itoh and H. Watanabe, *MRS Communications* **4**, 143 (2014).
- [15] L. M. Roth, *Phys. Rev.* **118**, 1534 (1960).
- [16] H. Hasegawa, *Phys. Rev.* **118**, 1523 (1960).
- [17] B. E. Kane, *Nature* **393**, 133 (1998).
- [18] G. Scappucci, G. Capellini, B. Johnston, W. M. Klesse, J. A. Miwa, and M. Y. Simmons, *Nano Letters* **11**, 2272 (2011), pMID: 21553900, <http://dx.doi.org/10.1021/nl200449v>.
- [19] G. Feher, D. K. Wilson, and E. A. Gere, *Phys. Rev. Lett.* **3**, 25 (1959).
- [20] R. E. Pontinen and T. M. Sanders, *Phys. Rev.* **152**, 850 (1966).
- [21] E. B. Hale, J. R. Dennis, and S.-H. Pan, *Phys. Rev. B* **12**, 2553 (1975).
- [22] K. Morigaki and T. Mitsuma, *Journal of the Physical Society of Japan* **18**, 462 (1963).
- [23] S. Verkhovskii, A. Yakubovskii, A. Trokiner, B. Malkin, S. Saikin, V. Ozhogin, A. Tikhomirov, A. Ananyev, A. Gerashenko, and Y. Piskunov, *Applied Magnetic Resonance* **17**, 557 (1999).
- [24] S. V. Verkhovskii, A. Y. Yakubovskiy, B. Z. Malkin, S. K. Saikin, M. Cardona, A. Trokiner, and V. I. Ozhogin, *Phys. Rev. B* **68**, 104201 (2003).
- [25] A. M. Panich, N. A. Sergeev, and I. Shlimak, *Phys. Rev. B* **76**, 155201 (2007).
- [26] K. Itoh, W. Hansen, E. Haller, J. Farmer, V. Ozhogin, A. Rudnev, and A. Tikhomirov, *Journal of Materials Research* **8**, 1341 (1993).
- [27] K. M. Itoh, E. E. Haller, W. L. Hansen, J. W. Beeman, J. W. Farmer, A. Rudnev, A. Tikhomirov, and V. I. Ozhogin, *Applied Physics Letters* **64** (1994).
- [28] M. Asen-Palmer, K. Bartkowski, E. Gmelin, M. Cardona, A. P. Zhernov, A. V. Inyushkin, A. Taldenkov, V. I. Ozhogin, K. M. Itoh, and E. E. Haller, *Phys. Rev. B* **56**, 9431 (1997).
- [29] M. Berglund and M. E. Wieser, *Pure Appl. Chem.* **83**, 397 (2011).
- [30] A. R. Stegner, H. Tezuka, T. Andlauer, M. Stutzmann, M. L. W. Thewalt, M. S. Brandt, and K. M. Itoh, *Phys. Rev. B* **82**, 115213 (2010).
- [31] C. Kittel and E. Abrahams, *Phys. Rev.* **90**, 238 (1953).
- [32] T. G. Castner, *Phys. Rev.* **155**, 816 (1967).
- [33] A. K. Ramdas and S. Rodriguez, *Reports on Progress in Physics* **44**, 1297 (1981).
- [34] A. Schweiger and G. Jeschke, *Principles of pulse electron paramagnetic resonance* (Oxford University Press, 2001).
- [35] E. Abe, A. M. Tyryshkin, S. Tojo, J. J. L. Morton, W. M. Witzel, A. Fujimoto, J. W. Ager, E. E. Haller, J. Isoya, S. A. Lyon, M. L. W. Thewalt, and K. M. Itoh, *Phys. Rev. B* **82**, 121201 (2010).
- [36] R. de Sousa and S. Das Sarma, *Phys. Rev. B* **68**, 115322 (2003).
- [37] W. B. Mims, K. Nassau, and J. D. McGee, *Phys. Rev.* **123**, 2059 (1961).
- [38] V. N. Smelyanskiy, V. V. Hafiychuk, F. T. Vasko, and A. G. Petukhov, *ArXiv e-prints* (2014), arXiv:1409.6285 [cond-mat.mes-hall].