



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Ferromagnetic Quantum Critical Point Avoided by the Appearance of Another Magnetic Phase in LaCrGe_3 under Pressure

Valentin Taufour, Udhara S. Kaluarachchi, Rustem Khasanov, Manh Cuong Nguyen, Zurab Guguchia, Pabitra Kumar Biswas, Pietro Bonfà, Roberto De Renzi, Xiao Lin, Stella K. Kim, Eun Deok Mun, Hyunsoo Kim, Yuji Furukawa, Cai-Zhuang Wang, Kai-Ming Ho, Sergey L. Bud'ko, and Paul C. Canfield

Phys. Rev. Lett. **117**, 037207 — Published 13 July 2016

DOI: [10.1103/PhysRevLett.117.037207](https://doi.org/10.1103/PhysRevLett.117.037207)

Ferromagnetic quantum critical point avoided by the appearance of another magnetic phase in LaCrGe_3 under pressure

Valentin Taufour,^{1,*} Udhara S. Kaluarachchi,^{1,2} Rustem Khasanov,³ Manh Cuong Nguyen,¹ Zurab Guguchia,³ Pabitra Kumar Biswas,⁴ Pietro Bonfà,⁵ Roberto De Renzi,⁵ Xiao Lin,² Stella K. Kim,^{1,2} Eun Deok Mun,² Hyunsoo Kim,² Yuji Furukawa,^{1,2} Cai-Zhuang Wang,¹ Kai-Ming Ho,^{1,2} Sergey L. Bud'ko,^{1,2} and Paul C. Canfield^{1,2}

¹*The Ames Laboratory, US Department of Energy, Iowa State University, Ames, Iowa 50011, USA*

²*Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, U.S.A.*

³*Laboratory for Muon Spin Spectroscopy, Paul Scherrer Institute, CH-5232 Villigen PSI, Switzerland*

⁴*ISIS facility, STFC Rutherford Appleton Laboratory,*

Harwell Science and Innovation Campus, Oxfordshire OX11 0QX, United Kingdom

⁵*Dipartimento di Fisica e Scienze della Terra, Parco Area delle Scienze 7/A, I-43124 Parma, Italy*

The temperature-pressure phase diagram of the ferromagnet LaCrGe_3 is determined for the first time from a combination of magnetization, muon spin-rotation and electrical resistivity measurements. The ferromagnetic phase is suppressed near 2.1 GPa, but quantum criticality is avoided by the appearance of a magnetic phase, likely modulated, AFM_Q . Our density functional theory total energy calculations suggest a near degeneracy of antiferromagnetic states with small magnetic wavevectors, Q , allowing for the potential of an ordering wavevector evolving from $Q = 0$ to finite Q , as expected from the most recent theories on ferromagnetic quantum criticality. Our findings show that LaCrGe_3 is a very simple example to study this scenario of avoided ferromagnetic quantum criticality and will inspire further study on this material and other itinerant ferromagnets.

Systems with a quantum phase transition (QPT), a phase transition that occurs at 0 K, have revealed a wide variety of enigmatic phenomena. The case of the paramagnetic to ferromagnetic (PM-FM) QPT itself can lead to various phase diagrams with the occurrence of tricritical wings [1–3], a quantum Griffiths region [4, 5], superconductivity [2, 6–9], or non-Fermi liquid behavior [10]. Several theories have been proposed to explain these intriguing effects [11–14]. Current theoretical proposals suggest that a continuous PM-FM QPT is not possible in clean, fully ordered, systems. Instead, the transition can be of the first order, or a modulated magnetic phase can appear [15–21]. In this letter, we identify a new system, the compound LaCrGe_3 , where a continuous PM-FM QPT under pressure is avoided by the appearance of a magnetic phase, most likely a modulated phase characterized by a small wavevector Q . LaCrGe_3 provides a clean example of a simple $3d$ -shell transition metal system in which such a phase appears.

Long-wavelength correlation effects are essential to the appearance of the modulated magnetic phase (AFM_Q) which is therefore characterized by a small wavevector Q [15]. In order to study such phases experimentally, it is necessary to identify a system with a FM state that can be tuned to a QPT using a clean tuning parameter. When chemical substitutions are used to drive the PM-FM transition to 0 K, defects (and sometimes even changes in band filling) are inevitably introduced. Such quenched disorder is expected to smear the QPTs [13]. Pressure is considered as one of the cleanest parameters to tune a system towards a QPT, but usually limits the number of experimental techniques that can be used to probe an eventual new phase. In this study, resistivity measurements are used for a precise mapping

of the temperature-pressure phase diagram of LaCrGe_3 . We combine these with magnetization and muon-spin rotation (μSR) measurements that probe the new phase AFM_Q and show that AFM_Q has a similar magnetic moment as the FM phase but without net macroscopic magnetization. Finally, using thermodynamic considerations as well as total energy calculations, we show that there is a near degeneracy of AFM ordered states near 2 GPa that can allow for the evolution of an ordering wavevector from $Q = 0$ to $Q > 0$. Taken together, these data firmly establish LaCrGe_3 as a clear example of avoided ferromagnetic quantum criticality by the appearance of modulated magnetic phase.

LaCrGe_3 crystallizes in the hexagonal BaNiO_3 -type structure [space group $P6_3/mmc$ (194)] [22, 23]. At ambient pressure, LaCrGe_3 is ferromagnetic below the Curie temperature $T_C = 85$ K [24] with an ordered magnetic moment at low temperature of $1.25 \mu_B/\text{Cr}$ aligned along the c -axis [23, 24]. This rather small value of the magnetic moment compared with the effective moment above T_C ($\mu_{\text{eff}} = 2.4 \mu_B/\text{Cr}$) suggests some degree of delocalization of the magnetism [24, 25] in agreement with band structure calculations [22].

Figure 1a shows the temperature-pressure phase diagram of LaCrGe_3 obtained from resistivity, magnetization and μSR measurements which will be described below. The ferromagnetic phase is suppressed at $p = 2.1$ GPa and a modulated magnetic phase, labeled AFM_Q , is observed for $1.5 < p < 5.3$ GPa. The very steep pressure dependence of T_C near 2.1 GPa and the abrupt doubling of the residual ($T = 2$ K) resistivity shown in Fig. 1b suggests that the FM- AFM_Q transition is of the first order. Indeed, the Clausius-Clapeyron relation imposes that dT_C/dp tends to infinity for a first

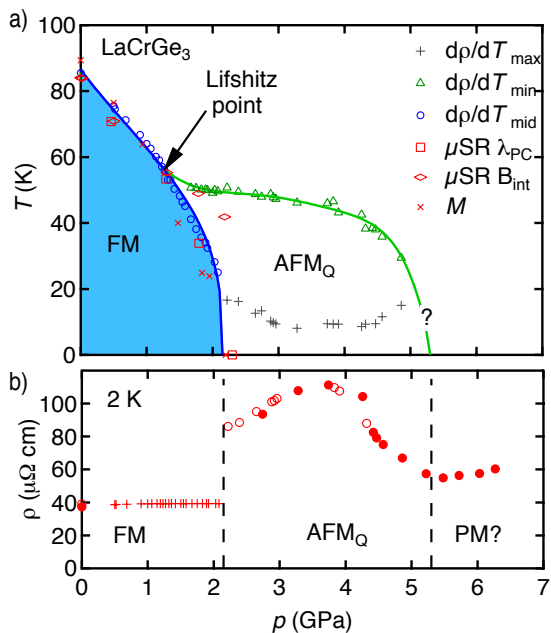


FIG. 1. (Color online) a) Temperature-pressure phase diagram of LaCrGe_3 from various measurements showing the ferromagnetic (FM) and modulated magnetic phase (AFM_Q). b) Pressure dependence of the resistivity at 2 K. Different symbols (cross, open circle, filled circle) represent data of different samples from different pressure run.

order transition at $T = 0$ K; and a peak in the resistivity, rather than a discontinuous step, is expected for a second order quantum phase transition [26–28]. The discontinuous step disappears near 40 K [29] above which the resistivity isotherms are a continuous function of pressure. Therefore, there exists a tricritical point near 40 K below which the FM- AFM_Q transition is of the first order. The merging of the three transition lines (FM- AFM_Q , FM-PM and AFM_Q -PM) is called the Lifshitz point [30].

The suppression of the FM phase with applying pressure can be seen directly from the magnetization measurements (Fig. 2). The FM phase is revealed by a sharp increase of the magnetization upon cooling below T_C . The pressure evolution of the transition can be followed up to 1.95 GPa. At 2.2 GPa, no FM transition can be observed.

A similar decrease of T_C is observed in the μSR experiments. The μSR spectra obtained in zero field at 5 K are shown in Fig. 3a from which we obtain the internal field at the muon site B_{int} (Fig. 3b). Another set of spectra shown in Fig. 3c was measured with a weak transverse field $\mu_0 H = 10$ mT from which the relaxation from the pressure cell contribution λ_{pc} was obtained (Fig. 3d). For $p < 1.4$ GPa, a simultaneous increase of B_{int} and λ_{pc} can be observed upon cooling through T_C , indicating that the sample is ferromagnetic and induces a field in the pressure cell body. At 1.78(1) GPa, the increase is no longer

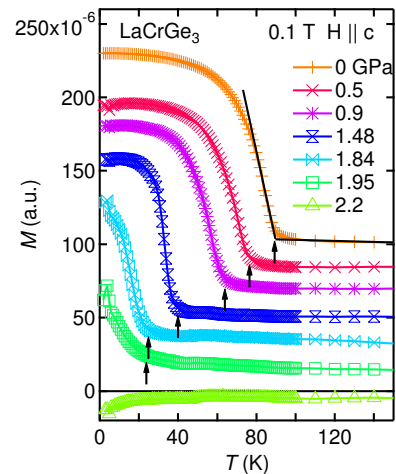


FIG. 2. (Color online) Temperature dependence of the magnetization at various pressure. The Curie temperature is indicated by arrows at the position of the change of slope as illustrated by lines for the curve at 0 GPa. Data are offset for clarity. Because such measurement is sensitive to the large background of the pressure cell with comparison to the sample signal, the applied field is rather low (0.1 T). Since at such low field the magnetization does not reach saturation, the change of magnetization at low temperature is better determined by μSR experiments.

simultaneous, which corresponds to the pressure range where the AFM_Q phase has a higher transition temperature than T_C . Above 2.1 GPa, the ferromagnetic phase is completely suppressed: no field is induced around the muon spin polarization from the cell body is measured (Fig 3c and d). However, the AFM_Q phase transition is still observed as an increase of B_{int} upon cooling (Fig 3b) demonstrating that the AFM_Q phase is magnetic in nature. It is important to note that the internal field at the muon site at low temperatures does not change significantly with pressure. In particular, it is nearly unchanged between the FM and the AFM_Q phase. This is consistent with the AFM_Q phase having similar ferromagnetic planes as the FM phase but with a modulation (wavevector Q) so that there is no macroscopic magnetization.

We show the temperature dependence of the resistivity of LaCrGe_3 at representative pressures in Fig. 4a and the corresponding temperature derivatives in Fig. 4b. The PM-FM transition, which later becomes the AFM_Q -FM transition, is revealed as a sharp increase in $d\rho/dT$ upon cooling (e.g. at 0 GPa) which progressively evolves into a sharp peak (e.g. at 1.23 GPa). Below the PM-FM transition at 0 GPa, a broad maximum is observed in $d\rho/dT$ (gray triangle in Fig. 4b) whereas no corresponding anomaly can be observed in magnetization (Fig. 2), internal field (Fig. 3) or specific heat [24]. This may correspond to a crossover within the ferromagnetic state as observed in the superconducting ferromagnet

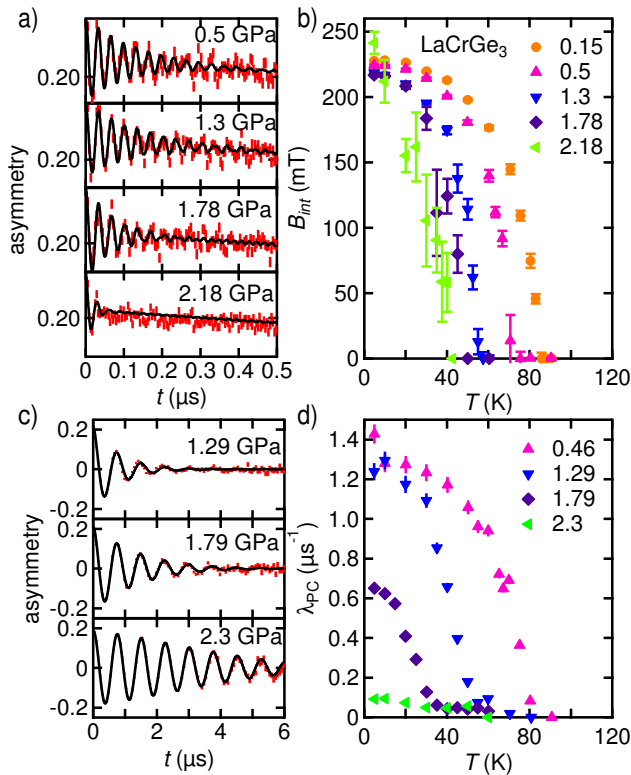


FIG. 3. (Color online) a) Zero field μ SR spectra at 5 K and various pressures. The solid lines are fits using eqns. 1-3 in Ref. [29]. b) Temperature dependence of the internal field at various pressures. c) μ SR spectra at 5 K in a weak transverse field $\mu_0 H = 10$ mT at various pressures. The solid lines are fits by using eqn.4 in Ref. [29]. d) Temperature dependence of the pressure cell relaxation λ_{PC} at various pressures.

UGe₂ [3, 31]. The PM-AFM_Q transition is revealed as a small bump in $\rho(T)$ upon cooling which is better seen as a kink in $d\rho/dT$ (e.g. at 1.92 GPa and at 2.27 GPa in Fig.SI. 3 [29]). This is often characteristic of a modulated magnetic order (spin density wave) as a small gap in the density of states opens around a nesting vector of the Fermi surface. With the disappearance of the AFM_Q-FM transition above 2.1 GPa, a sharp decrease in $\rho(T)$ upon cooling is observed (another peak in $d\rho/dT$), that probably indicates a transition to a state with another Q vector in the AFM_Q phase (e.g. at 2.65 GPa). Above 3.7 GPa, this sharp decrease seems to become broader (e.g. at 4.57 GPa). These other anomalies within the AFM_Q phase are compatible with a temperature and pressure dependence of the wavevector Q . The PM-AFM_Q transition can still be seen at 4.57 GPa but not at 6 GPa (Fig. 4b) and we estimate that the AFM_Q phase is suppressed around 5.3 GPa where a minimum is also observed in the low temperature resistivity (Fig. 1b).

We now discuss the implication of the very peculiar phase diagram of LaCrGe₃. When the FM-AFM_Q transition is of the second-order near the Lifshitz-point, the

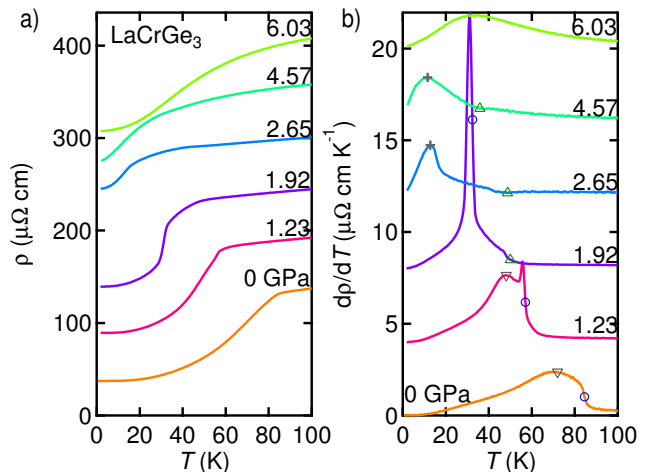


FIG. 4. (Color online) a) Temperature dependence of the electrical resistivity at various pressure. Data are offset by 50 $\mu\Omega$ cm for clarity. b) Temperature dependence of the temperature derivative of the resistivity $d\rho/dT$ at various pressure. Data are offset by 4 $\mu\Omega$ cm K^{-1} for clarity. Symbols represent the position of the anomalies.

order parameter must change continuously between these two phases, i.e. the magnetization M_0 vanishes whereas the staggered magnetization M_Q increases continuously. A possibility is to have the magnetic Q vector varying continuously at the transition from $Q = 0$ to $Q > 0$. In essence, the internal field would not change on a few \AA level, but, as soon as Q becomes finite, the average of magnetization over the magnetic unit cell becomes zero. In this case, the Q -vector would take very small values near the FM-AFM_Q transition and grow to larger values deeper in the AFM_Q phase. Within the AFM_Q region of the phase diagram, the Q -vector can change with pressure and temperature, but at a given temperature and pressure value, the sample has a given Q -vector. As the system evolves away from the Lifshitz point, it is likely that the Q -vector will “lock” at some specific values at low temperature which is consistent with a transition to other phases with different wavevectors in the AFM_Q region. A finite Q -vector is also consistent with the first order nature of the FM-AFM_Q transition at low temperature. Although it can be very difficult to measure small Q wavevectors at pressures above 2 GPa, computational studies support such an evolution of the ordering wavevector. In the following, we present total energy calculations based on density functional theory indicating that, indeed, there is a trend towards pressure-induced small- Q AFM phases and that several small- Q phases are nearly degenerate.

Figure 5 shows the calculated enthalpy difference $\Delta H = H_Q - H_{\text{non magnetic}}$ as a function of the magnetic wavevector Q along the c -axis for different pressures. Because of the rapid increase of computational resources

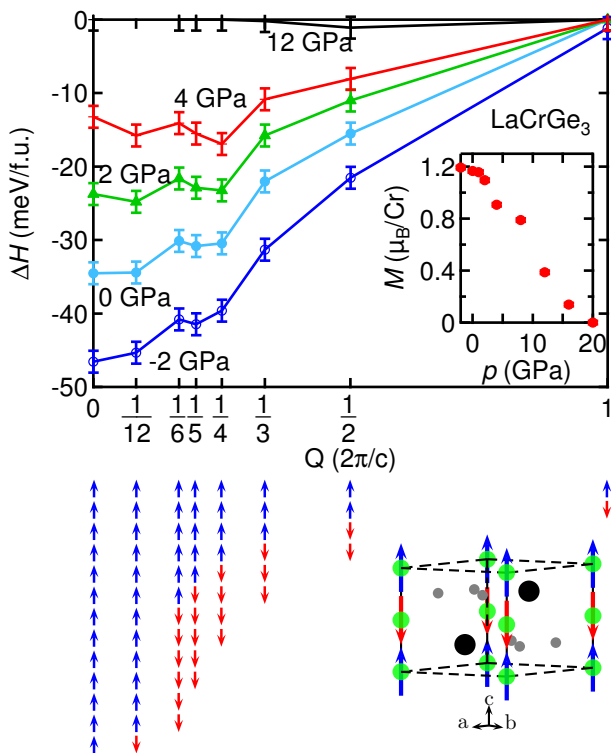


FIG. 5. (Color online) Calculated enthalpy difference $\Delta H = H_Q - H_{\text{non magnetic}}$ as a function of the magnetic wavevector Q for different pressures. The magnetic moment is not fixed in the calculation and the inset shows the pressure dependence of the calculated averaged moment for the most stable state. When a magnetic phase is not stable, the calculated moment is zero so that $H_Q = H_{\text{non magnetic}}$. The error bar is estimated from calculating the FM state enthalpy with various unit cell sizes [29]. The Cr moment of a simple antiferromagnetic state ($Q = 2\pi/c$) is represented by arrows in the crystallographic unit cell and the red and blue arrows for various Q -vector are shown.

and time with the system size (number of atoms), we limited our calculations to $Q = 1/12$ reciprocal lattice units (r.l.u.), which contains 120 atoms in the unit cell. We can see clearly from Fig. 5 that at 0 GPa, the ferromagnetic ($Q = 0$) state is stable. With increasing pressure, the FM state becomes less stable compared with states with small but finite Q values. At 2 GPa, the various states with $Q < 1/4$ r.l.u. are nearly degenerate. First-principles density functional theory results are at 0 K so that a small thermal smearing out of the enthalpy levels at finite temperature would make these states degenerate. These results are in agreement with a continuous evolution from $Q = 0$ to $Q > 0$ at finite temperature (near the Lifshitz point), whereas, at 0 K, the wavevector may jump discontinuously to a finite value. At 2 GPa, we found that Q is at most $1/4$ r.l.u. whereas it could become $1/2$ r.l.u. at 12 GPa, although a non-magnetic ground state is within the error of the calculations (Experimentally, we did not

detect any anomaly above 5.3 GPa). The calculations support very well the basic ideas that i) the AFM_Q have long wavelength, ii) the value of $Q \gtrsim 0$ can change with pressure and temperature and iii) the Cr moment does not change significantly at the FM- AFM_Q transition (inset of Fig. 5).

The observed phase diagram of LaCrGe_3 where the ferromagnetic ordering is driven to a QPT with a clean tuning parameter such as pressure agrees with many of the recent predictions from the theories of quantum criticality. This phase diagram is consistent with the interesting prediction that modulated magnetic phases with small finite wavevectors should appear. This scenario is based on soft particle-hole excitations, which are always present in metals [12]. The soft modes couples to the magnetization and their correlation functions diverge in the limit of vanishing wavevector Q . One possible outcome is that the PM-FM transition becomes of the first order near $T = 0$ K as observed in several compounds [1–3]. Another possibility, which seems revealed in LaCrGe_3 , is that the ground state of the system is a modulated magnetic phase with a small Q wavevector that can vary with the tuning parameter such as spin-density wave and spiral phases [15–21].

Phases with small ordering vectors can also arise from competing exchange interactions between local moments [32] as used to explain the complex magnetic structures of some rare-earth metals [32, 33]. However, the applicability of such model to LaCrGe_3 is unclear because of the itinerant nature of the magnetism [22, 24]. In itinerant systems, spin density waves with a long period can form due to Fermi surface nesting at a small propagation vector near a ferromagnetic instability [34]. In this scenario, the nature of the QPT relies on detailed band-structure effects and seems less generic than the scenario based on soft particle-hole excitations [12]. In fact, determining whether the modulated magnetic phase is driven by quantum fluctuations or by electronic band dispersions is difficult [17]. So far, most materials studied with a clean tuning parameter such as pressure have a complex magnetism. In the helimagnet MnSi , partial long-range order was observed under pressure [35]. In another helimagnet MnP , another magnetic phase also appears under pressure with superconductivity near the antiferromagnetic quantum critical point [9]. Kondo systems such as CeRuPO [36, 37] or the induced moment magnet PrPtAl [21] have shown evidence for a modulated phase. For those systems, a detailed comparison with band structure calculations will be difficult since magnetism originates from rare-earth elements. LaCrGe_3 , a simple $3d$ electrons system, with a simple ferromagnetic structure at ambient pressure, provides a unique opportunity for a quantitative comparison with band structure calculations. Our results indicate that band structure effects provide a trend toward the formation of small- Q AFM phases in LaCrGe_3 . The near degeneracy of differ-

ent Q-phases provides a relatively flat energy landscape allowing quantum fluctuations to play an important role in the selection of modulated phases.

To conclude, the discovery of a new magnetic phase in place of a ferromagnetic quantum critical point in LaCrGe_3 provides a clear example of avoided quantum criticality when a ferromagnetic transition is suppressed by a clean tuning parameter such as pressure. Our transport, thermodynamic and microscopic measurements under pressure strongly establish this phase diagram which is compatible with band structure calculations as well as general predictions based on soft excitations. The results presented here pose a formidable challenge for both models as to provide enough quantitative predictions allowing to distinguish band structure or quantum fluctuations effects. Experimentally, the exact nature of the Q -vector in the new magnetic phase at high pressure, as well as its temperature and pressure evolution, remains to be determined. Theoretically, it needs to be clarified when the ferromagnetic-paramagnetic transition becomes of the first order and when a new modulated phase will appear.

We would like to thank V. G. Kogan, A. Kreyssig, P. Kumar, and D. K. Finnemore for useful discussions, as well as D. Belitz, T. R. Kirkpatrick, F. Krüger, and A. G. Green for their critical reading of the manuscript. This work was supported by the Materials Sciences Division of the Office of Basic Energy Sciences of the U.S. Department of Energy. Part of this work was performed at the Ames Laboratory, US DOE, under Contract No. DE-AC02-07CH11358. Magnetization measurements under pressure (V. T.) were supported by Ames Laboratory's laboratory-directed research and development (LDRD) funding. X. Lin, E. D. Mun and H. Kim were supported by the AFOSR-MURI grant No. FA9550-09-1-0603.

* taufour@ameslab.gov

- [1] Y. J. Uemura *et al.*, *Nature Physics* **3**, 29 (2007).
- [2] F. Levy, I. Sheikin, and A. Huxley, *Nature Physics* **3**, 460 (2007).
- [3] V. Taufour, D. Aoki, G. Knebel, and J. Flouquet, *Phys. Rev. Lett.* **105**, 217201 (2010).
- [4] T. Westerkamp, M. Deppe, R. Küchler, M. Brando, C. Geibel, P. Gegenwart, A. P. Pikul, and F. Steglich, *Phys. Rev. Lett.* **102**, 206404 (2009).
- [5] S. Ubaid-Kassis, T. Vojta, and A. Schroeder, *Phys. Rev. Lett.* **104**, 066402 (2010).
- [6] S. S. Saxena *et al.*, *Nature* **406**, 587 (2000).
- [7] D. Aoki, A. D. Huxley, E. Ressouche, D. Braithwaite, J. Flouquet, J. Brison, E. Lhotel, and C. Paulsen, *Nature* **413**, 613 (2001).
- [8] N. T. Huy, A. Gasparini, D. E. de Nijs, Y. Huang, J. C. P. Klaasse, T. Gortenmulder, A. de Visser, A. Hamann, T. Gorklach, and H. v. Lohneysen, *Phys. Rev. Lett.* **99**, 067006 (2007).
- [9] J.-G. Cheng, K. Matsubayashi, W. Wu, J. P. Sun, F. K. Lin, J. L. Luo, and Y. Uwatoko, *Phys. Rev. Lett.* **114**, 117001 (2015).
- [10] C. Pfleiderer, S. Julian, and G. Lonzarich, *Nature* **414**, 427 (2001).
- [11] T. Vojta, *Phys. Rev. Lett.* **90**, 107202 (2003).
- [12] D. Belitz, T. R. Kirkpatrick, and J. Rollbühler, *Phys. Rev. Lett.* **94**, 247205 (2005).
- [13] J. A. Hoyos and T. Vojta, *Phys. Rev. Lett.* **100**, 240601 (2008).
- [14] F. Krüger, C. J. Pedder, and A. G. Green, *Phys. Rev. Lett.* **113**, 147001 (2014).
- [15] D. Belitz, T. R. Kirkpatrick, and T. Vojta, *Phys. Rev. B* **55**, 9452 (1997).
- [16] A. V. Chubukov, C. Pepin, and J. Rech, *Phys. Rev. Lett.* **92**, 147003 (2004).
- [17] G. J. Conduit, A. G. Green, and B. D. Simons, *Phys. Rev. Lett.* **103**, 207201 (2009).
- [18] U. Karahasanovic, F. Krüger, and A. G. Green, *Phys. Rev. B* **85**, 165111 (2012).
- [19] S. J. Thomson, F. Krüger, and A. G. Green, *Phys. Rev. B* **87**, 224203 (2013).
- [20] C. J. Pedder, F. Krüger, and A. G. Green, *Phys. Rev. B* **88**, 165109 (2013).
- [21] G. Abdul-Jabbar, D. A. Sokolov, C. D. O'Neill, C. Stock, D. Wermeille, F. Demmel, F. Krüger, A. G. Green, F. Levy-Bertrand, B. Grenier, and A. D. Huxley, *Nature Physics* **11**, 321 (2015).
- [22] H. Bie, O. Y. Zelinska, A. V. Tkachuk, and A. Mar, *Chem. Mat.* **19**, 4613 (2007).
- [23] J. M. Cadogan, P. Lemoine, B. R. Slater, A. Mar, and M. Avdeev, *Solid State Phenomena* **194**, 71 (2013).
- [24] X. Lin, V. Taufour, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **88**, 094405 (2013).
- [25] P. Rhodes and E. P. Wohlfarth, *Proc. R. Soc. Lond. A* **273**, 247 (1963).
- [26] K. Miyake and O. Narikiyo, *J. Phys. Soc. Jpn.* **71**, 867 (2002).
- [27] S. Raymond and D. Jaccard, *J. Low Temp. Phys.* **120**, 107 (2000).
- [28] G. Knebel, D. Aoki, J.-P. Brison, and J. Flouquet, *J. Phys. Soc. Jpn.* **77**, 114704 (2008).
- [29] See Supplementary Material available online at [url], which includes Refs. [38–59].
- [30] R. M. Hornreich, M. Luban, and S. Shtrikman, *Phys. Rev. Lett.* **35**, 1678 (1975).
- [31] C. Pfleiderer and A. D. Huxley, *Phys. Rev. Lett.* **89**, 147005 (2002).
- [32] P. Bak and J. von Boehm, *Phys. Rev. B* **21**, 5297 (1980).
- [33] R. J. Elliott, *Phys. Rev.* **124**, 346 (1961).
- [34] F. Honda, N. Metoki, T. D. Matsuda, Y. Haga, and Y. Onuki, *Journal of Physics: Condensed Matter* **18**, 479 (2006).
- [35] C. Pfleiderer, D. Reznik, L. Pintschovius, H. von Lohneysen, M. Garst, and A. Rosch, *Nature* **427**, 227 (2004).
- [36] H. Kotegawa, T. Toyama, S. Kitagawa, H. Tou, R. Yamachi, E. Matsuoka, and H. Sugawara, *J. Phys. Soc. Jpn.* **82**, 123711 (2013).
- [37] E. Lengyel, M. E. Macovei, A. Jesche, C. Krellner, C. Geibel, and M. Nicklas, *Phys. Rev. B* **91**, 035130 (2015).
- [38] S. L. Bud'ko, A. N. Voronovskii, A. G. Gapotchenko, and E. S. Itskevich, *Zhurnal Eksperimentalnoi Teor. Fiz.* **86**, 778 (1984).

- [39] A. N. Voronovsky, E. M. Dizhur, and E. S. Itskevich, *Zhurnal Eksperimentalnoi Teor. Fiz.* **77**, 1119 (1979).
- [40] S. K. Kim, M. S. Torikachvili, E. Colombier, A. Thaler, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **84**, 134525 (2011).
- [41] E. Colombier and D. Braithwaite, *Rev. Sci. Instrum.* **78**, 093903 (2007).
- [42] N. Tateiwa and Y. Haga, *Rev. Sci. Instrum.* **80**, 123901 (2009).
- [43] G. J. Piermarini, S. Block, and J. D. Barnett, *J. Appl. Phys.* **44**, 5377 (1973).
- [44] B. Bireckoven and J. Wittig, *J. Phys. E: Sci. Instrum.* **21**, 841 (1988).
- [45] P. L. Alireza, S. Barakat, A.-M. Cumberlandidge, G. Lonzarich, F. Nakamura, and Y. Maeno, *J. Phys. Soc. Jpn.* **76SA**, 216 (2007).
- [46] K. Murata, K. Yokogawa, H. Yoshino, S. Klotz, P. Munsch, A. Irizawa, M. Nishiyama, K. Iizuka, T. Nanba, T. Okada, Y. Shiraga, and S. Aoyama, *Rev. Sci. Instrum.* **79**, 085101 (2008).
- [47] G. J. Piermarini, S. Block, J. D. Barnett, and R. A. Forman, *J. Appl. Phys.* **46**, 2774 (1975).
- [48] R. Khasanov, Z. Guguchia, A. Maisuradze, D. Andreica, M. Elender, A. Raselli, Z. Shermadini, T. Goko, F. Knecht, E. Morenzoni, and A. Amato, *High Pressure Research* **36**, 140 (2016).
- [49] A. Eiling and J. S. Schilling, *J. Phys. F: Met. Phys.* **11**, 623 (1981).
- [50] A. Avella and F. Mancini, eds., *Strongly Correlated Systems Experimental Techniques*, Vol. 180 (Springer, 2015).
- [51] A. Maisuradze, A. Shengelaya, A. Amato, E. Pomjakushina, and H. Keller, *Phys. Rev. B* **84**, 184523 (2011).
- [52] T. R. Kirkpatrick and D. Belitz, *Phys. Rev. Lett.* **115**, 020402 (2015).
- [53] M. Brando, D. Belitz, F. M. Grosche, and T. R. Kirkpatrick, *Rev. Mod. Phys.* **88**, 025006 (2016).
- [54] W. Kohn and L. J. Sham, *Phys. Rev.* **140**, 1133 (1965).
- [55] J. P. Perdew and A. Zunger, *Phys. Rev. B* **23**, 5048 (1981).
- [56] P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994).
- [57] G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [58] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996).
- [59] H. J. Monkhorst and J. D. Pack, *Phys. Rev. B* **13**, 5188 (1976).