

This is the accepted manuscript made available via CHORUS. The article has been published as:

Magnetoelectric Coupling through the Spin Flop Transition in $\text{Ni}_{\{3\}}\text{TeO}_{\{6\}}$

M. O. Yokosuk, Amal al-Wahish, Sergey Artyukhin, K. R. O'Neal, D. Mazumdar, P. Chen, Junjie Yang, Yoon Seok Oh, Stephen A. McGill, K. Haule, Sang-Wook Cheong, David Vanderbilt, and J. L. Musfeldt

Phys. Rev. Lett. **117**, 147402 — Published 30 September 2016

DOI: [10.1103/PhysRevLett.117.147402](https://doi.org/10.1103/PhysRevLett.117.147402)

Magnetoelectric coupling through the spin flop transition in Ni_3TeO_6

M. O. Yokosuk,¹ Amal al-Wahish,¹ Sergey Artyukhin,^{2,3} K. R. O'Neal,¹ D. Mazumdar,¹ P. Chen,¹ Junjie Yang,⁴ Yoon Seok Oh,^{2,5} Stephen A. McGill,⁶ K. Haule,² Sang-Wook Cheong,^{2,4,5} David Vanderbilt,² and J. L. Musfeldt^{1,7}

¹*Department of Chemistry, University of Tennessee, Knoxville, Tennessee 37996 USA*

²*Department of Physics and Astronomy, Rutgers University, Piscataway, New Jersey 08854, USA*

³*Quantum Materials Theory, Italian Institute of Technology, Via Morego 30, 16163 Genova, Italy*

⁴*Laboratory for Pohang Emergent Materials and Max Planck POSTECH Center for Complex Phase Materials, Pohang University of Science and Technology, Pohang 790-784, Korea*

⁵*Rutgers Center for Emergent Materials, Rutgers University, Piscataway, New Jersey 08854, USA*

⁶*National High Magnetic Field Laboratory, Florida State University, Tallahassee, Florida 32310, USA*

⁷*Department of Physics and Astronomy, University of Tennessee, Knoxville, Tennessee 37996 USA*

(Dated: August 26, 2016)

We combined high field optical spectroscopy and first principles calculations to analyze the electronic structure of Ni_3TeO_6 across the 53 K and 9 T magnetic transitions, both of which are accompanied by large changes in electric polarization. The color properties are sensitive to magnetic order due to field-induced changes in the crystal field environment, with those around Ni1 and Ni2 most affected. These findings advance the understanding of magnetoelectric coupling in materials in which magnetic 3d centers coexist with non-magnetic heavy chalcogenide cations.

PACS numbers: 78.20.Ls, 75.85.+t, 78.40.Ha, 71.20.Ps, 71.70.Ej

Spin and polarization flop transitions are fascinating, especially when controlled by external stimuli like magnetic and electric fields and accompanied by large material responses involving multiple degrees of freedom [1–7]. Multiferroics like MnWO_4 and TbMnO_3 are flagship examples and owe their remarkable properties, including field control of polarization and polarization reversal accompanied by spin-helix reorientation, to the heavy ions that bring strong spin-orbit coupling and magnetic anisotropy [8–11]. Ni_3TeO_6 drew our attention due to the presence of both 3d and 5p cations, an unusual spin-flop transition [12–14], and a complex magnetic field-temperature phase diagram (Fig. 1). A magnetically induced electric polarization ($P = 3,280 \mu\text{C}/\text{m}^2$) arises in the antiferromagnetic I (AFM I) phase below $T_N = 53 \text{ K}$ due to Heisenberg exchange striction in the polar structure, and a continuous spin-flop transition occurs at 9 T into the AFM II phase, altering the polarization ($\Delta P = 290 \mu\text{C}/\text{m}^2$ at 2 K) [13]. Moreover, Ni_3TeO_6 sports the largest linear magnetoelectric coupling constant in a single-phase material known to date ($\alpha = 1,300 \text{ ps}/\text{m}$) [13]. Metamagnetic transitions accompanied by extraordinarily large polarization changes have been discovered at 52 and 70 T [15], and indications of an unexplored transition between 30 and 35 T were observed as well [16]. The colossal polarization, rich magnetic phase diagram, and large spin-orbit coupling due to incorporation of the Te centers raise the possibility of large dynamic magnetoelectric coupling in this system.

In this Letter, we reach beyond static probes of magnetoelectric coupling in Ni_3TeO_6 to reveal the dynamic interactions between spin and charge sectors. In addition to interband transitions above 2 eV, we uncover a series of Ni *d*-to-*d* excitations below 3 eV that are sen-

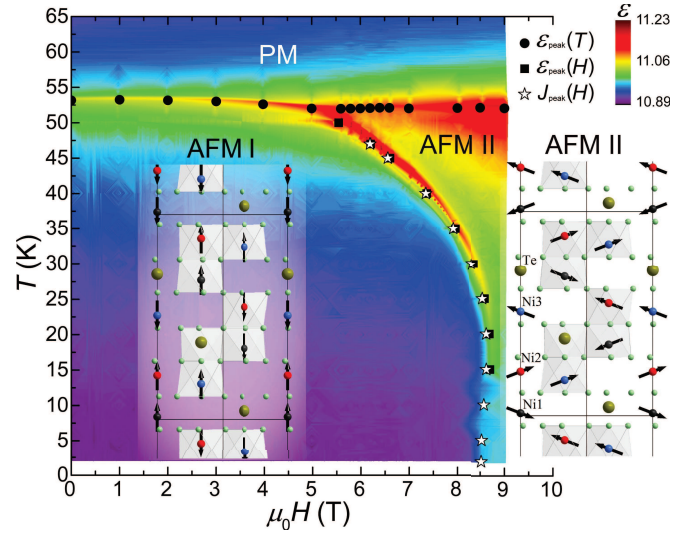


FIG. 1. (Color online) Phase diagram of Ni_3TeO_6 determined by variations in the dielectric constant ϵ (color scale at upper right) and magnetoelectric current. Closed circles, closed squares, and open asterisks indicate peak-center positions for $\epsilon(T)$, $\epsilon(H)$, and magnetoelectric current $J(H)$, respectively [13]. These peaks map the boundaries between the paramagnetic (PM) phase and antiferromagnetic phases (AFM I, AFM II). The structure of Ni_3TeO_6 is of the corundum type with a polar $R3$ space group, three inequivalent $S=1$ Ni sites along *c*, and significant distortions of oxygen octahedra surrounding Ni ions [12]. The spin configurations in the AFM I and AFM II phases are shown schematically in the insets.

sitive to magnetic order, evidence that spin-charge coupling persists to much higher energies than previously supposed. Moreover, by comparing field-induced changes in the color band excitations with predictions of Ni centers in specific crystal field environments, we determine

how and why the crystal field environments - particularly around the Ni1 and Ni2 centers - respond to different microscopic spin arrangements. This technique of decomposing on-site excitations according to their precise local environment and analyzing the relative importance of different energy transfer processes can be applied to other materials in which transition metal and heavy chalcogenide cations coexist as well as those with complicated magnetic sublattices, thereby offering a site-specific perspective on electronic excitations in magnetic solids.

High quality single crystals were grown as described previously [13] and polished to thicknesses of $\approx 28 \mu\text{m}$. Optical transmittance was measured as a function of temperature in the ab -plane and along the c -direction using a series of spectrometers (0.4-3.0 eV; 4.2-300 K). Absorption was calculated as $\alpha(E) = -(1/d)\ln T(E)$, where $T(E)$ is the transmittance and d is the sample thickness. Magneto-optical measurements were carried out at the National High Magnetic Field Laboratory in Tallahassee, Florida (4.2 K, 0 - 35 T). The first-principles calculations were performed using the Elk full-potential code using linearized augmented plane-wave basis [17], LDA+U in the fully localized limit [18] with Slater parameters $F^{(0)} = 8.0 \text{ eV}$, $F^{(2)} = 8.18 \text{ eV}$, $F^{(4)} = 5.11 \text{ eV}$ [19], and the Perdew-Wang/Ceperley-Alder exchange-correlation functional [20]. The 20-atom rhombohedral magnetic unit cell with the $\uparrow\uparrow\downarrow\downarrow\downarrow\uparrow$ magnetic ordering was used in the calculations, and a $4 \times 4 \times 4$ k -point grid was employed for reciprocal-space sampling.

Figure 2 displays the absorption of Ni_3TeO_6 in the ab -plane and c -direction at 300 and 4.2 K. We clearly observe two broad bands below 2 eV. Focusing first on the ab -plane data, we find color band excitations near 1.0, 1.55, and 1.72 eV. Each appears with significant oscillator strength due to non-centrosymmetric local environments around each of the Ni sites. Combined with the absorption minimum near 2.25 eV and small shoulder at 2.5 eV, these features are responsible for the striking green color of the crystal. The absorption rises sharply above 2.6 eV, suggesting the start of strong interband transitions. As shown in the Supplemental Information, there are no spectral changes across the Néel transition.

To test whether the lower-energy peaks might arise from interband transitions, we calculated the Kohn-Sham band structure at the LDA+U level for Ni_3TeO_6 in the zero-temperature antiferromagnetic configuration. The results are shown in Fig. 2, and where comparable, they are in excellent agreement with Ref. 14. The gap, clearly visible in the density of states plot in Fig. 2(c), is determined to be 2.2 eV, which rules out any interband transitions below 2 eV. To drive this point home, the components of LDA+U optical dielectric response tensor calculated within the random phase approximation in the $q \rightarrow 0$ limit are plotted in Fig. 2(d). The interband transitions naturally account for the sharply rising absorption near 2.6 eV (Fig. 2(a)). They are dominated


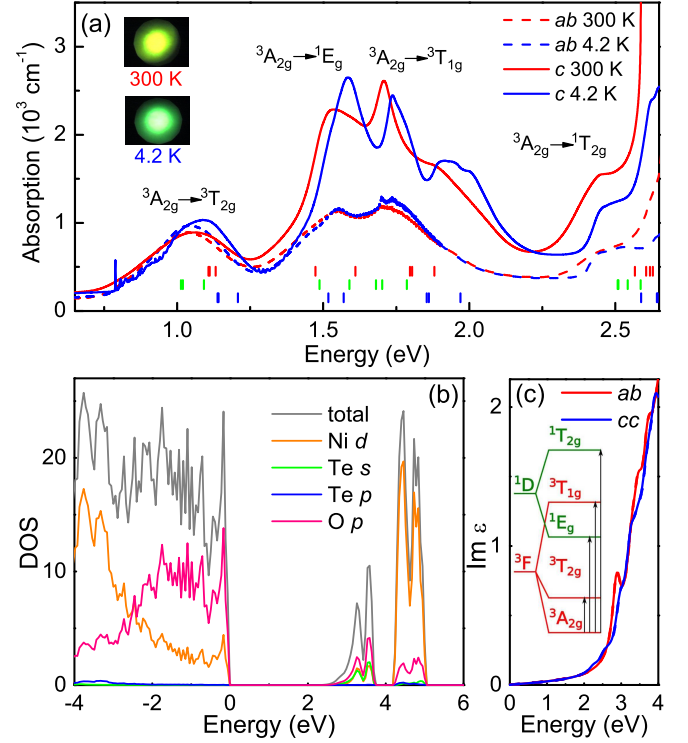


FIG. 2. (Color online) (a) Absorption coefficient of Ni_3TeO_6 , $\alpha(E)$, in the ab -plane and the c -direction at 300 and 4.2 K. Vertical lines near the bottom mark the computed d -to- d excitations for the d^8 Ni ions, with red, green, and blue indicating excitations on Ni1, Ni2, and Ni3 sites, respectively. The insets show photographs of the crystal along c . (b) Ion-projected density of states per magnetic unit cell obtained from DFT and (c) components of linear optical dielectric response tensor calculated within the random phase approximation in the $q \rightarrow 0$ limit with no microscopic contributions (solid lines: with spin-orbit coupling included; dashed: without). The splitting of free Ni ion d^8 multiplets in the presence of an octahedral crystal field and the crystal field excitations between these levels is shown in the inset.

by excitations from hybridized O p and majority Ni e_g states at the top of the valence band to Te s and minority Ni e_g conduction bands. We therefore assign the features below 2 eV to on-site Ni d -to- d excitations, an assignment that is strengthened by the resemblance to $\text{Ni}_3\text{V}_2\text{O}_8$ [5], where similar d -to- d transitions occur and where the charge-transfer gap of 2.4 eV is only slightly smaller than ours. We shall give further theoretical support for this assignment shortly.

Returning to the experimental data and focusing now on comparing the c -axis response of Ni_3TeO_6 with the in-plane spectra (Fig. 2(a)), we immediately notice that while the intensities of the 1.2 eV peaks are similar, there is a large anisotropy between 1.5 and 2.2 eV, with the absorption being much stronger along c ($\approx 2500 \text{ cm}^{-1}$) than in the ab plane ($\approx 1300 \text{ cm}^{-1}$). Temperature effects are also more interesting in this direction, with the 4.2 K

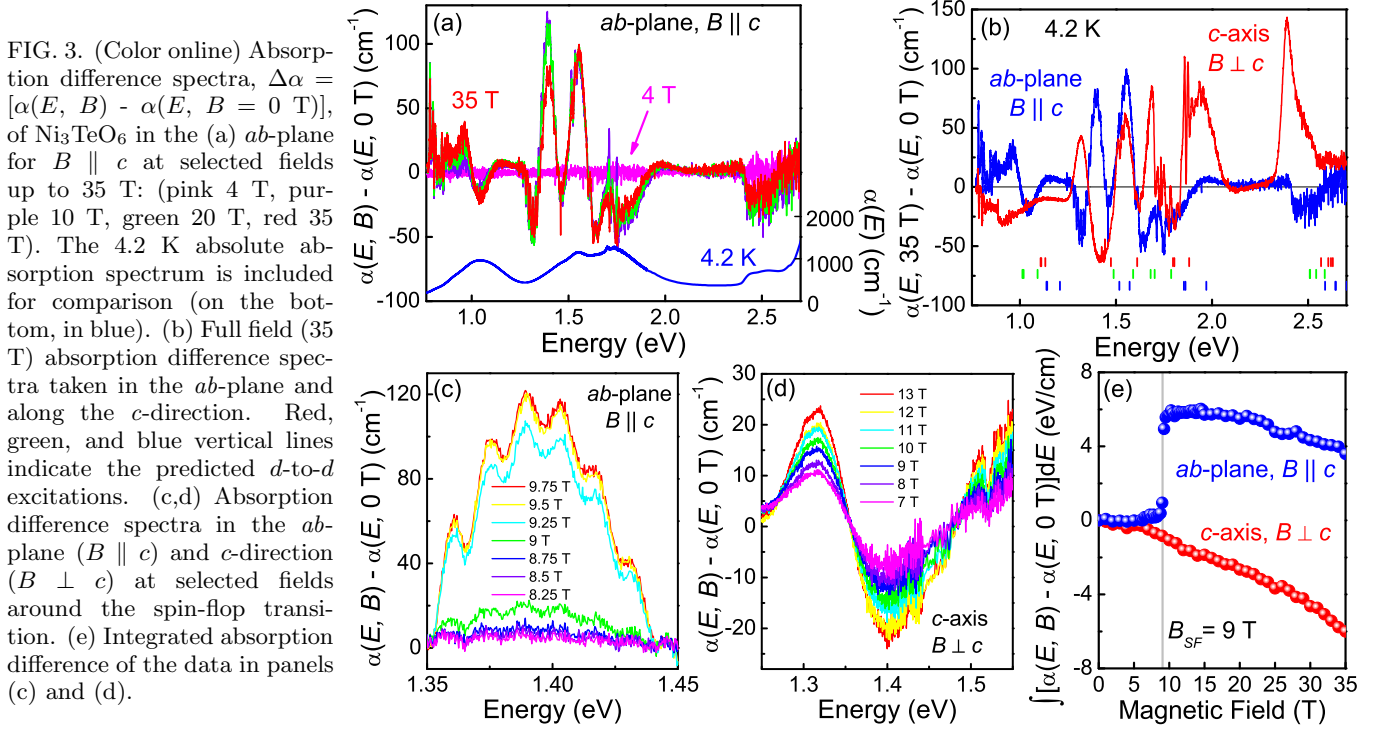

data showing (i) an overall hardening of the excitations, (ii) an intensity increase near 1.9 eV, and (iii) fine structure on the leading edge of the 1.1 eV band that may correspond to phonon side bands [16]. Examination of the 1.9 eV excitation reveals that the peak shape is a strong function of temperature. The additional orange light absorption at 4.2 K causes Ni_3TeO_6 to appear more green to the naked eye (inset, Fig. 2(a)).

As noted above, we have assigned the color-band excitations below 2.5 eV to on-site d -to- d transitions, which are not expected to appear in a single-particle framework such as DFT+U. To confirm this assignment, we turn to a crystal field model. The Coulomb interactions for a spherically symmetric d^8 ion give rise to the ground state 3F . These are correlated states that generally cannot be represented as a single Slater determinant. In particular, the state with the largest orbital moment, 2^+2^- , where both holes in the d shell have $m_l = 2$ and opposite spins (indicated by superscripts “+” and “-”), is a single Slater determinant. Instead, the state obtained by applying the angular momentum lowering operator L^- , and thus belonging to the same multiplet, is made up of the microstates 2^+1^- and 2^-1^+ , and so is not a single-determinant state [21, 22]. The next multiplet is 1D , followed by 3P , 1G , and 1S states. In the (approximately) octahedral crystal field of the oxygen cage surrounding the Ni ions, the lowest multiplet splits as $^3F \rightarrow \Gamma_2 = ^3A_{2g}$ ($E = -12Dq$), $\Gamma_5 = ^3T_{2g}$ ($E = -2Dq$), and $\Gamma_4 = ^3T_{1g}$ ($E = 6Dq$), where $10Dq$ corresponds to the splitting of a single d -level that would be produced by the same octahedral crystal field. The next lowest multi-

plet splits as $^1D \rightarrow \Gamma_3 = ^1E_g$ ($E = 5F_2 + 45F_4 - \frac{24}{7}Dq$) and $^1T_{2g}$ ($E = 5F_2 + 45F_4 + \frac{16}{7}Dq$). These splittings are shown schematically in Fig. 2(b), where the vertical black arrows indicate the optical excitations of interest.

In order to estimate the d -to- d transition energies, we performed exact diagonalization of an atomic Hamiltonian in the d^8 sector for each of the three inequivalent Ni sites. The Hamiltonian included the Hund’s exchange energy, $J_H = 0.9$ eV, and the orbital energies in the crystal field, approximated by the energies of Wannier functions obtained from the DFT calculations for each of the three Ni ions. The vertical marks in Fig. 2(a) show that these predicted excitation energies coincide well with the peaks observed in our experiment. The excitations near 1.0, 1.55, 1.72, and above 2.5 eV are therefore associated with transitions to the Γ_5 , Γ_3 , Γ_4 , and Γ_5 multiplets, respectively. This confirms the interpretation of the absorption bands below 2 eV as resulting from d -to- d transitions. The assignment also clarifies that the shoulder near 2.5 eV is related to on-site excitations and not yet the beginning of the interband transitions. This framework and the position of the spectral peaks allow us to estimate that Dq and the Racah parameter B are both (coincidentally) equal to 0.11 eV, consistent with expectations for a Ni^{2+} complex [23].

We now turn to the optical response in applied field. Figures 3(a) and (b) summarize the magneto-optical properties of Ni_3TeO_6 in the ab -plane ($B \parallel c$) and in the c -direction ($B \perp c$) at 4.2 K. The data are displayed as a set of absorption difference spectra, $\Delta\alpha(E, B) = \alpha(E, B) - \alpha(E, B = 0)$, for selected fields ranging from

4 to 35 T. The zero-field linear absorption $\alpha(E)$ is also shown at the bottom of panel (a) for reference. In general, the contrast increases with field, although the peak near 1.4 eV (related to changes in ${}^3A_{2g} \rightarrow {}^1E_g$ excitations) is an exception.

Figure 3(b) brings together the full field absorption difference spectra, $\Delta\alpha(E, B) = \alpha(E, B = 35 \text{ T}) - \alpha(E, B = 0 \text{ T})$, with the theoretical locations of the three different sets of d -to- d transitions indicated at the bottom as in Fig. 2. Comparison of these spectra with the predicted crystal-field excitations verifies that the observed features are due to field-induced changes in the Ni d -to- d excitations.

Inspection of Fig. 3(c) reveals that the ab -plane absorption difference spectra ($B \parallel c$) display a sharp discontinuity across the 9 T spin flop transition. This discontinuity is not seen in the c -axis data of Fig. 3(d), which is not surprising since these were taken with $B \perp c$ where the spin-flop transition does not occur. Figure 3(e) quantifies these trends by plotting the absorption difference, integrated over an energy window near 1.4 eV, as a function of magnetic field. The ab -plane response to the magnetic field ($B \parallel c$) displays a sharp jump across the 9 T transition, along with precursor effects (both below and above the spin-flop transition) and no hysteresis (not shown). This indicates that the electronic properties are sensitive to changes in the microscopic spin pattern - a direct consequence of spin-charge coupling and analogous to the dielectric response in Fig. 1. By contrast, in the absence of a spin-flop transition, the c -axis response ($B \perp c$) shows only a gradual decrease in the integrated $\Delta\alpha$ with no distinguishing characteristics.

Another interesting aspect of the magneto-optical response is that $\Delta\alpha$ has not saturated by 35 T, suggesting that higher fields are likely to uncover new magnetic phases. Recent magnetization and magneto-infrared experiments do in fact reveal the possibility of an unexplored transition between 30 and 35 T as well as metamagnetic transitions at 52 and 70 T for $B \parallel c$ [15, 16].

A close-up view of the color bands of Ni_3TeO_6 (Fig. 4) along with an analysis of the local structure [12, 24] unveils the role of each of the three distinct Ni ions. The Ni3 centers, for instance, have a relatively irregular environment and strong crystal field associated with their face-shared proximity to the unusual Te^{6+} cations (inset, Fig. 1). As expected, this distorted environment correlates with the appearance of d -to- d transitions (blue vertical lines) on the high-energy side of each cluster of predicted excitations. This is precisely the range with little or no magneto-optical response. By contrast, the Ni2 ions have the least distorted environment and weakest crystal field, and their predicted on-site excitations (green lines) are at lower energies compared to those of the other two Ni centers. Since absorption difference structures always appear on the leading edge of each band - both in the ab -plane and along c - we can conclude that

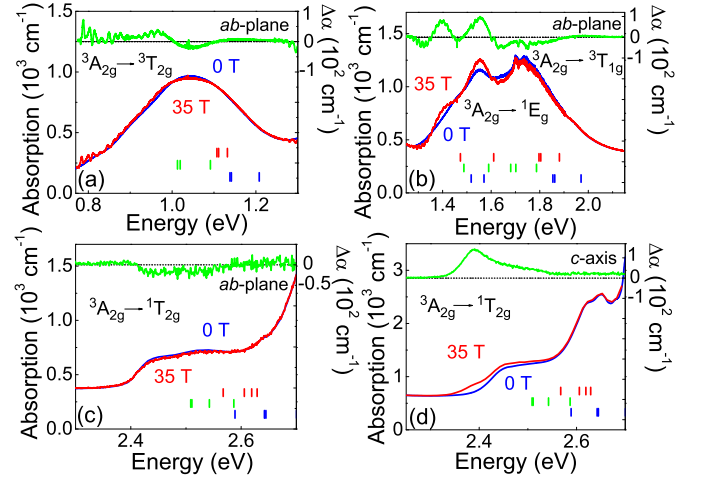


FIG. 4. (Color online) (a,b) Close-up view of the ${}^3A_{2g} \rightarrow {}^3T_{2g}$, ${}^3A_{2g} \rightarrow {}^1E_g$, and ${}^3A_{2g} \rightarrow {}^3T_{1g}$ absorption bands at 0 and 35 T along with the full field absorption difference in the ab -plane. (c,d) Close-up views of the ${}^3A_{2g} \rightarrow {}^1T_{2g}$ excitation in the ab -plane and c -directions. The red, green, and blue hash marks indicate calculated d -to- d excitations for Ni1, Ni2, and Ni3.

Ni2 ions are involved. The same is true for the Ni1-related features, which are predicted to be in the middle. We therefore surmise that electronic structure changes through the spin flop transition derive from field-induced modifications to the crystal field environment of Ni1 and Ni2 (and associated adaptations in hybridization). Recent calculations support the dominant contribution of Ni1...Ni2 interactions to the magnetic properties [14] and magnetically-induced electric polarization [15].

In summary, we bring together optical spectroscopy and first principles calculations to reveal how and why the electronic properties of Ni_3TeO_6 can be controlled by magnetic field, and we trace the color property tunability to field-induced changes in crystal field environments of the associated Ni d -to- d excitations. The decomposition of on-site excitations according to their precise local environment offers a very useful perspective on electronic excitations in magnetic materials. Here, the comparison exposes dominant Ni1...Ni2 interactions. In addition to providing a superb platform for the exploration of coupled charge and spin degrees of freedom, these findings reveal that the remarkable polarization properties and magnetoelectric coupling in Ni_3TeO_6 extend to much higher energies than previously supposed [13]. This is interesting and important because similar energy transfer processes may exist in other materials - particularly those in which transition metal centers and heavy chalcogenide cations coexist.

Research at the University of Tennessee and Rutgers University is supported by the NSF-DMREF program (DMR-1233118 and DMR-1233349). Work at Postech is funded by the Max Planck POSTECH/KOREA Re-

search Initiative Program 2011-0031558 through NRF of Korea funded by MEST. A portion of this research was performed at the National High Magnetic Field Laboratory which is supported by the National Science Foundation Cooperative Agreement DMR-1157490, the State of Florida, and the U.S. Department of Energy.

-
- [1] D. I. Khomskii, *Physics* **2**, 20 (2009).
 - [2] F. Matsukura, Y. Tokura, and H. Ohno, *Nat. Nanotech.* **10**, 209 (2015).
 - [3] W. Eerenstein, N. D. Mathur, and J. F. Scott, *Nature* **442**, 759 (2006).
 - [4] S.-W. Cheong and M. Mostovoy, *Nat. Mater.* **6**, 13 (2007).
 - [5] P. Chen, B. S. Holinsworth, K. R. O’Neal, T. V. Brinzari, D. Mazumdar, Y. Q. Wang, S. McGill, R. J. Cava, B. Lorenz, and J. L. Musfeldt, *Phys. Rev. B* **89**, 165120 (2014).
 - [6] H. Matsuzaki, H. Nishioka, H. Uemura, A. Sawa, S. Sota, T. Tohyama, and H. Okamoto, *Phys. Rev. B* **91**, 081114(R) (2015).
 - [7] N. Poudel, K.-C. Liang, Y.-Q. Wang, Y. Y. Sun, B. Lorenz, F. Ye, J. A. Fernandez-Baca, and C. W. Chu, *Phys. Rev. B* **89**, 054414 (2014).
 - [8] K. Taniguchi, N. Abe, T. Takenobu, Y. Iwasa, and T. Arima, *Phys. Rev. Lett.* **97**, 097203 (2006).
 - [9] O. Heyer, N. Hollmann, I. Klassen, S. Jodlauk, L. Bohaty, P. Becker, J. A. Mydosh, T. Lorenz, and D. Khomskii, *J. Phys. Condens. Matter* **18**, L471 (2006).
 - [10] F. Ye, R. S. Fishman, J. A. Fernandez-Baca, A. A. Podlesnyak, G. Ehlers, H. A. Mook, Y. Wang, B. Lorenz, and C. W. Chu, *Phys. Rev. B* **83**, 140401(R) (2011).
 - [11] T. Aoyama, K. Yamauchi, A. Iyama, S. Picozzi, K. Shimizu, and T. Kimura, *Nat. Commun.* **5**, 4927 (2014).
 - [12] I. Živković, K. Prša, O. Zaharko, and H. Berger, *J. Phys.: Condens. Matter* **22**, 056002 (2010).
 - [13] Y. S. Oh, S. Artyukhin, J. J. Yang, V. Zapf, J. W. Kim, D. Vanderbilt, and S.-W. Cheong, *Nat. Commun.* **5**, 3201 (2014).
 - [14] F. Wu, E. Kan, C. Tian, and M. -H. Whangbo, *Inorg. Chem.* **49**, 7545 (2010).
 - [15] J. W. Kim, S. Artyukhin, E. D. Mun, M. Jaime, N. Harrison, A. Hansen, J. J. Yang, Y. S. Oh, D. Vanderbilt, V. S. Zapf, and S.-W. Cheong, *Phys. Rev. Lett.* **115**, 137201 (2015).
 - [16] M. O. Yokosuk, S. Artyukhin, A. al-Wahish, X. Wang, J. Wang, Z. Li, S.-W. Cheong, D. Vanderbilt, J. L. Musfeldt, *Phys. Rev. B* **92**, 144305 (2015).
 - [17] K. Dewhurst, S. Sharma, L. Nordström, F. Cricchio, F. Bultmark, O. Grånäs, H. Gross, C. Ambrosch-Draxl, C. Persson, C. Brouder, *et al.* The Elk FP-LAPW Code [Online]. 2015. <http://elk.sourceforge.net> [July 2015].
 - [18] F. Bultmark, F. Cricchio, O. Grånäs, and L. Nordström, *Phys. Rev. B* **80**, 035121 (2009).
 - [19] V. I. Anisimov, I. V. Solov'yev, M. A. Korotin, M. T. Czyżyk, and G. A. Sawatzky, *Phys. Rev. B* **48**, 16929 (1993).
 - [20] J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
 - [21] C. J. Ballhausen, *Introduction to Ligand Field Theory*, McGraw-Hill Book Co., Inc. 1962
 - [22] R. Eder, Multiplets in transition metal ions, in E. Pavarini, E. Koch, F. Anders, and M. Jarrell (eds.) *Correlated Electrons: From Models to Materials Modeling and Simulation*, Vol. 2 Verlag des Forschungszentrum Jülich, 2012.
 - [23] S. L. Reddy, T. Endo, and G. S. Reddy, *Electronic (Absorption) Spectra of 3d Transition Metal Complexes*, in M. A. Farrukh (ed.) *Advanced Aspects of Spectroscopy*, InTech, 2012.
 - [24] Ni1 is strongly distorted, Ni2 is the most symmetric C₃ site, and Ni3 is the most distorted of all [12].