



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Magnetic Excitations and Electronic Interactions in $\text{Sr}_{\{2\}}\text{CuTeO}_{\{6\}}$: A Spin-1/2 Square Lattice Heisenberg Antiferromagnet

P. Babkevich, Vamshi M. Katukuri, B. Fåk, S. Rols, T. Fennell, D. Pajić, H. Tanaka, T. Pardini, R. R. P. Singh, A. Mitrushchenkov, O. V. Yazyev, and H. M. Rønnow

Phys. Rev. Lett. **117**, 237203 — Published 2 December 2016

DOI: [10.1103/PhysRevLett.117.237203](https://doi.org/10.1103/PhysRevLett.117.237203)

Magnetic excitations and electronic interactions in $\text{Sr}_2\text{CuTeO}_6$: a spin-1/2 square lattice Heisenberg antiferromagnet

P. Babkevich,^{1,*} V. M. Katukuri,^{2,†} B. Fåk,³ S. Rols,³ T. Fennell,⁴ D. Pajić,⁵ H. Tanaka,⁶
T. Pardini,⁷ R. R. P. Singh,⁸ A. Mitrushchenkov,⁹ O. V. Yazyev,² and H. M. Rønnow¹

¹Laboratory for Quantum Magnetism, Institute of Physics,
École Polytechnique Fédérale de Lausanne (EPFL), CH-1015 Lausanne, Switzerland

²Chair of Computational Condensed Matter Physics, Institute of Physics,
École Polytechnique Fédérale de Lausanne (EPFL), CH-1015 Lausanne, Switzerland

³Institut Laue-Langevin, CS 20156, F-38042 Grenoble Cedex 9, France

⁴Laboratory for Neutron Scattering and Imaging,
Paul Scherrer Institut, CH-5232 Villigen, Switzerland

⁵Department of Physics, Faculty of Science, University of Zagreb, Bijenička c. 32, HR-10000 Zagreb, Croatia

⁶Department of Physics, Tokyo Institute of Technology, Meguro, Tokyo 152-8551, Japan

⁷Lawrence Livermore National Laboratory, Livermore, California 94550, USA

⁸Department of Physics, University of California, Davis, California 95616, USA

⁹Laboratoire Modélisation et Simulation Multi Echelle, MSME UMR 8208 CNRS,
Université Paris-Est, 5 bd Descartes, 77454 Marne-la-Vallée, France

(Dated: November 1, 2016)

$\text{Sr}_2\text{CuTeO}_6$ presents an opportunity for exploring low-dimensional magnetism on a square lattice of $S = 1/2$ Cu^{2+} ions. We employ *ab initio* multi-reference configuration interaction calculations to unravel the Cu^{2+} electronic structure and to evaluate exchange interactions in $\text{Sr}_2\text{CuTeO}_6$. The latter results are validated by inelastic neutron scattering using linear spin-wave theory and series-expansion corrections for quantum effects to extract true coupling parameters. Using this methodology, which is quite general, we demonstrate that $\text{Sr}_2\text{CuTeO}_6$ is an almost ideal realization of a nearest-neighbor Heisenberg antiferromagnet but with relatively weak coupling of 7.18(5) meV.

Mott insulators are a subject of intense interest due to the observation of many different quantum phenomena [1, 2]. In low-dimensional systems, frustration and quantum fluctuations can destroy long-range magnetic order giving rise to quantum paramagnetic phases such as valence-bond solids with broken lattice symmetry or spin liquids where symmetry is conserved but with possible new collective behaviors involving emergent gauge fields and fractional excitations [3–5]. The spin-1/2 frustrated square-lattice with nearest-neighbour (NN) J_1 and next-nearest neighbour J_2 exchange interactions is one of the simplest models for valence-bond solids and spin liquids [4, 6]. Yet, despite the many theoretical efforts, experimental realisations of the J_1 - J_2 model have been rather scarce. The double perovskite oxides are particularly interesting as magnetic interactions can be tuned by changing structure, stoichiometry and cation order [7, 8]. In the search for a quantum magnet with weak exchange energies, $\text{Sr}_2\text{CuTeO}_6$ has been proposed [9, 10].

The tetragonal crystal structure of the double perovskite $\text{Sr}_2\text{CuTeO}_6$ [11] consists of corner sharing CuO_6 and TeO_6 octahedra that are rotated in a staggered fashion about the c -axis, see Fig. 1(a) and 1(b). The CuO_6 octahedra are elongated along the c -axis, effectively resulting in the ground state of Cu^{2+} ($3d^9$) ion having a hole in the in-plane $d_{x^2-y^2}$ orbital, where z is along the c -axis. This could eventually result in quasi-2D magnetism in $\text{Sr}_2\text{CuTeO}_6$ with dominant intra-plane exchange interactions. In the basal ab -plane, the exchange that couples the Cu^{2+} ions is the super-superexchange interaction me-

diated through the bridging TeO_6 octahedra as shown in Fig. 1(b), which is expected to reduce the coupling strength in $\text{Sr}_2\text{CuTeO}_6$.

Magnetic susceptibility and heat capacity measurements on $\text{Sr}_2\text{CuTeO}_6$ indicate a quasi-2D magnetic behavior, suggesting that it is a realization of the square-lattice J_1 - J_2 model [10]. More recently, neutron diffraction measurements on $\text{Sr}_2\text{CuTeO}_6$ have shown it to order in a Néel antiferromagnetic (AFM) structure below $T_N \simeq 29$ K with moments in the ab -plane [12], see Fig. 1(a). The ordered moment at 1.5 K was found to be reduced to 0.69(6) μ_B , from the classical value of 1 μ_B [12] indicating a renormalization by quantum fluctuations [13, 14]. These observations demand further investigation into the magnetic ground state and excitations that elucidate the role of quantum effects in $\text{Sr}_2\text{CuTeO}_6$.

In this Letter, we show that $\text{Sr}_2\text{CuTeO}_6$ is an almost ideal realization of a two-dimensional square lattice Heisenberg antiferromagnet. This is achieved by novel *ab initio* configuration interaction calculation of relevant exchange interactions, which are reaffirmed by modelling the inelastic magnetic spectrum using spin-wave theory and correcting the exchange interactions by series-expansion.

Let us first consider the electronic interactions in $\text{Sr}_2\text{CuTeO}_6$. For a Cu^{2+} ($3d^9$) ion in O_6 octahedral ligand cage, the degenerate $3d$ levels are split into low-energy t_{2g} and high-energy e_g manifolds with a hole in the latter. In the tetragonally elongated CuO_6 octahedra in $\text{Sr}_2\text{CuTeO}_6$, the degeneracy of t_{2g} and e_g is further

TABLE I. Relative energies of the Cu^{2+} ion d -level excitations in $\text{Sr}_2\text{CuTeO}_6$ (in hole representation). The composition of wavefunctions at the CASSCF level is also provided. Only the five $3d$ orbitals of the Cu^{2+} ion were included in the CASSCF active space. At MRCI level, the wavefunction would also contain contributions from the other correlated orbitals (see text).

Symmetry of d^9 states	Rel. E (eV) CASSCF/MRCI	CASSCF wavefunction
a_{1g}	0.00/0.00	$0.97 d_{x^2-y^2}\rangle + 0.24 d_{xy}\rangle$
b_{2g}	0.778/0.856	$-0.24 d_{x^2-y^2}\rangle + 0.97 d_{xy}\rangle$
b_{1g}	0.796/0.863	$1.0 d_{z^2}\rangle$
e'_g	1.013/1.098	$0.94 d_{yz}\rangle - 0.34 d_{zx}\rangle$
	1.013/1.098	$0.34 d_{yz}\rangle + 0.94 d_{zx}\rangle$

reduced into states with e'_g , b_{2g} (t_{2g}) and b_{1g} , a_{1g} (e_g) symmetry as shown in Fig 1c. The ground state wavefunction composition of Cu^{2+} in $\text{Sr}_2\text{CuTeO}_6$ and the d -level excited state energies and corresponding wavefunctions are summarized in Table I. These are obtained from calculations at complete-active-space self-consistent-field (CASSCF) and multireference configuration-interaction (MRCI) levels of many-body wavefunction theory [15], on embedded cluster of atoms containing a single reference CuO_6 octahedron and the surrounding six TeO_6 octahedra, see Supplemental Material (SM) [16] for computational details. In contrast to correlated calculations based on density functional theory in conjunction with dynamical mean field theory (DFT+DMFT), our calculations are parameter free and accurately describe correlations within the cluster of atoms in a systematic manner. An active space of nine electrons in five $3d$ orbitals of the Cu^{2+} ion was considered at CASSCF level to capture the correlations among the $3d$ electrons. In the subsequent correlated calculation, on top of the CASSCF wavefunction all single and double (MR-SDCI) excitations were allowed from the Cu $3s$, $3p$, $3d$ and O $2p$ orbitals of the reference CuO_6 octahedron into virtual orbital space to account for correlations involving those electrons [17, 18]. All calculations were done using MOLPRO quantum chemistry package [19].

From Table I it is evident that, at CASSCF level, the ground state hole orbital predominantly has $d_{x^2-y^2}$ character with a small d_{xy} component. This admixture is due to the staggered rotation of CuO_6 and TeO_6 octahedra. Note that the wavefunction obtained in MR-SDCI calculation also contains non-zero weights from those configurations involving single and double excitations into O $2p$ orbitals. The MR-SDCI calculations predict the lowest crystal field excitation (a_{1g} - b_{1g} and a_{1g} - b_{2g}) to be nearly degenerate at 0.86 eV, an accidental degeneracy very specific to $\text{Sr}_2\text{CuTeO}_6$. The highest d -level excitation is at 1.01 eV, see Fig. 1c. It is interesting

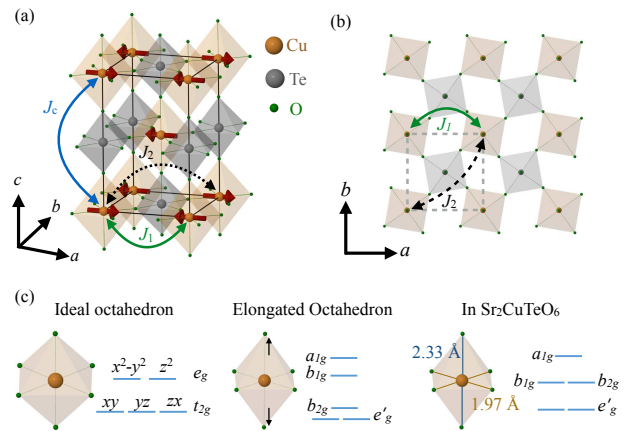


FIG. 1. (Color online) (a) and (b) Crystallographic and magnetic structure of $\text{Sr}_2\text{CuTeO}_6$. The Cu^{2+} ions order magnetically into an arrangement indicated by the red arrows. The different exchange couplings are shown by arrows connecting two Cu^{2+} ions. (c) Energy level diagram of d -states in octahedral (O_h) symmetry, for a tetragonally elongated octahedron and for the Cu^{2+} ion in $\text{Sr}_2\text{CuTeO}_6$ whose Cu-O bond lengths are labelled.

to note that the on-site d - d excitations in $\text{Sr}_2\text{CuTeO}_6$ occur at rather low energies in comparison with 1D or 2D layered cuprates [17, 18, 20]. The presence of highly charged Te^{6+} ions around the CuO_6 octahedron effectively decrease the effect of the ligand field on the Cu d -orbitals [16], a phenomena observed in layered perovskite compound Sr_2IrO_4 [21].

Having established the ground state hole orbital character and Cu^{2+} on-site d - d excitations in $\text{Sr}_2\text{CuTeO}_6$, we evaluate the exchange interactions shown in Fig. 1a. The exchange couplings were derived from a set of three different MRCI calculations on three different embedded clusters. To estimate J_1 a cluster consisting of two active CuO_6 octahedral units and two bridging TeO_6 octahedra was considered, for J_2 and J_c only one bridging TeO_6 octahedron was include in the active region [16].

The coupling constants were obtained by mapping the energies of the magnetic configurations of the two unpaired electrons in two Cu^{2+} ions onto that of a two-spin Heisenberg Hamiltonian $\mathcal{H}_{ij} = J_{ij} \mathbf{S}_i \cdot \mathbf{S}_j$. A CASSCF reference wavefunction with two electrons in the two Cu^{2+} ground state $d_{x^2-y^2}$ -type orbitals was first constructed for the singlet and triplet spin multiplicities [22], state averaged. In the MRCI calculations the electrons in the doubly occupied Cu $3d$ orbitals and the Te $4d$ and O $2p$ orbitals of the bridging TeO_6 octahedron were correlated. We adopted a difference dedicated configuration interaction (MR-DDCI) scheme [23, 24] recently implemented within MOLPRO, where a subset of the MR-SDCI determinant space [25] that *excludes* all the double excitations from the inactive orbitals to the virtuals, is used to con-

TABLE II. Heisenberg exchange couplings derived from *ab initio* CASSCF/MR-DDCI data and experimentally for Sr₂CuTeO₆. The experimental in-plane couplings were obtained from fits to INS using SWT and corrected by SE, see text. Values are given in meV.

J	CASSCF	MR-DDCI	Exp.
J_1	2.320	7.386	7.18(5)
J_2	0.006	0.051	0.21(6)
J_c	0.000	0.003	0.04

struct the many-body wavefunction. This approach has resulted in exchange couplings for several quasi-2D and quasi-1D cuprates that are in excellent agreement with experimental estimates, e.g. see Ref. 26.

In Table II the Heisenberg couplings derived at CASSCF and MR-DDCI level with Davidson corrections for size-consistency errors [27] are listed. We see that all the interactions are AFM. At the fully correlated MR-DDCI level of calculation we obtain the in-plane exchange coupling J_1 to be the largest at 7.39 meV. At the CASSCF level where the Anderson type of exchange is accounted for, i.e. related to intersite d - d excitations of the $d_{x^2-y^2}^0-d_{x^2-y^2}^2$ type [28, 29], only 30% of the J_1 exchange is obtained. The MR-DDCI treatment, which now includes excitations of the kind $t_{2g}^5 e_g^1 - t_{2g}^6 e_g^2$ etc. and O $2p$ to Cu $3d$ charge-transfer virtual states as well, enhances J_1 . Our calculations estimates a second neighbor in-plane coupling $J_2 = 0.007J_1$ and the coupling along the c -axis to be practically zero, see Table II.

Although it may perhaps be expected that the dominant superexchange comes from bridging Te $4d$ -orbitals – the path $\text{Cu}^{2+}-\text{O}^{2-}-\text{Te}^{6+}-\text{O}^{2-}-\text{Cu}^{2+}$, we find that the Te outer most occupied $4d$ orbitals are core-like at ≈ 50 eV below the valence Cu $3d$ and the oxygen $2p$ orbitals, and hence a negligible contribution to the magnetic exchange. An MR-DDCI calculation that does not take into account the virtual hopping through the Te d states results in $J_1 = 7.79$ meV. Thus we conclude that the dominant superexchange path is $\text{Cu}^{2+}-\text{O}^{2-}-\text{O}^{2-}-\text{Cu}^{2+}$ along the two bridging TeO₆ octahedra, see [16]. Interestingly we find that the superexchange involving virtual hoppings from the doubly occupied Cu $3d$ orbitals of t_{2g} symmetry and the d_{z^2} of e_g symmetry, 0.86-1.1 eV lower than the $d_{x^2-y^2}$ orbitals (see Table I), contribute almost half to the exchange coupling – a calculation without the doubly occupied Cu d orbitals in the inactive space result in a J_1 of 4.51 meV.

Next, we turn to inelastic powder neutron scattering (INS) measurements to determine experimentally the nature of magnetic interactions. The experiments were performed at Paul Scherrer Institute, using the spectrometer FOCUS (not shown), and Institut Laue-Langevin on the thermal time-of-flight spectrometer IN4 [30].

The data was collected on a sealed Al envelope containing 24.1 g of Sr₂CuTeO₆ powder at temperatures of 2, 60, and 120 K with incident neutron energy of 25.2 meV and Fermi chopper at 250 Hz. The raw data was corrected for detector efficiency, time-independent background, attenuation, and normalized to a vanadium calibration following standard procedures using LAMP and Mslice software packages [31].

The spin-spin correlations between Cu ions can be probed using INS as a function of momentum and energy transfer ($|\mathbf{Q}|, \hbar\omega$), where the former is defined as $|\mathbf{Q}| = |h\mathbf{a}^* + k\mathbf{b}^* + l\mathbf{c}^*|$ in terms of reciprocal lattice vectors. The magnetic neutron scattering cross-section is directly related to the imaginary part of the dynamical susceptibility $\chi''(|\mathbf{Q}|, \omega)$. At sufficiently high temperatures above T_N , the magnetic excitations are generally heavily damped and uncorrelated [32]. In the case of Sr₂CuTeO₆, some magnetic correlations persist even at 60 K ($\approx 2T_N$), indicative of the low-dimensionality of the system, see [16]. On warming to 120 K, the magnetic signal can no longer be observed and we subtract this data from the 2 K measurements to reveal a purely magnetic contribution to the signal.

In Fig. 2 we present the measured and calculated magnetic spectra. Figure 2(a) shows the inelastic powder $\chi''(|\mathbf{Q}|, \omega)$ spectrum mapped over momentum and energy transfer. We observe dispersive modes originating

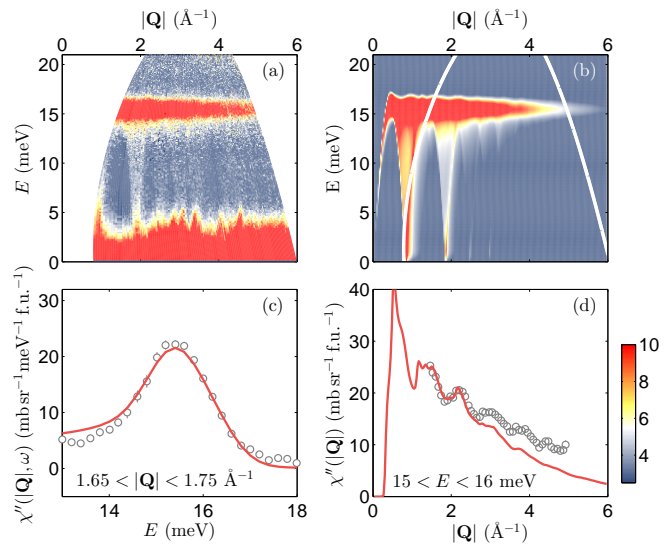


FIG. 2. (Color online) (a) Dynamic susceptibility $\chi''(|\mathbf{Q}|, E)$ map obtained by subtraction of 120 K from 2 K data. (b) Calculated powder average inelastic spectrum using $\tilde{J}_1 = 7.60(3)$ meV and $\tilde{J}_2 = 0.60(3)$ meV. The solid white lines show the detector edges. The SWT intensity is scaled to match the measured pattern in units of $\text{mb sr}^{-1} \text{meV}^{-1} \text{f.u.}^{-1}$. (c) A constant wavevector cut for $|\mathbf{Q}| \approx 1.7 \text{ \AA}^{-1}$ through the dynamic susceptibility with a solid red line showing the calculated cut from SWT. (d) $|\mathbf{Q}|$ -dependence of the magnetic band around 15.4 meV and a comparison to SWT calculations.

from the magnetic Bragg peak positions around $|\mathbf{Q}| = 0.9$ and 1.87 \AA^{-1} , which correspond to $(0.5, 0.5, 0)$ and $(1.5, 0.5, 0)$. The dispersion is linear, which is consistent with AFM spin waves and remains gapless within the energy resolution of our measurements of 1.4 meV at the elastic line (FWHM).

The dominant feature in our spectrum is a strong, flat band around 15.4 meV , shown in Fig. 2(c). The intensity decreases with increasing $|\mathbf{Q}|$ as expected for magnetic scattering, see Fig. 2(d). For low-dimensional systems, powder averaging produces a van Hove-like maximum at the zone boundary. Therefore, we interpret the flat band as due to the zone boundaries and not to a dispersionless excitation. We observe that the signal at 15.4 meV has a FWHM of 1.7 meV , which is significantly larger than the 1.2 meV instrumental resolution at this energy transfer. This implies that there is dispersion along the zone boundary.

There are two potential sources of zone boundary dispersion. Firstly, a finite J_2 leads to dispersion along the zone boundary. This effect can be captured by spin wave theory (SWT). Secondly, it has been well established that even the purely nearest neighbor ($J_2 = 0$) spin-1/2 Heisenberg antiferromagnet on a square lattice exhibit a quantum effect with two results: i) at $(\pi, 0)$ the sharp spin-wave peak develops a lineshape extending towards higher energies – a quantum effect that has often been explained in terms of spinon deconfinement [33]; ii) a 6-8% zone boundary dispersion where $E(\pi, 0)$ is lower than $E(\pi/2, \pi/2)$. The latter effect cannot be captured by SWT but by several other theoretical approaches – series expansion (SE) [34, 35], exact diagonalization [36], quantum Monte-Carlo (QMC) [37, 38], variational wavefunction (VA) [33], etc. In the presence of an AFM J_2 coupling, the quantum dispersion and the J_2 dispersion reinforce each other.

For calculating the powder-averaged neutron spectra, classical (large- S) linear spin-wave (SWT) works best owing to significantly faster computation time. Therefore, our approach is to fit the magnetic spectrum using SWT to extract effective \tilde{J}_1 and \tilde{J}_2 parameters and then to use SE to correct these values to obtain true J_1 and J_2 parameters. In doing so, we consider a Heisenberg Hamiltonian, $\mathcal{H} = \tilde{J}_1 \sum_{\langle ij \rangle} \mathbf{S}_i \cdot \mathbf{S}_j + \tilde{J}_2 \sum_{\langle\langle ij \rangle\rangle} \mathbf{S}_i \cdot \mathbf{S}_j$. We neglect the very small c -axis coupling as obtained in our calculations, see Table II. The magnetic dispersion can be described as $\hbar\omega = Z_c \sqrt{A^2 - B^2}$, where $A = 2\tilde{J}_1 + \tilde{J}_2 [\cos(2\pi h - 2\pi k) + \cos(2\pi h + 2\pi k) - 2]$ and $B = \tilde{J}_1 (\cos 2\pi h + \cos 2\pi k)$ [39]. To fit the data we calculate the imaginary part of the dynamic susceptibility including an anisotropic Cu^{2+} magnetic form factor [40, 41]. The resulting spectrum is shown in Fig. 2(b) which has been calculated using $\tilde{J}_1 = 7.60(3) \text{ meV}$ and $\tilde{J}_2 = 0.60(3) \text{ meV}$. Comparing the spectra in Figs. 2(a) and 2(b), we find good agreement across the entire wavevector and energy transfer range. The SWT simulation is able to reproduce

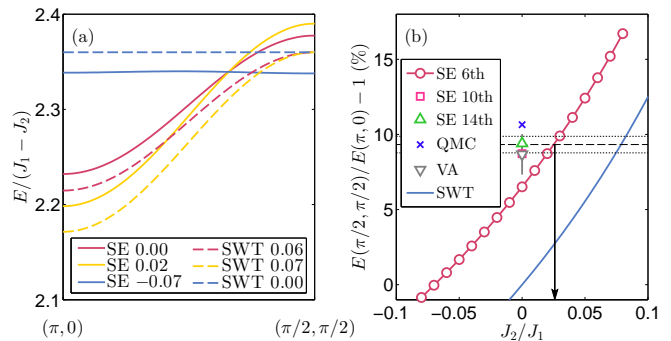


FIG. 3. (Color online) (a) Dispersion between $(\pi, 0)$ and $(\pi/2, \pi/2)$ calculated using SE and SWT methods for $J_1 = 1$ and J_2/J_1 values given in the legend. (b) Calculated change of zone boundary energies at $(\pi, 0)$ and $(\pi/2, \pi/2)$ obtained from SE and SWT. The dashed horizontal line denotes the dispersion expected for the calculated ratio of $\tilde{J}_2/\tilde{J}_1 = 0.078$ and the horizontal lines either side show the corresponding uncertainty of ± 0.005 in \tilde{J}_2/\tilde{J}_1 .

the strong flat mode around 15.4 meV and spin-waves emerging from the AFM positions. At larger- $|\mathbf{Q}|$, we find that the intensity is predicted to decrease more rapidly than observed, see Fig. 2(d). This could be an artifact of imperfect subtraction of the phonon spectrum, a small mixing of the d_{xy} orbitals influencing the magnetic form factor or multiple scattering.

We now turn to series-expansion method up to 6th order for J_1 - J_2 to correct the exchange coupling parameters derived from SWT for the quantum effects [34, 42]. Figure 3(a) shows the calculated single-magnon energies for the SE and SWT calculations for different relative strengths J_2/J_1 and \tilde{J}_2/\tilde{J}_1 . We employ the convention where $(\pi/2, \pi/2)$ and $(\pi, 0)$ correspond to points $(h, k) = (1/2, 0)$ and $(1/4, 1/4)$ (and equivalent) in reciprocal space, respectively. The SE calculations show a zone-boundary dispersion of around 7% when second neighbor exchange is absent. Comparing this to SWT calculations, see Fig. 3(a), it is clear that a non-zero AFM \tilde{J}_2 parameter modifies this part of the dispersion in a similar manner.

From SWT fits, we find that $\tilde{J}_2/\tilde{J}_1 = 0.079(3)$ which leads to a $9.3(5)\%$ dispersion between $(\pi/2, \pi/2)$ and $(\pi, 0)$. However, in SE, the same dispersion is explained largely by quantum fluctuations, see Fig. 3(b), such that $J_2/J_1 = 0.025(5)$, or $J_2 = 0.21(6) \text{ meV}$. By correcting the SWT results by SE, we obtain a more realistic value of the ratio of the exchange coupling parameters. The zone boundary dispersion can be estimated by other theoretical approaches for $J_2 = 0$ [33, 35–38]. In Fig. 3(a) we show that the same amount of dispersion as we observe can also be explained in the absence of J_2 interaction. Nonetheless, our experimental results place an upper limit on the size of J_2 . We note that reducing J_2 must increase J_1 accordingly $J_1 \approx \tilde{J}_1 (1 - \tilde{J}_2/\tilde{J}_1)/(1 - J_2/J_1)$,

which results in $J_1 \approx 7.18(5)$ meV. For a quasi-2D system, T_N can be used to estimate the coupling J_c between layers using $T_N \approx J_c[\xi(T_N)/a]^2$. We find the correlation length is $\xi(T_N)/a \approx 10$ from three-loop order given in Ref. [43]. This gives an out-of-plane coupling on the order of 0.04 meV. Comparing experimentally obtained exchange parameters with *ab initio* calculations in Table II, we find remarkably good agreement. Indeed, this demonstrates the power of our approach in obtaining a complete description of the magnetic interactions which has rather rarely been applied to strongly correlated electron systems.

We note that neutron scattering measurements have recently been performed on the related Sr_2CuWO_6 compound where the $J_2 \gg J_1$ leads to columnar antiferromagnetic order [44, 45]. Exchange parameters have been estimated using calculations based on density functional theory corrected for Hubbard type interactions and are in reasonable agreement with experiments without corrections for quantum fluctuations [44, 45]. It would be interesting to validate the proposed exchange interaction mechanisms in Sr_2CuWO_6 using more accurate many-body calculations similar to those adopted in this work.

In summary, we have characterized magnetic interactions in a new layered antiferromagnet $\text{Sr}_2\text{CuTeO}_6$ using detailed *ab initio* configuration interaction calculations and inelastic neutron scattering measurements. The calculations accurately predict the exchange interactions, and further determine the dominant exchange path i.e via $\text{Cu}^{2+}-\text{O}^{2-}-\text{O}^{2-}-\text{Cu}^{2+}$ and not via Te $4d$ orbitals, as previously suggested. By simulating the magnetic excitations using classical SWT corrected by SE, we show that NN exchange coupling is around 7.18(5) meV with very weak next-nearest interactions on the order of $< 3\%$ of J_1 . The low-energy scale of interactions in $\text{Sr}_2\text{CuTeO}_6$ should make it an appealing system to study theoretically and experimentally as an almost ideal realization of a nearest-neighbor Heisenberg antiferromagnet. Moreover, our work brings to the fore a novel strategy for exploring Heisenberg antiferromagnets from *ab initio* calculations to simulations of magnetic spectra taking into account quantum effects.

We wish to thank I. Živković, S. Katrych, L. Hozoi, and N. A. Bogdanov for fruitful discussions. P.B. is grateful for help from R.S. Ewings in implementing spherical powder averaging. V.M.K. and O.V.Y. acknowledge the support from ERC project ‘TopoMat’ (grant No. 306504). This work was funded by the European Research Council grant CONQUEST, the SNSF and its Sinergia network MPBH. Series expansion simulations were performed under the auspices of the U.S. Department of Energy by Lawrence Livermore National Laboratory under Contract DE-AC52-07NA27344. Document Release Number LLNL-JRNL-692712. This work was supported by a Grant-in-Aid for Scientific Research (A) (Grant No. 26247058) from Japan Society for the Promotion of Sci-

ence. D.P. acknowledges partial support of Croatian Science Foundation under the project 8276.

* peter.babkevich@epfl.ch

† vamshi.katukuri@epfl.ch

- [1] D. Khomskii, *Transition Metal Compounds* (Cambridge University Press, Cambridge, 2014).
- [2] W. Witczak-Krempa, G. Chen, Y. B. Kim, and L. Balents, *Ann. Rev. Condens. Matter Phys.* **5**, 57 (2014).
- [3] P. W. Anderson, *Mater. Res. Bull.* **8**, 153 (1973).
- [4] P. W. Anderson, *Science* **235**, 1196 (1987).
- [5] L. Balents, *Nature* **464**, 199 (2010).
- [6] G. Shirane, Y. Endoh, R. J. Birgeneau, M. A. Kastner, Y. Hidaka, M. Oda, M. Suzuki, and T. Murakami, *Phys. Rev. Lett.* **59**, 1613 (1987).
- [7] G. King and P. M. Woodward, *J. Mater. Chem.* **20**, 5785 (2010).
- [8] S. Vasala and M. Karppinen, *Prog. Solid State Chem.* **43**, 1 (2015).
- [9] D. Iwanaga, Y. Inaguma, and M. Itoh, *J. Solid State Chem.* **147**, 291 (1999).
- [10] T. Koga, N. Kurita, and H. Tanaka, *J. Phys. Soc. Jpn.* **83**, 115001 (2014).
- [11] D. Reinen and H. Weitzel, *Z. Anorg. Allg. Chem.* **424**, 31 (1976).
- [12] T. Koga, N. Kurita, M. Avdeev, S. Danilkin, T. J. Sato, and H. Tanaka, *Phys. Rev. B* **93**, 054426 (2016).
- [13] J. D. Reger and A. P. Young, *Phys. Rev. B* **37**, 5978 (1988).
- [14] R. R. P. Singh, *Phys. Rev. B* **39**, 9760 (1989).
- [15] T. Helgaker, P. Jørgensen, and J. Olsen, *Molecular Electronic-Structure Theory* (Wiley, Chichester, 2000).
- [16] Supplemental Material, which includes Refs. 46–68.
- [17] L. Hozoi, L. Siurakshina, P. Fulde, and J. van den Brink, *Sci. Rep.* **1**, 65 (2011).
- [18] H.-Y. Huang, N. A. Bogdanov, L. Siurakshina, P. Fulde, J. van den Brink, and L. Hozoi, *Phys. Rev. B* **84**, 235125 (2011).
- [19] H. J. Werner, P. J. Knowles, G. Knizia, F. R. Manby, and M. Schütz, *Wiley Rev. Comp. Mol. Sci.* **2**, 242 (2012).
- [20] M. M. Sala, V. Bisogni, C. Aruta, G. Balestrino, H. Berger, N. B. Brookes, G. M. de Luca, D. D. Castro, M. Grioni, M. Guarise, P. G. Medaglia, F. M. Granozio, M. Minola, P. Perna, M. Radovic, M. Salluzzo, T. Schmitt, K. J. Zhou, L. Braicovich, and G. Ghiringhelli, *New J. Phys.* **13**, 043026 (2011).
- [21] N. A. Bogdanov, V. M. Katukuri, J. Romhányi, V. Yushankhai, V. Kataev, B. Büchner, J. van den Brink, and L. Hozoi, *Nat. Commun.* **6**, 7306 (2015).
- [22] C. de Graaf and Broer, eds., ‘‘Magnetic Interactions in Molecules and Solids,’’ (Springer International Publishing, 2015) Chap. Two (or More) Magnetic Centers, pp. 69–73.
- [23] J. Miralles, J.-P. Daudey, and R. Caballol, *Chem. Phys. Lett.* **198**, 555 (1992).
- [24] J. Miralles, O. Castell, R. Caballol, and J.-P. Malrieu, *Chem. Phys.* **172**, 33 (1993).
- [25] In MR-SDCI all configurations involving single and double excitations from the active and inactive orbitals to the virtual orbital space are considered in the wavefunction

- expansion.
- [26] D. Muñoz, F. Illas, and I. de P. R. Moreira, *Phys. Rev. Lett.* **84**, 1579 (2000); D. Muñoz, C. de Graaf, and F. Illas, *J. Comput. Chem.* **25**, 1234 (2004); A. M. Pradipto, R. Maurice, N. Guihéry, C. de Graaf, and R. Broer, *Phys. Rev. B* **85**, 014409 (2012); R. Maurice, A.-M. Pradipto, C. de Graaf, and R. Broer, *Phys. Rev. B* **86**, 024411 (2012).
- [27] R. J. Cave and E. R. Davidson, *J. Chem. Phys.* **89**, 6798 (1988).
- [28] P. W. Anderson, *Phys. Rev.* **79**, 350 (1950).
- [29] P. W. Anderson, *Phys. Rev.* **115**, 2 (1959).
- [30] G. Cicognani, H. Mutka, and F. Sacchetti, *Physica B* **276 - 278**, 83 (2000).
- [31] LAMP, the Large Array Manipulation Program, http://www.ill.eu/data_treat/lamp/the-lamp-book; R. Coldea, “MSLICE: a data analysis program for time-of-flight neutron spectrometers,” http://mslice.isis.rl.ac.uk/Main_Page.
- [32] H. M. Rønnow, D. F. McMorrow, R. Coldea, A. Harrison, I. D. Youngson, T. G. Perring, G. Aeppli, O. Syljuåsen, K. Lefmann, and C. Rischel, *Phys. Rev. Lett.* **87**, 037202 (2001).
- [33] B. Dalla Piazza, M. Mourigal, N. B. Christensen, G. J. Nilsen, P. Tregenna-Piggott, T. G. Perring, M. Enderle, D. F. McMorrow, D. A. Ivanov, and H. M. Rønnow, *Nature Phys.* **11**, 62 (2015).
- [34] R. R. P. Singh and M. P. Gelfand, *Phys. Rev. B* **52**, R15695 (1995).
- [35] W. Zheng, J. Oitmaa, and C. J. Hamer, *Phys. Rev. B* **71**, 184440 (2005).
- [36] G. Chen, H.-Q. Ding, and W. A. Goddard, *Phys. Rev. B* **46**, 2933 (1992).
- [37] O. F. Syljuåsen and H. M. Rønnow, *J. Phys.: Condens. Matter* **12**, L405 (2000).
- [38] A. W. Sandvik and R. R. P. Singh, *Phys. Rev. Lett.* **86**, 528 (2001).
- [39] The first order quantum correction to SWT is to multiply the calculated dispersion by $Z_c = 1.18$ [14]. In presence of J_2 , Z_c becomes very weakly \mathbf{Q} -dependent. However, for $J_2 \ll J_1$ it is a good approximation to use a constant $Z_c = 1.18$.
- [40] P. J. Brown, in *International Tables for Crystallography, Vol. C* (Kluwer Academic Publishers, Dordrecht, 2006) pp. 454–461.
- [41] Y. Zhu, ed., “Modern techniques for characterizing magnetic materials,” (Springer US, Boston, MA, 2005) Chap. Magnetic neutron scattering, pp. 3–64.
- [42] N. Tsyrlin, T. Pardini, R. R. P. Singh, F. Xiao, P. Link, A. Schneidewind, A. Hiess, C. P. Landee, M. M. Turnbull, and M. Kenzelmann, *Phys. Rev. Lett.* **102**, 197201 (2009).
- [43] P. Hasenfratz and F. Niedermayer, *Phys. Lett. B* **268**, 231 (1991).
- [44] H. C. Walker, O. Mustonen, S. Vasala, D. J. Voneshen, M. D. Le, D. T. Adroja, and M. Karppinen, *Phys. Rev. B* **94**, 064411 (2016).
- [45] O. J. Burrows, G. J. Nilsen, E. Suard, M. Telling, J. R. Stewart, and M. A. de Vries, arXiv:1602.04075 (2016).
- [46] M. Klintonberg, S. Derenzo, and M. Weber, *Comp. Phys. Comm.* **131**, 120 (2000).
- [47] R. Pou-Amerigo, M. Merchan, P.-O. Widmark, and B. Roos, *Theor. Chim. Acta* **92**, 149 (1995).
- [48] P.-O. Widmark, P.-A. Malmqvist, and B. O. Roos, *Theor. Chim. Acta* **77**, 291 (1990).
- [49] A. Bergner, M. Dolg, W. Kuechle, H. Stoll, and H. Preuss, *Mol. Phys.* **80**, 1431 (1993).
- [50] P.-O. W. K. Pierloot, B. Dumez and B. O. Roos, *Theor. Chim. Acta* **90**, 87 (1995).
- [51] P. Fuentealba, L. von Szentpaly, H. Preuss, and H. Stoll, *J. Phys. B* **18**, 1287 (1985).
- [52] R. Broer, L. Hozoi, and W. C. Nieuwpoort, *Mol. Phys.* **101**, 233 (2003).
- [53] R. Maurice, A. Pradipto, C. de Graaf, and R. Broer, *Phys. Rev. B* **86**, 024411 (2012).
- [54] V. M. Katukuri, H. Stoll, J. van den Brink, and L. Hozoi, *Phys. Rev. B* **85**, 220402 (2012).
- [55] K. Peterson, D. Figgen, E. Goll, H. Stoll, and M. Dolg, *J. Chem. Phys.* **119**, 11113 (2003).
- [56] R. Dovesi, R. Orlando, A. Erba, C. M. Zicovich-Wilson, B. Civalieri, S. Casassa, L. Maschio, M. Ferrabone, M. De La Pierre, P. D’Arco, Y. Nol, M. Caus, M. Rrat, and B. Kirtman, *International Journal of Quantum Chemistry* **114**, 1287 (2014).
- [57] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- [58] “Jmol: an open-source Java viewer for chemical structures in 3D,” <http://www.jmol.org>.
- [59] K. Fink, R. Fink, and V. Staemmler, *Inorg. Chem.* **33**, 6219 (1994).
- [60] C. J. Calzado, S. Evangelisti, and D. Maynau, *J. Phys. Chem. A* **107**, 7581 (2003).
- [61] A. B. van Oosten, R. Broer, and W. C. Nieuwpoort, *Chem. Phys. Lett.* **257**, 207 (1996).
- [62] V. M. Katukuri, S. Nishimoto, V. Yushankhai, A. Stoyanova, H. Kandpal, S. K. Choi, R. Coldea, I. Rousochatzakis, L. Hozoi, and J. van den Brink, *New J. Phys.* **16**, 013056 (2014).
- [63] N. A. Bogdanov, V. M. Katukuri, H. Stoll, J. van den Brink, and L. Hozoi, *Phys. Rev. B* **85**, 235147 (2012).
- [64] V. M. Katukuri, V. Yushankhai, L. Siurakshina, J. van den Brink, L. Hozoi, and I. Rousochatzakis, *Phys. Rev. X* **4**, 021051 (2014).
- [65] J. Pipek and P. G. Mezey, *J. Chem. Phys.* **90**, 4916 (1989).
- [66] G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [67] A. A. Mostofi, J. R. Yates, G. Pizzi, Y.-S. Lee, I. Souza, D. Vanderbilt, and N. Marzari, *Computer Physics Communications* **185**, 2309 (2014).
- [68] H.-J. Schmidt, A. Lohmann, and J. Richter, *Phys. Rev. B* **84**, 104443 (2011).