

This is the accepted manuscript made available via CHORUS. The article has been published as:

Uncompensated Polarization in Incommensurate Modulations of Perovskite Antiferroelectrics

Tao Ma, Zhongming Fan, Bin Xu, Tae-Hoon Kim, Ping Lu, Laurent Bellaiche, Matthew J.
Kramer, Xiaoli Tan, and Lin Zhou

Phys. Rev. Lett. **123**, 217602 — Published 19 November 2019

DOI: [10.1103/PhysRevLett.123.217602](https://doi.org/10.1103/PhysRevLett.123.217602)

Uncompensated Polarization in Incommensurate Modulations of Perovskite Antiferroelectrics

Tao Ma^{1,‡}, Zhongming Fan^{2,‡}, Bin Xu^{3,4}, Tae-Hoon Kim¹, Ping Lu⁵, Laurent Bellaiche³, Matthew J. Kramer^{1,2}, Xiaoli Tan^{2,*}, and Lin Zhou^{1,2,†}

¹*Ames Laboratory, U.S. Department of Energy, Ames, IA 50011, USA*

²*Department of Materials Science and Engineering, Iowa State University, Ames, IA 50011, USA*

³*Physics Department and Institute for Nanoscience and Engineering, University of Arkansas, Fayetteville, AR 72701, USA*

⁴*School of Physical Science and Technology, Soochow University, Suzhou, Jiangsu 215006, China*

⁵*Sandia National Laboratories, PO Box 5800, MS 1411, Albuquerque, NM 87185, USA*

*Corresponding author: xtan@iastate.edu

†Corresponding author: linzhou@ameslab.gov

‡These authors contributed equally to this work.

Complex polar structures of incommensurate modulations (ICMs) are revealed in chemically modified PbZrO₃ perovskite antiferroelectrics using advanced transmission electron microscopy techniques. The Pb-cation displacements, previously assumed to arrange in a fully-compensated antiparallel fashion, are found to be either antiparallel but with different magnitudes, or in a nearly orthogonal arrangement in adjacent stripes in the ICMs. *Ab initio* calculations corroborate the low-energy state of these arrangements. Our discovery corrects the atomic understanding of ICMs in PbZrO₃-based perovskite antiferroelectrics.

Antiferroelectric (AFE) crystals possess dipoles within unit cells in an antiparallel arrangement so that the macroscopic polarization is fully compensated [1]. Under the application of an electric field above the critical value, E_F , the antiparallel dipoles can be forced to align parallel, leading to the transition to a ferroelectric (FE) phase [2]. And presumably, they resume the antiparallel arrangements upon removal of the applied field [3–5]. Consequently, double hysteresis loops with nearly zero remanent polarizations are recorded from the polarization vs. electric-field (P - E) measurement [4,6]. The most widely studied AFEs are based on PbZrO_3 , which crystallizes in a distorted perovskite structure with antiparallel Pb-cation displacements. Such a structure is equivalent to a perovskite with commensurate modulations (CMs) of $\frac{1}{4}\{110\}_c$, *i.e.*, a wavelength of four layers of its pseudocubic $\{110\}_c$ plane [7–10]. As shown in Fig. 1(a), the antiparallel arrangement of the Pb-cation displacements in PbZrO_3 is directly verified by the mapping of Pb-displacement vectors on a high-angle annular dark-field scanning transmission electron microscopy (HAADF-STEM) image. A schematic diagram [7] illustrating the antiparallel arrangement in adjacent stripes is redrawn in Fig. 1(b).

Because E_F in PbZrO_3 at room temperature exceeds its dielectric strength [11], Sn and Ti in conjunction with a small amount of Nb or La are added to reduce E_F for practical applications [12–17]. The reduction in E_F is accompanied by the formation of $\frac{1}{n}\{110\}_c$ (n is non-integer, typically between 6 and 8) incommensurate modulations (ICMs), which manifest themselves as fine fringes in diffraction-contrast TEM images and satellite spots in reciprocal space [Fig. 1(c)] [12,15–17]. However, the dipole arrangement in these incommensurate phases remains elusive, due largely to their complex sub-domain microstructure [15,16]. Earlier studies interpreted the ICMs as an ensemble of commensurate phases with coexisting different integer n values (e.g., $n = 6, 7$, or 8) [17–19]. The dipoles in adjacent stripes were believed to keep a constant magnitude

in an antiparallel arrangement across neighboring stripes, so that the overall polarization in AFE domains remain fully-compensated [Fig. 1(d)] [18].

Here we demonstrate that the classic view of the dipole arrangement in ICMs is incorrect. With direct cation displacement mapping in a series of PbZrO_3 -based compositions ($\text{Pb}_{0.99}\text{Nb}_{0.02}[(\text{Zr}_{0.57}\text{Sn}_{0.43})_{1-y}\text{Ti}_y]_{0.98}\text{O}_3$, referred to as PZ-100y hereafter), we reveal that the Pb-displacements in adjacent stripes of ICMs are not fully compensated most of the time. Instead, they are either antiparallel but with different magnitudes along opposing directions, or in a nearly orthogonal arrangement, *i.e.*, these previously thought fully-compensated AFE domains, in fact, bear a net polarization. These polar AFE domains transition into the FE phase under applied electric fields and resume their original configuration upon removal of the field, leading to the AFE-like double P - E hysteresis loops (see Fig. S1 in Supplemental Material [20]).

Figure 2 illustrates the representative TEM micrographs of chemically modified PbZrO_3 ceramics. Bright-field TEM images in Fig. 2(a), (d) and (g) (top row) from PZ-3, PZ-5, and PZ-6, respectively, show typical 90° AFE domains with textured contrast. Selected area electron diffraction (SAED) patterns along $[001]_c$ zone-axis (shown in the insets) taken from the domain boundary region present the satellite spots, $ha^* + kb^* + lc^* \pm 1/n (a^* + b^*)$ (h, k, l are integers, n represents the periodicity of ICMs indicated in SAED), which are resulted from the ICMs inside each domain [5]. Atomic-resolution HAADF-STEM images were recorded from the upper and the lower domains of each sample, shown in the second and the third rows, respectively. The atomic positions of both A-site (Pb) and B-site (Zr, Sn, Ti, and Nb) columns were determined by fitting the intensity maxima in these images using a two-dimensional Gaussian function (see Supplemental Material [20] for details). The off-center displacements of Pb-cations were calculated with respect to the geometric center of the four surrounding B-site columns and

overlaid on the HAADF images. Strikingly, we found that the dipole arrangement in ICMs deviates from the “fully-compensated antiparallel model” depicted in Fig. 1(d). In the upper domains, despite the Pb-displacement vectors are basically antiparallel in adjacent stripes, those in the wider stripes (blue) have larger magnitudes than the ones in the narrower stripes (yellow), as shown in Fig. 2(b), (e), and (h). This imbalance in the magnitudes becomes more obvious from PZ-3 [Fig. 2(b)] to PZ-6 [Fig. 2(h)] when Ti content gets higher. In the lower domains, Fig. 2(c), (f), and (i), the Pb-displacements tend to rotate from the two antiparallel $\langle 110 \rangle_c$ toward the two orthogonal $\langle 100 \rangle_c$ directions. Such rotation becomes more apparent when Ti content increases. In PZ-3, the rotation is mainly noticed in the narrower stripes [yellow in Fig. 2(c)], whereas in PZ-5 almost all the Pb-displacement vectors in the narrower stripes [yellow in Fig. 2(f)] and a large portion of those in the wider stripes [blue in Fig. 2(f)] turned to the $\langle 100 \rangle_c$ directions. In PZ-6, the Pb-displacements are almost along either $[100]_c$ or $[0\bar{1}0]_c$ [Fig. 2(i)], forming an orthogonal arrangement of dipoles in adjacent stripes.

We conducted HAADF-STEM image simulations under our experimental conditions. The results confirmed that the observed Pb-displacements reflect the real atomic configuration of dipoles rather than artifacts from the optical system, sample thickness and/or crystal tilts [28,29] (see Table S1 and Fig. S2 in Supplemental Material [20]). Moreover, HAADF-STEM imaging and atomic-scale energy-dispersive X-ray spectroscopy (EDS) mapping show uniform chemistry across the domain boundaries as well as within the neighboring stripes (see Fig. S3 in Supplemental Material [20]), indicating that the observed dipole arrangement is not directly associated with local element distribution. Since the atomic structures found in the composition series are distinct from **both the classic AFE and FE models**, we denote these 90° domains as

“transitional state” and differentiate the two across the boundary as the “antiparallel” side, Fig. 2(b), (e), and (h), and the “orthogonal” side, Fig. 2(c), (f), and (i).

To better compare the Pb-displacements in the series with different Ti content, we extract the magnitudes of Pb-displacements from the vector maps in Fig. 2 by averaging 10 atomic layers of Pb along the stripes. The corresponding polarization due to Pb-displacements are quantified through the equation:

$$P = \frac{e}{V} \sum_{i=1}^N Z^* \cdot \delta_i$$

where N is the number of Pb atoms in the box under consideration, V is the volume of the box, δ_i is the displacement of i th Pb, and Z^* is the Born effective charge for Pb, given as 3.92 in cubic PbZrO_3 by Zhong *et al* [30]. These data are plotted against the Pb positions in Fig. 3(a)–(c). It can be seen that the polarization due to Pb-displacements fluctuates across the modulations, rendering wave-like curves. This sinusoidal fashion of the Pb-displacements across the ICMs was previously reported by MacLaren *et al* [31]. However, in the “antiparallel” side, these polarization curves (blue) shift toward one side of the two $\langle 110 \rangle_c$, corresponding to the imbalanced Pb-displacements in opposing directions. In addition, the shift gets more severe as Ti content increases in the composition series. Accompanying with the shift in the “antiparallel” side is a slight increase in polarization components along $\langle 100 \rangle_c$ in the “orthogonal” side (pink).

Such unique dipole arrangements in the ICMs lead to uncompensated polarization within these transitional-state domains. The magnitude of the net polarization is estimated by summing the polarization vectors from corresponding vector maps and displayed in Fig. 3(d). The calculated net polarization increases with Ti content in the series, e.g., $5.89 \mu\text{C}/\text{cm}^2$ and $5.46 \mu\text{C}/\text{cm}^2$ for the “antiparallel” and the “orthogonal” side, respectively, in PZ-3; and $11.48 \mu\text{C}/\text{cm}^2$

and $11.07 \mu\text{C}/\text{cm}^2$ for the “antiparallel” and the “orthogonal” side, respectively, in PZ-6. This tendency of increasing net polarization in **transitional-state** domains, together with the reduced E_F (see Fig. S1 in Supplemental Material [20]) in the composition series, confirms that Ti on B-sites in perovskite oxides promotes FE ordering. Furthermore, the presence of uncompensated polarization may be the reason for the fact that all 90° boundaries analyzed in this work have the “antiparallel” arrangement on one side and the “orthogonal” arrangement on the other side. A 90° boundary with the same dipole arrangement on both sides would carry a very high depolarization energy.

More insight on the formation of the “antiparallel” and “orthogonal” domains was gained from density functional theory (DFT) calculations (at 0 K). To assess the stability of these polar domain structures, they were studied for both PbZrO_3 and $\text{Pb}(\text{Zr}_{0.5}\text{Sn}_{0.5})\text{O}_3$ and compared with the AFE phase (*Pbam*-like), the ground state of PbZrO_3 . Note that $\text{Pb}(\text{Zr}_{0.5}\text{Sn}_{0.5})\text{O}_3$ is considered to largely resemble the experimental compositions at a feasible computational cost. **The DFT optimized “antiparallel” and “orthogonal” domain structures for PbZrO_3 and $\text{Pb}(\text{Zr}_{0.5}\text{Sn}_{0.5})\text{O}_3$ are displayed in Fig 4(b)–(e), and their ground state structures (*Pbam*-like) are present in Fig. S4(a) and S4(b). Note that the Pb-displacements obtained by DFT are mostly in the $(001)_c$ plane with zero or negligible out-of-plane components (see detailed atom position and displacement data in Table S2–S7 in the Supplemental Material [20]).** For the relaxed **transitional-state** domain structures in pure PbZrO_3 as shown in Fig. 4(b) and 4(c), they retain the characteristics of the “antiparallel” and “orthogonal” domains found in the HAADF-STEM images, and their energies are only slightly higher than the AFE phase [Fig. 4(a)]. The “antiparallel” structure has an energy of 4.3 meV/f.u. higher than AFE, and it is 6.8 meV/f.u. for the “orthogonal” structure. Similarly, the “antiparallel” and “orthogonal” structures are also stable in $\text{Pb}(\text{Zr}_{0.5}\text{Sn}_{0.5})\text{O}_3$, as shown in Fig.

4(d) and 4(e); and compared with PbZrO_3 the relative energies are only 2.8 and 6.7 meV/f.u. higher than AFE. A close examination of the “orthogonal” structure reveals that the Pb-displacements in the “blue” and “yellow” stripes in $\text{Pb}(\text{Zr}_{0.5}\text{Sn}_{0.5})\text{O}_3$ are aligned closer to the $[100]_c$ and $[010]_c$ directions, respectively, than in PbZrO_3 . The optimized structures and the small energy differences indicate that the “antiparallel” and “orthogonal” domain structures are metastable, and the stability improves with the substitution of Sn on the B-sites. Note that the **transitional-state domain** structures are more complex than the AFE phase; therefore, they are likely to be more favorable at finite temperature due to the entropy contribution to the free energy. Furthermore, the stabilization of the **transitional-state** domain structures is related to the existence of a bi-linear coupling between the Pb-displacements and the oxygen octahedral tilting [32,33], such that the octahedra develop an accommodating pattern to lower the energy cost of forming Pb-modulations (details are discussed in Supplemental Material [20]).

The presence of net polarization in the **transitional-state** domains appears to contradict the measurement of double P - E hysteresis loops on bulk samples in this composition series (Fig. S1 in Supplemental Material [20]). To reconcile this conflict, we performed *in-situ* electric-biasing TEM experiments. The results show the transition of a **transitional-state** domain to the FE phase under an applied electric field, and its resumption to the original **transitional-state** domain structure upon the removal of the field (see Fig. S5 in Supplemental Material [20] for details). The full recovery of the hierarchical structure (domains, boundary, ICMs, and cation-displacements) hence explains the nearly zero remnant polarization measured on bulk samples.

In summary, we uncover at the atomic-scale that the Pb-displacements in ICMs of PbZrO_3 -based AFEs are either antiparallel but imbalanced or in a nearly orthogonal arrangement. The uncompensated dipole moments introduce non-zero net polarizations in 90° AFE domains,

and their magnitudes increase with Ti content. In contrast to the polar nature of the microstructure, macroscopically these ceramics behave in an AFE manner with the characteristic *P-E* double hysteresis loops of negligible remnant polarization. Such unique structures in incommensurate modulated PbZrO₃-based AFEs can be viewed as a transitional state between long-range FE and AFE orderings. Experiments on other inorganic AFE oxides may also find such transitional state in the future.

This work was supported by the National Science Foundation (NSF) through Grant DMR-1700014. All electron microscopy work was performed at the Sensitive Instrument Facility at Ames Laboratory, which is operated for the U.S. DOE by Iowa State University under Contract No. DE-AC02-07CH11358. B.X. acknowledges funding from Air Force Office of Scientific Research (AFOSR) under Grant FA9550-16-1-0065. L.B. acknowledges support from Office of Naval Research (ONR) under Grant N00014-17-1-2818.

-
- [1] C. Kittel, Phys. Rev. **82**, 729 (1951).
 - [2] G. Shirane, E. Sawaguchi, and Y. Takagi, Phys. Rev. **84**, 476 (1951).
 - [3] X. Tan, J. Frederick, C. Ma, W. Jo, and J. Rödel, Phys. Rev. Lett. **105**, 255702 (2010).
 - [4] S.-E. Park, M.-J. Pan, K. Markowski, S. Yoshikawa, and L. E. Cross, J. Appl. Phys. **82**, 1798 (1997).
 - [5] X. Tan, C. Ma, J. Frederick, S. Beckman, and K. G. Webber, J. Am. Ceram. Soc. **94**, 4091 (2011).
 - [6] B. K. Mani, C. -M. Chang, S. Lisenkov, and I. Ponomareva, Phys. Rev. Lett. **115** 097601 (2015).
 - [7] E. Sawaguchi, H. Maniwa, and S. Hoshino, Phys. Rev. **83**, 1078 (1951).

- [8] K. Yamasaki, Y. Soejima, and K. F. Fischer, *Acta Crystallogr.* **B54**, 524 (1998).
- [9] F. Jona, G. Shirane, and R. Pepinsky, *Phys. Rev.* **105**, 849 (1957).
- [10] D. L. Corker, A. M. Glazer, J. Dec, K. Roleder, and R. W. Whatmore, *Acta Crystallogr.* **B53**, 135 (1997).
- [11] O. E. Fesenko, R. V. Kolsesova, and Y. G. Sindeyev, *Ferroelectrics* **20**, 177 (1978).
- [12] Y. J. Chang, J. Y. Lian, and Y. ling Wang, *Appl. Phys. A* **36**, 221 (1985).
- [13] D. Berlincourt, *IEEE Trans. Sonics Ultrason.* **SU13**, 116 (1966).
- [14] W. Pan, Q. Zhang, A. Bhalla, and L. E. Cross, *J. Am. Ceram. Soc.* **72**, 571 (1989).
- [15] D. Viehland, D. Forst, Z. Xu, and J. F. Li, *J. Am. Ceram. Soc.* **78**, 2101 (1995).
- [16] D. Viehland, X. H. Dai, J. F. Li, and Z. Xu, *J. Appl. Phys.* **84**, 458 (1998).
- [17] T. Asada and Y. Koyama, *Phys. Rev. B* **69**, 104108 (2004).
- [18] H. He and X. Tan, *Phys. Rev. B* **72**, 024102 (2005).
- [19] Y. Cai, F. Phillipp, A. Zimmermann, L. Zhou, F. Aldinger, and M. Rühle, *Acta Mater.* **51**, 6429 (2003).
- [20] See Supplemental Material at [URL will be inserted by publisher] for experimental details, computational details, a discussion on a bi-linear coupling between the Pb-displacements and oxygen octahedral tiltings, *P-E* hysteresis loops of bulk samples, HAADF-STEM image simulations, an evaluation of chemistry variation by low-mag STEM and atomic-scale EDS, and *in-situ* electric-biasing TEM results, which includes Ref. [21–27].
- [21] F. de la Peña, *et al.*, hyperspy/hyperspy: HyperSpy 1.3.2. (2018).
doi:10.5281/ZENODO.1304308.

- [22] M. Nord, P. E. Vullum, I. MacLaren, T. Tybell, and R. Holmestad, *Adv. Struct. Chem. Imaging* **3**, 9 (2017).
- [23] C. Koch, Ph.D. thesis, Arizona State University, 2002.
- [24] P. Lu, L. Zhou, M. J. Kramer, and D. J. Smith, *Sci. Rep.* **4**, 3945 (2014).
- [25] G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [26] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [27] H. Guo and X. Tan, *Phys. Rev. B* **91**, 144104 (2015).
- [28] Y. Liu, Y. L. Zhu, Y. L. Tang, and X. L. Ma, *J. Mater. Res.* **32**, 947 (2017).
- [29] J. Cui, Y. Yao, Y. G. Wang, X. Shen, and R. C. Yu, *Ultramicroscopy* **182**, 156 (2017).
- [30] W. Zhong, R. D. King-Smith, and D. Vanderbilt, *Phys. Rev. Lett.* **72**, 3618 (1994).
- [31] I. MacLaren, R. Villafrutia, B. Schaffer, L. Houben, and A. Peláiz-Barranco, *Adv. Funct. Mater.* **22**, 261 (2012).
- [32] K. Patel, S. Prosandeev, Y. Yang, B. Xu, J. Íñiguez, and L. Bellaiche, *Phys. Rev. B* **94**, 054107 (2016).
- [33] B. Xu, O. Hellman, and L. Bellaiche, *Phys. Rev. B* **100**, 020102(R) (2019).

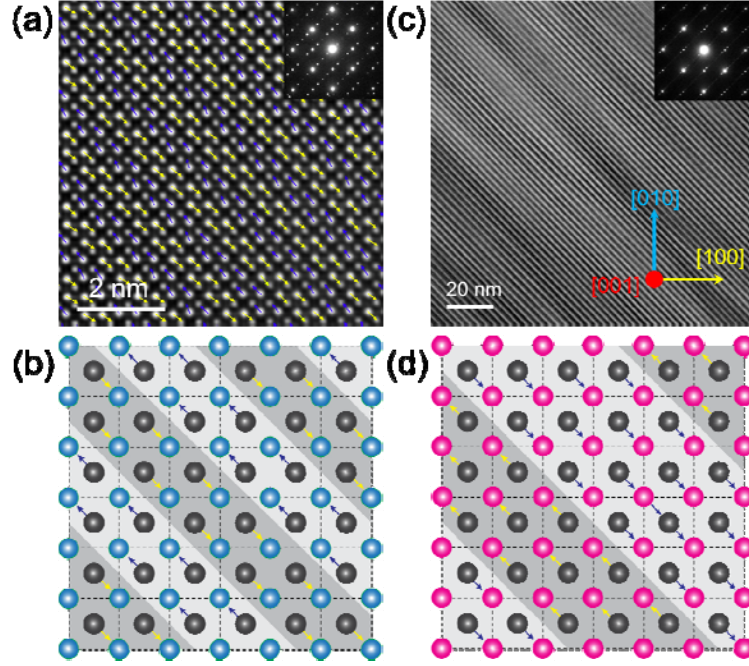


FIG. 1. (a) Typical HAADF-STEM image of CMs in PbZrO_3 , with the SAED pattern shown in the inset. A Pb-displacement vector map is overlaid on the image, showing the antiparallel displacements of Pb-cations in adjacent stripes. (b) Schematic model of the CMs for PbZrO_3 proposed by Sawaguchi *et al* [7]. A-site (Pb): gray; B-site (Zr): blue. (c) Typical bright-field TEM image of ICMs in a Sn, Ti, Nb co-modified PbZrO_3 ceramic, with the SAED pattern shown in the inset. The ICMs render as fine fringes with a periodicity of ~ 2 nm. (d) Schematic model of the ICMs as a mixture of stripes with a stochastic thickness of 2–4 layers of $\{110\}_c$ plane, proposed by He *et al* [18]. A-site (Pb): gray; B-site (Zr, Sn, Ti, Nb): pink.

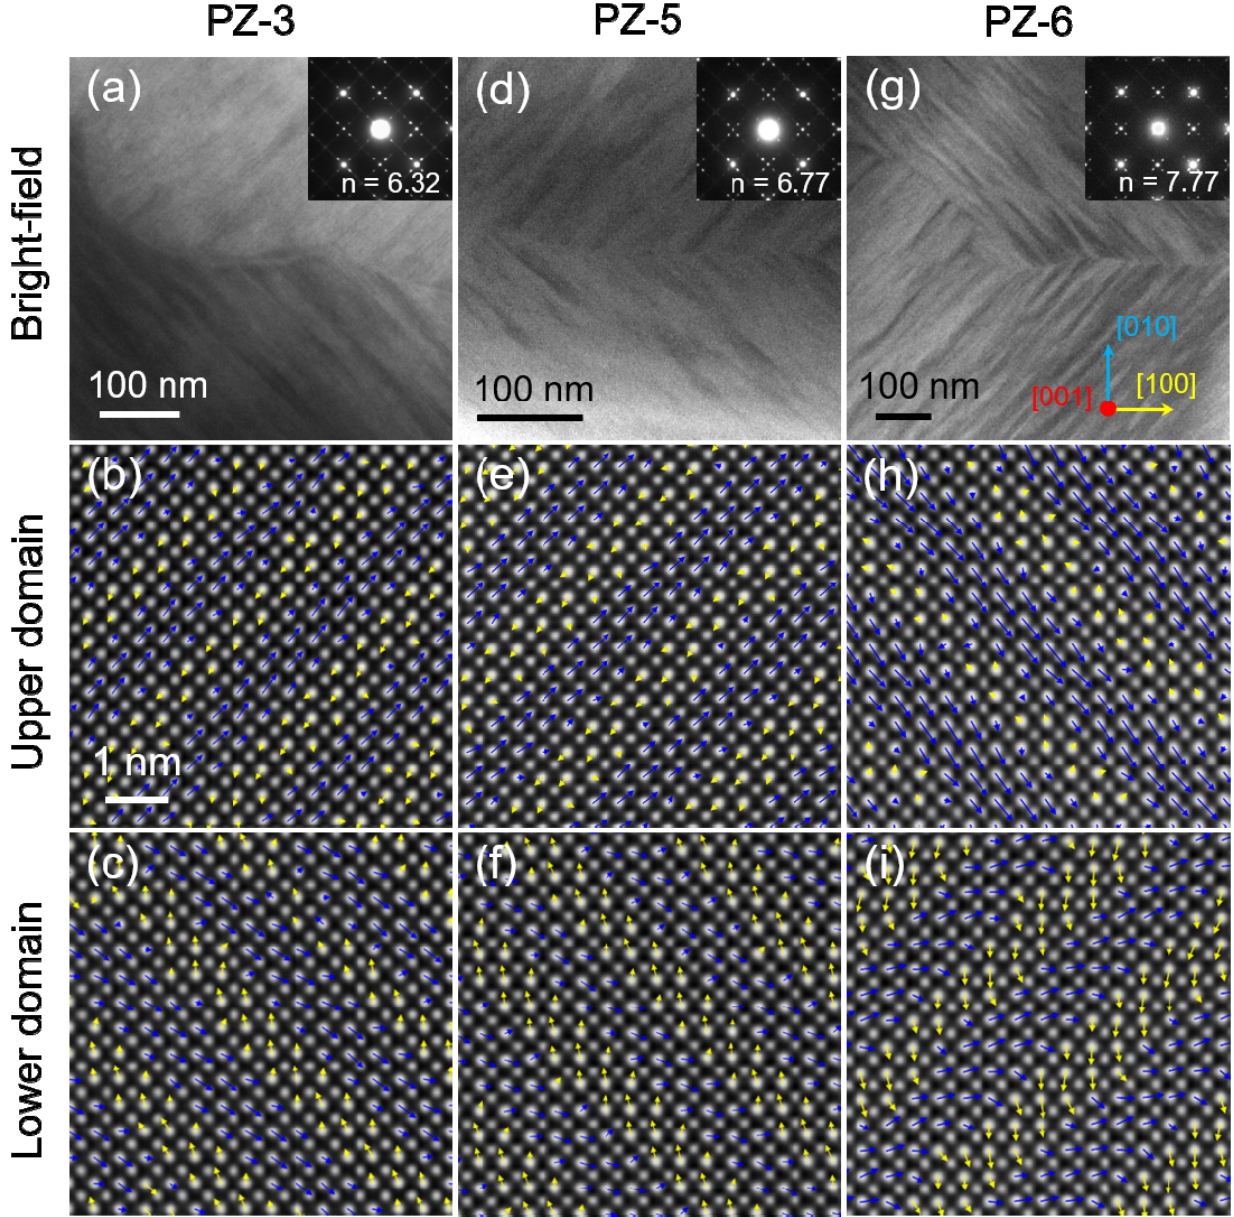


FIG. 2. The top row is the typical bright-field TEM images of 90° domains in PZ-3 (a), PZ-5 (d), and PZ-6 (g). The insets are the SAED patterns taken from the domain boundary region showing two sets of satellite spots, from which the periodicity of the ICMs (n value) was calculated. The middle row shows the Pb-displacement vector maps overlaid on the HAADF-STEM images taken from the upper domains in PZ-3 (b), PZ-5 (e), and PZ-6 (h). The Pb-displacements in this row are in an antiparallel arrangement, but those in the wider stripes (blue) have a larger

magnitude than the ones in the narrower stripes (yellow). The bottom row presents the Pb-displacement vector maps taken from the lower domains in PZ-3 (c), PZ-5 (f), and PZ-6 (i), where the Pb-displacements tend to form in a nearly orthogonal arrangement in adjacent stripes.

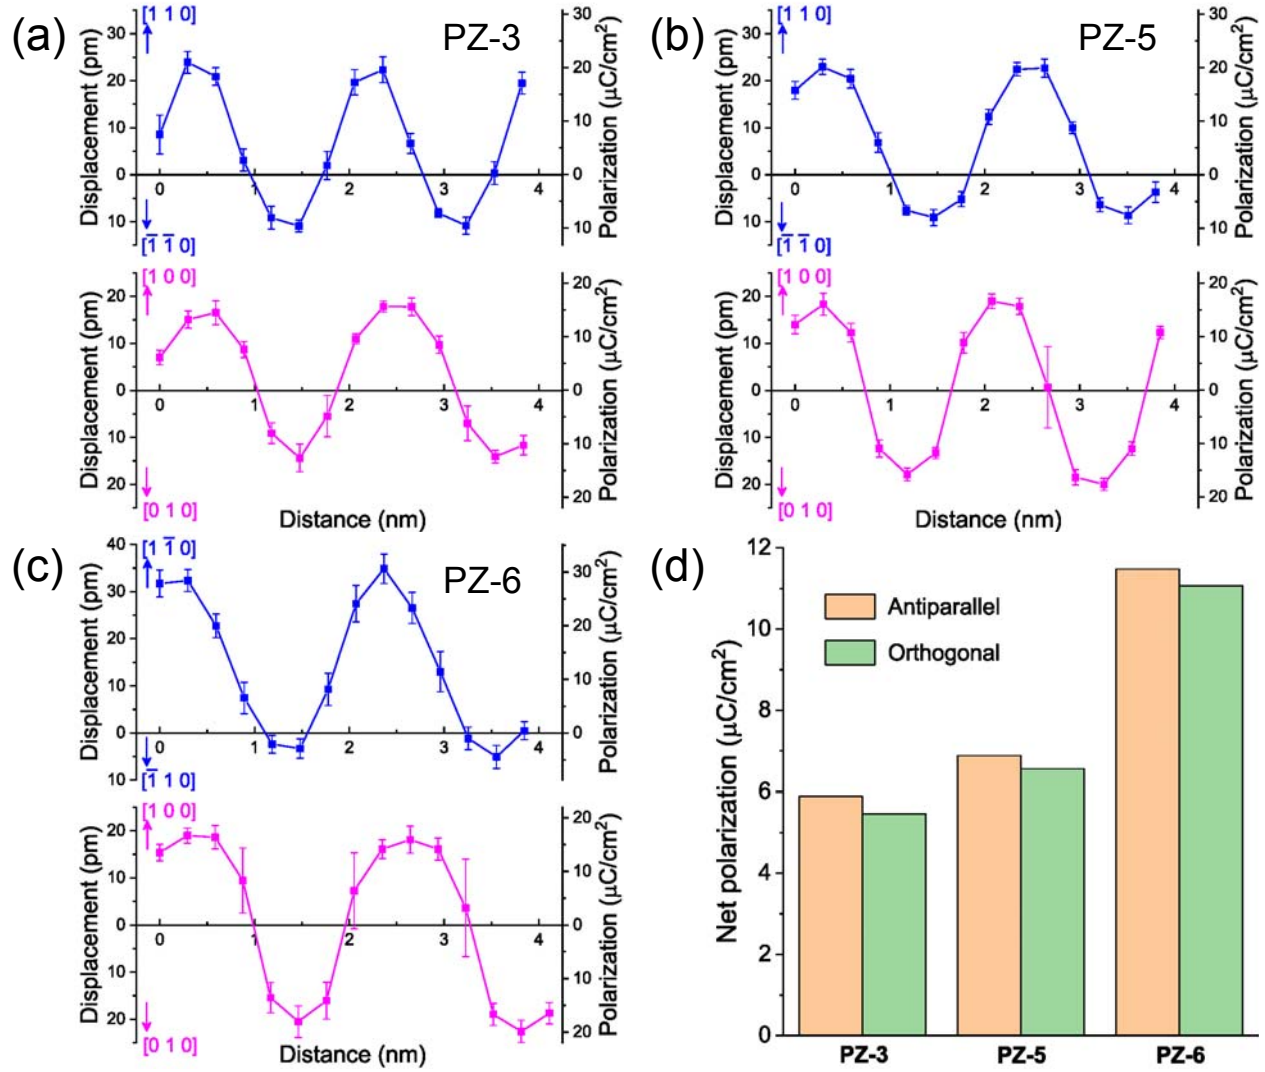


FIG. 3. (a–c) Pb-displacement magnitudes, extracted from the Pb-displacement vector maps, and the corresponding polarizations in PZ-3 (a), PZ-5 (b), and PZ-6 (c). The upper plots in each panel (blue) are from the “antiparallel” side showing the components along the two antiparallel $\langle 110 \rangle_c$ directions, whereas the lower plots in each panel (pink) are from the “orthogonal” sides showing the components along the two orthogonal $\langle 100 \rangle_c$ directions. The displacements were

averaged from 10 layers of Pb-cations along the length direction of the ICM stripes. (d) Overall polarizations in the “antiparallel” and “orthogonal” sides of the three specimens calculated from the corresponding vector maps.

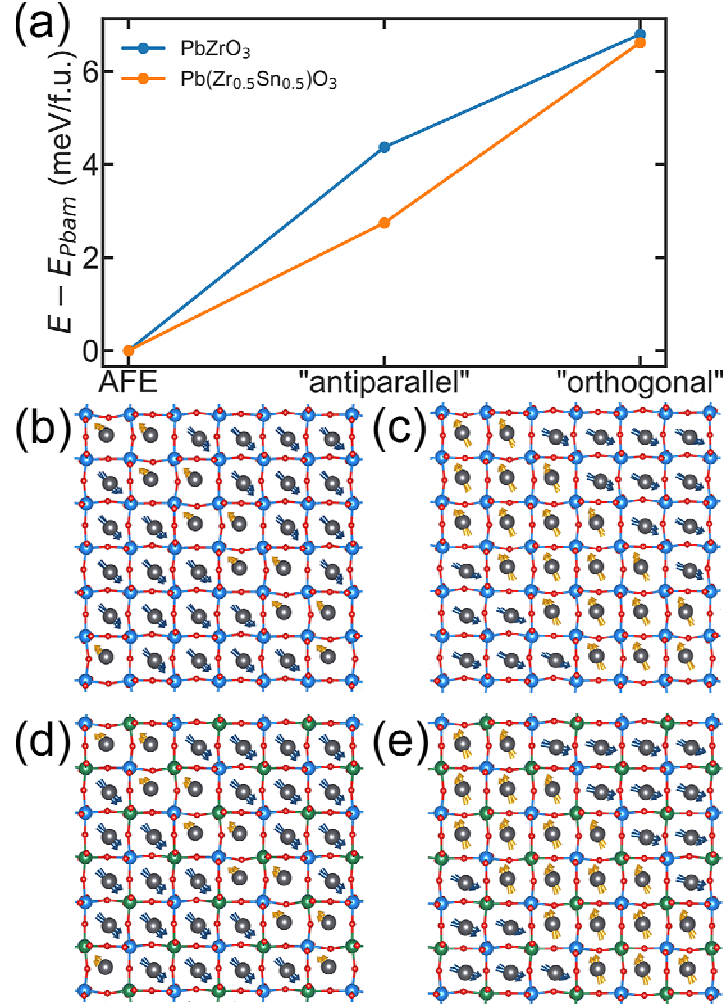


FIG. 4. (a) Energies of the “antiparallel” and “orthogonal” domain structures relative to the AFE phase (*Pbam*-like) for $PbZrO_3$ and $Pb(Zr_{0.5}Sn_{0.5})O_3$. (b, c) DFT optimized “antiparallel” and “orthogonal” domain structures of $PbZrO_3$. (d, e) DFT optimized “antiparallel” and “orthogonal” domain structures of $Pb(Zr_{0.5}Sn_{0.5})O_3$. Pb: gray; Zr: blue; Sn: green; O: red. Pb-displacements are denoted in blue and yellow colors in different stripes. **The atom position and displacement data**

used to create (b), (c), (d), and (e) are listed in Table S4, S5, S6, and S7, respectively, in the Supplemental Material [20].