



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Keldysh Space Control of Charge Dynamics in a Strongly Driven Mott Insulator

Xinwei Li, Honglie Ning, Omar Mehio, Hengdi Zhao, Min-Cheol Lee, Kyungwan Kim, Fumihiko Nakamura, Yoshiteru Maeno, Gang Cao, and David Hsieh

Phys. Rev. Lett. **128**, 187402 — Published 6 May 2022

DOI: [10.1103/PhysRevLett.128.187402](https://doi.org/10.1103/PhysRevLett.128.187402)

# Keldysh space control of charge dynamics in a strongly driven Mott insulator

Xinwei Li,<sup>1,2,\*</sup> Honglie Ning,<sup>1,2,\*</sup> Omar Mehio,<sup>1,2,\*</sup> Hengdi Zhao,<sup>3</sup> Min-Cheol Lee,<sup>4,5</sup> Kyungwan Kim,<sup>6</sup> Fumihiko Nakamura,<sup>7</sup> Yoshiteru Maeno,<sup>8</sup> Gang Cao,<sup>3</sup> and David Hsieh<sup>1,2,†</sup>

<sup>1</sup>*Institute for Quantum Information and Matter,  
California Institute of Technology, Pasadena, CA 91125, USA*

<sup>2</sup>*Department of Physics, California Institute of Technology, Pasadena, CA 91125, USA*

<sup>3</sup>*Department of Physics, University of Colorado, Boulder, CO 80309, USA*

<sup>4</sup>*Center for Integrated Nanotechnologies, Los Alamos National Laboratory, Los Alamos, NM 87545, USA*

<sup>5</sup>*Center for Correlated Electron Systems, Institute for Basic Science, Seoul 08826, Republic of Korea*

<sup>6</sup>*Department of Physics, Chungbuk National University, Cheongju, Chungbuk 28644, Republic of Korea*

<sup>7</sup>*Department of Education and Creation Engineering,*

*Kurume Institute of Technology, Fukuoka 830-0052, Japan*

<sup>8</sup>*Department of Physics, Graduate School of Science, Kyoto University, Kyoto 606-8502, Japan*

(Dated: April 12, 2022)

The fate of a Mott insulator under strong low frequency optical driving conditions is a fundamental problem in quantum many-body dynamics. Using ultrafast broadband optical spectroscopy, we measured the transient electronic structure and charge dynamics of an off-resonantly pumped Mott insulator  $\text{Ca}_2\text{RuO}_4$ . We observe coherent bandwidth renormalization and nonlinear doublon-holon pair production occurring in rapid succession within a sub-100 femtosecond pump pulse duration. By sweeping the electric field amplitude, we demonstrate continuous bandwidth tuning and a Keldysh cross-over from a multi-photon absorption to quantum tunneling dominated pair production regime. Our results provide a procedure to control coherent and nonlinear heating processes in Mott insulators, facilitating the discovery of novel out-of-equilibrium phenomena in strongly correlated systems.

The response of a Mott insulator to a strong electric field is a fundamental question in the study of non-equilibrium correlated many-body systems [1–15]. In the DC limit, a breakdown of the insulating state occurs when the field strength exceeds the threshold for producing pairs of doubly-occupied (doublon) and empty (holon) sites by quantum tunneling, in analogy to the Schwinger mechanism for electron-positron pair production out of the vacuum [16]. Recently, the application of strong low frequency AC electric fields has emerged as a potential pathway to induce insulator-to-metal transitions [17–20], realize efficient high-harmonic generation [21, 22], and coherently manipulate band structure and magnetic exchange interactions in Mott insulators [23–28]. Therefore there is growing interest to understand doublon-holon (d-h) pair production and their non-thermal dynamics in the strong field AC regime.

Strong AC field induced d-h pair production has been theoretically studied using Landau-Dykhne adiabatic perturbation theory [29] along with a suite of non-equilibrium numerical techniques [17, 21, 22, 29–32]. Notably, d-h pairs are primarily produced through two nonlinear mechanisms: multi-photon absorption and quantum tunneling [29, 33]. The two regimes are characterized by distinct electric field scaling laws and momentum space distributions of d-h pairs. By tuning the Keldysh adiabaticity parameter  $\gamma_K = \hbar\omega_{\text{pump}}/(eE_{\text{pump}}\xi)$  through unity, where  $\omega_{\text{pump}}$  is the pump frequency,  $E_{\text{pump}}$  is the pump electric field,  $e$  is electron charge, and  $\xi$  is the d-h correlation length, a cross-over from a multi-photon dominated ( $\gamma_K > 1$ ) to a tunneling dominated ( $\gamma_K < 1$ ) regime can in principle be induced. However, direct ex-

perimental tests are lacking owing to the challenging need to combine strong tunable low frequency pumping fields with sensitive ultrafast probes of non-equilibrium distribution functions.

We devise a protocol to study these predicted phenomena using ultrafast broadband optical spectroscopy. As a testbed, we selected the multiband Mott insulator  $\text{Ca}_2\text{RuO}_4$ . Below a metal-to-insulator transition temperature  $T_{\text{MIT}} = 357$  K, a Mott gap ( $\Delta = 0.6$  eV) opens within its  $2/3$ -filled Ru  $4d$   $t_{2g}$  manifold [34–37], with a concomitant distortion of the lattice [38]. Upon further cooling, the material undergoes an antiferromagnetic transition at  $T_N = 113$  K into a Néel ordered state. It has recently been shown that for temperatures below  $T_{\text{MIT}}$ , re-entry into a metallic phase can be induced by a remarkably weak DC electric field of order 100 V/cm [39], making  $\text{Ca}_2\text{RuO}_4$  a promising candidate for exhibiting efficient nonlinear pair production.

To estimate the response of  $\text{Ca}_2\text{RuO}_4$  to a low frequency AC electric field, we calculated the d-h pair production rate ( $\Gamma$ ) over the Keldysh parameter space using a Landau-Dykhne method developed by Oka [29]. Experimentally determined values of the Hubbard model parameters for  $\text{Ca}_2\text{RuO}_4$  were used as inputs [40]. As shown in Figure 1(a),  $\Gamma$  is a generally increasing function of  $E_{\text{pump}}$  and  $\hbar\omega_{\text{pump}}$ . For a fixed  $\omega_{\text{pump}}$ , the predicted scaling of  $\Gamma$  with  $E_{\text{pump}}$  is clearly different on either side of the Keldysh cross-over line ( $\gamma_K = 1$ ), evolving from power law behavior  $\Gamma \propto (E_{\text{pump}})^a$  in the multi-photon regime to threshold behavior  $\Gamma \propto \exp(-b/E_{\text{pump}})$  in the tunneling regime [Fig. 1(b)].

At time delays where coherent nonlinear processes are

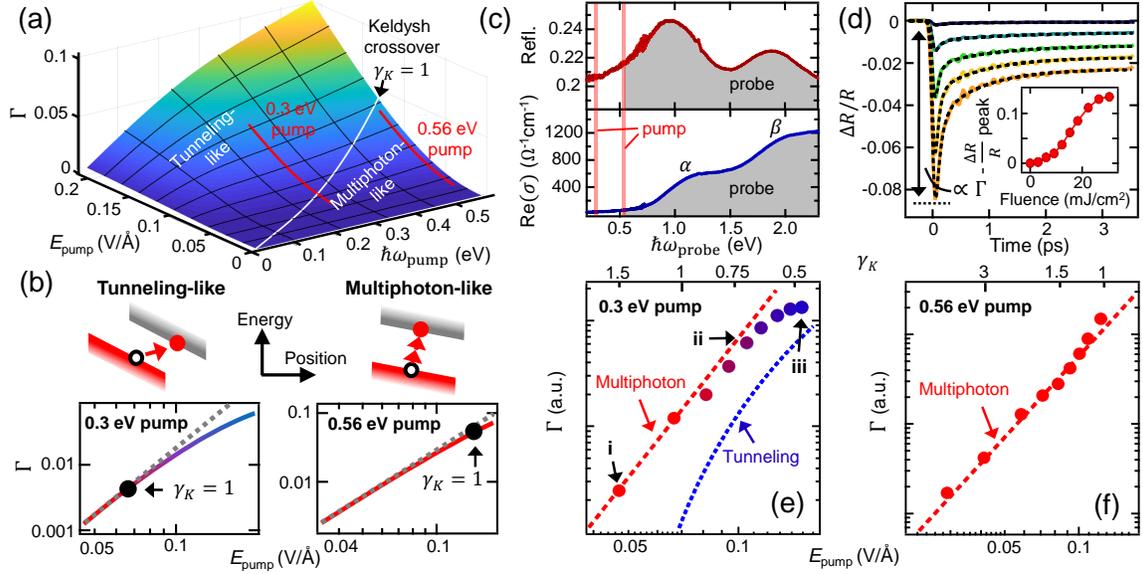


FIG. 1. Resolving Keldysh tuning using pump-probe spectroscopy. (a)  $\Gamma$  calculated across Keldysh space using the Landau-Dykhne method. (b) Constant energy cuts along the red lines shown in (a) plotted on a logarithmic scale. Black dots mark the Keldysh cross-over. Gray dashed lines: scaling relation in the multi-photon regime. Schematics of the multi-photon and tunneling processes are shown above. (c) Equilibrium reflectivity (top) and conductivity (bottom) spectra of  $\text{Ca}_2\text{RuO}_4$  at 20 K. The 0.3 eV and 0.56 eV pump energies are marked by vertical red lines. The probe energy range is shaded grey. (d) Select 0.3 eV pump 1.77 eV probe  $\Delta R/R$  traces at fluences of 3, 9, 15, 22, and 30  $\text{mJ}/\text{cm}^2$  (top to bottom). Dashed lines are fits detailed in [40]. Inset: Peak  $\Delta R/R$  versus fluence showing nonlinearity. (e, f) Experimental cuts through the same regions of parameter space as in (b). Error bars are smaller than data markers. Scaling relations for multi-photon and tunneling behavior are overlaid as red and blue dashed lines respectively.

absent, the transient pump-induced change in reflectivity of a general gapped material is proportional to the density of photo-excited quasi-particles [41–43], which, upon dividing by a constant pump pulse duration ( $\sim 100$  fs), yields  $\Gamma$ . Differential reflectivity ( $\Delta R/R$ ) transients from  $\text{Ca}_2\text{RuO}_4$  single crystals were measured at  $T = 80$  K using several different subgap pump photon energies ( $\hbar\omega_{\text{pump}} < \Delta$ ) in the mid-infrared region, and across an extensive range of probe photon energies ( $\hbar\omega_{\text{probe}}$ ) in the near-infrared region spanning both the  $\alpha$  and  $\beta$  absorption peaks [Fig. 1(c)]. These two band edge features can be assigned to optical transitions within the Ru  $t_{2g}$  manifold [37, 44]. Figure 1(d) shows reflectivity transients at various fluences measured using  $\hbar\omega_{\text{pump}} = 0.3$  eV and  $\hbar\omega_{\text{probe}} = 1.77$  eV. Upon pump excitation, we observe a rapid resolution-limited drop in  $\Delta R/R$ . With increasing fluence, the minimum value of  $\Delta R/R$  becomes larger, indicating a higher value of  $\Gamma$  within the pump pulse duration. This is followed by exponential recovery as the d-h pairs thermalize and recombine [40]. By plotting  $\Gamma$  against the peak value of  $E_{\text{pump}}$  (measured in vacuum), we observe a change from power law scaling to threshold behavior when  $E_{\text{pump}} > 0.07$  V/Å [Fig. 1(e)], in remarkable agreement with our calculated Keldysh cross-over [Figs. 1(a),(b)]. In contrast, measurements performed using 0.56 eV pumping exhibit exclusively power law scaling over the same  $E_{\text{pump}}$  range [Fig. 1(f)], again

consistent with our model.

A predicted hallmark of the Keldysh cross-over is a change in width of the non-thermal distribution of d-h pairs in momentum space [29]. In the multi-photon regime, doublons and holons primarily occupy the conduction and valence band edges respectively, resulting in a pair distribution function ( $P_p$ ) sharply peaked about zero momentum ( $p = 0$ ). In the tunneling regime, the peak drastically broadens, reflecting the increased spatial localization of d-h pairs. Using the Landau-Dykhne method [40], we calculated the evolution of  $P_p$  for  $\text{Ca}_2\text{RuO}_4$  as a function of  $E_{\text{pump}}$  through the Keldysh cross-over. Figure 2(a) displays  $P_p$  curves at three successively larger  $E_{\text{pump}}$  values corresponding to (i)  $\gamma_K = 1.49$ , (ii)  $\gamma_K = 0.75$  and (iii)  $\gamma_K = 0.47$ , which show a clearly broadening width along with increasing amplitude.

To demonstrate how signatures of a changing  $P_p$  width are borne out in experiments, we simulate the effects of different non-thermal electronic distribution functions on the broadband optical response of a model insulator. Assuming a direct-gap quasi-two-dimensional insulator with cosine band dispersion in the momentum plane ( $p_x, p_y$ ), the optical susceptibility computed using the density matrix formalism can be expressed as [40, 45]:

$$\chi = \sum_{P_x, P_y} C \mathcal{L}[\hbar\omega_{\text{probe}} - \Delta(p_x, p_y)][N_v(p_x, p_y) - N_c(p_x, p_y)]$$

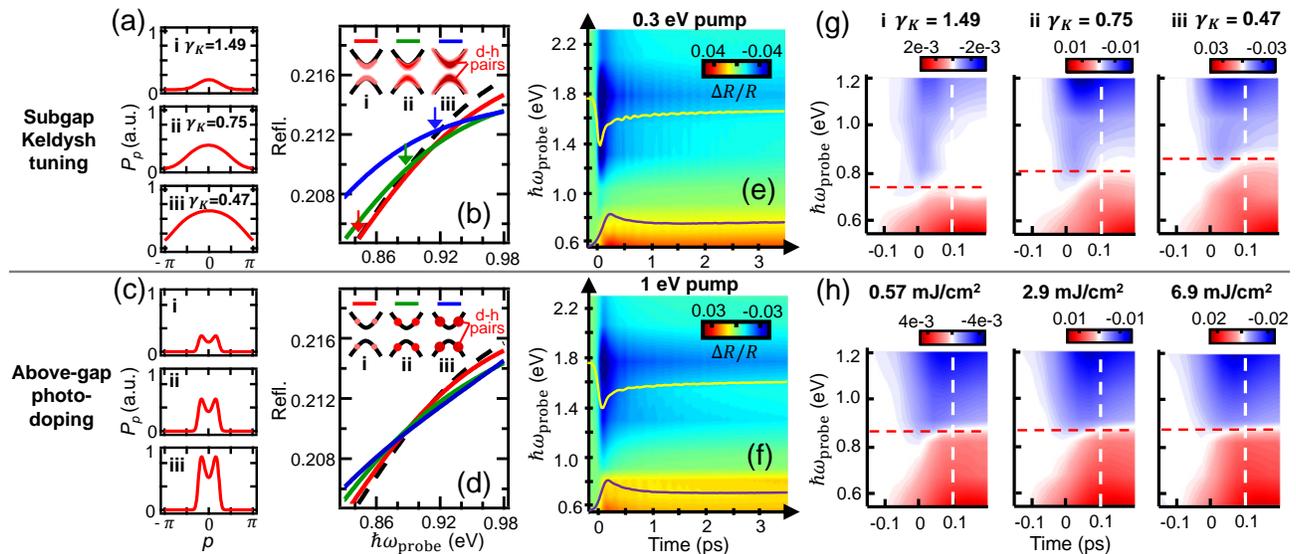


FIG. 2. Non-thermal pair distribution through the Keldysh crossover. (a) Calculated  $P_p$  for conditions i to iii using the Landau-Dykhne method. (b) Simulated non-equilibrium reflectivity spectra for subgap pumping. (c, d) Analogues of (a) and (b) but simulated for above-gap pumping. Fluence increases from i to iii. Black curves in (b) and (d) are the equilibrium spectra. Arrows in (b) mark the crossing points between the non-equilibrium and equilibrium curves. Experimental  $\Delta R/R$  maps of  $\text{Ca}_2\text{RuO}_4$  for (e) 0.3 eV pump (fluence: 30  $\text{mJ}/\text{cm}^2$ ) and (f) 1 eV pump (fluence: 7  $\text{mJ}/\text{cm}^2$ ). Two representative constant energy cuts (yellow: 1.77 eV, purple: 0.56 eV) are overlaid. (g) Zoom-in  $\Delta R/R$  maps for 0.3 eV pump using three pump fluences [marked in Fig. 1(e)] corresponding to conditions (i) to (iii) in (a). (h) Zoom-in  $\Delta R/R$  maps for 1 eV pump using three pump fluences indicated above. White dashed lines mark  $t = 0.1$  ps. Red dashed lines: guides to the eye for the  $\hbar\omega_{\text{probe}}$  where  $\Delta R/R$  changes sign at  $t = 0.1$  ps.

where  $C$  is a constant incorporating the transition matrix element,  $\mathcal{L}$  represents a Lorentzian oscillator centered at the gap energy  $\Delta(p_x, p_y)$ , and  $N_v$  and  $N_c$  are the occupations of the valence and conduction bands, respectively. As will be shown later [Fig. 3(a)], it is valid to assume that  $\Delta(p_x, p_y)$  decreases in proportion to the number of excitations [40]. Figure 2(b) shows simulated reflectivity spectra around the band edge - converted from  $\chi$  via the Fresnel equations - using Gaussian functions for  $N_v$  and  $N_c$  of variable width to approximate the  $P_p$  lineshapes [Fig. 2(a)] [40]. As  $P_p$  evolves from condition (i) to (iii), we find that the intersection between the non-equilibrium and equilibrium reflectivity spectra shifts to progressively higher energy. For comparison, we also performed simulations under resonant photo-doping conditions using the direct-gap insulator model. Figure 2(c) displays three  $P_p$  curves at successively larger  $E_{\text{pump}}$  values, which were chosen such that the total number of excitations match those in Figure 2(a). Each curve exhibits maxima at non-zero momenta where  $\hbar\omega_{\text{pump}} = \Delta(|p|)$  is satisfied. In stark contrast to the subgap pumping case, the amplitude of  $P_p$  increases with  $E_{\text{pump}}$  but the width remains unchanged. This results in the non-equilibrium reflectivity spectra all intersecting the equilibrium spectrum at the same energy, forming an isosbestic point [Fig. 2(d)]. The presence or absence of an isosbestic point is therefore a key distinguishing feature between Keldysh space tuning and photo-doping. This criterion can be derived

from a more general analytical model [40], which shows that a key condition for identifying a Keldysh crossover is that  $\Delta R/R$  spectra at difference fluences do not scale.

Probe photon energy-resolved  $\Delta R/R$  maps of  $\text{Ca}_2\text{RuO}_4$  were measured in both the Keldysh tuning ( $\hbar\omega_{\text{pump}} = 0.3$  eV) and photo-doping ( $\hbar\omega_{\text{pump}} = 1$  eV) regimes. As shown in Figures 2(e) & (f), the extremum in  $\Delta R/R$ , denoting the peak d-h density, occurs near a time  $t = 0.1$  ps measured with respect to when the pump and probe pulses are exactly overlapped ( $t = 0$ ). This is followed by a rapid thermalization of d-h pairs as indicated by the fast exponential relaxation in  $\Delta R/R$ , which will be discussed later [40]. Figure 2(g) shows  $\Delta R/R$  maps acquired in the subgap pumping regime for three different pump fluences corresponding to conditions (i) to (iii) in Figure 2(a) and 1(e). Focusing on the narrow time window around  $t = 0.1$  ps where the d-h distribution is highly non-thermal, we observe that  $\Delta R/R$  changes sign across a well-defined probe energy (dashed red line), marking a crossing point of the transient and equilibrium reflectivity spectra. As  $\gamma_K$  decreases, the crossing energy increases, evidencing an absence of an isosbestic point. Analogous maps acquired in the photo-doping regime [Fig. 2(h)] also exhibit a sign change. However, the crossing energy remains constant over an order of magnitude change in fluence, consistent with an isosbestic point. These measurements corroborate our simulations and highlight the unique distribution control afforded by Keldysh tuning.

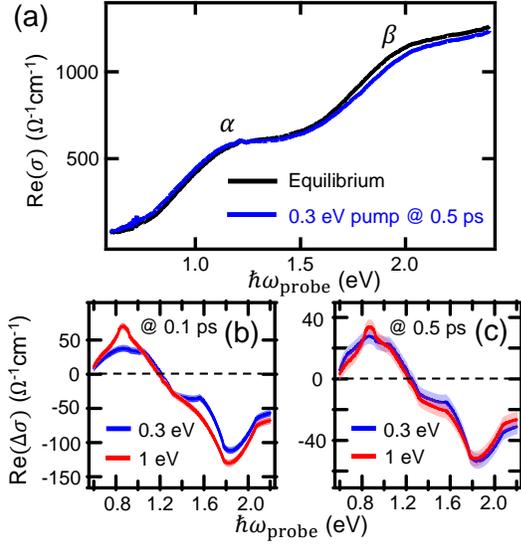


FIG. 3. Non-equilibrium conductivity transients. (a) Conductivity spectra of  $\text{Ca}_2\text{RuO}_4$  in the un-pumped equilibrium state at 80 K and the 0.3 eV pumped non-equilibrium state at  $t = 0.5$  ps (fluence:  $26 \text{ mJ/cm}^2$ ). (b) Comparison of differential conductivity spectra between 0.3 eV pump ( $\Delta\sigma_{0.3 \text{ eV}}$ ) and scaled 1 eV pump ( $A\Delta\sigma_{1 \text{ eV}}$ ) cases at  $t = 0.1$  ps and (c)  $t = 0.5$  ps. Red and blue shades indicate error estimated from the  $\omega_{\text{probe}}$ -dependent fluctuations of the experimental  $\Delta\sigma$  spectra.

To study the d-h thermalization dynamics in more detail, we used a Kramers-Kronig transformation to convert our differential reflectivity spectra into differential conductivity ( $\Delta\sigma$ ) spectra [40]. Figure 3(a) shows the real part of the transient conductivity measured in the thermalized state ( $t = 0.5$  ps) following an 0.3 eV pump pulse of fluence  $26 \text{ mJ/cm}^2$  ( $\gamma_{\text{K}} = 0.5$ ), overlaid with the equilibrium conductivity. Subgap pumping induces a spectral weight transfer from the  $\beta$  to  $\alpha$  peak and a slight red-shift of the band edge, likely due to free carrier screening of the Coulomb interactions [46]. Unlike in the DC limit, there is no sign of Mott gap collapse despite  $E_{\text{pump}}$  exceeding  $10^9 \text{ V/m}$ . To verify that the electronic subsystem indeed thermalizes by  $t = 0.5$  ps, we compare the real parts of  $\Delta\sigma_{0.3 \text{ eV}}$  (fluence:  $26 \text{ mJ/cm}^2$ ) and  $\Delta\sigma_{1 \text{ eV}}$  (fluence:  $4 \text{ mJ/cm}^2$ ), the change in conductivity induced by subgap and above-gap pumping respectively, at both  $t = 0.1$  ps and  $0.5$  ps. A scaling factor  $A$  is applied to  $\Delta\sigma_{1 \text{ eV}}$  to account for any differences in excitation density. As shown in Figure 3(b), the  $t = 0.1$  ps curves do not agree within any scale factor. This is expected because the linear and nonlinear pair production processes initially give rise to very different non-thermal distributions (Fig. 2). Conversely, by  $t = 0.5$  ps, the curves overlap very well [Fig. 3(c)], indicating that the system has lost memory of how the d-h pairs were produced and is thus completely thermalized.

Based on the observations in Figures 3(b) and (c), the

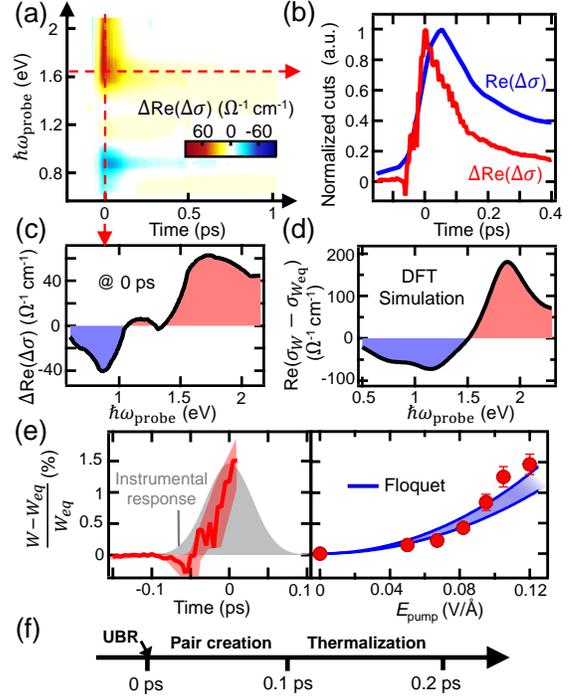


FIG. 4. Ultrafast coherent bandwidth renormalization. (a)  $\Delta(\Delta\sigma)$  map obtained by subtracting scaled  $\Delta\sigma_{1 \text{ eV}}$  from  $\Delta\sigma_{0.3 \text{ eV}}$  spectra. (b) A constant probe energy cut at 1.65 eV [dashed horizontal line in (a)] plotted together with  $\Delta\sigma_{0.3 \text{ eV}}$ . (c) A constant time cut at  $t = 0$  [dashed vertical line in (a)]. (d) DFT simulation of the spectrum change induced by bandwidth broadening.  $\sigma_W$  ( $\sigma_{W_{\text{eq}}}$ ): conductivity with (without) bandwidth broadening. (e) (left) Quantitative extraction of pump-induced bandwidth modification versus  $t$  (with  $E_{\text{pump}} = 0.12 \text{ V/\AA}$ ) and (right) versus  $E_{\text{pump}}$  (with  $t = 0$  ps) based on fitting to DFT calculations. Red shaded region: error bar. Blue shaded region: Floquet theory prediction based on a periodically driven two-site cluster Hubbard model. Upper and lower bounds assume  $U = 3 \text{ eV}$  [37] and  $U = 3.5 \text{ eV}$  [34] respectively, where  $U$  is the on-site Coulomb energy, with no other adjustable parameters. (f) Chronology of non-thermal processes following an impulsive subgap drive.

non-thermal window can be directly resolved by evaluating the time interval over which the quantity  $\Delta(\Delta\sigma) = \Delta\sigma_{0.3 \text{ eV}} - A \times \Delta\sigma_{1 \text{ eV}}$  is non-zero [40]. Figure 4(a) shows the complete temporal mapping of  $\Delta(\Delta\sigma)$  spectra. The signal is finite only around  $t = 0$  ps and is close to zero otherwise, supporting the validity of our subtraction protocol. By taking a constant energy cut, we can extract a thermalization time constant of around 0.2 ps [Fig. 4(b)]. Interestingly,  $\Delta R/R$  and  $\Delta\sigma_{0.3 \text{ eV}}$ , which both track the d-h pair density, peak near 0.1 ps whereas  $\Delta(\Delta\sigma)$  peaks earlier at  $t = 0$  when the d-h pair density is still quite low. This implies the existence of an additional coherent non-thermal process that scales with  $E_{\text{pump}}$ , which peaks at  $t = 0$ , rather than with the d-h density.

To identify the physical process responsible for the  $t = 0$  signal, we examined how the electronic structure of

$\text{Ca}_2\text{RuO}_4$  would need to change in order to produce the  $\Delta(\Delta\sigma)$  profile observed at  $t = 0$  [Fig. 4(c)]. Using density functional theory (DFT), we performed an *ab initio* calculation of the optical conductivity of  $\text{Ca}_2\text{RuO}_4$  based on its reported lattice and magnetic structures below  $T_N$ . The tilt angle of the  $\text{RuO}_6$  octahedra was then systematically varied in our calculation as a means to simulate a changing electronic bandwidth [40]. We find that both the real and imaginary parts of the measured  $\Delta(\Delta\sigma)$  spectrum at  $t = 0$  are reasonably well reproduced by our calculations if we assume the bandwidth of the driven system ( $W$ ) to exceed that in equilibrium  $W_{\text{eq}}$  [Fig. 4(d)] [40]. This points to the coherent non-thermal process being a unidirectional ultrafast bandwidth renormalization (UBR) process that predominantly occurs under subgap pumping conditions [Fig. 4(f)].

Coherent UBR can in principle occur via photo-assisted virtual hopping between lattice sites, which has recently been proposed as a pathway to dynamically engineer the electronic and magnetic properties of Mott insulators [23–28]. To quantitatively extract the time- and  $E_{\text{pump}}$ -dependence of the fractional bandwidth change  $(W - W_{\text{eq}})/W_{\text{eq}}$ , we collected  $\Delta(\Delta\sigma)$  spectra as a function of both time delay and pump fluence and fit them to DFT simulations [40]. As shown in Figure 4(e), the bandwidth change exhibits a pulse-width limited rise with a maximum  $t = 0$  value that increases monotonically with the peak pump field, reaching up to a relatively large amplitude of 1.5 % at  $E_{\text{pump}} = 0.12 \text{ V/\AA}$ , comparable to the bandwidth increases induced by doping [36] and pressure [47]. Independently, we also calculated the field dependence of  $(W - W_{\text{eq}})/W_{\text{eq}}$  expected from photo-assisted virtual hopping by solving a periodically driven two-site Hubbard model in the Floquet formalism [23, 40], using the same model parameters for  $\text{Ca}_2\text{RuO}_4$  as in our Landau-Dykhne calculations [Fig. 1(a)]. We find a remarkable match to the data without any adjustable parameters [Fig. 4(e)]. Since bandwidth renormalization increases with the Floquet parameter  $(eaE_{\text{pump}})/\hbar\omega_{\text{pump}}$  in the case of photo-assisted virtual hopping, where  $a$  is the inter-site distance, this naturally explains why subgap pumping induces the much larger UBR effect compared to above-gap pumping.

The ability to rationally tune a Mott insulator *in situ* over Keldysh space enables targeted searches for exotic out-of-equilibrium phenomena such as strong correlation assisted high harmonic generation [21, 22], coherent dressing of quasiparticles [48], Wannier-Stark localization [2, 17], AC dielectric breakdown [29] and dynamical Franz-Keldysh effects [32, 49], which are predicted to manifest in separate regions of Keldysh space. It also provides control over the nonlinear d-h pair production rate - the primary source of heating and decoherence under subgap pumping conditions - in Mott systems, which is crucial for experimentally realizing coherent Floquet engineering of strongly correlated electronic phases.

We thank Swati Chaudhary, Nicolas Tancogne-Dejean, and Tae Won Noh for useful discussions. The first-principles calculations in this work were performed using the QUANTUM ESPRESSO package. Time-resolved spectroscopic measurements were supported by the Institute for Quantum Information and Matter (IQIM), an NSF Physics Frontiers Center (PHY-1733907). D.H. also acknowledges support for instrumentation from the David and Lucile Packard Foundation and from ARO MURI Grant No. W911NF-16-1-0361. X.L. acknowledges support from the Caltech Postdoctoral Prize Fellowship and the IQIM. G.C. acknowledges NSF support via grant DMR 1903888. M.C.L. acknowledges funding supports from the Research Center Program of IBS (Institute for Basic Science) in Korea (IBS-R009-D1). K.W.K. was supported by the National Research Foundation of Korea (NRF) grant funded by the Korea government (MSIT) (No. 2020R1A2C3013454). Y. M. was supported by the JSPS Core-to-Core Program No. JPJSCCA20170002 as well as the JSPS Kakenhi No. JP17H06136.

---

\* These authors contributed equally to this work

† email: dhsieh@caltech.edu

- [1] M. Eckstein, T. Oka, and P. Werner, Phys. Rev. Lett. **105**, 146404 (2010).
- [2] W.-R. Lee and K. Park, Phys. Rev. B **89**, 205126 (2014).
- [3] Z. Lenarčič and P. Prelovšek, Phys. Rev. Lett. **108**, 196401 (2012).
- [4] J. Li, C. Aron, G. Kotliar, and J. E. Han, Phys. Rev. Lett. **114**, 226403 (2015).
- [5] T. Oka and H. Aoki, Phys. Rev. Lett. **95**, 137601 (2005).
- [6] P. Diener, E. Janod, B. Corraze, M. Querré, C. Adda, M. Guilloux-Viry, S. Cordier, A. Camjayi, M. Rozenberg, M. P. Besland, and L. Cario, Phys. Rev. Lett. **121**, 016601 (2018).
- [7] A. Asamitsu, Y. Tomioka, H. Kuwahara, and Y. Tokura, Nature **388**, 50 (1997).
- [8] H. Chu, M.-J. Kim, K. Katsumi, S. Kovalev, R. D. Dawson, L. Schwarz, N. Yoshikawa, G. Kim, D. Putzky, Z. Z. Li, H. Raffy, S. Germanskiy, J.-C. Deinert, N. Awari, I. Ilyakov, B. Green, M. Chen, M. Bawatna, G. Cristiani, G. Logvenov, Y. Gallais, A. V. Boris, B. Keimer, A. P. Schnyder, D. Manske, M. Gensch, Z. Wang, R. Shimano, and S. Kaiser, Nat. Commun. **11**, 1793 (2020).
- [9] S. Wall, D. Brida, S. R. Clark, H. P. Ehrke, D. Jaksch, A. Ardavan, S. Bonora, H. Uemura, Y. Takahashi, T. Hasegawa, H. Okamoto, G. Cerullo, and A. Cavalleri, Nat. Phys. **7**, 114 (2011).
- [10] H. Okamoto, H. Matsuzaki, T. Wakabayashi, Y. Takahashi, and T. Hasegawa, Phys. Rev. Lett. **98**, 037401 (2007).
- [11] M. Mitrano, G. Cotugno, S. R. Clark, R. Singla, S. Kaiser, J. Stähler, R. Beyer, M. Dressel, L. Baldassarre, D. Nicoletti, A. Perucchi, T. Hasegawa, H. Okamoto, D. Jaksch, and A. Cavalleri, Phys. Rev. Lett. **112**, 117801 (2014).

- [12] N. Strohmaier, D. Greif, R. Jördens, L. Tarruell, H. Moritz, T. Esslinger, R. Sensarma, D. Pekker, E. Altman, and E. Demler, *Phys. Rev. Lett.* **104**, 080401 (2010).
- [13] Z. Lenarčič and P. Prelovšek, *Phys. Rev. Lett.* **111**, 016401 (2013).
- [14] R. Sensarma, D. Pekker, E. Altman, E. Demler, N. Strohmaier, D. Greif, R. Jördens, L. Tarruell, H. Moritz, and T. Esslinger, *Phys. Rev. B* **82**, 224302 (2010).
- [15] M. Eckstein and P. Werner, *Phys. Rev. B* **84**, 035122 (2011).
- [16] J. Schwinger, *Phys. Rev.* **82**, 664 (1951).
- [17] Y. Murakami and P. Werner, *Phys. Rev. B* **98**, 075102 (2018).
- [18] F. Giorgianni, J. Sakai, and S. Lupi, *Nat. Commun.* **10**, 1159 (2019).
- [19] B. Mayer, C. Schmidt, A. Grupp, J. Bühler, J. Oelmann, R. E. Marvel, R. F. Haglund, T. Oka, D. Brida, A. Leitenstorfer, and A. Pashkin, *Phys. Rev. B* **91**, 235113 (2015).
- [20] H. Yamakawa, T. Miyamoto, T. Morimoto, T. Terashige, H. Yada, N. Kida, M. Suda, H. Yamamoto, R. Kato, K. Miyagawa, K. Kanoda, and H. Okamoto, *Nat. Mater.* **16**, 1100 (2017).
- [21] S. Imai, A. Ono, and S. Ishihara, *Phys. Rev. Lett.* **124**, 157404 (2020).
- [22] R. E. F. Silva, I. V. Blinov, A. N. Rubtsov, O. Smirnova, and M. Ivanov, *Nat. Photonics* **12**, 266 (2018).
- [23] J. H. Mentink, K. Balzer, and M. Eckstein, *Nat. Commun.* **6**, 6708 (2015).
- [24] K. Hejazi, J. Liu, and L. Balents, *Phys. Rev. B* **99**, 205111 (2019).
- [25] R. V. Mikhaylovskiy, E. Hendry, A. Secchi, J. H. Mentink, M. Eckstein, A. Wu, R. V. Pisarev, V. V. Kruglyak, M. I. Katsnelson, T. Rasing, and A. V. Kimel, *Nat. Commun.* **6**, 8190 (2015).
- [26] G. Batignani, D. Bossini, N. Di Palo, C. Ferrante, E. Pontecorvo, G. Cerullo, A. Kimel, and T. Scopigno, *Nat. Photonics* **9**, 506 (2015).
- [27] M. Claassen, H.-C. Jiang, B. Moritz, and T. P. Devereaux, *Nat. Commun.* **8**, 1192 (2017).
- [28] Y. Wang, T. P. Devereaux, and C.-C. Chen, *Phys. Rev. B* **98**, 245106 (2018).
- [29] T. Oka, *Phys. Rev. B* **86**, 075148 (2012).
- [30] N. Tsuji, T. Oka, P. Werner, and H. Aoki, *Phys. Rev. Lett.* **106**, 236401 (2011).
- [31] A. Takahashi, H. Itoh, and M. Aihara, *Phys. Rev. B* **77**, 205105 (2008).
- [32] N. Tancogne-Dejean, M. A. Sentef, and A. Rubio, *Phys. Rev. B* **102**, 115106 (2020).
- [33] S. Y. Kruchinin, F. Krausz, and V. S. Yakovlev, *Rev. Mod. Phys.* **90**, 021002 (2018).
- [34] E. Gorelov, M. Karolak, T. O. Wehling, F. Lechermann, A. I. Lichtenstein, and E. Pavarini, *Phys. Rev. Lett.* **104**, 226401 (2010).
- [35] Q. Han and A. Millis, *Phys. Rev. Lett.* **121**, 067601 (2018).
- [36] Z. Fang, N. Nagaosa, and K. Terakura, *Phys. Rev. B* **69**, 045116 (2004).
- [37] J. H. Jung, Z. Fang, J. P. He, Y. Kaneko, Y. Okimoto, and Y. Tokura, *Phys. Rev. Lett.* **91**, 056403 (2003).
- [38] M. Braden, G. André, S. Nakatsuji, and Y. Maeno, *Phys. Rev. B* **58**, 847 (1998).
- [39] F. Nakamura, M. Sakaki, Y. Yamanaka, S. Tamaru, T. Suzuki, and Y. Maeno, *Sci. Rep.* **3**, 2536 (2013).
- [40] See Supplemental Material at [URL] for extensive simulation and experimental details, which includes Refs. [50-59].
- [41] N. Gedik, P. Blake, R. C. Spitzer, J. Orenstein, R. Liang, D. A. Bonn, and W. N. Hardy, *Phys. Rev. B* **70**, 014504 (2004).
- [42] E. E. M. Chia, J.-X. Zhu, H. J. Lee, N. Hur, N. O. Moreno, E. D. Bauer, T. Durakiewicz, R. D. Averitt, J. L. Sarrao, and A. J. Taylor, *Phys. Rev. B* **74**, 140409(R) (2006).
- [43] J. Demsar, K. Biljaković, and D. Mihailovic, *Phys. Rev. Lett.* **83**, 800 (1999).
- [44] L. Das, F. Forte, R. Fittipaldi, C. G. Fatuzzo, V. Granata, O. Ivashko, M. Horio, F. Schindler, M. Dantz, Y. Tseng, D. E. McNally, H. M. Rønnow, W. Wan, N. B. Christensen, J. Pellicari, P. Olalde-Velasco, N. Kikugawa, T. Neupert, A. Vecchione, T. Schmitt, M. Cuoco, and J. Chang, *Phys. Rev. X* **8**, 011048 (2018).
- [45] E. Rosencher and B. Vinter, *Optoelectronics*, edited by P. G. Piva (Cambridge University Press, 2002).
- [46] D. Golež, M. Eckstein, and P. Werner, *Phys. Rev. B* **92**, 195123 (2015).
- [47] F. Nakamura, T. Goko, M. Ito, T. Fujita, S. Nakatsuji, H. Fukazawa, Y. Maeno, P. Alireza, D. Forsythe, and S. R. Julian, *Phys. Rev. B* **65**, 220402(R) (2002).
- [48] F. Novelli, G. De Filippis, V. Cataudella, M. Esposito, I. Vergara, F. Cilento, E. Sindici, A. Amaricci, C. Giannetti, D. Prabhakaran, S. Wall, A. Perucchi, S. Dal Conte, G. Cerullo, M. Capone, A. Mishchenko, M. Grninger, N. Nagaosa, F. Parmigiani, and D. Fausti, *Nat. Commun.* **5**, 5112 (2014).
- [49] A. Srivastava, R. Srivastava, J. Wang, and J. Kono, *Phys. Rev. Lett.* **93**, 157401 (2004).
- [50] G. Cao, S. McCall, V. Dobrosavljevic, C. S. Alexander, J. E. Crow, and R. P. Guertin, *Phys. Rev. B* **61**, R5053 (2000).
- [51] T. F. Qi, O. B. Korneta, S. Parkin, J. Hu, and G. Cao, *Phys. Rev. B* **85**, 165143 (2012).
- [52] M.-C. Lee, C. H. Kim, I. Kwak, J. Kim, S. Yoon, B. C. Park, B. Lee, F. Nakamura, C. Sow, Y. Maeno, T. W. Noh, and K. W. Kim, *Phys. Rev. B* **98**, 161115 (2018).
- [53] C. A. Stafford and A. J. Millis, *Phys. Rev. B* **48**, 1409 (1993).
- [54] D. M. Roessler, *Br. J. Appl. Phys.* **16**, 1119 (1965).
- [55] A. Eschenmoser and C. Wintner, *Science* **196**, 1410 (1977),.
- [56] L. M. Woods, *Phys. Rev. B* **62**, 7833 (2000).
- [57] J. Bertinshaw, N. Gurung, P. Jorba, H. Liu, M. Schmid, D. T. Mantadakis, M. Daghofer, M. Krautloher, A. Jain, G. H. Ryu, O. Fabelo, P. Hansmann, G. Khaliullin, C. Pfleiderer, B. Keimer, and B. J. Kim, *Phys. Rev. Lett.* **123**, 137204 (2019).
- [58] M.-C. Lee, C. H. Kim, I. Kwak, C. W. Seo, C. Sohn, F. Nakamura, C. Sow, Y. Maeno, E.-A. Kim, T. W. Noh, and K. W. Kim, *Phys. Rev. B* **99**, 144306 (2019).
- [59] N. Tancogne-Dejean, M. A. Sentef, and A. Rubio, *Phys. Rev. Lett.* **121**, 097402 (2018)