



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Excitonic Polarons and Self-Trapped Excitons from First-Principles Exciton-Phonon Couplings

Zhenbang Dai, Chao Lian, Jon Lafuente-Bartolome, and Feliciano Giustino

Phys. Rev. Lett. **132**, 036902 — Published 17 January 2024

DOI: [10.1103/PhysRevLett.132.036902](https://doi.org/10.1103/PhysRevLett.132.036902)

Excitonic polarons and self-trapped excitons from first-principles exciton-phonon couplings

Zhenbang Dai,^{1,2} Chao Lian,^{1,2} Jon Lafuente-Bartolome,^{1,2} and Feliciano Giustino^{1,2,*}

¹*Oden Institute for Computational Engineering and Sciences,
The University of Texas at Austin, Austin, Texas 78712, USA*

²*Department of Physics, The University of Texas at Austin, Austin, Texas 78712, USA*

(Dated: November 1, 2023)

Excitons consist of electrons and holes held together by their attractive Coulomb interaction. Although excitons are neutral excitations, spatial fluctuations in their charge density couple with the ions of the crystal lattice. This coupling can lower the exciton energy and lead to the formation of a localized excitonic polaron, or even a self-trapped exciton in the presence of strong exciton-phonon interactions. Here, we develop a theoretical and computational approach to compute excitonic polarons and self-trapped excitons from first principles. Our methodology combines the many-body Bethe-Salpeter approach with density-functional perturbation theory, and does not require explicit supercell calculations. As a proof of concept, we demonstrate our method for a compound of the halide perovskite family.

One of the most striking manifestation of electron-phonon interactions in solids is the formation of polarons. These quasiparticles form when an electron creates a small distortion of the surrounding crystal lattice, which in turn acts as a potential well that promotes electron localization [1]. Polarons have been investigated extensively in a wide variety of materials, including alkali halides [2–5], metal oxides [6–9], hybrid perovskites [10–13], and two-dimensional materials [14].

A similar feedback mechanism between charge and lattice can occur for neutral excitations such as excitons [15, 16]. While the exciton is charge-neutral overall, local spatial fluctuations of its electron and hole charge densities can induce lattice distortions as in the case of polarons. In turn, these distortions can stabilize the exciton and promote its localization. The resulting quasiparticle is referred to as an excitonic polaron [17]. In the presence of strong exciton-phonon interactions, the same mechanism can lead to the formation of self-trapped excitons [18–21] [22].

Excitonic polarons are often invoked to explain large Stokes shifts observed between absorption and luminescence spectra [19, 20, 23]. In these cases, the photoluminescence red-shift is interpreted as the result of the lattice relaxation in the optically-excited state, within a Franck-Condon picture [24]. These conceptual models are ubiquitous in solid-state spectroscopy and have been in use for decades, but detailed *ab initio* calculations remain exceedingly rare [25–28]. The main difficulties are that (i) calculations of Hellman-Feynman forces in the excited state using the Bethe-Salpeter equation (BSE) approach are challenging [26]; (ii) since exciton localization breaks the translational invariance of the crystal unit cell, BSE calculations on large supercells are needed [19], and this poses a significant computational challenge.

Here, we develop an *ab initio* theoretical and computational method for calculating excitonic polarons and

self-trapped excitons without resorting to supercells. Following a strategy similar in spirit to previous work on polarons [2, 14, 29–31], we express the wavefunction of the excitonic polaron as a coherent superposition of finite-momentum excitons, and we recast the BSE total energy functional in the excited state as a self-consistent eigenvalue problem in the exciton coefficients. Alongside the excitonic wavefunction, our present approach provides the accompanying atomic displacements and their spectral decomposition into normal vibrational modes, thereby offering a detailed picture of the excitonic polaron and the atomic-scale mechanisms that drive its formation. To demonstrate this method, we investigate excitonic polarons in Cs_2ZrBr_6 , a vacancy-ordered double perovskite that attracted interest in the context of energy-efficient lighting, and which exhibits signatures of exciton self-trapping [23, 32]. Additional *ab initio* calculations of excitonic polarons in LiF , applications to model Hamiltonians, and a more in-depth analysis of the theoretical formalism are presented in the companion manuscript [33].

The total energy of a crystal in a neutral excited state can be expressed as [26]:

$$\begin{aligned}
 E[\Psi(\mathbf{r}_e, \mathbf{r}_h), \{\Delta\tau_{\kappa\alpha p}\}] &= E_0 \\
 &+ \int_{\text{sc}} \Psi^*(\mathbf{r}_e, \mathbf{r}_h) H_{\text{BSE}}(\mathbf{r}_e, \mathbf{r}_h; \mathbf{r}'_e, \mathbf{r}'_h) \Psi(\mathbf{r}'_e, \mathbf{r}'_h) d\mathbf{r} \\
 &+ \frac{1}{2} \sum_{\substack{\kappa\alpha p \\ \kappa'\alpha'p'}} C_{\kappa\alpha p, \kappa'\alpha'p'} \Delta\tau_{\kappa\alpha p} \Delta\tau_{\kappa'\alpha'p'}, \quad (1)
 \end{aligned}$$

where E_0 denotes the ground-state energy with the atoms in their equilibrium positions; H_{BSE} is the BSE Hamiltonian [15, 16]; $\Psi(\mathbf{r}_e, \mathbf{r}_h)$ is the exciton wavefunction, with \mathbf{r}_e and \mathbf{r}_h denoting the electron and hole coordinates, respectively. The integral extends over the Born-von Kármán (BvK) supercell, and the integration variable $d\mathbf{r}$ is a short-hand notation for $d\mathbf{r}_e d\mathbf{r}_h d\mathbf{r}'_e d\mathbf{r}'_h$. $C_{\kappa\alpha p, \kappa'\alpha'p'}$

denotes the matrix of interatomic force constants, and $\Delta\tau_{\kappa\alpha p}$ is the displacement of the atom κ in the unit cell p along the Cartesian direction α , with respect to the ground-state structure. The term on the last line of Eq. (1) describes the elastic energy associated with the lattice distortion. The energy functional is truncated to the second order in the displacements; this approximation proved successful in calculations of both small and large polarons, comparing well with direct hybrid-functional calculations [2, 14, 29–31]. In Eq. (1), the BSE Hamiltonian and wavefunctions depend implicitly on the atomic positions, and the interatomic force constants are assumed to be the same for the ground and excited state. This approximation was shown to be reliable for large and small polarons [29].

To obtain the exciton wavefunction and the atomic displacements that minimize the total energy in Eq. (1), we use the method of Lagrange multipliers, and set to zero the functional derivatives of $E[\Psi(\mathbf{r}_e, \mathbf{r}_h), \{\Delta\tau_{\kappa\alpha p}\}]$ with respect to $\Psi(\mathbf{r}_e, \mathbf{r}_h)$ and $\{\Delta\tau_{\kappa\alpha p}\}$, subject to the normalization constraint $\int_{sc} |\Psi(\mathbf{r}_e, \mathbf{r}_h)|^2 d\mathbf{r}_e d\mathbf{r}_h = 1$. After some algebra, we arrive at the following coupled nonlinear eigenvalue problem:

$$\begin{aligned} & \int_{sc} H_{BSE}^0(\mathbf{r}_e, \mathbf{r}_h; \mathbf{r}'_e, \mathbf{r}'_h) \Psi(\mathbf{r}'_e, \mathbf{r}'_h) d\mathbf{r}'_e d\mathbf{r}'_h \\ & + \sum_{\kappa\alpha p} \int_{sc} \frac{\partial H_{BSE}^0(\mathbf{r}_e, \mathbf{r}_h; \mathbf{r}'_e, \mathbf{r}'_h)}{\partial \tau_{\kappa\alpha p}} \Psi(\mathbf{r}'_e, \mathbf{r}'_h) d\mathbf{r}'_e d\mathbf{r}'_h \Delta\tau_{\kappa\alpha p} \\ & = \varepsilon \Psi(\mathbf{r}_e, \mathbf{r}_h), \end{aligned} \quad (2)$$

$$\begin{aligned} \Delta\tau_{\kappa\alpha p} & = - \sum_{\kappa'\alpha'p'} C_{\kappa\alpha p, \kappa'\alpha'p'}^{-1} \\ & \times \int_{sc} \Psi^*(\mathbf{r}_e, \mathbf{r}_h) \frac{\partial H_{BSE}^0(\mathbf{r}_e, \mathbf{r}_h; \mathbf{r}'_e, \mathbf{r}'_h)}{\partial \tau_{\kappa'\alpha'p'}} \Psi(\mathbf{r}'_e, \mathbf{r}'_h) d\mathbf{r}, \end{aligned} \quad (3)$$

where H_{BSE}^0 is the BSE Hamiltonian for the undistorted system, and the eigenvalue ε is the Lagrange multiplier.

To solve Eqs. (2) and (3) without resorting to supercells, we express $\Psi(\mathbf{r}_e, \mathbf{r}_h)$ as a linear combination of exciton states $\Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h)$ of the undistorted ground-state structure, and we express the displacements $\Delta\tau_{\kappa\alpha p}$ as a linear combination of normal vibrational modes of the undistorted structure:

$$\Psi(\mathbf{r}_e, \mathbf{r}_h) = \frac{1}{\sqrt{N}} \sum_{s\mathbf{Q}} A_{s\mathbf{Q}} \Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h), \quad (4)$$

$$\Delta\tau_{\kappa\alpha p} = - \frac{2}{N} \sum_{\mathbf{q}\nu} B_{\mathbf{q}\nu} \left(\frac{\hbar}{2M_\kappa\omega_{\mathbf{q}\nu}} \right)^{1/2} e_{\kappa\alpha, \nu}(\mathbf{q}) e^{i\mathbf{q}\cdot\mathbf{R}_p}. \quad (5)$$

In these expressions, s is the exciton band index, \mathbf{Q} is the exciton momentum, and N is the number of unit cells in the BvK supercell; M_κ is the mass of atom κ , $e_{\kappa\alpha, \nu}(\mathbf{q})$ is polarization vector of the phonon with momentum \mathbf{q} , branch ν , and frequency $\omega_{\mathbf{q}\nu}$; \mathbf{R}_p is the lattice vector of the p -th unit cell in the BvK supercell [34]. The sums

are carried out over uniform Brillouin zone grids with N points. The expansion coefficients $A_{s\mathbf{Q}}$ and $B_{\mathbf{q}\nu}$ in Eqs. (4) and (5) can be interpreted as the contribution of each exciton and each phonon of the undistorted lattice to the excitonic polaron, respectively.

The exciton states of the undistorted lattice appearing in Eq. (4), $\Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h)$, can be expressed in terms of Kohn-Sham single-particle states. To this end, we employ the Tamm-Dancoff approximation [16, 35]:

$$\Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h) = \sum_{vck} a_{vck}^{s\mathbf{Q}} \psi_{vk}^*(\mathbf{r}_h) \psi_{ck+\mathbf{Q}}(\mathbf{r}_e), \quad (6)$$

where $\psi_{n\mathbf{k}}(\mathbf{r})$ are Kohn-Sham eigenstates of the undistorted ground-state, v and c refer to valence and conduction bands, respectively, and the coefficients $a_{vck}^{s\mathbf{Q}}$ denote the eigenvectors of the ground-state BSE Hamiltonian, H_{BSE}^0 , with eigenvalue $E_{s\mathbf{Q}}^0$.

Upon substituting Eqs.(4)-(6) inside Eqs. (2)-(3), we obtain a coupled nonlinear system of equations for the coefficients $A_{s\mathbf{Q}}$ and $B_{\mathbf{q}\nu}$:

$$\begin{aligned} & \sum_{s'\mathbf{Q}'} \left[E_{s'\mathbf{Q}'}^0 \delta_{ss'} \delta_{\mathbf{Q}\mathbf{Q}'} - \frac{2}{N} \sum_{\nu} B_{\mathbf{Q}-\mathbf{Q}'\nu} \mathcal{G}_{ss'\nu}(\mathbf{Q}', \mathbf{Q}-\mathbf{Q}') \right] \\ & \times A_{s'\mathbf{Q}'} = \varepsilon A_{s\mathbf{Q}}, \\ B_{\mathbf{Q}\nu} & = \frac{1}{N\hbar\omega_{\mathbf{Q}\nu}} \sum_{ss'\mathbf{Q}'} A_{s'\mathbf{Q}'}^* A_{s\mathbf{Q}'+\mathbf{Q}} \mathcal{G}_{ss'\nu}^*(\mathbf{Q}', \mathbf{Q}), \end{aligned} \quad (7)$$

having introduced the exciton-phonon coupling matrix element [36, 37]:

$$\begin{aligned} \mathcal{G}_{ss'\nu}(\mathbf{Q}, \mathbf{q}) & = \sum_{vck} a_{vck}^{s\mathbf{Q}+\mathbf{q}*} \left[\sum_{c'} g_{cc'\nu}(\mathbf{k}+\mathbf{Q}, \mathbf{q}) a_{vc'\mathbf{k}}^{s'\mathbf{Q}} \right. \\ & \left. - \sum_{v'} g_{v'\nu}(\mathbf{k}, \mathbf{q}) a_{v'\mathbf{k}+\mathbf{q}}^{s'\mathbf{Q}} \right]. \end{aligned} \quad (9)$$

In this expression, $g_{mn\nu}(\mathbf{k}, \mathbf{q})$ is the standard electron-phonon coupling matrix element between the Kohn-Sham states $n\mathbf{k}$ and $m\mathbf{k}+\mathbf{q}$ via the phonon $\mathbf{q}\nu$ [34].

Equations (7) and (8) constitute the central result of this work. The solution of these equations describes the formation of excitonic polarons and self-trapped excitons via the exciton-phonon interaction. All quantities appearing in Eqs. (7)-(9) can be obtained from calculations performed in the crystal unit cell, without requiring supercells. The breaking of lattice periodicity comes from the coherent superposition of exciton states with different momenta. The largest size of the exciton polaron that can be studied is set by the BvK supercell, which in the present formalism translates into the number N of grid-points in the Brillouin zone.

The dissociation energy of the excitonic polaron **into fully delocalized free electron-hole pair** is $E_{\text{gap}}^{\text{GW}} - E_{\text{xp}}$, where E_{xp} is given by:

$$E_{\text{xp}} = \frac{1}{N_p} \sum_{s\mathbf{Q}} |A_{s\mathbf{Q}}|^2 E_{s\mathbf{Q}}^0 - \frac{1}{N_p} \sum_{\mathbf{q}\nu} |B_{\mathbf{q}\nu}|^2 \hbar\omega_{\mathbf{q}\nu}. \quad (10)$$

The first term on the right-hand side of this equation represents the average energy of the exciton states participating to the excitonic polarons; the second term is the stabilization energy resulting from the lattice distortion. Similarly, the formation energy of the excitonic polaron is $\Delta E_f^{\text{xp}} = E_{\text{xp}} - E_{\text{ex}}^0$, where E_{ex}^0 is the energy of the lowest-lying exciton.

To demonstrate the present methodology, we consider the vacancy-ordered halide double perovskite Cs_2ZrBr_6 as a test system. All calculations details are described in the Supplemental Information [38]. Cs_2ZrBr_6 crystallizes in the $\text{Fm}\bar{3}\text{m}$ space group, and consists of a rock-salt lattice of alternating $(\text{ZrBr}_6)^{2-}$ octahedra and vacancies, with Cs^{1+} cations acting as spacers, see supplemental Fig. S1. Optical absorption and photoluminescence spectra of this perovskite reveal a large Stokes shift, which has tentatively been assigned to the presence of self-trapped excitons [23, 32].

In agreement with the experimental proposal, we do find a highly localized excitonic polaron in Cs_2ZrBr_6 . Figure 1 shows the charge densities of the electron polaron, the hole polaron, and the excitonic polaron in Cs_2ZrBr_6 . We find small electron and hole polarons; in particular, the electron polaron in Fig. 1(a) primarily consists of a single Zr-4d orbital of t_{2g} character (d_{xz} and d_{yz}), while the hole polaron in Fig. 1(b) is derived from a single Br-4p orbital. Our findings are consistent with the Zr- d and Br- p characters of the conduction and valence band edges, respectively (supplemental Fig. S2). The highly localized nature of polarons reflects the weakly-interacting nature of ZrBr_6 octahedra in the vacancy-ordered double perovskite structure [32]. In Figs. 1(c) and (d) we show the electron density and the hole density in the excitonic polaron state, respectively, which are given by $n_e(\mathbf{r}_e) = \int_{\text{sc}} |\Psi(\mathbf{r}_e, \mathbf{r}_h)|^2 d\mathbf{r}_h$ and $n_h(\mathbf{r}_h) = \int_{\text{sc}} |\Psi(\mathbf{r}_e, \mathbf{r}_h)|^2 d\mathbf{r}_e$. As for the polarons, the charge densities of the excitonic polaron are localized in real space. By comparing Figs. 1(b) and (d), we see that the hole density is distributed among all six Br atoms of a ZrBr_6 octahedron, unlike the hole polaron which is localized on a single atom.

Localization is a distinctive feature of the excitonic polaron, whereas free excitons in the undistorted structure are fully delocalized. In fact, using Eq. (6) and the orthogonality of Kohn-Sham states, it is immediate to see that the charge densities of the excitons in the ground-state structure, $\int_{\text{sc}} |\Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h)|^2 d\mathbf{r}_h$ and $\int_{\text{sc}} |\Omega_{s\mathbf{Q}}(\mathbf{r}_e, \mathbf{r}_h)|^2 d\mathbf{r}_e$, are lattice-periodic. This observation is consistent with the fact that, to plot the exciton wavefunction, one must fix the position of the hole to obtain a localized electron charge distribution [39]. This type of plot is shown in Figs. 1(e) and (f) for the excitons in Cs_2ZrBr_6 .

Figure 2 and supplemental Fig. S3 show the atomic displacements accompanying the electron polaron, the hole

polaron, and the excitonic polaron in Cs_2ZrBr_6 . The electron polaron, which is localized on the Zr atom, tends to attract the eight positively-charged nearest-neighbor Cs cations in a symmetric pattern [Fig. S3(a)]. Conversely, the hole polaron, which is centered on a Br atom, tends to repel a single positively-charged nearest-neighbor Zr cation [Fig. S3(b)]. The atomic displacement pattern of the excitonic polaron, shown in Fig. 2(a), resembles the pattern for the electron polaron in Fig. S3(a), but additionally includes significant displacements of the nearest-neighbor Br atoms surrounding the central Zr atom. This behavior can be rationalized by noting that, **due to the crystal symmetry of Cs_2ZrBr_6 , the hole polaron shown Fig. 1(b) and Fig. S3(b) is only one of the six degenerate solutions localized at the six Br atoms, respectively, and when forming the excitonic polaron, the six degenerate solutions contribute to making the hole density of the excitonic polaron carry the approximate spherical symmetry around the Zr atom.**

Our present formalism allows us to identify the phonon modes that are responsible for the formation of the excitonic polaron. Figure 2(b) shows the magnitude of the coefficients $|B_{\mathbf{q}\nu}|^2$ overlaid on the phonon dispersion relations of Cs_2ZrBr_6 . The dominant contributions arise from the phonon branches associated with the A_{1g} mode at 23.2 meV and the T_{1u} mode at 6.2 meV. The former is the octahedral breathing mode [Fig. 2(c)], and the latter corresponds to displacements of the Cs atoms [Fig. 2(d)]. This decomposition is consistent with the atomic displacement patterns shown in Fig. 2(a). We emphasize that, while the largest atomic displacements occur for the Br atoms that are nearest neighbors to the central Zr atom, we find significant atomic displacements of Cs atoms in more distant neighbors within other unit cells. This result underscores the importance of being able to perform this type of calculations on large supercells, such as the 576-atoms equivalent supercell that we can access in the present study by solving Eqs. (7)-(8). Performing direct BSE calculations on such large unit cells would be prohibitive using existing methods [25–28].

We now compare the formation energies for electron, hole, and excitonic polarons, as shown in Fig. 3. Fig. 3(a) shows a schematic illustration of the many-body quasiparticle energy diagram; Fig. 3(b) shows the corresponding many-body BSE diagram for neutral excitations (exciton band structures and the BSE absorption coefficients are shown in supplemental Fig. S4 for completeness). We see that the electron and hole polaron have relatively large formation energies (302 meV and 550 meV, respectively) which can be rationalized in terms of the heavy electron and hole effective masses [29, 32]; instead, the formation energy of the excitonic polaron is of one magnitude smaller (48 meV). In line with this weaker formation energy, we observe that the charge densities of the excitonic polaron [Figs. 1(c) and 1(d)] are more diffuse than those of the electron polaron and of the hole polaron

[Figs. 1(a) and 1(b)].

The difference between the formation energy and localization of the polaron and of the excitonic polaron can be rationalized by inspecting the exciton-phonon coupling matrix element in Eq. (9). In this expression, the two terms associated with electron-phonon and hole-phonon couplings appear with opposite signs and tend to cancel out. Physically, this partial cancellation stems from the fact that, when small polarons with similar localization length and opposite charge combine to produce an exciton, the net charge density tends to cancel out, **which can be seen by the similar shape and distribution of the electron density and hole density of the excitonic polaron [Figs. 1(c) and 1(d)]**, thus weakening the lattice distortion and leading to a smaller polaronic stabilization of the free exciton. This observation indicates that, to observe large polaronic effects in excitons, one needs to look for materials with large differences in the electron-phonon and hole-phonon interaction strengths.

In summary, we developed a theoretical and computational method that enables, for the first time, *ab initio* calculations of excitonic polarons and self-trapped excitons in real materials. This method does not require computationally prohibitive supercell calculations, and can seamlessly be used to investigate small and large excitonic polarons as well as self-trapped excitons. This work will make it possible to investigate the physics of exciton-phonon couplings and self-trapped excitons in diverse classes of materials with potential for solar energy harvesting, photocatalysis, energy-efficient lighting, and light-driven quantum matter.

We are grateful to Bruno Cucco and George Volonakis for bringing the self-trapped exciton in Cs_2ZrBr_6 to our attention. This research is primarily supported by the National Science Foundation, Office of Advanced Cyberinfrastructure and Division of Materials Research under Grant No. 2103991 of the Cyberinfrastructure for Sustained Scientific Innovation program, and the NSF Characteristic Science Applications for the Leadership Class Computing Facility program under Grant No. 2139536 (development of the excitonic polaron module, calculations, interoperability). This research was also supported by the Computational Materials Sciences Program funded by the US Department of Energy, Office of Science, Basic Energy Sciences, under award no. DE-SC0020129 (development of the polaron module). This research used resources of the National Energy Research Scientific Computing Center and the Argonne Leadership Computing Facility, which are DOE Office of Science User Facilities supported by the Office of Science of the U.S. Department of Energy, under Contracts No. DE-AC02-05CH11231 and DE-AC02-06CH11357, respectively. The authors acknowledge the Texas Advanced Computing Center (TACC) at The University of Texas at Austin for providing access to Frontera, Lonestar6, and Texascale Days, that have con-

tributed to the research results reported within this paper (<http://www.tacc.utexas.edu>).

* fgiustino@oden.utexas.edu

- [1] C. Franchini, M. Reticcioli, M. Setvin, and U. Diebold, Polarons in materials, *Nat. Rev. Mater.* **6**, 560 (2021).
- [2] W. H. Sio, C. Verdi, S. Poncé, and F. Giustino, Polarons from first principles, without supercells, *Phys. Rev. Lett.* **122**, 246403 (2019).
- [3] G. Iadonisi, Electron-phonon interaction: Effects on the excitation spectrum of solids, *Riv. del Nuovo Cim.* **7**, 1 (1984).
- [4] M. Inoue, C. Mahutte, and S. Wang, Electronic polarons in alkali halides, *Phys. Rev. B* **2**, 539 (1970).
- [5] N.-E. Lee, H.-Y. Chen, J.-J. Zhou, and M. Bernardi, Facile ab initio approach for self-localized polarons from canonical transformations, *Phys. Rev. Mater.* **5**, 063805 (2021).
- [6] M. Setvin, C. Franchini, X. Hao, M. Schmid, A. Janotti, M. Kaltak, C. G. Van de Walle, G. Kresse, and U. Diebold, Direct view at excess electrons in TiO_2 rutile and anatase, *Phys. Rev. Lett.* **113**, 086402 (2014).
- [7] S. Yang, A. Brant, N. Giles, L. Halliburton, *et al.*, Intrinsic small polarons in rutile TiO_2 , *Phys. Rev. B* **87**, 125201 (2013).
- [8] H. Frederikse, W. Thurber, and W. Hosler, Electronic transport in strontium titanate, *Phys. Rev.* **134**, A442 (1964).
- [9] S. Falletta and A. Pasquarello, Polarons free from many-body self-interaction in density functional theory, *Phys. Rev. B* **106**, 125119 (2022).
- [10] B. Guzelurk, T. Winkler, T. W. Van de Goor, M. D. Smith, S. A. Bourelle, S. Feldmann, M. Trigo, S. W. Teitelbaum, H.-G. Steinrück, G. A. de la Pena, *et al.*, Visualization of dynamic polaronic strain fields in hybrid lead halide perovskites, *Nat. Mater.* **20**, 618 (2021).
- [11] M. Z. Mayers, L. Z. Tan, D. A. Egger, A. M. Rappe, and D. R. Reichman, How lattice and charge fluctuations control carrier dynamics in halide perovskites, *Nano Lett.* **18**, 8041 (2018).
- [12] K. Miyata, D. Meggiolaro, M. T. Trinh, P. P. Joshi, E. Mosconi, S. C. Jones, F. De Angelis, and X.-Y. Zhu, Large polarons in lead halide perovskites, *Sci. Adv.* **3**, e1701217 (2017).
- [13] X.-Y. Zhu and V. Podzorov, Charge carriers in hybrid organic-inorganic lead halide perovskites might be protected as large polarons, *J. Phys. Chem. Lett.* **6**, 4758 (2015).
- [14] W. H. Sio and F. Giustino, Polarons in two-dimensional atomic crystals, *Nat. Phys.* **19**, 629 (2023).
- [15] M. Rohlfing and S. G. Louie, Electron-hole excitations in semiconductors and insulators, *Phys. Rev. Lett.* **81**, 2312 (1998).
- [16] M. Rohlfing and S. G. Louie, Electron-hole excitations and optical spectra from first principles, *Phys. Rev. B* **62**, 4927 (2000).
- [17] G. Iadonisi and F. Bassani, Polaronic correction to the exciton effective mass, *Il Nuovo Cimento D* **9**, 703 (1987).
- [18] W. B. Fowler, M. Marrone, and M. Kabler, Theory of self-trapped exciton luminescence in halide crystals, *Phys.*

- Rev. B **8**, 5909 (1973).
- [19] S. Ismail-Beigi and S. G. Louie, Self-trapped excitons in silicon dioxide: mechanism and properties, *Phys. Rev. Lett.* **95**, 156401 (2005).
- [20] R. Williams and K. Song, The self-trapped exciton, *J. Phys. Chem. Solids* **51**, 679 (1990).
- [21] J. Li, H. Wang, and D. Li, Self-trapped excitons in two-dimensional perovskites, *Front. Optoelectron.* **13**, 225 (2020).
- [22] We note that the names “excitonic polarons” and “self-trapped excitons” refer to the same physical mechanism of polaronic stabilization of the exciton. The difference between these two concepts resides in the strength of the electron-phonon coupling, the resulting phonon-induced localization of the exciton wavefunction, and the magnitude of the hopping barrier for exciton migration. Therefore, in this Letter, we use the two naming conventions interchangeably.
- [23] A. Abfalterer, J. Shamsi, D. J. Kubicki, C. N. Savory, J. Xiao, G. Divitini, W. Li, S. Macpherson, K. Galkowski, J. L. MacManus-Driscoll, *et al.*, Colloidal synthesis and optical properties of perovskite-inspired cesium zirconium halide nanocrystals, *ACS Mater. Lett.* **2**, 1644 (2020).
- [24] A. Nitzan, *Chemical dynamics in condensed phases: relaxation, transfer and reactions in condensed molecular systems* (Oxford university press, 2006).
- [25] F. Mauri and R. Car, First-principles study of excitonic self-trapping in diamond, *Phys. Rev. Lett.* **75**, 3166 (1995).
- [26] S. Ismail-Beigi and S. G. Louie, Excited-state forces within a first-principles green’s function formalism, *Phys. Rev. Lett.* **90**, 076401 (2003).
- [27] K. W. Sattelmeyer, J. F. Stanton, J. Olsen, and J. Gauss, A comparison of excited state properties for iterative approximate triples linear response coupled cluster methods, *Chem. Phys. Lett.* **347**, 499 (2001).
- [28] J. F. Stanton, J. Gauss, N. Ishikawa, and M. Head-Gordon, A comparison of single reference methods for characterizing stationary points of excited state potential energy surfaces, *J. Chem. Phys.* **103**, 4160 (1995).
- [29] W. H. Sio, C. Verdi, S. Ponc e, and F. Giustino, Ab initio theory of polarons: Formalism and applications, *Phys. Rev. B* **99**, 235139 (2019).
- [30] J. Lafuente-Bartolome, C. Lian, W. H. Sio, I. G. Gurtubay, A. Eiguren, and F. Giustino, Ab initio self-consistent many-body theory of polarons at all couplings, *Phys. Rev. B* **106**, 075119 (2022).
- [31] J. Lafuente-Bartolome, C. Lian, W. H. Sio, I. G. Gurtubay, A. Eiguren, and F. Giustino, Unified approach to polarons and phonon-induced band structure renormalization, *Phys. Rev. Lett.* **129**, 076402 (2022).
- [32] B. Cucco, C. Katan, J. Even, M. Kepenekian, and G. Volonakis, Fine structure of excitons in vacancy-ordered halide double perovskites, *ACS Mater. Lett.* **5**, 52 (2022).
- [33] Z. Dai, C. Lian, J. Lafuente-Bartolome, and F. Giustino, Theory of excitonic polarons: From models to first-principles calculations, submitted (2023).
- [34] F. Giustino, Electron-phonon interactions from first principles, *Rev. Mod. Phys.* **89**, 015003 (2017).
- [35] G. Onida, L. Reining, and A. Rubio, Electronic excitations: density-functional versus many-body green’s-function approaches, *Rev. Mod. Phys.* **74**, 601 (2002).
- [36] H.-Y. Chen, D. Sangalli, and M. Bernardi, Exciton-phonon interaction and relaxation times from first principles, *Phys. Rev. Lett.* **125**, 107401 (2020).
- [37] G. Antonius and S. G. Louie, Theory of exciton-phonon coupling, *Phys. Rev. B* **105**, 085111 (2022).
- [38] See Supplemental Material at [URL will be inserted by publisher] for the computational setup, crystal structure of Cs₂ZrBr₆, DFT band structure and projected density of states, the displacement patterns of electron polaron and hole polaron in Cs₂ZrBr₆, optical absorption spectra, contribution of each exciton states to the excitonic polaron, and benchmarks, which includes Refs. [2, 16, 31, 32, 39–49].
- [39] J. Deslippe, G. Samsonidze, D. A. Strubbe, M. Jain, M. L. Cohen, and S. G. Louie, Berkeleygw: A massively parallel computer package for the calculation of the quasiparticle and optical properties of materials and nanostructures, *Comput. Phys. Commun.* **183**, 1269 (2012).
- [40] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, *et al.*, Quantum espresso: a modular and open-source software project for quantum simulations of materials, *J. Condens. Matter Phys.* **21**, 395502 (2009).
- [41] P. Giannozzi, O. Andreussi, T. Brumme, O. Bunau, M. B. Nardelli, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, M. Cococcioni, *et al.*, Advanced capabilities for materials modelling with quantum espresso, *J. Condens. Matter Phys.* **29**, 465901 (2017).
- [42] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized gradient approximation made simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [43] D. Hamann, Optimized norm-conserving vanderbilt pseudopotentials, *Phys. Rev. B* **88**, 085117 (2013).
- [44] M. J. van Setten, M. Giantomassi, E. Bousquet, M. J. Verstraete, D. R. Hamann, X. Gonze, and G.-M. Rignanese, The pseudodojo: Training and grading a 85 element optimized norm-conserving pseudopotential table, *Comput. Phys. Commun.* **226**, 39 (2018).
- [45] H. Lee, S. Ponc e, K. Bushick, S. Hajinazar, J. Lafuente-Bartolome, J. Leveillee, C. Lian, F. Macheda, H. Paudyal, W. H. Sio, *et al.*, Electron-phonon physics from first principles using the epw code, arXiv preprint arXiv:2302.08085 (2023).
- [46] S. Ponc e, E. R. Margine, C. Verdi, and F. Giustino, Epw: Electron–phonon coupling, transport and superconducting properties using maximally localized wannier functions, *Comput. Phys. Commun.* **209**, 116 (2016).
- [47] G. Pizzi, V. Vitale, R. Arita, S. Bl ugel, F. Freimuth, G. G eranton, M. Gibertini, D. Gresch, C. Johnson, T. Koretsune, *et al.*, Wannier90 as a community code: new features and applications, *J. Condens. Matter Phys.* **32**, 165902 (2020).
- [48] M. S. Hybertsen and S. G. Louie, Electron correlation in semiconductors and insulators: Band gaps and quasiparticle energies, *Phys. Rev. B* **34**, 5390 (1986).
- [49] K. Momma and F. Izumi, VESTA 3 for three-dimensional visualization of crystal, volumetric and morphology data, *J. Appl. Crystallogr.* **44**, 1272 (2011).

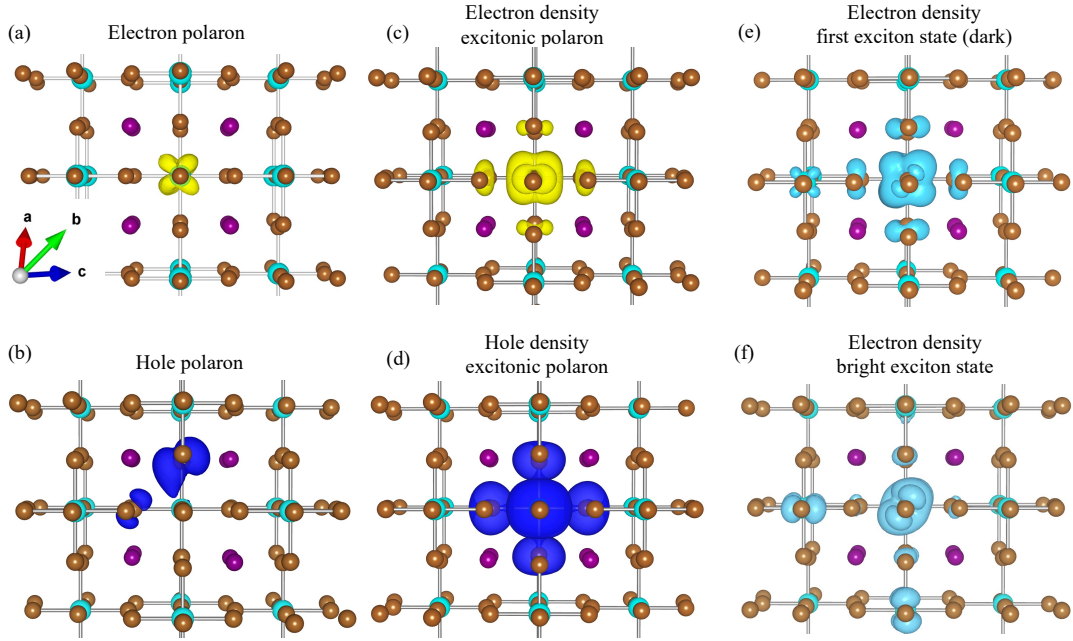


FIG. 1. Charge density isosurfaces of electron polaron, hole polaron, exciton polaron, and excitons in Cs₂ZrBr₆. The atomic color code is: Cs purple, Zr cyan, Br brown. (a) Charge density isosurface of the electron polaron (yellow). (b) Charge density isosurface of the hole polaron (dark blue). (c) Electron density isosurface $n_e(\mathbf{r}_e)$ of the excitonic polaron (yellow). (d) Hole density isosurface $n_h(\mathbf{r}_h)$ of the excitonic polaron (dark blue). (e) Electron density isosurface of the lowest energy exciton (dark) of Cs₂ZrBr₆ in the ground-state undistorted structure (light blue). (f) Electron density isosurface of the bright exciton corresponding to the first absorption peak of Cs₂ZrBr₆, as shown in Fig. S4(a), in the ground-state undistorted structure (light blue). In (e) and (f), the hole position \mathbf{r}_h is chosen to coincide with a Br atom.

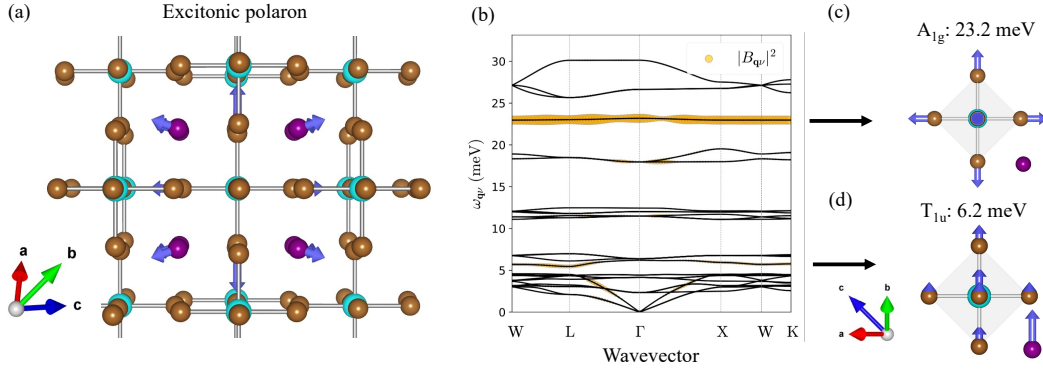


FIG. 2. Atomic displacements accompanying the excitonic polaron of Cs₂ZrBr₆. We only display significant displacements for clarity. The atomic color code is: Cs purple, Zr cyan, Br brown. (a) Atomic displacements (blue arrows) associated with the excitonic polaron, whose electron and hole charge densities are shown in Figs. 1(c) and (d), respectively. (b) Phonon contribution to the formation of the excitonic polaron. Black lines are the phonon dispersion relations, and the yellow discs are proportional to $|B_{\text{qv}}|^2$. (c) Eigendisplacements of the A_{1g} mode at 23.2 meV at the zone center. (d) Eigendisplacements of the T_{1u} mode at 6.2 meV at the zone center. In (c) and (d), only one octahedron and one Cs atom are displayed since all other octahedra and Cs atoms have the same displacement pattern.

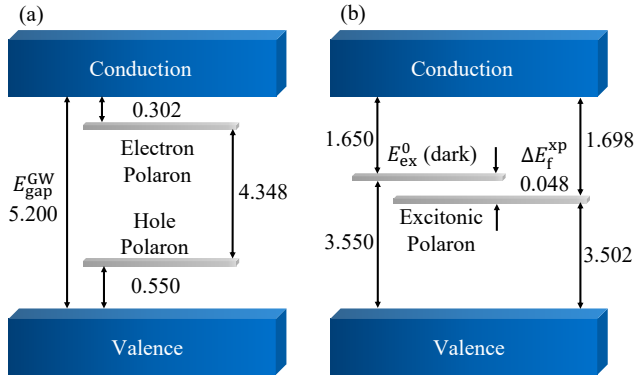


FIG. 3. Energetics of polarons and excitonic polarons in Cs_2ZrBr_6 . All values in (a) and (b) are in the unit of eV. (a) GW quasiparticle band gap and formation energies of the electron polaron and of the hole polaron. (b) Energetics of exciton and excitonic polaron. On the left-hand side of this panel we show the excitation energy of the lowest (dark) exciton state with respect to the ground state, and its binding energy as measured with respect to the GW quasiparticle band gap. On the right-hand side of this panel, we show the excitation energy of the excitonic polaron with respect to the ground state, the binding energy with respect to the quasiparticle gap, and the stabilization energy from the free exciton state to the excitonic polaron state.