



CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

Spin canting and orbital order in spinel vanadate thin films

Christie J. Thompson, Dalmau Reig-i-Plessis, Lazar Kish, Adam A. Aczel, Biwen Zhang, Evguenia Karapetrova, Gregory J. MacDougall, and Christianne Beekman

Phys. Rev. Materials **2**, 104411 — Published 25 October 2018

DOI: [10.1103/PhysRevMaterials.2.104411](https://doi.org/10.1103/PhysRevMaterials.2.104411)

Spin Canting and Orbital Order in Spinel Vanadate Thin Films

Christie Thompson,^{1,2} Dalmau Reig-i-Plessis,³ Lazar Kish,³ Adam A. Aczel,⁴ Biwen Zhang,^{2,5} Evguenia Karapetrova,⁶ Gregory J. MacDougall,³ and Christianne Beekman^{2,5}

¹Materials Science and Engineering Program, FSU, Tallahassee, FL 32310, USA

²National High Magnetic Field Laboratory, FSU, Tallahassee, FL 32310, USA

³Department of Physics, University of Illinois at Urbana-Champaign, USA

⁴Neutron Scattering Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA

⁵Department of Physics, FSU, Tallahassee, FL 32306, USA

⁶Advanced Photon Source, Argonne National Laboratory, Argonne, Illinois 60439, USA

(Dated: August 28, 2018)

We report on the epitaxial film growth and characterization of CoV_2O_4 , a near-itinerant spinel vanadate, grown on (001) SrTiO_3 . The symmetry lowering of the unit cell from cubic in the bulk to orthorhombic in the films results in dramatic differences in the magnetic anisotropy compared to bulk, as determined from structural and magnetic characterization. Bulk cubic CoV_2O_4 has been found to defy predictions by showing orbital degeneracy seemingly lasting to very low temperatures, with only small anomalies in magnetization and neutron experiments signaling a possible spin/orbital glass transition at $T = 90$ K. In epitaxial thin films presented in this paper, structurally tuning the CoV_2O_4 away from cubic symmetry leads to a completely different low temperature non-collinear ground state. Via magnetization and neutron scattering measurements we show that the 90 K transition is associated with a major spin reorientation away from the ferrimagnetic easy axis [001] to the [110] direction. Furthermore, the V-spins cant away from this direction with extracted perpendicular moments providing evidence of a larger canting angle compared to bulk. This result indicates that compressive strain pushes the system deeper into the insulating state, i.e., away from the localized - itinerant crossover regime.

Magnetic oxides composed of a frustrated magnetic network of 3d transition metals, in which orbital, spin and structural degrees of freedom are strongly coupled¹, have been an active playground for researchers due to the promise of finding routes to new behaviors. In recent years the focus has been more and more on geometrically frustrated systems in which spin-spin interaction result in macroscopically degenerate ground state manifolds²⁻⁴, lots of entropy, a large density of states that can be manipulated, and emergence of unusual low temperature properties when perturbations are applied. Furthermore, localized spin and itinerant electron behavior are strongly coupled in geometrically frustrated systems⁵ leading to spin liquid behavior⁶ and other exotic phases⁷⁻⁹ as observed in pyrochlores. **More importantly, it has been shown that spin ice physics in thin films of pyrochlore titanates can be modified by application of epitaxial strain^{10,11}.**

Spinel vanadates, in which itinerancy and frustration can be controlled via manipulation of the V-V distance¹²⁻¹⁷, are poster materials for orbital physics in frustrated antiferromagnets. They have been intensely studied to gain a better understanding on how orbital order can help relieve spin degeneracy. Vanadates (AV_2O_4) with non-magnetic atoms on the A-site ($A = \text{Zn}, \text{Cd}, \text{Mg}$ ^{1,18-23}) show two successive transitions, first a structural transition that leads to orbital order, and at lower temperature, a transition to an antiferromagnetic state. It has been shown before that these vanadates can have different structural distortions and thus different low temperature orbital states¹. Vanadates with magnetic atoms on the A-site ($A = \text{Fe}, \text{Mn}$) show multiple struc-

tural phase transitions as a function of temperature, eventually leading to non-collinear and orbitally ordered ground states²⁴; **reports on the magnetic and magnetodielectric properties of FeV_2O_4 epitaxial thin films have started to emerge²⁵.** The origin of the spin canting transitions in vanadates is still under debate²⁶, although recently hyperfine magnetic interactions have been indicated as a possible cause in bulk FeV_2O_4 ²⁷.

CoV_2O_4 has garnered extra attention in the study of the vanadates, because it is the closest known material to an identified localized-itinerant cross-over^{14,15,28}. Experimentally, bulk CoV_2O_4 defies predictions by showing orbital degeneracy seemingly lasting to very low temperatures. Only recently a weak spin canting and a first order structural transition associated with an orbital glass transition has been identified at $T = 90$ K at the edge of detectability^{29,30}. The proximity to itinerancy has been indicated as the cause for the difficulties in observing these transitions reproducibly. In contrast to the weak effects seen in cubic bulk samples, here we show that **epitaxial** orthorhombic CoV_2O_4 thin films grown onto SrTiO_3 substrates demonstrate unmistakable signatures of spin canting and structural effects that indicate long-ranged orbital order. From these experimental results we conclude that a symmetry lowering due to application of in-plane compressive strain can drive the system deeper into the insulating state. **Furthermore, as confirmed by synchrotron x-ray measurements, the new resultant structure is stable to near-bulk thicknesses, showing no signs of relaxation to the cubic structure in films up to 300 nm. Our results indicate that the film growth process and the lattice mismatch with the substrate play**

a role in stabilizing this structure, i.e., there is a clear epitaxial relationship with the substrate and the unit cell is altered compared to bulk. Under practically the same growth conditions we can also fabricate more bulk-like CoV_2O_4 films, but at the cost of the epitaxy and overall quality of the crystal. So the resultant structure is not strained in the conventional sense, but it is a consequence of the constraints imposed by the substrate. This shows that structural tuning in thin films via exposure to a substantial lattice mismatch (i.e. epitaxial strain) is a viable knob for manipulation of non-collinear spin states, orbital states, and itinerancy in spinel vanadates.

High quality thin films of CoV_2O_4 have been grown onto (001) SrTiO_3 substrates via pulsed laser deposition using a home-made pressed pellet of CoV_2O_6 . The films were grown in a background pressure of $P = 1 \times 10^{-7}$ Torr, while the substrate was held at 600 °C. The laser fluence was $\sim 0.6 \text{ J/cm}^2$ and repetition rate of the laser was 1 Hz. Atomic force microscopy (AFM) measurements were performed on the SrTiO_3 substrates before growth, and on the CoV_2O_4 films after growth was completed, using an Asylum MFP-3D system in tapping mode. AFM measurements indicate film surfaces are smooth (root-mean-square roughness $\sim 2.5 \text{ nm}$) with small grains visible on the surface (see supplemental material³¹). Film thicknesses were determined with x-ray reflectivity measurements or from transmission electron microscope (TEM) images. Representative TEM images of the film-substrate interface are shown in the supplemental material³¹. Structural characterization was performed with four-circle synchrotron x-ray diffraction (XRD) measurements at the Advance Photon Source at Argonne National Laboratory, on beamline 33-BM-C³² ($\lambda = 0.77504 \text{ nm}$). Magnetization measurements in an applied field of $H = 1000 \text{ Oe}$ as a function of temperature were performed in a Quantum Design magnetic properties measurement system (MPMS). Elastic neutron scattering experiments were performed at the HB-1A beamline at the High Flux Isotope Reactor at Oak Ridge National Laboratory (HFIR-ORNL) (see supplemental material for further details)³¹.

Synchrotron XRD measurements were performed to determine the structure, the epitaxy, and the sample to sample variations in crystallinity. The lattice mismatch between CoV_2O_4 (bulk: 8.4 \AA) and two unit cells of SrTiO_3 ($2 \times 3.905 = 7.81 \text{ \AA}$) is $\sim 7.5\%$, which is relatively large, and should lead to compressive strain assuming that one film unit cell grows on a block of two by two substrate unit cells. Measurement of the (hkl) positions of six or more reflections were used to determine the orientation matrix of each film³³, which yields typical lattice parameters $a = 8.36(2) \text{ \AA}$, $b = 8.24(5) \text{ \AA}$ and $c = 8.457(3) \text{ \AA}$ ($\alpha = \beta = \gamma = 90^\circ$), showing an orthorhombic unit cell for the films. **It is important to emphasize that all measured orthorhombic films with thicknesses ranging from 55 - 300 nm have these lattice parameters.** X-ray Φ -scans through $(h0l)$ and (hhl) film reflections showed no indication of peak splitting, confirming the single crystal

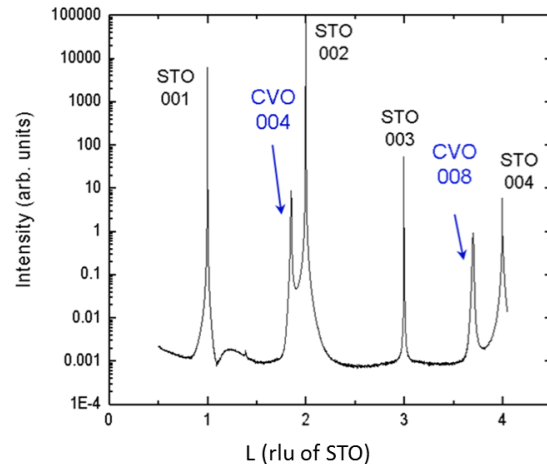


Figure 1: (Color online) XRD scan of the 00L peaks of a 100 nm thick CoV_2O_4 film and the SrTiO_3 substrate.

The film and substrate peaks are indicated with CVO and STO, respectively.

nature of the samples. It is interesting to note that, despite the large difference in lattice parameters, our films still exhibited cube on cube epitaxy, i.e., the major crystallographic axes of film and substrate are aligned³⁴ (see supplemental material for more details³¹). Furthermore, the lattice parameters are such that we can conclude that the films display asymmetric compressive in-plane strain (along $a \sim 0.5\%$, along $b \sim 2\%$). **Defying expectations, this orthorhombic structure was observed in films up to 300 nm in thickness with no signs of relaxation to the bulk cubic structure.**

The 00L scan of a representative sample is presented in Fig. 1. Both the film and substrate peaks are prominently visible in the L-scan supporting the conclusion on the epitaxial relationship with the substrate. **One of the films presented in this paper (which we will refer to as "the cubic polymorph") showed a structure with the c -axis very close to the bulk cubic lattice parameter ($a = 8.34 \text{ \AA}$, $b = 8.30 \text{ \AA}$, $c = 8.39 \text{ \AA}$) with clear signatures of peak splitting indicating multiple structural domains were present (data not shown).** The preparation of this one sample differed from the others, in that the fluence during growth was a little lower, indicating that growth parameters, *not film thickness*, are crucial in structural control of thin films of spinel vanadates. Strikingly, the slight differences in structure and crystallinity between the cubic polymorph and the more orthorhombic films have dramatic consequences for the magnetic properties of the sample as will be discussed next.

In Fig. 2a, magnetization as a function of temperature is shown. All measurements were taken in $H = 1000 \text{ Oe}$ while warming. The solid curves represent measurements taken after cooling the sample in $H = 1000 \text{ Oe}$ (FC); the dashed curves represent measurements taken after cooling the sample in zero field (ZFC). **Representative curves are shown for three orthorhombic samples**

(confirmed via XRD measurements) with different film thicknesses (black: 300 nm, red: 100 nm and blue: 55 nm) and for the cubic polymorph (inset: 300 nm). All films with the orthorhombic structure, with thicknesses ranging from 55 - 300 nm, display a ferrimagnetic phase transition at $T \sim 150$ K similar to bulk samples. However, the orthorhombic films reproducibly show a very obvious second magnetic phase transition at $T = 90$ K. **Note, there is no clear thickness trend in the size of the low temperature magnetic moment, and with $H = 1000$ Oe applied along a or b , the samples are never saturated.** In bulk this transition has been difficult to observe reproducibly and is associated with a small first order cubic-to-tetragonal structural distortion and spin canting on the pyrochlore V-sublattice (canting angles: 5° ²⁹ and 20° ³⁰ have been reported for bulk polycrystalline CoV_2O_4 , and 11° for single crystalline $\text{Co}_{1.3}\text{V}_{1.7}\text{O}_4$ ³⁰). Note, the cubic polymorph (see inset in Fig. 2a) does not show a second phase transition at 90 K. The appearance of the 90 K magnetic transition thus directly ties to the changed unit cell parameters away from cubic symmetry. In Fig. 2b, for the 300 nm thick orthorhombic film, the magnetization as a function of temperature with $H = 1000$ Oe applied in and out of the film plane (black squares and red triangles, respectively) are compared. The out of plane measurement shows a larger increase in magnetization at 150 K, which is associated with the transition to a collinear ferrimagnetic state. This indicates that the c -axis direction (out of plane) is the easy axis in the ferrimagnetic state. Surprisingly, this shows that in the orthorhombic structure the single ion anisotropy wins out over the shape anisotropy of the film (which would prefer to have the moment in the plane of the film); this was also observed in the thinner films. Furthermore, the large decrease (increase) at the magnetic phase transition at 90 K when the field is applied along the c -axis (along the a - or b -axis) indicates that there is a significant re-orientation of the magnetic moment associated with this transition in which most of the moment rotates from the c -axis to an in plane direction. This implies that a change in the local symmetry of the sites takes place at 90 K, which affects the strength of the single ion anisotropy, and that the shape anisotropy wins out over the single ion anisotropy.

Elastic neutron scattering studies in zero applied magnetic field on a ~ 300 nm thick CoV_2O_4 film grown on a $10 \times 10 \text{ mm}^2$ SrTiO_3 substrate are presented in Figs. 3 and 4. The (111), $(\bar{2}20)$, (202), and (002) peaks were monitored as a function of temperature. The onset of the (111) (Fig. 3a) peak can be fit with a power law to reveal the ferrimagnetic phase transition at $T_N = 153$ K, which is in good agreement with the magnetization data (see Fig. 2b). Strikingly, a clear difference between the $(\bar{2}20)$ and (202) order parameter curves is observed (see Fig. 3b). Note, neutrons probe spin directions perpendicular to the direction of the scattering vector Q and are not sensitive to components of the magnetic moment that are parallel to Q . Thus, the increase of both the

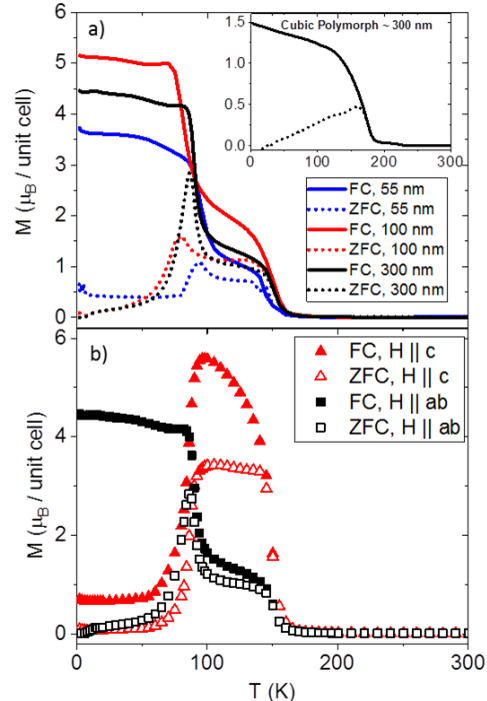


Figure 2: (Color online) a) M vs. T for a 55 nm orthorhombic film (blue curve), a 100 nm orthorhombic film (red curve), and for a 300 nm orthorhombic film (black curve); each are measured while warming in $H = 1000$ Oe after cooling the sample in zero field (ZFC), and after cooling the sample in the measurement field (FC). The field is applied in the film plane, along a or b . Inset: M vs. T for the 300 nm thick cubic polymorph film. b) M vs. T for the 300 nm thick orthorhombic film measured in $H = 1000$ Oe (red triangles: H applied out-of-plane of the film, along c -axis; black squares: H applied in the film plane along a or b), ZFC open symbols and FC closed symbols.

(202) and $(\bar{2}20)$ peaks below 150 K, and a faster growth of the $(\bar{2}20)$ order parameter, confirms that the initial direction of magnetization in the ferrimagnetic state is collinear with the c -axis, i.e., the easy axis. The large drop of the $(\bar{2}20)$ order parameter at 90 K indicates that the Co-spins are reorienting themselves into the plane of the film when the sample is cooled below 90 K. Fig. 4 shows the (002) order parameter as a function of temperature, which clearly shows that the (002) reflection appears below the 90 K magnetic phase transition (the inset shows radial scans of the (002) Bragg peak at 120 K and at 6 K.). The (002) is a structurally forbidden peak traditionally associated with spin-canting on the V-sites²⁹. These results strongly imply that in our films the 90 K transition is associated with the V-spin canting away from the Co-spin direction also.

Based on the experimental evidence presented we can construct a picture of the magnetic properties of CoV_2O_4 films under compressive strain. The drop in intensity

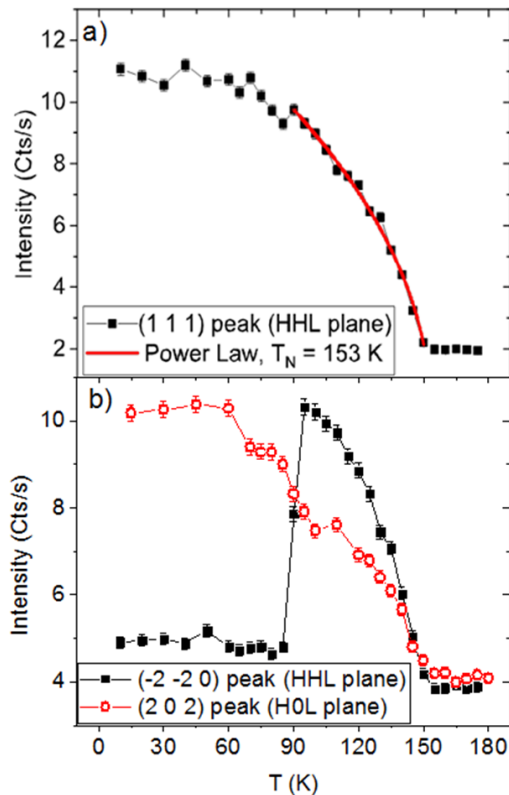


Figure 3: (Color online) Elastic neutron scattering of a ~ 300 nm thick CoV_2O_4 film grown on a $10 \times 10 \text{ mm}^2$ SrTiO_3 substrate. a) (111) Bragg peak intensity as a function of temperature. The red line is a power law fit. b) $(\bar{2}\bar{2}0)$ (black squares), and (202) (red open circles) Bragg peak intensities as a function of temperature.

of the $(\bar{2}\bar{2}0)$ peak, and the subtle increase in the (202) peak intensity, ambiguously leads to the conclusion that Co^{2+} spin points in the $[110]$ direction below 90 K. Furthermore, the low temperature data presented in Figs. 3 and 4 can only be explained if we assume a single domain picture for the magnetization, i.e., this implies that the in-plane symmetry is broken in strained thin films. The direction of the vanadium spins is less clear. Previous work on bulk samples suggests that vanadium spins are mostly aligned antiparallel to A-site spins in ferrimagnetic spinels, canting away below an orbital transition^{29,30}. The finite intensity we observe at the (002) position strongly implies we are seeing a similar canting in a way that breaks the glide plane symmetry of the $\text{Fd}\bar{3}m$ spacegroup. However, we found the (200) reflection to be absent, which provides clues as to how the V- spins cant. In particular, we have confirmed that any model wherein V^{3+} spins cant towards local $\langle 111 \rangle$ directions, similar to what is seen in other vanadates²⁴, is incapable of explaining our results. Based on the idea that the shape anisotropy wins out at low temperatures, we adopt a planar model, wherein the Co spins point along the $[110]$ direction and the V spins cant away from

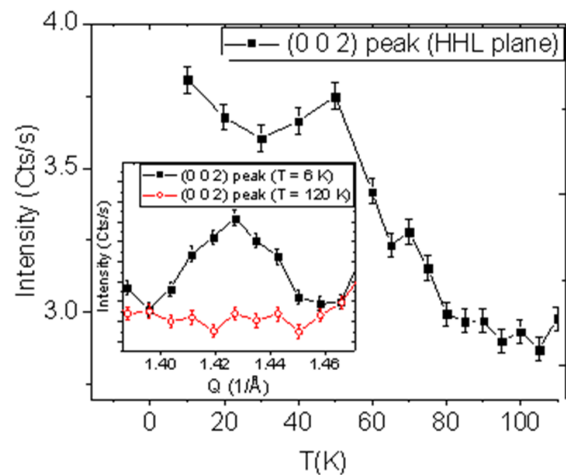


Figure 4: (Color online) Elastic neutron scattering of a ~ 300 nm thick CoV_2O_4 film grown on a $10 \times 10 \text{ mm}^2$ SrTiO_3 substrate: (002) Bragg peak intensity as a function of temperature. Inset: radial scan of the (002) Bragg peak at 6 K (black squares) and at 120 K (red circles).

the $[\bar{1}\bar{1}0]$ direction but remain in the film plane. This model is consistent with the observed scattering and allows us to extract moment sizes at each atom. The intensity of the (002) and (220) reflections depends only on the canted portion of the V spins, the intensity of the (202) reflection arises from the Co moments, and the intensity of the (111) reflection contains contributions from both the Co and V moments.

Based on the normalized intensity of the (202) reflection we find a Co moment of $3.1 (\pm 0.4) \mu_B/\text{Co}$. As expected from our magnetization data and from observations by others we find the full ordered moment on the Co-site. The (002) intensity provides us with a V moment $M_{\perp} = 0.42 (\pm 0.07) \mu_B/\text{V}$ that represents the portion that is canted away from the collinear $[\bar{1}\bar{1}0]$ direction, the $(\bar{2}\bar{2}0)$ intensity confirms this value. If we assume that the (111) reflection is from a purely magnetic origin we obtain a collinear moment on the V-site of about $1.2 (\pm 0.8) \mu_B/\text{V}$. Note that for V^{3+} ordered moments between $0.6 - 1.3 \mu_B/\text{V}$ have been observed in various materials¹⁸ due to partial quenching of the orbital moment^{18,19,24,29,35-42}. Utilizing the calculated perpendicular and parallel moments we find that the V-spins cant by $\sim 20^\circ$ away from the $[\bar{1}\bar{1}0]$ direction, but the spins remain in the ab -plane. Furthermore, we believe the small residual out of plane moment seen in magnetization (see Fig.2b) could be the result of applied fields overcoming the weak shape anisotropy for vanadium spins.

It is possible that we overestimate the parallel V moment by overlooking a possible intensity change of the (111) reflection due to structural distortions, i.e., movement of the oxygen atoms away from the bulk positions will increase the structural contribution to the (111) reflection. Note, if the parallel moment is indeed smaller the canting angle will increase since the intensity of the

(002), and thus the size of the perpendicular moment, should not change due to a structural distortion involving the oxygen atom positions. The magnetic reorientation of the Co moments at 90 K, supported by both magnetization and neutron scattering measurements, indicates that a structural distortion likely accompanies this magnetic transition. This conclusion is indirectly supported by measured changes in scattering intensity at (115), (440) and (222) between high and low temperature by an amount which is too large to be explained by the spin ordering inferred from peaks at lower scattering angle. These changes are consistent with subtle displacements of oxygen anions, which would be difficult to observe with x-ray scattering but could lead to a modification of the single ion anisotropy of the Co atoms that would explain the strong drop in the $(\bar{2}20)$ peak intensity and stabilize the observed low-temperature spin state. Similar shifts in oxygen anions have been observed in other orbitally ordered compounds^{23,36,38,40,43-50}. Note, there is a structural transition of the substrate at 105 K^{51,52} from cubic to tetragonal (associated with a change in the octahedral rotation); the temperature at which we observe magnetic phase transitions are far removed from this transition.

We have grown epitaxial thin films of spinel vanadates. The strain-induced symmetry lowering and introduction of single ion anisotropy leads to dramatic differences in the low temperature non-collinear spin state compared to bulk. At the 90 K transition, a presumed structural

distortion leads to a full reorientation of the Co moment from the [001] (c-axis, the easy axis in the collinear ferromagnetic state) to the [110] direction in the film plane. Furthermore, the much larger perpendicular component of the V moment, compared to values for M_{\perp} seen in powder samples²⁹, indicates that the films display a canting angle of at least $\sim 20^{\circ}$. This finding implies longer-ranged orbital order and an increased localized character of the V moments in strained CoV_2O_4 thin films relative to bulk samples. This work clearly shows that epitaxial strain is a viable knob to tune orbital order and itinerancy in spinel vanadates. More importantly, strain can be utilized in a wide variety of materials allowing more precise control of spin and orbital states, frustration, and itinerancy in thin films of frustrated antiferromagnets.

A portion of this work was performed at the National High Magnetic Field Laboratory, which is supported by National Science Foundation Cooperative Agreement No. DMR-1157490, No. DMR-1644779, and the State of Florida. A portion of this research used resources at the High Flux Isotope Reactor, a DOE Office of Science User Facility operated by the Oak Ridge National Laboratory. Use of the Advanced Photon Source was supported by the U. S. Department of Energy, Office of Science, Office of Basic Energy Sciences, under Contract No. DE-AC02-06CH11357. GM and DR were supported by the National Science Foundation, under Grant No: DMR-1455264.

-
- ¹ S.-H. Lee, H. Takagi, D. Louca, M. Matsuda, S. Ji, H. Ueda, Y. Ueda, T. Katsufuji, J.-H. Chung, S. Park, S.-W. Cheong, and C. Broholm, *Journal of the Physical Society of Japan* **79**, 011004 (2010).
- ² J. W. F. Venderbos, M. Daghofer, J. van den Brink, and S. Kumar, *Physical Review Letters* **107**, 076405 (2011).
- ³ R. Moessner and A. P. Ramirez, *Physics Today* **59**, 24 (2006).
- ⁴ A. P. Ramirez, *Annual Review of Materials Science* **24**, 453 (1994).
- ⁵ P. M. Claudine Lacroix, Frederic Mila, *Introduction to frustrated magnetism: materials, experiments and theory* (Springer-Verlag Berlin Heidelberg, 2011).
- ⁶ S. Nakatsuji, Y. Machida, Y. Maeno, T. Tayama, T. Sakakibara, J. vanDuijn, L. Balicas, J. N. Millican, R. T. Macaluso, and J. Y. Chan, *Phys. Rev. Lett.* **96**, 087204 (2006).
- ⁷ N. Hanasaki, K. Watanabe, T. Ohtsuka, I. Kézsmárki, S. Iguchi, S. Miyasaka, and Y. Tokura, *Phys. Rev. Lett.* **99**, 086401 (2007).
- ⁸ S. Iguchi, N. Hanasaki, M. Kinuhara, N. Takeshita, C. Terakura, Y. Taguchi, H. Takagi, and Y. Tokura, *Phys. Rev. Lett.* **102**, 136407 (2009).
- ⁹ S. Kumar and J. van den Brink, *Phys. Rev. Lett.* **105**, 216405 (2010).
- ¹⁰ D. P. Leusink, F. Coneri, M. Hoek, S. Turner, H. Idrissi, G. V. Tendeloo, and H. Hilgenkamp, *APL Materials* **2**, 032101 (2014), <https://doi.org/10.1063/1.4867222>.
- ¹¹ L. Bovo, X. Moya, D. Prabhakaran, Y.-A. Soh, A. T. Boothroyd, N. D. Mathur, G. Aeppli, and S. T. Bramwell, *Phys. Rev. Lett.* **5**, 3439 (2014).
- ¹² Y. Huang, Z. Yang, and Y. Zhang, *Journal of Physics: Condensed Matter* **24**, 056003 (2012).
- ¹³ J. Ma, J. H. Lee, S. E. Hahn, T. Hong, H. B. Cao, A. A. Aczel, Z. L. Dun, M. B. Stone, W. Tian, Y. Qiu, J. R. D. Copley, H. D. Zhou, R. S. Fishman, and M. Matsuda, *Physical Review B* **91**, 020407 (2015).
- ¹⁴ R. Kaur, T. Maitra, and T. Nautiyal, *Journal of Physics: Condensed Matter* **26**, 045505 (2014).
- ¹⁵ A. Kismarahardja, J. S. Brooks, A. Kiswandhi, K. Matsubayashi, R. Yamanaka, Y. Uwatoko, J. Whalen, T. Siegrist, and H. D. Zhou, *Physical Review Letters* **106**, 056602 (2011).
- ¹⁶ A. Kismarahardja, J. S. Brooks, H. D. Zhou, E. S. Choi, K. Matsubayashi, and Y. Uwatoko, *Physical Review B* **87**, 054432 (2013).
- ¹⁷ A. Kiswandhi, J. S. Brooks, J. Lu, J. Whalen, T. Siegrist, and H. D. Zhou, *Physical Review B* **84**, 205138 (2011).
- ¹⁸ Q. Zhang, K. Singh, F. Guillou, C. Simon, Y. Breard, V. Caignaert, and V. Hardy, *Physical Review B* **85**, 054405 (2012).
- ¹⁹ S.-H. Lee, D. Louca, H. Ueda, S. Park, T. J. Sato, M. Isobe, Y. Ueda, S. Rosenkranz, P. Zschack, J. Íñiguez, Y. Qiu, and R. Osborn, *Physical Review Letters* **93**, 156407 (2004).
- ²⁰ Yutaka Ueda and Naoki Fujiwara and Hiroshi Yasuoka, *Journal of the Physical Society of Japan* **66**, 778 (1997).
- ²¹ H. Mamiya and M. Onoda and T. Furubayashi and J. Tang and I. Nakatani, *Journal of Applied Physics* **81**, 5289

- (1997).
- ²² Noriaki Nishiguchi and Masashige Onoda, *Journal of Physics: Condensed Matter* **14**, L551 (2002).
- ²³ E. M. Wheeler, B. Lake, A. T. M. N. Islam, M. Reehuis, P. Steffens, T. Guidi, and A. H. Hill, *Physical Review B* **82**, 140406 (2010).
- ²⁴ G. J. MacDougall, V. O. Garlea, A. A. Aczel, H. D. Zhou, and S. E. Nagler, *Physical Review B* **86**, 060414 (2012).
- ²⁵ Z. Dongyi, T. Ryota, Z. Yanyu, K. Dohyung, S. V. Kumar, C. Yinghao, H. Qing, M. Paul, L. Mikk, S. Jan, and V. Nagarajan, *Advanced Electronic Materials* **3**, 1600295 (2017).
- ²⁶ J. H. Lee, J. Ma, S. E. Hahn, H. B. Cao, Tao Hong, S. Okamoto, H. D. Zhou, M. Matsuda, and R. S. Fishman, *Scientific Reports* **7**, 17129 (2017).
- ²⁷ B. R. Myoung, S. J. Kim, J. T. Lim, T. Kouh, and C. S. Kim, *AIP Advances* **7**, 055828 (2017).
- ²⁸ S. Blanco-Canosa, F. Rivadulla, V. Pardo, D. Baldomir, J.-S. Zhou, M. García-Hernández, M. A. López-Quintela, J. Rivas, and J. B. Goodenough, *Phys. Rev. Lett.* **99**, 187201 (2007).
- ²⁹ D. Reig-i Plessis, D. Casavant, V. O. Garlea, A. A. Aczel, M. Feyngenson, J. Neufeind, H. D. Zhou, S. E. Nagler, and G. J. MacDougall, *Physical Review B* **93**, 014437 (2016).
- ³⁰ R. Koborinai, S. E. Dissanayake, M. Reehuis, M. Matsuda, T. Kajita, H. Kuwahara, S.-H. Lee, and T. Katsufuji, *Physical Review Letters* **116**, 037201 (2016).
- ³¹ See Supplemental Material at [URL will be inserted by publisher] for the AFM measurement, TEM images, details on the film substrate epitaxy, and details on the neutron scattering experiments..
- ³² E. Karapetrova, G. Ice, J. Tischler, H. Hong, and P. Zschack, *Nuclear Instruments and Methods in Physics Research Section A: Accelerators, Spectrometers, Detectors and Associated Equipment* **649**, 52 (2011), national Synchrotron Radiation Instrumentation conference in 2010.
- ³³ W. R. Busing and H. A. Levy, *Acta Crystallogr.* **22**, 457 (1967).
- ³⁴ J. D. Budai, M. F. Chisholm, R. Feenstra, D. H. Lowndes, D. P. Norton, L. A. Boatner, and D. K. Christen, *Applied Physics Letters* **58**, 2174 (1991).
- ³⁵ M. Reehuis, A. Krimmel, N. Büttgen, A. Loidl, and A. Prokofiev, *The European Physical Journal B - Condensed Matter and Complex Systems* **35**, 311 (2003).
- ³⁶ Y. Motome and H. Tsunetsugu, *Physical Review B* **70**, 184427 (2004).
- ³⁷ V. O. Garlea, R. Jin, D. Mandrus, B. Roessli, Q. Huang, M. Miller, A. J. Schultz, and S. E. Nagler, *Physical Review Letters* **100**, 066404 (2008).
- ³⁸ S. Sarkar, T. Maitra, R. Valentí, and T. Saha-Dasgupta, *Physical Review Letters* **102**, 216405 (2009).
- ³⁹ R. Plumier and M. Sougi, *Solid State Communications* **64**, 53 (1987).
- ⁴⁰ Z. Zhang, D. Louca, A. Visinoinu, S.-H. Lee, J. D. Thompson, T. Proffen, A. Llobet, Y. Qiu, S. Park, and Y. Ueda, *Physical Review B* **74**, 014108 (2006).
- ⁴¹ T. M. McQueen, P. W. Stephens, Q. Huang, T. Klimczuk, F. Ronning, and R. J. Cava, *Physical Review Letters* **101**, 166402 (2008).
- ⁴² A. V. Mahajan, D. C. Johnston, D. R. Torgeson, and F. Borsa, *Physical Review B* **46**, 10966 (1992).
- ⁴³ P. G. Radaelli, *New Journal of Physics* **7**, 53 (2005).
- ⁴⁴ Y. Tokura and N. Nagaosa, *Science* **288**, 462 (2000).
- ⁴⁵ H. Tsunetsugu and Y. Motome, *Phys. Rev. B* **68**, 060405 (2003).
- ⁴⁶ H. Ishibashi, S. Shimono, K. Tomiyasu, S. Lee, S. Kawaguchi, H. Iwane, H. Nakao, S. Torii, T. Kamiyama, and Y. Kubota, *Physical Review B* **96**, 144424 (2017).
- ⁴⁷ E. D. Mun, G.-W. Chern, V. Pardo, F. Rivadulla, R. Sinclair, H. D. Zhou, V. S. Zapf, and C. D. Batista, *Physical Review Letters* **112**, 017207 (2014).
- ⁴⁸ T. Maitra and R. Valentí, *Phys. Rev. Lett.* **99**, 126401 (2007).
- ⁴⁹ S. Niitaka, H. Ohsumi, K. Sugimoto, S. Lee, Y. Oshima, K. Kato, D. Hashizume, T. Arima, M. Takata, and H. Takagi, *Phys. Rev. Lett.* **111**, 267201 (2013).
- ⁵⁰ A. B. Sushkov, O. Tchernyshyov, W. Ratcliff II, S. W. Cheong, and H. D. Drew, *Phys. Rev. Lett.* **94**, 137202 (2005).
- ⁵¹ T. Riste, E. Samuelsen, K. Otnes, and J. Feder, *Solid State Communications* **9**, 1455 (1971).
- ⁵² M. Sato, Y. Soejima, N. Ohama, A. Okazaki, H. J. Scheel, and K. A. Müller, *Phase Transitions* **5**, 207 (1985).