



# CHORUS

This is the accepted manuscript made available via CHORUS. The article has been published as:

## Uncorrelated Bi off-centering and the insulator-to-metal transition in ruthenium $A_{2}Ru_{2}O_{7}$ pyrochlores

Geneva Laurita, Danilo Puggioni, Daniel Hickox-Young, James M. Rondinelli, Michael W. Gaultois, Katharine Page, Leo K. Lamontagne, and Ram Seshadri

Phys. Rev. Materials **3**, 095003 — Published 17 September 2019

DOI: [10.1103/PhysRevMaterials.3.095003](https://doi.org/10.1103/PhysRevMaterials.3.095003)

# Uncorrelated Bi off-centering and the insulator-to-metal transition in ruthenium $A_2Ru_2O_7$ pyrochlores

Geneva Laurita\*

*Department of Chemistry and Biochemistry, Bates College, Lewiston, Maine 04240, United States*

Danilo Puggioni, Daniel Hickox-Young, and James M. Rondinelli

*Department of Materials Science and Engineering, Northwestern University, Evanston IL, 60208, USA*

Michael W. Gaultois

*Leverhulme Research Centre for Functional Materials Design, The Materials Innovation Factory  
Department of Chemistry, University of Liverpool, 51 Oxford Street, Liverpool, L7 3NY, United Kingdom*

Katharine Page

*Chemical and Engineering Materials Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831*

Leo K. Lamontagne and Ram Seshadri

*Materials Department and Materials Research Laboratory, University of California, Santa Barbara, CA 93106*

(Dated: August 31, 2019)

The study of insulator-to-metal transitions is of interest from the viewpoint of fundamental understanding of the underlying physics, and materials at the brink of such transitions possess useful functionality. Driving this transition through compositional tuning can help engineer useful material properties. Here we study the role of disorder in the form of cation off-centering on the compositionally-controlled insulator-to-metal transition in the solid solution oxide pyrochlore  $(Pr_{1-x}Bi_x)_2Ru_2O_7$ . Prior work has established site disorder by the  $Bi^{3+}$  cations shifting incoherently away from their ideal crystallographic site in the Bi end-member pyrochlore as a consequence of stereochemical activity of the lone pair of electrons. However, less is known about the consequences of such off-centering in solid solutions and its role in determining the electronic ground state. Here we demonstrate through total scattering studies that even a small substitution of Bi on the pyrochlore A site leads to site disorder that enhances the average effective size of the A-site cation. This indirectly increases Ru–O–Ru covalency, which appears to play a crucial role in the cross-over from insulating to metallic behavior in the solid solution. Further, density functional electronic structure calculations suggest the combination of primary and secondary (due to size) electronic effects of the lone pair-driven incoherent cation displacements drive the solid solution into a metallic state.

## I. INTRODUCTION

Complex oxides of the  $4d$  transition metals — exemplified by oxides of Ru — are of interest because of the diminished extent of electron correlation compared to the more widely studied  $3d$  metal oxides, the enhanced role of spin-orbit coupling, and the greater prevalence of orbital degeneracy. Among the novel electronic and magnetic properties arising from the nature of the  $4d$  electrons are “clean” electrical conductivity in  $KRu_4O_8$ ,<sup>1–4</sup> spin-glass behavior in  $Ca_2Ru_2O_7$ ,<sup>5</sup> superconductivity in  $Sr_2RuO_4$ ,<sup>6</sup> and simultaneous metallic conductivity and ferromagnetism in  $SrRuO_3$ .<sup>7–10</sup> In particular, ruthenium pyrochlores have been studied for applications as electrode materials,<sup>11</sup> catalysts for oxygen evolution and oxygen reduction reactions,<sup>12,13</sup> materials in high-capacity Li batteries,<sup>14</sup> and components of thick-film resistors.<sup>15</sup> In these applications, electrical transport plays an important role in determining the viability of the material towards device application. However, there are still open questions with regard to electrical transport and magnetic ground states in  $A_2Ru_2O_7$  ( $A = Pr, \dots, Lu, Y, Bi, Pb, Tl$  etc.) pyrochlores.

The pyrochlore structure type, illustrated in Fig. 1, can be represented by the formula  $A_2B_2O_6O'$  with two crystallographically distinct oxygen positions: O in the  $48f$  Wyckoff position at  $(x, \frac{1}{8}, \frac{1}{8})$  and  $O'$  in the  $8b$  site at  $(\frac{3}{8}, \frac{3}{8}, \frac{3}{8})$ .<sup>16</sup> The structure is commonly described as two interpenetrating networks of (i) a diamond sublattice  $A_2O'$  and (ii) a corner-connected network of  $BO_6$  octahedra.<sup>16,17</sup> The  $BO_6$  network forms a fairly rigid channel in which the  $A_2O'$  chains are interspersed, and the channel allows for several modifications of the pyrochlore structure type in the form of nonstoichiometry on the A and  $O'$  sites.

The pyrochlore structure type is additionally tolerant to positional and site disorder of both A and  $O'$  sites, which may be difficult to determine through traditional crystallographic techniques such as neutron or X-ray diffraction. For example, both metallic  $Bi_2Ru_2O_7$ <sup>18</sup> and insulating  $Bi_2Ti_2O_7$ <sup>18,19</sup> exhibit apparent crystallographic disorder of the Bi cations observed as enlarged anisotropic atomic displacement parameters from Rietveld refinement of diffraction data. However, through the application of the neutron pair distribution function (PDF), which provides a real-space atom-atom correla-

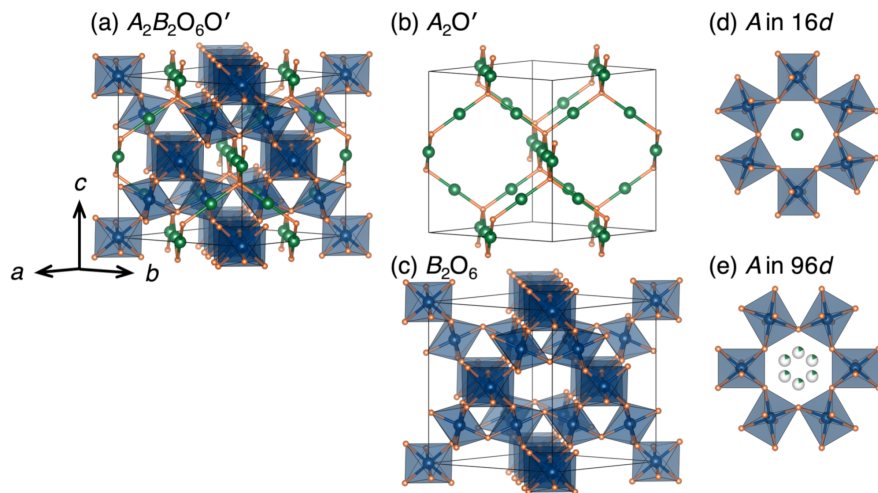


FIG. 1. (a) The  $A_2B_2O_6O'$  pyrochlore structure comprising interpenetrating networks of (b) a diamond  $A_2O'$  sublattice and (c) a sublattice of corner-connected  $BO_6$  octahedra. (d) The ideal  $A$ -site  $16d$  position in the center of the  $BO_6$  channel compared with (e) the off-centered (disordered)  $96g$  position.

tions and therefore a view of the *local* structure, it was determined that in both materials this apparent disorder arises from incoherent, local off-centering of the  $Bi^{3+}$  cations due to stereochemical activity of the associated lone pair of  $6s^2$  electrons.<sup>18</sup> The application of local techniques such as PDF and X-ray absorption spectroscopy (XAS) provides crucial insight on the nature of the disorder in a material, which can influence the observed properties, as demonstrated in various ruthenium oxide materials.<sup>20,21</sup> The incoherent off-centering of the  $A$ -site, and the frequent absence of ordered distorted structural ground states in this structure type could potentially be linked to frustration arising from the topology,<sup>22</sup> in analogy with the difficulty of obtaining long-range spin-ordered ground states.<sup>23,24</sup>

The electronic properties of  $A_2Ru_2O_7$  pyrochlores arise from the corner-sharing  $RuO_6$  sublattice.<sup>25–27</sup> Metallic character originates from  $\pi$ -type orbital interactions of  $Ru$   $4d$  and  $O$   $2p$  orbitals across the  $Ru$ – $O$ – $Ru$  bridges of the corner-shared octahedra. A combination of an increase in the size of the  $A$ -site cation and shorter  $Ru$ – $O$  bonds results in an increase in the  $Ru$ – $O$ – $Ru$  orbital overlap, facilitating greater interaction and promoting metallic transport behavior.<sup>25</sup> Insulating ruthenium pyrochlores such as  $Yb_2Ru_2O_7$  and  $Lu_2Ru_2O_7$  exhibit  $Ru$ – $O$ – $Ru$  bond angles of  $127^\circ$  and  $132^\circ$ , respectively, whereas metallic  $Bi_2Ru_2O_7$  has an increased bond angle of  $133^\circ$ .<sup>28</sup>

In the lanthanide ruthenium pyrochlores, the room temperature electrical resistivity decreases uniformly with increasing ionic radius of the lanthanide cation.<sup>29</sup> However, the introduction of any  $Bi^{3+}$  leads to substantial deviation from the trend created simply by size of the  $A$ -site as seen from tuning rare-earth radii, suggesting there are contributions other than size effects. The  $6s^2$  lone pair distinguishes  $Bi^{3+}$  from the  $Ln^{3+}$  lanthanide

ions that lead to insulating behavior. Previous Reverse Monte Carlo (RMC) analysis of neutron total scattering data collected from  $Bi_2Ti_2O_7$  and  $Bi_2Ru_2O_7$  revealed  $Bi$  nuclei are locally displaced from the average position described by the cubic pyrochlore crystal structure,<sup>18,19</sup> driven by stereochemical activity of the  $Bi$  lone pair.

Here we examine how the increase in the  $A$ -site cation radius results in a corresponding increase in the  $Ru$ – $O$ – $Ru$  bond angle, driving the system towards metallic behavior. We hypothesize that the local distortion caused by  $Bi$  cations is responsible for the observed metallic behavior and the distinct behavior of the  $Bi$ -containing pyrochlores when contrasted with the lanthanide end members. We employ neutron total scattering techniques and least-squares modeling to determine the influence of  $Bi^{3+}$  on the local structure in the series  $(Pr_{1-x}Bi_x)_2Ru_2O_7$  ( $x = 0.0, 0.1, 0.5, \text{ and } 1.0$ ). We find the  $Bi^{3+}$  are displaced from their ideal sites in all  $Bi$ -containing samples, influencing the effective size of the  $A$ -site cation and the resulting structural and physical properties throughout the series. The study is complemented with density functional theory (DFT)-based electronic structure calculations carried out on the ideal structure as well as structural models that represent the local off-centering disorder seen in experiment. The trends in the densities of states provide insights into the observed transport behavior.

## II. METHODS

Polycrystalline samples were prepared by direct reaction of constituent oxide powders ( $RuO_2$ , 99.99%, Sigma-Aldrich;  $Pr_6O_{11}$ , 99.99%, Alfa Aesar;  $Bi_2O_3$ , 99.99%, Alfa Aesar) with multiple firings. Powders were ground using an agate mortar and pestle, pressed into

13 mm diameter pellets using a uniaxial pellet press, and placed in a dense alumina crucible on a sacrificial bed of powder of the same composition. Samples were re-ground and pelleted between all firings.

$\text{Bi}_2\text{Ru}_2\text{O}_7$  was prepared by heating in air from room temperature to 1003 K over 3 h, annealing for 24 h and cooling to room temperature in the furnace. This was repeated once, followed by a 24 h firing 1073 K.  $\text{Pr}_2\text{Ru}_2\text{O}_7$  was prepared by heating in a box furnace in air from room temperature to 1173 K over 3 h, annealing for 24 h, and cooling to room temperature in the furnace. This process was repeated 4 times. Owing to the low melting point of  $\text{Bi}_2\text{O}_3$ , Bi-containing samples were prepared by heating in air from room temperature to 1003 K over 3 h, annealing for 24 h and cooling to room temperature in the furnace. This was repeated 2 times, followed by 2 additional 24 h firings at 1073 K, and 3 additional 24 h firings at 1173 K.

All samples were then annealed in a tube furnace at 1373 K (1173 K for  $\text{Bi}_2\text{Ru}_2\text{O}_7$ ) for 12 h under flowing ultra-high-purity Ar further purified using a Ti gettering furnace, and cooled to room temperature under Ar at  $2 \text{ K min}^{-1}$ . Owing to the volatility of Ru oxides in air at high temperatures ( $T \sim 1313 \text{ K}$ )<sup>29</sup>, these high(er) temperature annealing steps were performed under Ar.

Time-of-flight (TOF) neutron total scattering data were collected on powdered samples at the NPDF instrument at Los Alamos National Laboratory.<sup>30</sup> 3 g to 4 g of sample was placed into a vanadium can, and measurements were performed at 298 K for approximately 4 h. Rietveld refinements of the neutron diffraction data were conducted using the GSAS software with the interface EXPGUI.<sup>31,32</sup> Data reduction to obtain the PDF  $G(r)$  function was performed using the PDFgetN program<sup>33</sup> with  $Q_{\text{max}} = 35 \text{ \AA}^{-1}$ , which was selected to balance between resolution and termination ripples in the reduced data. Least-squares refinement of the PDF data were performed with PDFGUI<sup>34</sup> over a range of  $1.7 \text{ \AA}$  to  $5 \text{ \AA}$ . Crystal structures were visualized using the VESTA software suite.<sup>35</sup>

First-principles DFT calculations employed the Perdew-Burke-Ernzerhof exchange-correlation functional revised for solids (PBEsol)<sup>36</sup> as implemented in the Vienna *Ab initio* Simulation Package (VASP)<sup>37</sup> with the projector augmented wave (PAW) approach<sup>38</sup> to treat the core and valence electrons using the following electronic configurations:  $2s^2 2p^4$  (O),  $4p^6 4d^7 5s^1$  (Ru),  $5s^2 5p^6 6s^2 5d^1$  (La),  $5s^2 6s^2 5p^6 5d^1$  (Pr, Nd, and Sm),  $6s^2 5p^6 5d^1$  (Lu) and  $6s^2 5d^{10} 6p^3$  (Bi). A  $6 \times 6 \times 6$   $\Gamma$ -centered  $k$ -point mesh was generated and a 650 eV energy cutoff was used for the planewaves. For all calculations, the atomic positions were relaxed (forces  $< 0.1 \text{ meV \AA}^{-1}$ ) using Gaussian smearing (20 meV width) and the experimental lattice constants reported herein.

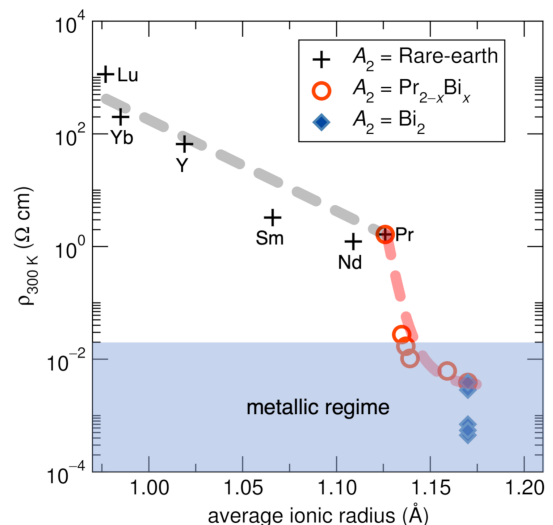


FIG. 2. Room temperature resistivity ( $\rho_{300\text{K}}$ ) as a function of the average A-site ionic radii for the series  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  ( $x=0.0, 0.1, 0.5, \text{ and } 1.0$ ), shown in filled squares, illustrates a cross-over from insulating to metallic conductivity between  $x=0.1$  and  $x=1.0$ . The data is compared to literature on other  $\text{A}_2\text{Ru}_2\text{O}_7$  pyrochlores,<sup>29,39-43</sup> and follows expected trends.

### III. RESULTS AND DISCUSSION

A recent compilation was created of the trends in room-temperature electrical resistivity<sup>29</sup> ( $\rho_{300\text{K}}$ ) as a function of A-site ionic radii (for 3+ cations in 8-coordination<sup>44</sup>) from the extensive pyrochlore literature.<sup>16,26,39,40,42,45-47</sup> When  $A$  = rare earth, there is a simple trend of a logarithmic decrease in the room temperature resistivity taking the materials closer to metallicity, as the rare-earth radius increases. Data on the series  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  ( $x = 0.0, 0.1, 0.5, 1.0$ ) with  $\text{Bi}^{3+}$  substitution behaves anomalously. Samples with  $x = 0.0$  and  $x = 0.1$  exhibit electrical resistivity above the metallic threshold, while a rapid crossover into the metallic regime is observed at room temperature for the  $x = 0.5$  and  $x = 1.0$  samples, at a rate not explained simply by an averaging of the size of A-site ions.

To investigate the transition to metallic behavior with increasing Bi content from both an average, crystallographic and local perspective, neutron total scattering data was collected at 300 K. Rietveld refinements of the data indicate all samples can be indexed to the  $Fd\bar{3}m$  space group, and the data is well described by the cubic pyrochlore structure. Refined occupancies are close to the nominal values within error, with the exception of Bi and O' vacancies in the nominal  $\text{Bi}_2\text{Ru}_2\text{O}_7$  compound. Vacancies in both the Bi and 8b oxygen sites appear to be intrinsic for the Bi end member, and has been reported in the literature.<sup>18,48-50</sup> These vacancies decrease as the solid solution progresses towards the Pr-rich end. A summary of the refined crystallographic data is presented in Table I, and a summary of the refined atomic data is pre-

TABLE I. Crystallographic information from the Rietveld refinements of neutron diffraction data of  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  at 300 K.

	Source neutron TOF	neutron TOF	neutron TOF	neutron TOF
Chemical formula	$\text{Pr}_2\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.83(2)}\text{Bi}_{0.17(2)}\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.12(2)}\text{Bi}_{0.88(2)}\text{Ru}_2\text{O}_{6.94}$	$\text{Bi}_{1.92(1)}\text{Ru}_2\text{O}_{6.88(1)}$
Formula weight	595.95	607.67	578.24	712.02
Temperature (K)	300	300	300	300
Crystal system	cubic	cubic	cubic	cubic
Space Group	$Fd\bar{3}m$	$Fd\bar{3}m$	$Fd\bar{3}m$	$Fd\bar{3}m$
$a$ ( $\text{\AA}$ )	10.3689(5)	10.3607(3)	10.3299(5)	10.2969(5)
Volume ( $\text{\AA}^3$ )	1114.8(5)	1112.17(9)	1102.28(5)	1091.76(3)
Z	8	8	8	8
$d$ -space range ( $\text{\AA}^{-1}$ )	0.491 to 7.095	0.491 to 7.097	0.491 to 7.097	0.492 to 7.097
$\chi^2$	15.64	18.63	12.22	17.43
$R_p$ (%)	3.11	3.09	2.52	2.76
$R_{wp}$ (%)	4.77	4.65	3.95	4.28

TABLE II. Select refined atomic parameters from the Rietveld refinements of neutron diffraction data of  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  at 300 K.

	$\text{Pr}_2\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.83(2)}\text{Bi}_{0.17(2)}\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.12(2)}\text{Bi}_{0.88(2)}\text{Ru}_2\text{O}_{6.94}$	$\text{Bi}_{1.92(1)}\text{Ru}_2\text{O}_{6.88(1)}$
Chemical formula	$\text{Pr}_2\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.83(2)}\text{Bi}_{0.17(2)}\text{Ru}_2\text{O}_7$	$\text{Pr}_{1.12(2)}\text{Bi}_{0.88(2)}\text{Ru}_2\text{O}_{6.94}$	$\text{Bi}_{1.92(1)}\text{Ru}_2\text{O}_{6.88(1)}$
$O_x$	0.3292(2)	0.3286(5)	0.3277(5)	0.3271(5)
Ru–O–Ru ( $^\circ$ )	131.69(5)	132.01(5)	132.54(5)	132.83(5)
$A U_{xx}$ ( $\text{\AA}^2$ )	0.0038(5)	0.0053(7)	0.0114(7)	0.0160(7)
$A U_{xy}$ ( $\text{\AA}^2$ )	−0.0011(7)	−0.0014(6)	−0.0042(6)	−0.0055(5)
Ru $U_{\text{iso}}$ ( $\text{\AA}^2$ )	0.0009(3)	0.0016(3)	0.0015(3)	0.0029(3)
O1 $U_{\text{iso}}$ ( $\text{\AA}^2$ )	0.0032(2)	0.0044(2)	0.0053(2)	0.0067(2)
O2 $U_{\text{iso}}$ ( $\text{\AA}^2$ )	0.0026(6)	0.0039(6)	0.010(8)	0.017(5)
Bi occupancy	0	0.08(2)	0.44(2)	0.97(5)
O2 occupancy	1.0	1.0	0.93(2)	0.88(3)

sented in Table II.

The trends in refined parameters upon Bi-substitution is illustrated in Fig. 4, presented as a function of increasing Bi content. Lattice parameters decrease with increasing Bi content (Fig. 4a), which counters the trend expected when replacing smaller  $\text{Pr}^{3+}$  (ionic radii of 1.13  $\text{\AA}$  in an 8 coordinate site) with  $\text{Bi}^{3+}$  (ionic radii of 1.17  $\text{\AA}$  in an 8 coordinate site).<sup>44</sup> This is a direct result of the chemical properties of Bi, and directly influences the observed metallic behavior in the Bi-rich samples.<sup>28</sup> The presence of the softer Bi cation leads to a shift in the 48*f* O atomic position (Fig. 4b), which leads to a larger Ru–O–Ru bond angle (Fig. 4c). This enhances the Ru 4*d* and O 2*p* orbital overlap, thus shortening the Ru–O bond length and the unit cell dimensions.

The atomic displacement parameters (ADPs) of the A-site cations were modeled anisotropically ( $U_{ani}$ ) to determine if any directionality was present in the atomic displacements. Upon Bi substitution, displacement towards the edge of the surrounding  $\text{RuO}_6$  octahedra is observed, perpendicular to the channel formed by the

octahedral network (Fig. 5). The magnitude of this perpendicular displacement, described by the  $U_{11,22,33}$  components of the  $U_{ani}$ , increases with Bi content (Fig. 4d), indicating that more disorder on the A-site is observed when Bi is present. Both the directionality and magnitude of the anisotropic displacements upon increasing Bi content point towards the stereochemical activity of the  $6s^2$  lone pair of electrons associated with  $\text{Bi}^{3+}$  and subsequent off-centering of the A-site cation.

To better understand the nature of the observed disorder on the A site, analysis of the neutron PDF was performed against two crystallographic models: the 16*d* model where the A-site cations are placed in the center of the channel in the 16*d* Wyckoff position at  $(\frac{1}{2}, \frac{1}{2}, \frac{1}{2})$  and the 96*g* model where the A-site cations are allowed to off-center in the channel in the 96*g* Wyckoff position at  $(x, x, z)$ . These are respectively displayed in panels (d) and (e) of Fig. 1. The neutron PDF data for all samples were fit over a range of 1.5  $\text{\AA}$  to 5.0  $\text{\AA}$  against both the 16*d* and 96*g* models, shown in Fig. 6 for the  $x = 0.5$  and 1.0 samples. All samples are well described by the

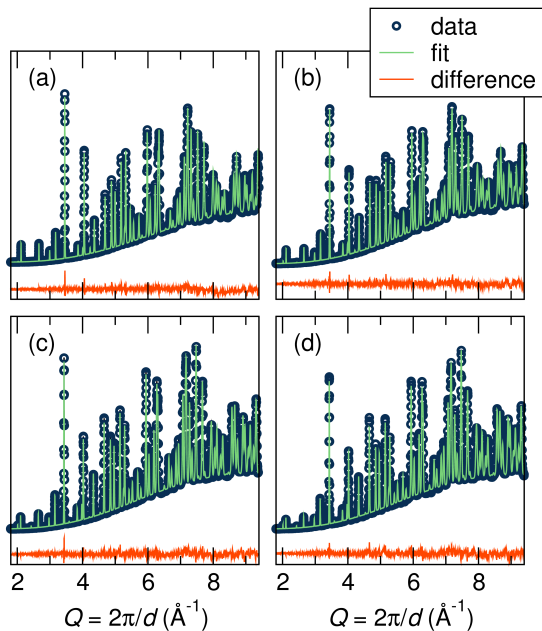


FIG. 3. Rietveld refinements of the neutron diffraction data (NPDF, Los Alamos National Laboratory) for the series  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  [(a)  $x = 0.0$ , (b)  $x = 0.1$ , (c)  $x = 0.5$ , and (d)  $x = 1.0$ ] indicates all samples can be crystallographically described by the cubic pyrochlore structure with space group  $Fd\bar{3}m$  (no. 227).

16d model, but fits of the  $x = 0.5$  and 1.0 data are visibly improved below  $3 \text{ \AA}$  with the 96g model. The refined parameters from the two models are plotted in Fig. 7 as a function of Bi content. Both the 48f O positional parameter and Ru–O–Ru bond angle are similar for both models, and in agreement with the trends observed through analysis of the diffraction data. However, a clear difference in the success of the two models is seen in comparing the goodness-of-fit parameter  $R_w$  and Bi  $U_{\text{iso}}$  in the Bi-rich samples, both of which are lowered with the 96g model. Combined, these parameters suggest the 96g model is a better description of the behavior of the A-site cations when Bi is present. For the Bi end member, a maximum displacement of  $0.16 \text{ \AA}$  from the center of the channel is observed, in agreement with values obtained in the literature.<sup>48</sup> This off-centering indicates the  $6s^2$  lone pair is stereochemically active, resulting in a larger effective radius of the A site, and subsequent widening of the Ru–O–Ru bond angle, which in turn, gives rise to an enhanced bandwidth for the conduction band created from Ru and O states.

Analysis of both the average and local structure by means of neutron total scattering suggests with increasing Bi content the system progressively deviates from a simple model where the A-site atom occupies the ideal position; A-site off-centering and local disorder increases continuously. However, these models are based on the assumption that all A-site ions behave identically, and it is not clear whether Bi is strongly locally displaced at all

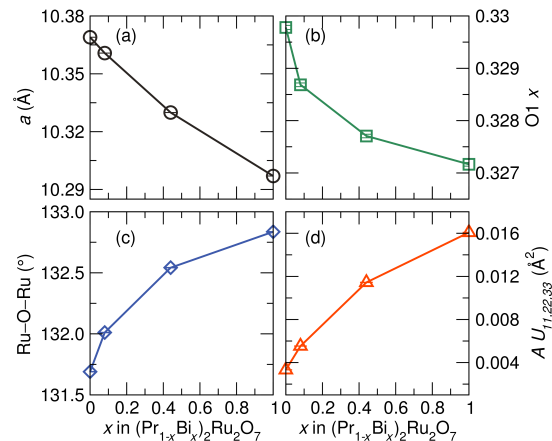


FIG. 4. Refined parameters from Rietveld refinement of neutron diffraction data. (a) Cell parameter  $a$ , (b) O1 variable  $x$  position, (c) Ru–O–Ru bond angle, and (d) anisotropic atomic displacement parameters (ADPs) of the A-site cation as a function of Bi content. A contraction of the lattice parameter, shift in the O1 position, and increase in the Ru–O–Ru bond angle are observed with increasing Bi content due to an increase in the covalency of the Ru–O bonds. An increase in the anisotropic ADPs indicates increased disorder on the A-site with increasing Bi content.

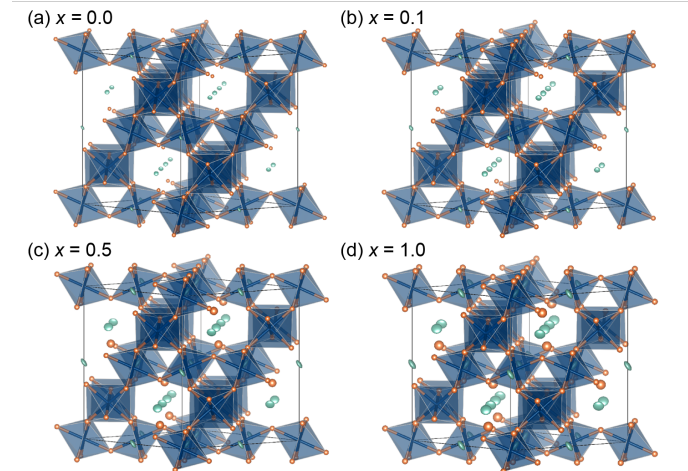


FIG. 5. Crystallographic structures for the series  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  [(a)  $x = 0.0$ , (b)  $x = 0.1$ , (c)  $x = 0.5$ , and (d)  $x = 1.0$ ] indicates anisotropic ADPs of the A-site cation (shown at 90% probability) increase with Bi concentration.

levels of substitution, or whether the displacement gradually increases with substitution. Particularly at low levels of Bi substitution, the total scattering is not sensitive to the small amount of Bi on the A-site, as the contribution is a weighted average of Pr/Bi. Regardless, it is apparent that even with small amounts of bismuth substitution, disorder is induced on the A-site despite  $\text{Pr}^{3+}$  and  $\text{Bi}^{3+}$  having fairly similar ionic radii, and the disorder plays a role in the effective size of the site in the structure. However, the local Ru–O–Ru bond angle evolution

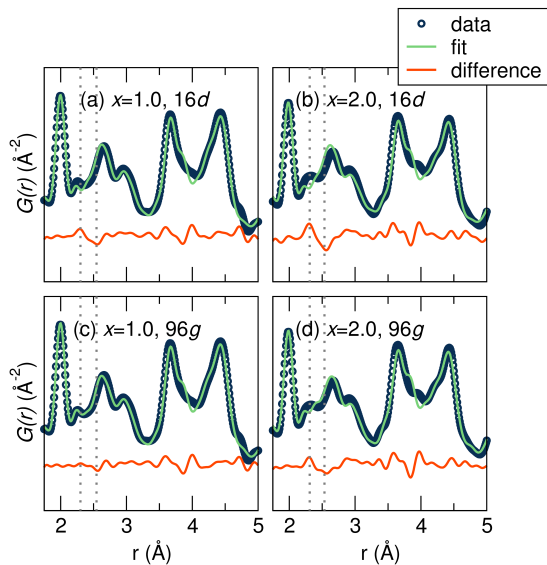


FIG. 6. Fits of the neutron PDF (NPDF, Los Alamos National Laboratory) against (a,b) the crystallographic structure with the A-site cation in the ideal  $16d$  Wyckoff site at  $(0.5, 0.5, 0.5)$  and (c,d) with the A-site cation displaced into the  $96g$  Wyckoff site at  $(x, x, z)$ . For both the  $x = 0.5$  (a,c) and  $x = 1.0$  (b,d) samples the data is better described by the  $96g$  model, suggesting the A-site cations are displaced from the ideal crystallographic site, a result of stereochemical activity of the  $6s^2$  lone pairs associated with  $\text{Bi}^{3+}$ . Dashed lines indicate A–O bond lengths when the A-site cation is placed in the ideal  $16d$  position.

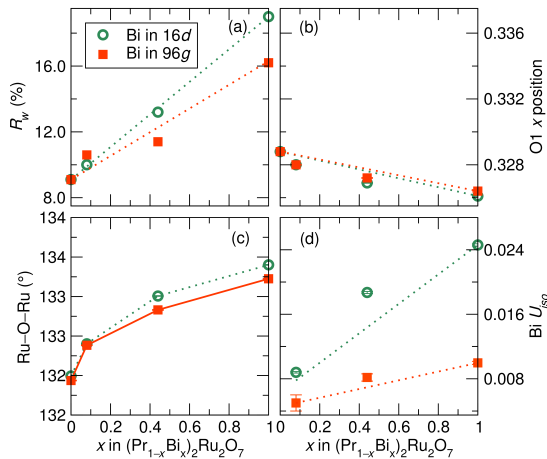


FIG. 7. Comparison of the refined data from fits of the NPDF data against the  $16d$  and  $96g$  models as a function of increasing Bi content. (a) For all Bi-containing samples, a lower goodness-of-fit parameter,  $R_w$ , is obtained with the  $96g$  model, suggesting the local structure is best described by the displaced model. (b) O1  $x$  position is relatively unaffected by the two models, supporting that the models are solely a modification of the A-site cation. (c) Ru–O–Ru bond angles are additionally similar for both models, whereas (d) isotropic ADPs of the A-site cation are significantly lowered in the  $96g$  displaced model, indicating this model approximates a better description of the local structure.

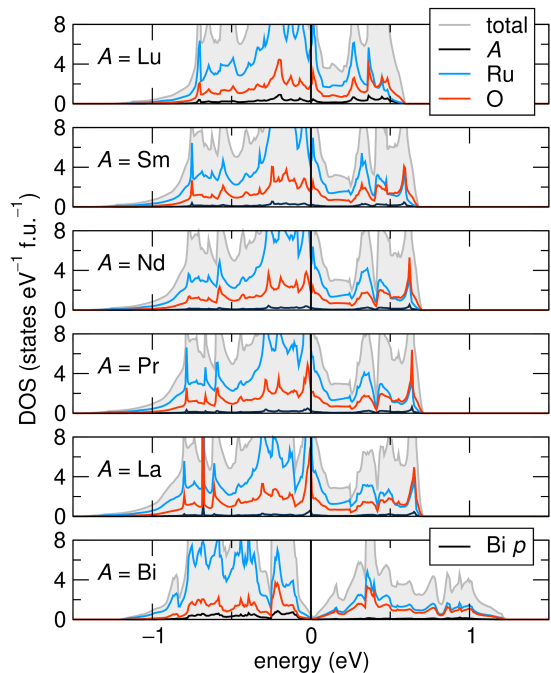


FIG. 8. (a) Total and projected density of states (DOS) for  $\text{Ln}_2\text{Ru}_2\text{O}_7$  ( $\text{Ln} = \text{Lu}, \text{Sm}, \text{Nd}, \text{Pr}, \text{and La}$ ) and  $\text{Bi}_2\text{Ru}_2\text{O}_7$ . The energies are referenced to the Fermi at 0 eV (vertical line).

follows a similar trend of a relatively small increase with Bi substitution, suggesting that more than sterics are at play for the observed electrical properties.

In order to relate the structural evolution to electronic properties, we performed DFT calculations of the electronic structure to examine the role of local structure on the low-energy electronic densities of states (DOS), which in turn, impacts electrical transport. The total and projected densities-of-states (DOS) for  $\text{Ln}_2\text{Ru}_2\text{O}_7$  and  $\text{Bi}_2\text{Ru}_2\text{O}_7$  with the cubic  $Fd\bar{3}m$  space group are presented in Fig. 8. For all the compounds, consistent with low-spin  $\text{Ru}^{4+}$ , the valence band is composed largely of Ru  $t_{2g}^4$  states hybridized with O  $2p$  states. The  $\text{Ln}_2\text{Ru}_2\text{O}_7$  ( $\text{Ln} = \text{Lu}, \text{Sm}, \text{Nd}, \text{Pr}, \text{and La}$ ) compositions exhibit relatively narrow and populous states at the Fermi level ( $E_F$ ) at the DFT-PBESol level, consistent with the potential for electron correlation driving insulating and magnetic behavior. In contrast,  $\text{Bi}_2\text{Ru}_2\text{O}_7$  exhibits fewer and less peaked DOS — almost pseudogapped<sup>48</sup> — with a redistribution of states above and below  $E_F$  that acts to renormalize the orbital bandwidth. The pseudogap opening near  $E_F$  originates from a localized feature in the energy range of  $-25$  meV with respect to  $E_F$ , wherein the strong hybridization between Ru  $4d$  and O  $2p$  states is modulated by the Bi  $6p$  states through the additional hybridization of Bi  $6p$  and Ru  $t_{2g}^4$  states.

Figure 9 presents the Ru  $t_{2g}$  bandwidth evolution as a function of DFT calculated Ru–O–Ru bond angles in  $\text{Ln}_2\text{Ru}_2\text{O}_7$  and  $\text{Bi}_2\text{Ru}_2\text{O}_7$ . For all of these calculations, the ideal crystallographic structures were employed, with no displaced atoms. In  $\text{Ln}_2\text{Ru}_2\text{O}_7$ , the band-

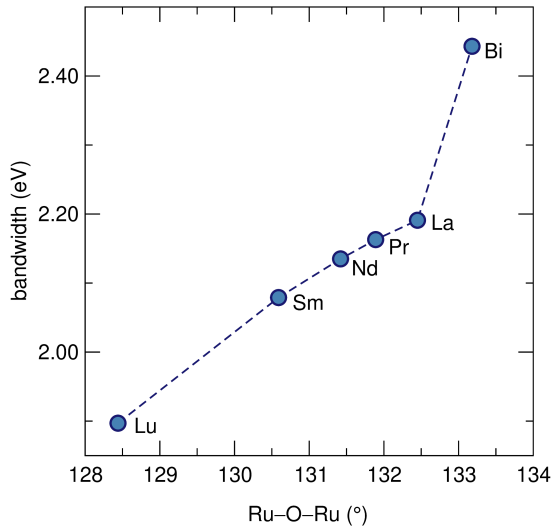


FIG. 9. Bandwidth values of the Ru  $t_{2g}$  bands as a function of the Ru–O–Ru bond angles in  $Ln_2Ru_2O_7$  ( $Ln = \text{Lu, Sm, Nd, Pr, and La}$ ) and  $\text{Bi}_2\text{Ru}_2\text{O}_7$  extracted from DFT electronic structures.

widths increase linearly as a function of the  $Ln^{3+}$  ionic radii and Ru–O–Ru bond angles. Although the difference in the Ru–O–Ru bond angles for  $\text{Bi}_2\text{Ru}_2\text{O}_7$  and  $\text{La}_2\text{Ru}_2\text{O}_7$  is less than  $1^\circ$ , the bandwidth of  $\text{Bi}_2\text{Ru}_2\text{O}_7$  is significantly larger, and markedly deviates from the trend followed by the other compounds in accordance with the reported room temperature electrical resistivities of  $Ln_2Ru_2O_7$  and  $\text{Bi}_2\text{Ru}_2\text{O}_7$  (see Fig. 2). Going from  $Ln_2Ru_2O_7$  to  $\text{Bi}_2\text{Ru}_2\text{O}_7$  it would appear that two things happen: The density of states is no longer peaked at  $E_F$  and the width of the band contributing charge carriers is enlarged. Both of these effects would suggest that while  $Ln_2Ru_2O_7$  are susceptible to electronic instabilities leading to magnetic and insulating ground states,  $\text{Bi}_2\text{Ru}_2\text{O}_7$  is a candidate for metallic behavior.

We anticipate the conductivity to be robust to small amounts of oxygen vacancies as observed in our samples. Previous work on stoichiometric samples of  $\text{Bi}_2\text{Ru}_2\text{O}_7$  (determined through compositional analysis<sup>51</sup> and neutron scattering<sup>18</sup>) report the same metallic conductivity as samples with vacancies, suggesting the enhanced metallicity is not an effect of the observed vacancies.

To examine how the  $\text{Bi}_2\text{Ru}_2\text{O}_7$  electronic structure is impacted by local off-centering of  $\text{Bi}^{3+}$  cations, we have computed the electronic properties while constraining the Ru–O–Ru bond angles to  $133.18^\circ$ , simulating the experimental displacements of the  $\text{Bi}^{3+}$  cations in the “96g” model (Fig. 10). When the  $\text{Bi}^{3+}$  cations occupy the 16d Wyckoff site at  $(1/2, 1/2, 1/2)$ , the Bi–O bond length is  $\sim 2.6 \text{ \AA}$  and  $\text{Bi}_2\text{Ru}_2\text{O}_7$  appears to be semimetallic with a pseudogap opening at  $E_F$  (Fig. 10, top panel). A more careful analysis of the DOS reveals strongly localized states at the top of the valence band, in the energy range of  $-25 \text{ meV}$  of  $E_F$ , wherein the hybridization between

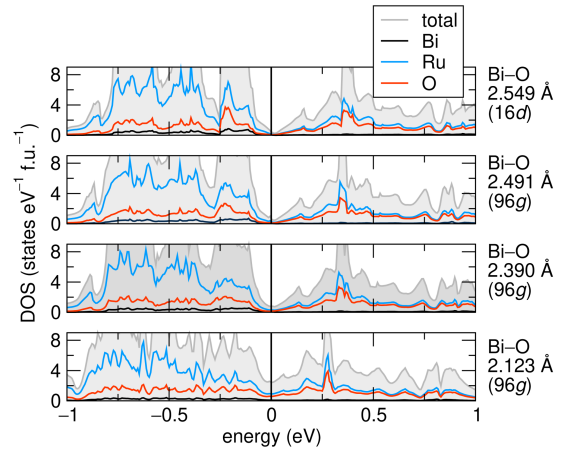


FIG. 10. (a) Total and projected density of states (DOS) for **stoichiometric**  $\text{Bi}_2\text{Ru}_2\text{O}_7$  as a function of the  $\text{Bi}^{3+}$  displacements from the 16d to 96g Wyckoff site. The energies are referenced to the Fermi at 0 eV (vertical line).

Ru 4d and O 2p states is mediated by partially filled Bi 6p states, which should nominally be empty. This results in strong covalent Ru–O bonds, as also suggested by the calculated electron localization function (ELF) shown in Fig. 11(a), and is robust to the effects of spin-orbit interactions.

The displacement of the  $\text{Bi}^{3+}$  cations into the 96g Wyckoff site to  $(x, x, z)$  shortens the Bi–O bond length, increasing the number of states at  $E_F$  (Fig. 10 three lower panels). In particular, when the Bi–O bond length is  $\approx 2.1 \text{ \AA}$ , the number of states at the Fermi level increases to  $N(E_F) \approx 2.5 \text{ states eV}^{-1} \text{ f.u.}^{-1}$ . Note that in the neutron PDF data (Fig. 6) the lowest boundary of the Bi–O peak sets the minimum Bi–O bond distance to  $2.1 \text{ \AA}$ . The local off-centering of the  $\text{Bi}^{3+}$  cations reduces the weight of the Bi 6p states in the valence band, decreasing the localization of the Ru 4d and O 2p states at the top of the valence band. The Bi off-centering and weak 6p hybridization results in a lower degree of covalency of the Ru–O bonds [Fig. 11(b)] with consequent enhanced metallic behavior. **The pseudo-gap that occurs when Bi is centered in the 16d position arises from strong Bi 6p and Ru  $t_{2g}^4$  hybridization, which strengthens the covalency of the Ru–O bond. Consequently, the nominally empty Bi 6p states are then partially occupied in the sense that they form part of the bonding state involved in the covalent bond. When the Bi atom displaces away from the 16d position, the Ru–O bonding interaction is weakened and the gap closes, enhancing the metallicity.** This behavior points to the dual role of  $\text{Bi}^{3+}$  cations in the electronic properties of  $\text{Bi}_2\text{Ru}_2\text{O}_7$ : cation off-centering favors enhanced metallicity *via* decreased orbital occupation in addition to the off-centering effectively enlarging the Ru–O–Ru bond distances resulting in more delocalized charge carriers. Together, these effects account for the dramatic changes in the electrical behavior upon Bi substitution.



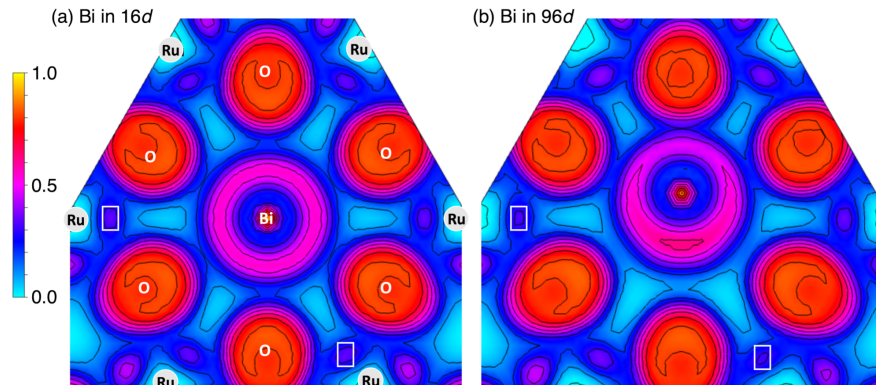


FIG. 11. (a) Electron localization function (ELF) of  $\text{Bi}_2\text{Ru}_2\text{O}_7$  with  $\text{Bi}^{3+}$  cations in the  $16d$  and (b) mimicked  $96g$  position. The white boxes highlight the difference in covalency of the Ru–O bonds.

We would imagine that since this role of  $\text{Bi}^{3+}$  is local, it would persist in any solid solution of  $\text{Ln}^{3+}$  and  $\text{Bi}^{3+}$  which could help explain why  $\text{Bi}^{3+}$  is a “magic pill”, driving these ruthenium pyrochlores metallic.

#### IV. CONCLUSIONS

The pyrochlore series  $(\text{Pr}_{1-x}\text{Bi}_x)_2\text{Ru}_2\text{O}_7$  has been prepared and examined through neutron total scattering techniques to understand the structural role of the A-site cation on the compositional insulator-to-metal transition observed across the series. This work explores the simple model that increasing the ionic size of the A-site cation will increase the Ru–O–Ru bond angle, which will in turn drive a transition from insulating to metallic behavior. We observe disorder in the form of local Bi off-centering in all Bi-containing compositions, resulting in a larger effective size of the A-site, causing a deviation from a linear increase in the Ru–O–Ru bond angle with increasing Bi-content. The increased bond angle produces a wider bandwidth and more effective screening against electron correlation. Electronic structure calculations also point out the first-order effect of the  $\text{Bi}^{3+}$ : when off-centered,  $\text{Bi}^{3+}$  decrease the Bi  $6p$  mediated covalency of Ru and O, allowing charge carriers to be further mobilized. Together, these effects drive the insulator-to-metal transi-

tion in the Bi-containing members of the solid-solution and explain the non-linear behavior of this dependence. This work highlights the importance of local disorder on transport properties, and suggests that lone pair stereochemical activity could be employed to control insulator-to-metal transitions in pyrochlores and related materials.

#### ACKNOWLEDGMENTS

G. L. gratefully acknowledges support for this work from Bates College, and from the National Science Foundation (NSF) through DMR 1904980. The work at Northwestern and at UC Santa Barbara was supported by NSF DMR 1729303. The computational contributions of D.P. was supported by the Army Research Office under W911NF-15-1-0017. The use of DOD-HPCMP resources for the computational work reported here is gratefully acknowledged. M. W. G. thanks the Leverhulme Trust for funding via the Leverhulme Research Centre for Functional Materials Design. This work was performed, in part, at the Los Alamos Neutron Science Center (LANSCE), a NNSA User Facility operated for the U.S. Department of Energy (DOE) by Los Alamos National Laboratory (Contract 89233218CNA000001). We thank Joan Siewenie for assistance with NPDF data collection.

\* glaurita@bates.edu

<sup>1</sup> M. Foo, W.-L. Lee, T. Siegrist, G. Lawes, A. P. Ramirez, N. Ong, and R. Cava, *Mat. Res. Bull.* **39**, 1663 (2004).

<sup>2</sup> W. Kobayashi, *Phys. Rev. B* **79**, 155116 (2009).

<sup>3</sup> T. Toriyama, M. Watanabe, T. Konishi, and Y. Ohta, *Phys. Rev. B* **83**, 195101 (2011).

<sup>4</sup> A. Pautrat and W. Kobayashi, *Europhys. Lett.* **97**, 67003 (2012).

<sup>5</sup> T. Taniguchi, T. Munenaka, and H. Sato, *J. Phys.: Conf. Ser.* **145**, 012017 (2008).

<sup>6</sup> Y. Maeno, H. Hashimoto, K. Yoshida, S. Nishizaki, T. Fujita, J. G. Bednorz, and F. Lichtenberg, *Nature* **372**, 532 (1994).

<sup>7</sup> Y. Maeno, T. M. Rice, and M. Siegrist, *Phys. Today* **54**, 42 (2001).

<sup>8</sup> A. Callaghan, C. W. Moeller, and R. Ward, *Inorg. Chem.* **5**, 1572 (1966).

<sup>9</sup> Y. Noro and S. Miyahara, *J. Phys. Soc. Jap.* **27**, 518A (1969).

<sup>10</sup> P. T. Barton, R. Seshadri, and M. J. Rosseinsky, *Phys. Rev. B* **83**, 064417 (2011).

- <sup>11</sup> R. G. Egdell, J. B. Goodenough, A. Hamnett, and C. C. Naish, *Journal of the Chemical Society, Farad. Trans.* **79**, 893 (1983).
- <sup>12</sup> H. S. Horowitz, J. M. Longo, H. H. Horowitz, and J. T. Lewandowski, *ACS Symp. Ser.* **127**, 143 (1985).
- <sup>13</sup> T. R. Felthouse, P. B. Fraundorf, M. Friedman, and C. L. Schosser, *J. Catal.* **127**, 421 (1991).
- <sup>14</sup> S. H. Oh, R. Black, E. Pomerantseva, J.-H. Lee, and L. F. Nazar, *Nature Chem.* **4**, 1004 (2012).
- <sup>15</sup> P. F. Garcia, A. Ferretti, and A. Suna, *J. Appl. Phys.* **53**, 5282 (1982).
- <sup>16</sup> M. A. Subramanian, G. Aravamudan, and G. V. Subba Rao, *Prog. Solid State Chem.* **55**, 55 (1983).
- <sup>17</sup> A. W. Sleight, *Inorg. Chem.* **7**, 1704 (1968).
- <sup>18</sup> D. P. Shoemaker, R. Seshadri, M. Tachibana, and A. L. Hector, *Phys. Rev. B* **84**, 064117 (2011).
- <sup>19</sup> D. P. Shoemaker, R. Seshadri, A. L. Hector, A. Llobet, T. Proffen, and C. J. Fennie, *Phys. Rev. B* **81**, 144113 (2010).
- <sup>20</sup> G. Herranz, V. Laukhin, F. Sanchez, P. Levy, C. Ferrater, M. V. Garcia-Cuenca, M. Varela, and J. Fontcuberta, *Phys. Rev. B* **77**, 165114 (2008).
- <sup>21</sup> G. Laurita, R. Grajczyk, M. Stolt, I. Coutinho, A. W. Sleight, and M. A. Subramanian, *Inorg. Chem.* **55**, 3462 (2016).
- <sup>22</sup> R. Seshadri, *Solid State Sci.* **8**, 259 (2006).
- <sup>23</sup> P. W. Anderson, *Phys. Rev.* **102**, 1008 (1956).
- <sup>24</sup> S. T. Bramwell and M. J. P. Gingras, *Science* **294**, 1495 (2001).
- <sup>25</sup> K.-S. Lee, D.-K. Seo, and M.-S. Whangbo, *J. Solid State Chem.* **131**, 405 (1997).
- <sup>26</sup> L. Li and B. Kennedy, *Chem. Mater.* **15**, 4060 (2003).
- <sup>27</sup> F. Ishii and T. Oguchi, *J. Phys. Soc. Jap. Japan* **69**, 526 (2000).
- <sup>28</sup> B. J. Kennedy and T. Vogt, *J. Solid State Chem.* **126**, 261 (1996).
- <sup>29</sup> M. W. Gaultois, P. T. Barton, C. S. Birkel, L. M. Misch, E. E. Rodriguez, G. D. Stucky, and R. Seshadri, *J. Phys.: Condens. Matt.* **25**, 186004 (2013).
- <sup>30</sup> T. Proffen, T. Egami, S. J. L. Billinge, A. K. Cheetham, D. Louca, and J. B. Parise, *Appl. Phys. A: Mater. Sci. Process* **74**, s163 (2002).
- <sup>31</sup> A. C. Larson and R. B. Von Dreele, *Los Alamos Nat. Lab. Rep. LAUR*, 89 (1994).
- <sup>32</sup> B. H. Toby, *J. Appl. Cryst.* **34**, 210 (2001).
- <sup>33</sup> P. F. Peterson, M. Gutmann, T. Proffen, and S. J. L. Billinge, *J. Appl. Cryst.* **34**, 1192 (2000).
- <sup>34</sup> C. L. Farrow, P. Juhas, J. W. Liu, D. B. Bryndin, E. S. J. Bloch, T. Proffen, and S. J. L. Billinge, *J. Phys.: Condens. Matt.* **19**, 335219 (2007).
- <sup>35</sup> K. Momma and F. Izumi, *J. Appl. Cryst.* **44**, 1272 (2011).
- <sup>36</sup> J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, *phys..*
- <sup>37</sup> G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996).
- <sup>38</sup> P. E. Blöchl, O. Jepsen, and O. K. Andersen, *phys..*
- <sup>39</sup> T. Yamamoto, R. Kanno, Y. Takeda, O. Yamamoto, Y. Kawamoto, and M. Takano, *J. Solid State Chem.* **109**, 24 (2002).
- <sup>40</sup> R. J. Bouchard and J. L. Gilson, *Mat. Res. Bull.* **6**, 669 (1971).
- <sup>41</sup> Y. Zhou, I. Matsubara, R. Funahashi, and S. Sodeoka, *Mater. Lett.* **51**, 347 (2001).
- <sup>42</sup> R. Kanno, Y. Takeda, T. Yamamoto, Y. Yamamoto, and O. Yamamoto, *J. Solid State Chem.* **102**, 106 (1993).
- <sup>43</sup> M. Yasukawa, S. Kuniyoshi, and T. Kono, *Solid State Comm.* **126**, 213 (2003).
- <sup>44</sup> R. D. Shannon and C. T. Prewitt, *Acta Crystallogr. Sect. B Struct. Crystallogr. Cryst. Chem.* **25**, 925 (1969).
- <sup>45</sup> S. Muñoz Perez, R. Cobas, J. M. Cadogan, J. Albino Aguiar, P. Bonville, T. Piug, and X. Obradors, *J. Appl. Phys.* **111**, 07E150 (2012).
- <sup>46</sup> R. A. Beyerlein, H. S. Horowitz, and J. M. Longo, *J. Solid State Chem.* **72**, 2 (1988).
- <sup>47</sup> A. W. Sleight and R. J. Bouchard, *NBS Special Publication 364: Solid State Chem.*, 227 (1972).
- <sup>48</sup> M. Avdeev, M. K. Haas, J. Jorgensen, and R. J. Cava, *J. Solid State Chem.* **169**, 24 (2002).
- <sup>49</sup> M. Tachibana, Y. Kohama, T. Shimoyama, A. Harada, T. Taniyama, M. Itoh, H. Kawaji, and T. Atake, *Phys. Rev. B* **73**, 1098 (2006).
- <sup>50</sup> A. L. Hector and S. B. Wiggins, *J. Solid State Chem.* **177**, 139 (2004).
- <sup>51</sup> B. Rehak, K. Horcic, M. Frumar, and L. Koudelka, *J. Cryst. Growth* **68**, 647 (1984).