

This is the accepted manuscript made available via CHORUS. The article has been published as:

Thermomagnetic properties of $\text{Bi}_{1-x}\text{Te}_x$ single crystal in the temperature range from 55 K to 380 K

Md Sabbir Akhanda, S. Emad Rezaei, Keivan Esfarjani, Sergiy Krylyuk, Albert V. Davydov, and Mona Zebarjadi

Phys. Rev. Materials **5**, 015403 — Published 21 January 2021

DOI: [10.1103/PhysRevMaterials.5.015403](https://doi.org/10.1103/PhysRevMaterials.5.015403)

Thermomagnetic properties of Bi_2Te_3 single crystal in the temperature range from 55 K to 380 K

Md. Sabbir Akhanda and S. Emad Rezaei

*Department of Electrical and Computer Engineering,
University of Virginia, Charlottesville, Virginia 22904, USA*

Keivan Esfarjani

*Department of Materials Science and Engineering,
University of Virginia, Charlottesville, Virginia 22904, USA
Department of Mechanical and Aerospace Engineering,
University of Virginia, Charlottesville, Virginia 22904, USA and
Department of Physics, University of Virginia, Charlottesville, Virginia 22904, USA*

Sergiy Krylyuk and Albert V. Davydov

Material Science and Engineering Division, National Institute of Standards and Technology, Gaithersburg, MD 20899, USA

Mona Zebarjadi

*Department of Electrical and Computer Engineering,
University of Virginia, Charlottesville, Virginia 22904, USA and
Department of Materials Science and Engineering,
University of Virginia, Charlottesville, Virginia 22904, USA
(Dated: December 1, 2020)*

Magneto-thermoelectric transport provides an understanding of coupled electron-hole-phonon current in topological materials and has applications in energy conversion and cooling. In this work, we study the Nernst coefficient, the magneto-Seebeck coefficient, and the magnetoresistance of single-crystalline Bi_2Te_3 under external magnetic field in the range of -3 T to 3 T and in the temperature range of 55 K to 380 K. Moreaus relation is employed to justify both the overall trend of the Nernst coefficient and the temperature at which this coefficient changes sign. We observe a non-linear relationship between the Nernst coefficient and the applied magnetic field in the temperature range of 55 K to 255 K. An increase in both the Nernst coefficient and the magneto-Seebeck coefficient is observed as the temperature is reduced which can be attributed to the increased mobility of the carriers at lower temperatures. First-principles density functional theory calculations were carried out to physically model the experimental data including electronic and transport properties. Simulation findings agreed with the experiments and provide a theoretical insight to justify the measurements.

I. INTRODUCTION

The first observation of cooling using a Bi_2Te_3 thermocouple about seventy-five years ago inspired a surge of interest in the field of thermoelectric energy conversion [1]. Identifying suitable new materials and enhancing the thermoelectric properties of the already recognized ones have been the major research drive of the thermoelectric research community since then [2–19]. The thermoelectric performance of a material is evaluated by its dimensionless figure of merit, $z_{TE}T$, defined as $\sigma S^2 T / \kappa$ where σ is the electrical conductivity, S is the Seebeck coefficient, κ is the thermal conductivity, and T is the average temperature of the material. Despite the discovery of numerous other thermoelectric materials to this date, Bi_2Te_3 and its alloys (with Sb_2Te_3 for p-type and with Bi_2Se_3 for n-type conductivity, respectively) are still the dominant materials used in commercial thermoelectric modules for near room-temperature applications [20]. Hence, it is no surprise that a large number of articles are focused on the study of Bi_2Te_3 thermoelectric transport properties [21–

25]. Bismuth Sesquitelluride Bi_2Te_3 is a layered material and inherently has low thermal conductivity [26]. At the same time, it is a topological material with a complex band structure [27]. Many detailed first-principles studies have been reported so far to better understand the electronic band structure and consequently thermoelectric properties of the Bi_2Te_3 family [27–35]. Due to spin-orbit interaction, Bi_2Te_3 has band inversion with band extrema that are not at the high symmetry Γ point [27]. The resulted valleys have small effective masses and high valley degeneracy, making the electronic band structure of Bismuth Sesquitelluride Bi_2Te_3 ideal for thermoelectric applications. Various reports on the Seebeck coefficient and the Hall measurement of doped samples pointed to the necessity of a six-valley band model to properly describe the relationship between the Hall coefficient and the carrier concentration [36–39]. While examining the thermal conductivity behavior at a temperature range of 77 K to 380 K, Satterthwaite and Ure reported a sharp rise in the thermal conductivity around room temperature and above due to ambipolar diffusion of electrons

and holes [26]. Goldsmid found that the lattice thermal conductivity of doped Bi_2Te_3 is independent of its electrical conductivity [40]. He reported that doping with halogen atoms is an exception and results in the reduction of lattice thermal conductivity due to the large cross-section of phonon-halogen atom scattering.

While the thermoelectric properties of Bi_2Te_3 have been well-studied to attain a higher figure of merit, the thermomagnetic properties lack the same research depth. When a magnetic field is applied in the z -direction, i.e., normal to the basal (0001) crystal plane in Bi_2Te_3 , the thermomagnetic figure of merit, $z_{TM}T$ is defined as $(N^2\sigma_{yy}T)/\kappa_{xx}$ where N is the Nernst coefficient in the unit of $\mu\text{V}/\text{K}$, σ_{yy} is the electrical conductivity in the y -direction, κ_{xx} is the thermal conductivity along the direction of the applied thermal gradient, and T is the average temperature of the material [41]. The Nernst coefficient in the thermomagnetic transport is the transverse equivalent of the Seebeck coefficient S_{xx} in the thermoelectric transport. Thermomagnetic power generators and coolers are an alternative to thermoelectric modules. They have several advantages compared to their thermoelectric counterparts such as exhibiting higher energy conversion efficiency for the same zT (adiabatic) (applicable when the zT (adiabatic) is greater than 0.2) [42, 43], better suitability for energy conversion in the case of thin films, and simpler design as the module can be made using only one material compared to two (n-type and p-type) in case of a thermoelectric module [43, 44]. The potential that the transverse thermomagnetic properties hold in energy conversion can duly be stressed by taking the Dirac semimetal Cd_3As_2 as an example. In a recently published paper, it has been reported that, primarily due to its large Nernst coefficient, Cd_3As_2 has a transverse thermomagnetic $z_{TM}T \approx 0.5$ at room temperature which is more than twice its longitudinal thermoelectric $z_{TE}T$ [45]. [The study of the Nernst effect is also important in spintronics. It has recently been shown that the Nernst voltage can be a source of spurious signal in spin-orbit torque measurements in topological insulators \[46\]. The magnetization dynamics can be controlled by thermally driven spin Nernst torque \[47\].](#) Therefore, taking a closer look at the thermomagnetic properties of Bi_2Te_3 is evidently fitting. To our best knowledge, only a few attempts have been made to study the Nernst effect in Bi_2Te_3 so far. Mansfield and Williams in 1958 measured the Nernst coefficient of Bi_2Te_3 under a magnetic field of 1.4 T and reported a slow increase in the coefficient with decreasing temperature [48]. In 1966, Champness and Kipling measured the Nernst coefficient for an n-type Bi_2Te_3 under a constant magnetic field of 1.88 T applied parallel to the cleavage plane and concluded that the electron to hole mobility ratio of their sample decreases up to room temperature [49]. In 1997, Zhitinskaya *et al.* used the Nernst measurement at 300 K in the weak magnetic field regime as a means to predict the degree of inhomogeneity present in the Bi_2Te_3 crystal [50]. All these studies revealed useful information but do not provide a

complete picture of the Nernst effect covering both wide magnetic fields and a large temperature range.

In this work, we report the measurement of the Nernst coefficient of Bi_2Te_3 over a wide range of magnetic fields and temperatures. We have observed a change in the sign of the Nernst coefficient (N) as predicted by the Moreaus relation[51] [Eq.(1)] around the same temperature at which the Seebeck coefficient peaks. We have also observed a non-linear behavior of the Nernst coefficient versus H in the high magnetic field regime ($\mu H > 1$). The measurement of thermoelectric properties, Hall coefficient, magneto-Seebeck, and magnetoresistance have been included in this report to provide a more complete perspective. We used First-principles calculations and analytical solutions of the Boltzmann transport equation (BTE) using the constant relaxation time approximation and in the presence of an externally applied magnetic field to calculate magneto-transport responses. In the absence of the magnetic field, theoretical Seebeck coefficients accurately reproduce the experimental ones. The presence of the magnetic field introduces the magneto-Seebeck, the magnetoresistance, and the Nernst signal. Finally, the Nernst signal was calculated using phenomenological models. The trends seen in the theoretical result agrees with that of the experiment, but these are not in quantitative agreement primarily due to the use of constant relaxation time approximation (CRTA) during the theoretical calculations.

$$N = TR_H \sigma \frac{\partial S}{\partial T} \quad (1)$$

II. MATERIALS AND METHODS

A. Experimental details

An undoped Bi_2Te_3 was grown by the vertical Bridgman method. Polycrystalline Bi_2Te_3 powder (≈ 15 g) was loaded in a graphitized quartz ampoule (10 mm diameter) that was sealed under vacuum and placed in a single-zone furnace. After homogenization of the melt at 630°C for several hours, the ampoule was transferred through a temperature gradient of $\approx 50^\circ\text{C}/\text{cm}$ at a speed of 0.5 mm/h. The growth run produced a single-crystalline Bi_2Te_3 ingot with the cleavage plane parallel to the ampoule axis. The sample ($8.7 \times 3.9 \times 1.5$ mm³ ($L \times W \times H$)) was cut from the central part of the ingot. Gold-plated flat copper wire of 0.5 mm width was used to make contact electrodes. A two-component silver-filled epoxy was used to glue the contact wires to the sample. The thermoelectric properties of the sample, at a temperature range 55 K to 380 K and magnetic field of -3 T to 3 T, were measured by the one-heater and two-thermometer configuration using the thermal transport option (TTO) of the VersaLab (Quantum design Inc.). The applied magnetic field was perpendicular to the direction of the thermal gradient and the cleavage plane. To establish a thermal gradient along the length of the

sample, a resistive heater was attached to one end of the sample. Another contact attached at the opposite end of the sample was clamped to the cold foot of the TTO puck which acted as a heatsink. Thus, the temperature difference is applied between two parallel heat sink and heat source placed 8.7 mm apart, implying that the slow transverse voltage measurements are done under nearly isothermal conditions, and the reported Nernst coefficients are the isothermal values rather than the smaller adiabatic values. Two TTO shoes placed 3.4 mm apart were employed to measure the temperature and the voltage difference simultaneously. For the Seebeck measurement over the entire range of temperature, an adaptive measurement mode was used that maintained the temperature difference within (1 to 3)% of the sample temperature. Taking into account the geometrical factor of the sample and Versalab system specification, the estimated errors in the Seebeck, thermal conductivity, and resistivity measurement were about 5%, 10%, and 3% respectively. Nernst measurement was also carried out using the one-heater two-thermometer configuration in the temperature range of 55 K to 300 K. Magnetic field with a step increase of 1 T was applied up to 3 T in both z and $-z$ directions. Transverse voltage was measured by two voltage probes attached to two gold-coated copper contacts placed perpendicular to the thermal gradient and the magnetic field directions. The estimated error in the Nernst measurement was $\approx 10\%$ (the main error sources include fitting errors of Versalab software, error in measurement of the sample size, non-uniformity of the temperature gradient, and instrumental errors). To determine the carrier concentration, a four-probe Hall measurement was carried out using the electrical transport option (ETO) of VersaLab (Quantum design Inc.) in the temperature range of 50 K to 380 K. In this measurement, two voltage leads were placed transversely to the direction in which the current and the magnetic field were applied. The estimated error in the measurement was $\approx 5\%$. The thermal gradient and magnetic field applied in all measurements described above were parallel and perpendicular to the materials cleavage plane, respectively.

B. Computational details

The QUANTUM-ESPRESSO software package [52] was employed to carry out first-principles density functional theory (DFT) calculations with ultra-soft pseudopotentials [53] and with the PerdewBurkeErnzerhof exchange-correlation functional [54]. An $8 \times 8 \times 8$ MonkhorstPack k -point mesh was chosen to reproduce electronic states in the first Brillouin zone and kinetic energy cutoffs for charge density and wave function were set to be 700 Ry and 70 Ry, respectively. Experimental lattice constants of $a = 10.473$ and $\theta_{BiTe} = 24.17^\circ$ [33] were utilized to simulate the structure. Atomic positions were relaxed to minimize energy. Transport properties

were assessed through the semiclassical Boltzmann theory as implemented in the BoltzTraP package [55]. Modifications under the magnetic field will be discussed in the results.

III. RESULTS AND DISCUSSION

The Spin-orbit coupling (SOC) effect plays an important role in the electronic structure calculations [56]. Fig. 1 (a) compares the band structure of Bi_2Te_3 with and without SOC. The inclusion of SOC results in a significant reduction in the bandgap from 0.29 eV to 0.11 eV and a significant change in the effective mass values. For example, at the Γ point, the conduction band effective mass increases from $0.15m_0$ to $0.7m_0$ after introducing SOC effects. Finally, band inversion happens at Γ point in the presence of the SOC effect. Our results are in agreement with previous calculations [57] and the obtained bandgap of 0.11 eV is close to the experimentally measured bandgap of 0.15 eV [58].

The contribution of each atomic orbital to the total density of states is shown in the Fig. 1b. The valence band is dominated by p-orbitals of tellurium and the conduction band is mostly composed of p-orbitals of bismuth, which is in agreement with the projected band structure (Fig. 2). The color bar in Fig. 2 indicates the contribution of a specific orbital in each band from the lowest (green) to the highest (yellow) contribution (e.g. in Fig. 2a valence band is more blue-red which shows a high contribution of p-orbitals of Bi). In this figure, band inversion of the Bi-p orbitals can be seen: the valence band acquires a Bi-p component near the Γ point.

Temperature dependence of the transport coefficients including the Seebeck coefficient, S , the electrical and thermal conductivity, the Hall coefficient, and the carrier mobility is shown in Fig. 3. Our measured sample has mobility of $227 \text{ cm}^2\text{V}^{-1}\text{s}^{-1}$ at 300 K which is very close to the ones reported by other sources on similar samples [26, 38, 59]. Carrier concentrations were computed from experimental Hall coefficient values, for which the corresponding chemical potentials were estimated through the first-principles calculations followed by Seebeck coefficient computation of each chemical potential. Experimentally measured Seebeck values were reproduced by first-principles calculations (explained in the computational detail sub-section). It is noteworthy to say that small deviations between theory and experiments could come from constant relaxation time approximation assumption.

The Seebeck coefficient trend over the entire temperature range can be divided into two distinct regions as also noted by many previous reports on Bi_2Te_3 [22, 36, 60]. The separation roughly lies around 273 K where the Seebeck coefficient reaches its peak value of $+287 \text{ } \mu\text{V/K}$. Below 273 K, the carrier concentration does not change significantly as evidenced by a weak change of the Hall

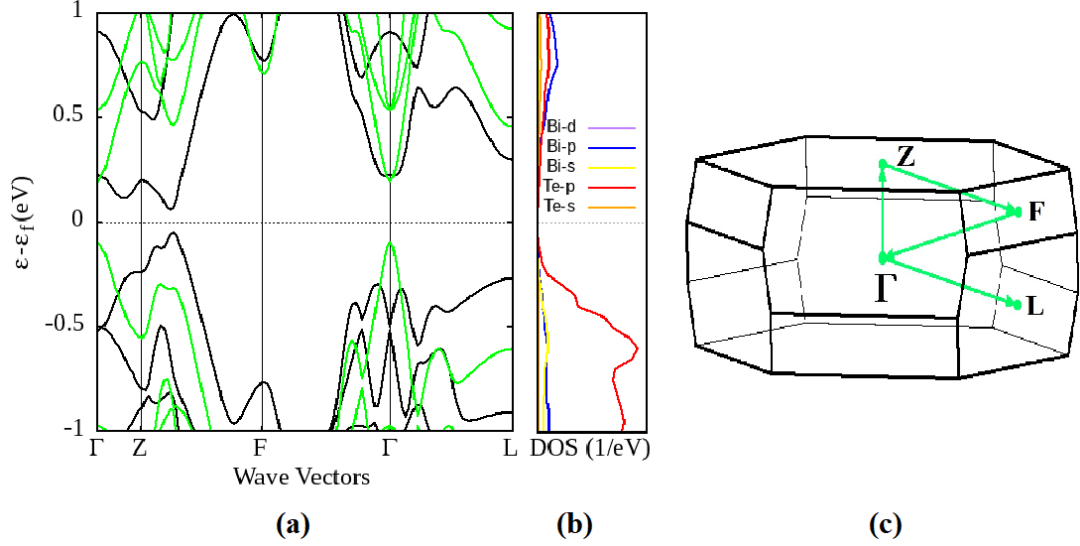


FIG. 1. a) Band structure of Bi_2Te_3 with (black) and without (green) SOC effect. The presence of SOC lowers the bandgap and Bi_2Te_3 turns to a narrow-gap semiconductor. b) the projected Density of States (DOS) including SOC shows that valence and conduction bands are mainly formed by Te and Bi p-orbitals, respectively. c) Brillouin zone for Bi_2Te_3 crystal structure

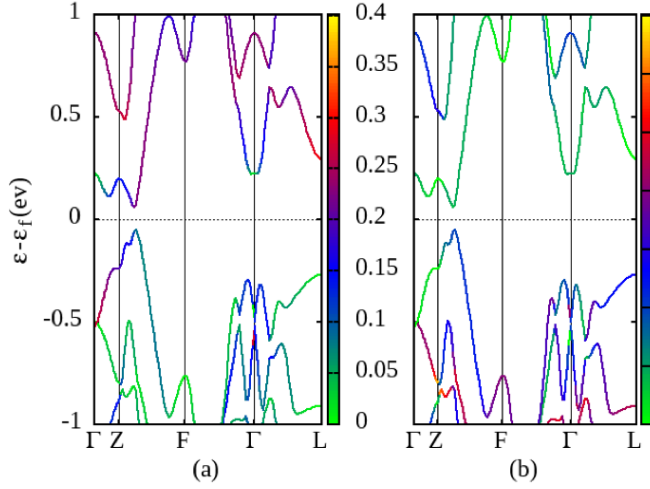


FIG. 2. Contribution of p-orbitals of Bi (a) and Te (b). Similar to projected DOS, p-orbitals of Bi and Te form valence and conduction bands. The color bar is identical for all projection. The valence band of Bi_2Te_3 is mostly of type Te-p (right figure) and the conduction band is mostly of type Bi-p (left figure)

coefficient (Fig. 3d). In this range, as temperature increases, the carrier mobility decreases due to the increase

in the electron-phonon scattering rates. Hence, we observe a metallic behavior where resistivity increases with temperature. In this regime, since the free carrier density is almost fixed, as we increase the temperature, the quasi-Fermi level moves closer to the middle of the gap increasing the Seebeck coefficient. Beyond 273 K, intrinsic carriers excited across the bandgap dominate conductivity. In this region, we see a decrease in the Seebeck coefficient with increasing temperature as both electrons and holes are generated (the bipolar effect). The resistivity starts to decrease due to the increase in carrier concentration. The sign of the Seebeck coefficient remains positive throughout the entire temperature range which is a confirmation that the sample is nominally p-type doped. Bi_2Te_3 is known as a topological insulator [27]. However, Bi_2Te_3 single crystal is naturally p-type and its bulk energy bands are characterized by a small bandgap and are strongly influenced by spin-orbit interactions. Hence, it is difficult to observe an electrically insulating bulk [61]. In particular, in the temperature range of our study, the sample behaves as a metal rather than an insulator. We also note that even though our calculations only included the bulk states, they can describe the Seebeck coefficient in agreement with the experiment (as shown in Fig. 3a). We expect the surface states are dominant at much lower temperatures [62] and much lower thicknesses [63]. In semiconductors, total thermal conductivity has contri-

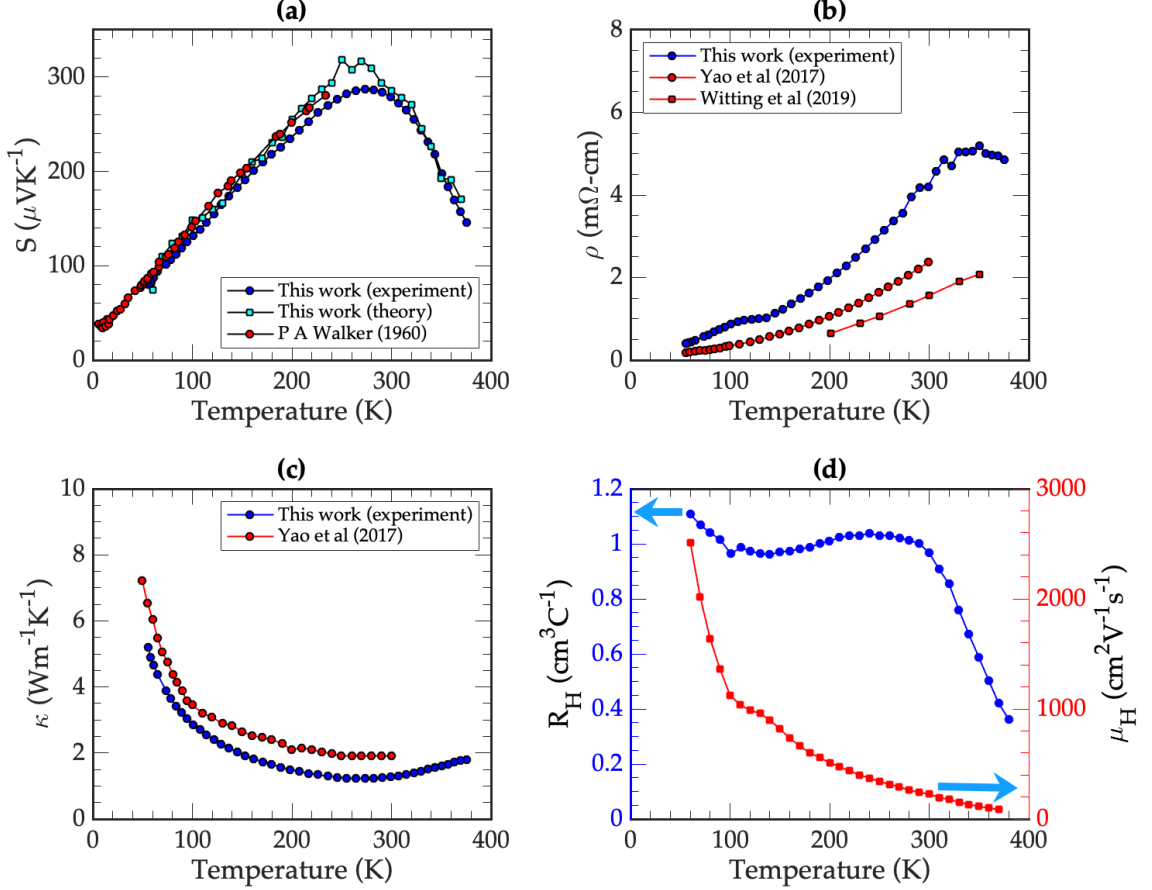


FIG. 3. Variation of electrical and thermal properties of single-crystal Bi₂Te₃ with temperature: a) Seebeck coefficient, b) Resistivity, c) Thermal conductivity, and d) Hall coefficient R_H and Hall mobility μ_H .

butions from phonons, electrons, and bipolar transport [64]. In the temperature range of 55 K to 200 K, thermal transport is dominated by phonon thermal conductivity. As we increase the temperature, we see a decreasing trend in the thermal conductivity due to the increase in anharmonic phonon scattering as shown in Fig. 3c. At higher temperatures (above 300 K), the bipolar contribution becomes significant and results in a rise in the total thermal conductivity. Fig. 3d shows the measured Hall coefficient and the extracted carrier Hall mobility. We need to point out that at temperatures above 273 K, where bipolar conduction starts, the extracted Hall mobility is very different from the drift mobility and we cannot separately extract the drift mobility of electrons and holes. The Hall coefficient is proportional to the inverse of the difference between the number of holes and electrons, while the electrical conductivity is the sum of the electron conductivity and hole conductivity. The Hall mobility is extracted by dividing the electrical conductivity by the Hall carrier concentration.

Fig. 4 shows the temperature dependence of the magneto-Seebeck and the magnetoresistance of the sam-

ple in the magnetic field range of 1 T to 3 T applied perpendicular to both the thermal gradient and the cleavage plane. Each data points were obtained by applying the magnetic field both in positive and negative directions and then averaging the corresponding ΔS_{xx} and $\Delta \rho_{xx}$ responses. The change in the Seebeck coefficient and the resistivity are always positive below 375 K. These results are consistent with the previously reported data [49]. The decrease in the value of the magneto-Seebeck and magnetoresistance versus temperature can be attributed to the reduced mobility at higher temperatures.

Fig. 5a shows the sample mounted on a TTO puck for the Nernst measurement. Temperature dependence of the Nernst coefficient is shown in Fig. 5b and temperature dependence of the thermoelectric and thermomagnetic zT has been included in the Supplemental Material [65]. Here also, for each data points, the magnetic field was applied both in positive and negative directions and the responses were averaged. The Nernst signal, similar to the magneto-Seebeck and magnetoresistance, increases as we decrease the temperature. In the same graph, we have also plotted the Nernst coefficient of this material

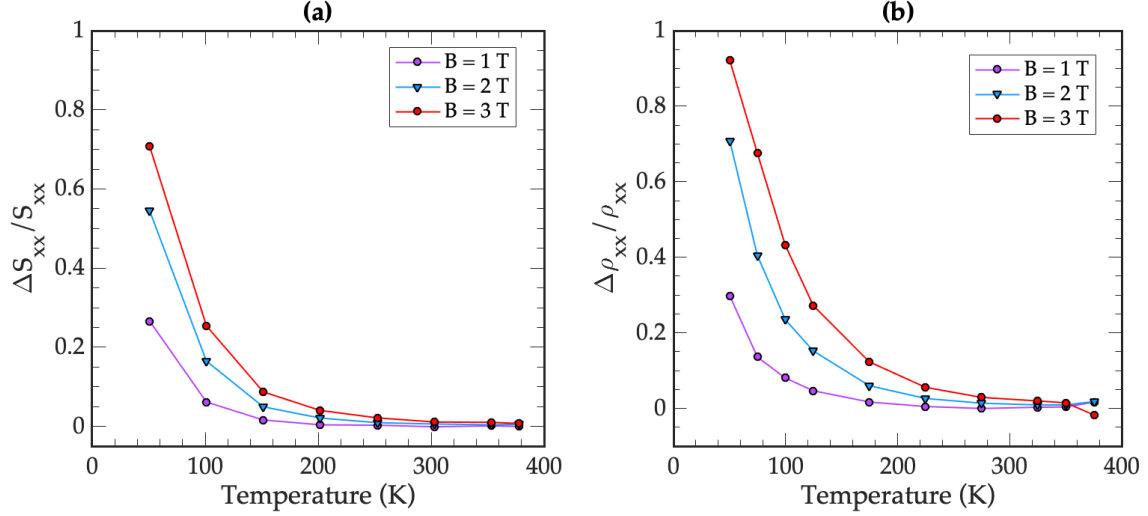


FIG. 4. Plot of the temperature dependence of a) Magneto-Seebeck and b) Magnetoresistance. Here, S_{xx} and ρ_{xx} are the Seebeck coefficient and resistivity measured along the length of the sample under zero magnetic field and ΔS_{xx} and $\Delta \rho_{xx}$ are the respective change in these quantities once a magnetic field is applied

calculated using the Moreaus relation [66]. According to this relation, the Nernst coefficient of a material can be written as the negative of the product of its Thompson coefficient (defined as the product of the temperature of the sample and the first derivative of its Seebeck coefficient with respect to the temperature) [67], Hall coefficient, and electrical conductivity. Moreaus relation predicts a change in the sign and a zero Nernst signal at the same temperature at which the Seebeck coefficient peaks (≈ 273 K for this sample). Our experimental data show that the Nernst signal changed its sign at about 255 K which is in close agreement with Moreaus prediction. The difference stems from the inaccuracy of the Moreaus relation as well as error bar in the measurements of the involved transport coefficients (the Seebeck coefficient, Hall coefficient, the electrical conductivity, and the Nernst coefficient). We note that Moreaus relation is only accurate for metals. However, as shown, it can still closely replicate the results of Bi_2Te_3 , a narrow-gap semiconductor. Above 255 K, the Nernst coefficient is positive and maintains a linear relationship with the applied magnetic field. But below 255 K, the linearity ceases quickly and non-linear behavior of the Nernst coefficient versus the magnetic field slowly emerges (Fig. 5d). This non-linear behavior intensifies as we go down in temperature. Moreaus relation cannot account for this non-linearity. The basis of this behavior becomes apparent when the Boltzmann Transport Equation under a magnetic field is solved. The following formalism is developed after Behnia [68] and following Smiths [69] notation. Electrical current density under an external magnetic field (H) can be written as:

$$\begin{bmatrix} J_x \\ J_y \end{bmatrix} = \begin{bmatrix} \sigma(H)_{xx} & \sigma(H)_{xy} \\ \sigma(H)_{yx} & \sigma(H)_{yy} \end{bmatrix} \begin{bmatrix} E_x \\ E_y \end{bmatrix}$$

$$+ \begin{bmatrix} B(H)_{xx} & B(H)_{xy} \\ B(H)_{yx} & B(H)_{yy} \end{bmatrix} \begin{bmatrix} -\frac{\partial_x T}{T^2} \\ -\frac{\partial_y T}{T^2} \end{bmatrix} \quad (2)$$

Assuming there is no temperature gradient along the y -direction (isothermal condition for the Nernst coefficient), for a rhombohedral single crystal of Bi_2Te_3 , which is an isotropic structure, Eq. (2) can be simplified as follows:

$$J_x = \sigma_{xx} E_x + \sigma_{xy} E_y - \frac{B_{xx}(H)}{T^2} \partial_x T \quad (3)$$

$$J_y = \sigma_{yx} E_x + \sigma_{yy} E_y - \frac{B_{yx}(H)}{T^2} \partial_x T \quad (4)$$

where σ and $B(H)$ are the response function tensors defined as:

$$\sigma_{ij} = q^2 \int \tau \nu_i \nu_j \left(-\frac{\partial f_0^k}{\partial E} \right) \frac{d^3 k}{4\pi^3} \quad (5)$$

$$[B(H)] = \frac{q}{T} \int (E_k - \mu) \frac{\partial f_0^k}{\partial E} \frac{\tau}{(1 + \mu H)^2} \times$$

$$\begin{bmatrix} \nu_x^2 & \nu_x \nu_y - \nu_x^2 \mu H & \nu_z \nu_x \\ \nu_x \nu_y + \nu_y^2 \mu H & \nu_y^2 & \nu_z \nu_y \\ \nu_z \nu_x & \nu_z \nu_y & \nu_z^2 (1 + \mu^2 H^2) \end{bmatrix} \frac{d^3 k}{4\pi^3} \quad (6)$$

The Nernst coefficient is defined under open-circuit conditions when the electrical current is zero in all directions and the magnetic field is applied only along

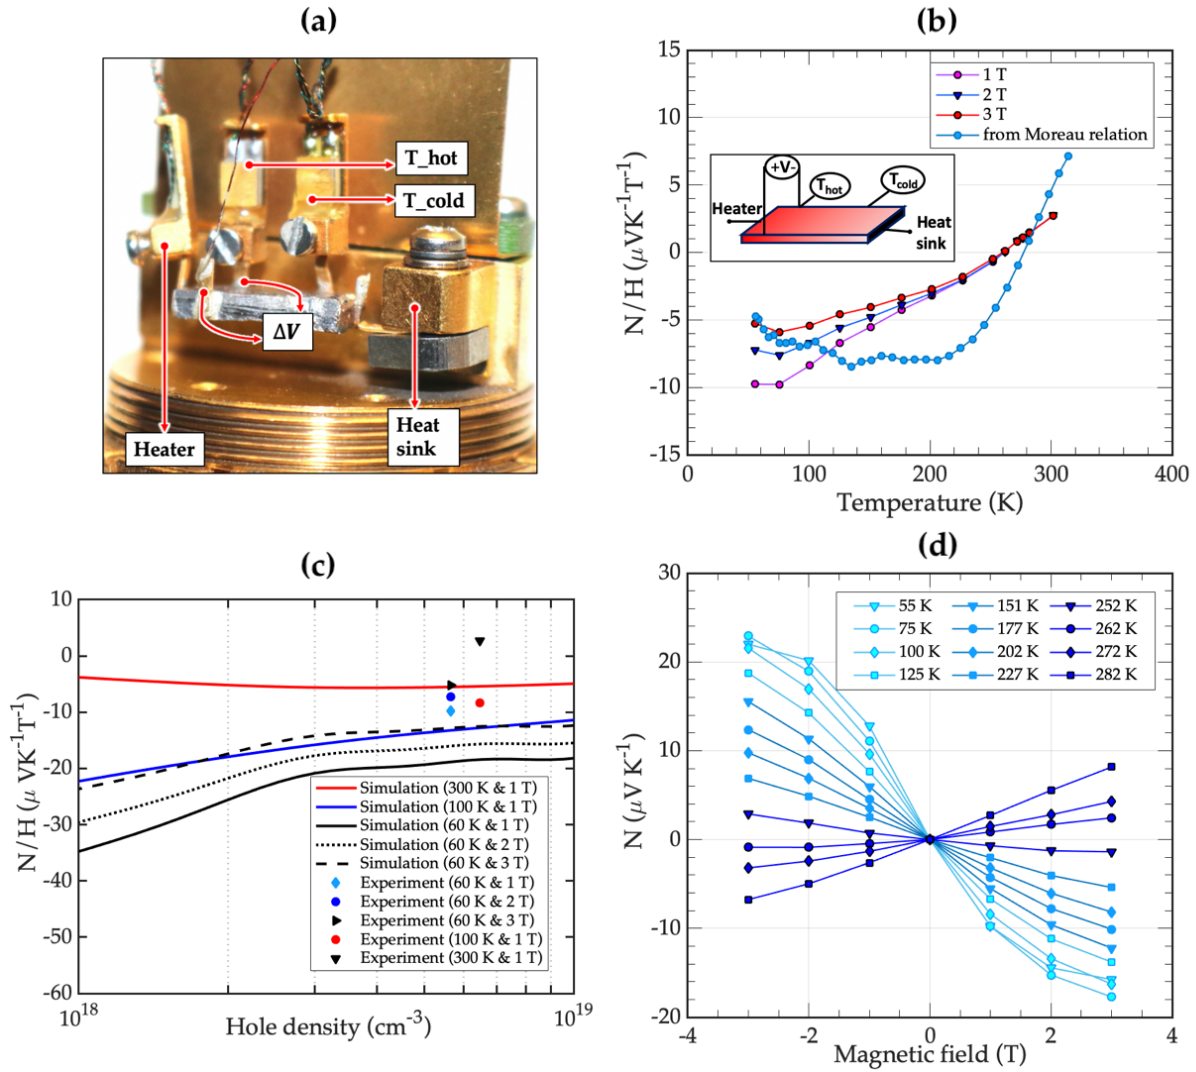


FIG. 5. a) Mounted sample on the TTO puck. b) Temperature dependence of Nernst coefficient (N/H) obtained from experiment and Moreau's relation. c) Nernst coefficient (N/H) at different hole concentration calculated using Eq. 5 and 6 with inputs from first-principles calculations. d) Magnetic field dependence of the Nernst coefficient (N)

the z -axis. In these circumstances, eliminating E_x using Eq. (3) and Eq. (4), and using the definition of the isothermal Nernst coefficient, we find:

$$N_{xyz} = \frac{E_y}{\partial_x T} = \frac{1}{T^2} \frac{\sigma_{xx} B_{yx} - \sigma_{yx} B_{xx}}{\sigma_{xx} \sigma_{yy} - \sigma_{yx} \sigma_{xy}} \quad (7)$$

To estimate the Nernst coefficient, we used the band structure and the differential conductivity calculated using first-principles calculations as described in the computational details section. The experimental mobility was used in Eq. (5). The Nernst coefficient computed from Eq. (6) is plotted in Fig. 5c and compared with the experimental data. The current calculation is performed under constant relaxation time approximation, assuming that the relaxation times do not change under an externally applied magnetic field. However, Smith et.al. [69]

have shown that the changes in the relaxation times versus the magnetic field add another term in the Nernst coefficient. Hence, we believe that the main discrepancy between the theory and experiment is the constant relaxation time approximation used in the theory. Finally, we note that Fig. 5c confirms that the general trend an increase in the Nernst coefficient at lower carrier concentrations, lower temperatures, and larger magnetic fields as reported in other materials [70] is also valid for this material. The non-linearity vs magnetic field, as can be seen in Fig. 5d, is strongest at the lowest measured temperature, 55 K, pointing to the suitability of the Nernst effect in cryogenic energy conversion application.

IV. CONCLUSION

In summary, we have studied the Nernst coefficient, magneto-Seebeck, and magnetoresistance of single-crystal Bi_2Te_3 under the effect of an external magnetic field (< 3 T) and temperature (55 K to 380 K). The Nernst coefficient changes its sign at about 255 K as predicted by the Moreaus relation. It shows a non-linear trend versus the applied magnetic field at low temperatures. The non-linearity gradually increases as the temperature decreases. The magnitudes of the magneto-Seebeck and magnetoresistance were also found to increase as the temperature was decreased. First-principles calculations along with constant relaxation time approximation (CTRA) were used within the framework of BoltzTrap to calculate the Seebeck coefficient and it is in close agreement with the experimentally measured values. The formalism developed by Behnia and Smith was used to calculate the Nernst coefficient of the sample. The theoretical calculations can successfully explain the trends observed in the experiment but are not in quantitative agreement. The discrepancy is attributed to the use of CTRA. [Our experimental data and theoretical calculation confirm that the material under study shows the general trend of exhibiting higher values of the Nernst and magneto-Seebeck coefficients at higher mobility values.](#) Our theoretical results show that the magnitude

of the Nernst coefficient is larger at lower temperatures, lower carrier concentrations, and larger magnetic fields. These observations could prove useful in evaluating the Nernst coefficient in other materials having similar band structures as that of Bi_2Te_3 .

ACKNOWLEDGMENTS

This work is supported in part by DOE-SBIR contract # DE-SC0019552. We acknowledge the Rivanna cluster of UVA for providing the computational resources. S.K. and A.V.D. acknowledge support from Material Genome Initiative funding allocated to NIST.

Disclaimer Certain commercial equipment, instruments, or materials are identified in this paper in order to specify the experimental procedure adequately. Such identification is not intended to imply recommendation or endorsement by the National Institute of Standards and Technology, nor is it intended to imply that the materials or equipment identified are necessarily the best available for the purpose.

-
- [1] H. J. Goldsmid and R. W. Douglas, The use of semiconductors in thermoelectric refrigeration, *British Journal of Applied Physics* **5**, 386 (1954).
 - [2] G. J. Snyder and E. S. Toberer, Complex thermoelectric materials, in *Materials for Sustainable Energy: A Collection of Peer-Reviewed Research and Review Articles from Nature Publishing Group* (World Scientific Publishing Co., 2010) pp. 101–110.
 - [3] G. D. Mahan and J. O. Sofo, The best thermoelectric, *Proceedings of the National Academy of Sciences of the United States of America* **93**, 7436 (1996).
 - [4] F. J. Disalvo, Thermoelectric cooling and power generation (1999).
 - [5] Y. I. Ravich and D. A. Pshena-Severin, Thermoelectric figure of merit of a p-n junction, *Semiconductors* **35**, 1161 (2001).
 - [6] A. I. Hochbaum, R. Chen, R. D. Delgado, W. Liang, E. C. Garnett, M. Najarian, A. Majumdar, and P. Yang, Enhanced thermoelectric performance of rough silicon nanowires, *Nature* **451**, 163 (2008).
 - [7] A. I. Boukai, Y. Bunimovich, J. Tahir-Kheli, J. K. Yu, W. A. Goddard, and J. R. Heath, Silicon nanowires as efficient thermoelectric materials, *Nature* **451**, 168 (2008).
 - [8] T. C. Harman, P. J. Taylor, M. P. Walsh, and B. E. LaForge, Quantum dot superlattice thermoelectric materials and devices, *Science* **297**, 2229 (2002).
 - [9] J. F. Li, W. S. Liu, L. D. Zhao, and M. Zhou, High-performance nanostructured thermoelectric materials (2010).
 - [10] C. Wood, Materials for thermoelectric energy conversion, *Reports on Progress in Physics* **51**, 459 (1988).
 - [11] G. Chen, M. S. Dresselhaus, G. Dresselhaus, J. P. Fleurial, and T. Caillat, Recent developments in thermoelectric materials, *International Materials Reviews* **48**, 45 (2003).
 - [12] S. Volz, *Topics in Applied Physics*, edited by S. Volz, Topics in Applied Physics, Vol. 118 (Springer Berlin Heidelberg, Berlin, Heidelberg, 2009).
 - [13] G. S. Nolas, J. L. Cohn, G. A. Slack, and S. B. Schujman, Semiconducting Ge clathrates: Promising candidates for thermoelectric applications, *Applied Physics Letters* **73**, 178 (1998).
 - [14] M. S. Dresselhaus, G. Dresselhaus, X. Sun, Z. Zhang, S. B. Cronin, and T. Koga, Low-dimensional thermoelectric materials, in *Physics of the Solid State*, Vol. 41 (American Institute of Physics Inc., 1999) pp. 679–682.
 - [15] M. Zebarjadi, G. Joshi, G. Zhu, B. Yu, A. Minnich, Y. Lan, X. Wang, M. Dresselhaus, Z. Ren, and G. Chen, Power factor enhancement by modulation doping in bulk nanocomposites, *Nano Letters* **11**, 2225 (2011).
 - [16] B. Yu, M. Zebarjadi, H. Wang, K. Lukas, H. Wang, D. Wang, C. Opeil, M. Dresselhaus, G. Chen, and Z. Ren, Enhancement of thermoelectric properties by modulation-doping in silicon germanium alloy nanocomposites, *Nano Letters* **12**, 2077 (2012).
 - [17] M. Zebarjadi, B. Liao, K. Esfarjani, M. Dresselhaus, and G. Chen, Enhancing the thermoelectric power factor by using invisible dopants, *Advanced Materials* **25**, 1577 (2013).
 - [18] M. Markov, X. Hu, H. C. Liu, N. Liu, S. J. Poon, K. Esfarjani, and M. Zebarjadi, Semi-metals as potential thermoelectric materials, *Scientific Reports* **8**, 9876 (2018).
 - [19] N. Liu, S. E. Rezaei, W. A. Jensen, S. Song, Z. Ren, K. Esfarjani, M. Zebarjadi, and J. A. Floro, Im-

- proved Thermoelectric Performance of Eco-Friendly β -FeSi₂SiGe Nanocomposite via Synergistic Hierarchical Structuring, Phase Percolation, and Selective Doping, *Advanced Functional Materials* **29**, 1903157 (2019).
- [20] Z. Soleimani, S. Zoras, B. Ceranic, S. Shahzad, and Y. Cui, A review on recent developments of thermoelectric materials for room-temperature applications, *Sustainable Energy Technologies and Assessments* **37**, 100604 (2020).
- [21] M. Yao, C. Opeil, S. Wilson, and M. Zebarjadi, Experimental determination of phonon thermal conductivity and Lorenz ratio of single-crystal bismuth telluride, *MRS Communications* **7**, 922 (2017).
- [22] I. T. Witting, T. C. Chasapis, F. Ricci, M. Peters, N. A. Heinz, G. Hautier, and G. J. Snyder, The Thermoelectric Properties of Bismuth Telluride, *Advanced Electronic Materials* **5**, 1800904 (2019).
- [23] P. Graziosi, C. Kumarasinghe, and N. Neophytou, Impact of the scattering physics on the power factor of complex thermoelectric materials, *Journal of Applied Physics* **126**, 155701 (2019).
- [24] M. Markov, S. E. Rezaei, S. N. Sadeghi, K. Esfariani, and M. Zebarjadi, Thermoelectric properties of semimetals, *Physical Review Materials* **3**, 095401 (2019), arXiv:1905.08282.
- [25] D. X. Qu, Y. S. Hor, J. Xiong, R. J. Cava, and N. P. Ong, Quantum oscillations and hall anomaly of surface states in the topological insulator Bi₂Te₃, *Science* **329**, 821 (2010).
- [26] C. B. Satterthwaite and R. W. Ure, Electrical and Thermal Properties of Bi₂Te₃, *Physical Review* **108**, 1164 (1957).
- [27] H. Zhang, C. X. Liu, X. L. Qi, X. Dai, Z. Fang, and S. C. Zhang, Topological insulators in Bi₂Se₃, Bi₂Te₃ and Sb₂Te₃ with a single Dirac cone on the surface, *Nature Physics* **5**, 438 (2009).
- [28] P. Larson, S. Mahanti, and M. Kanatzidis, Electronic structure and transport of Bi₂Te₃ and BaBi₂Te₃, *Physical Review B - Condensed Matter and Materials Physics* **61**, 8162 (2000).
- [29] S. J. Youn and A. J. Freeman, First-principles electronic structure and its relation to thermoelectric properties of Bi₂Te₃, *Physical Review B - Condensed Matter and Materials Physics* **63**, 085112 (2001).
- [30] T. J. Scheidmantel, C. Ambrosch-Draxl, T. Thonhauser, J. V. Badding, and J. O. Sofo, Transport coefficients from first-principles calculations, *Physical Review B* **68**, 125210 (2003).
- [31] M. Kim, A. J. Freeman, and C. B. Geller, Screened exchange LDA determination of the ground and excited state properties of thermoelectrics: Bi₂Te₃, *Physical Review B* **72**, 035205 (2005).
- [32] B.-L. Huang and M. Kaviani, Ab initio and molecular dynamics predictions for electron and phonon transport in bismuth telluride, *Physical Review B* **77**, 125209 (2008).
- [33] B. Y. Yavorsky, N. F. Hinsche, I. Mertig, and P. Zahn, Electronic structure and transport anisotropy of Bi₂Te₃ and Sb₂Te₃, *Physical Review B - Condensed Matter and Materials Physics* **84**, 165208 (2011), arXiv:1109.0186.
- [34] B. Ryu and M.-W. Oh, Computational Simulations of Thermoelectric Transport Properties, *Journal of the Korean Ceramic Society* **53**, 273 (2016).
- [35] T. Fang, X. Li, C. Hu, Q. Zhang, J. Yang, W. Zhang, X. Zhao, D. Singh, and T. Zhu, Complex Band Structures and Lattice Dynamics of Bi₂Te₃ Based Compounds and Solid Solutions, *Advanced Functional Materials* **29**, 1900677 (2019).
- [36] H. J. Goldsmid, The Electrical Conductivity and Thermoelectric Power of Bismuth Telluride, *Proceedings of the Physical Society* **71**, 633 (1958).
- [37] J. R. Drabble, R. D. Groves, and R. Wolfe, Galvanomagnetic Effects in n-Type Bismuth Telluride, *Proceedings of the Physical Society* **71**, 430 (1958).
- [38] J. R. Drabble, Galvanomagnetic effects in p-type bismuth telluride, *Proceedings of the Physical Society* **72**, 380 (1958).
- [39] P. A. Walker, The Thermal Conductivity and Thermoelectric Power of Bismuth Telluride at Low Temperatures, *Proceedings of the Physical Society* **76**, 113 (1960).
- [40] H. J. Goldsmid, Heat Conduction in Bismuth Telluride, *Proceedings of the Physical Society* **72**, 17 (1958).
- [41] H. J. Goldsmid, The Ettingshausen figure of merit of bismuth and bismuth - antimony alloys, *British Journal of Applied Physics* **14**, 271 (1963).
- [42] T. C. Harman and J. M. Honig, Theory of galvanothermomagnetic energy conversion devices. II. Refrigerators and heat pumps, *Journal of Applied Physics* **33**, 3188 (1962).
- [43] M. Mizuguchi and S. Nakatsuji, Energy-harvesting materials based on the anomalous Nernst effect (2019).
- [44] R. T. Delves, Thermomagnetic effects in semiconductors and semimetals, *Reports on Progress in Physics* **28**, 308 (1965).
- [45] J. S. Xiang, S. L. Hu, M. Lyu, W. L. Zhu, C. Y. Ma, Z. Y. Chen, F. Steglich, G. F. Chen, and P. J. Sun, Large transverse thermoelectric figure of merit in a topological Dirac semimetal, *Science China: Physics, Mechanics and Astronomy* **63**, 237011 (2020).
- [46] N. Roschewsky, E. S. Walker, P. Gowtham, S. Muschinske, F. Hellman, S. R. Bank, and S. Salahuddin, Spin-orbit torque and Nernst effect in Bi-Sb/Co heterostructures, *Physical Review B* **99**, 195103 (2019), arXiv:1810.05674.
- [47] A. Bose, A. S. Shukla, S. Dutta, S. Bhuktare, H. Singh, and A. A. Tulapurkar, Control of magnetization dynamics by spin-nernst torque, *Phys. Rev. B* **98**, 184412 (2018).
- [48] R. Mansfield and W. Williams, The Electrical Properties of Bismuth Telluride, *Proceedings of the Physical Society* **72**, 733 (1958).
- [49] C. Champness and A. Kipling, The nernst and magnetoresistance effects in nonstoichiometric bismuth telluride, *Journal of Physics and Chemistry of Solids* **27**, 1409 (1966).
- [50] M. K. Zhitinskaya, S. A. Nemov, and T. E. Svechnikova, Effect of inhomogeneities of Bi₂Te₃ crystals on the transverse Nernst-Ettingshausen effect, *Semiconductors* **31**, 375 (1997).
- [51] R. Mansfield and W. Williams, The electrical properties of bismuth telluride, *Proceedings of the Physical Society* **72**, 733 (1958).
- [52] P. Giannozzi, S. Baroni, N. Bonini, M. Calandra, R. Car, C. Cavazzoni, D. Ceresoli, G. L. Chiarotti, M. Cococcioni, I. Dabo, A. Dal Corso, S. De Gironcoli, S. Fabris, G. Fratesi, R. Gebauer, U. Gerstmann, C. Gougoussis, A. Kokalj, M. Lazzeri, L. Martin-Samos, N. Marzari, F. Mauri, R. Mazzarello, S. Paolini, A. Pasquarello, L. Paulatto, C. Sbraccia, S. Scandolo,

- G. Sciauzero, A. P. Seitsonen, A. Smogunov, P. Umari, and R. M. Wentzcovitch, QUANTUM ESPRESSO: A modular and open-source software project for quantum simulations of materials, *Journal of Physics Condensed Matter* **21**, 10.1088/0953-8984/21/39/395502 (2009), arXiv:0906.2569.
- [53] D. Vanderbilt, Soft self-consistent pseudopotentials in a generalized eigenvalue formalism, *Physical Review B* **41**, 7892 (1990).
- [54] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized Gradient Approximation Made Simple, *Physical Review Letters* **77**, 3865 (1996).
- [55] G. K. Madsen and D. J. Singh, BoltzTraP. A code for calculating band-structure dependent quantities, *Computer Physics Communications* **175**, 67 (2006), arXiv:0602203 [cond-mat].
- [56] T. Hirahara, T. Nagao, I. Matsuda, G. Bihlmayer, E. V. Chulkov, Y. M. Koroteev, P. M. Echenique, M. Saito, and S. Hasegawa, Role of Spin-Orbit Coupling and Hybridization Effects in the Electronic Structure of Ultrathin Bi Films, *Physical Review Letters* **97**, 146803 (2006).
- [57] K. Xiong, W. Wang, H. N. Alshareef, R. P. Gupta, J. B. White, B. E. Gnade, and K. Cho, Electronic structures and stability of Ni/Bi₂Te₃ and Co/Bi₂Te₃ interfaces, *Journal of Physics D: Applied Physics* **43**, 115303 (2010).
- [58] H. Zhang, X. Luo, C. Wang, Y. Xiong, S. Li, and X. Chen, Characterization of nanocrystalline bismuth telluride (Bi₂Te₃) synthesized by a hydrothermal method, *Journal of Crystal Growth* **265**, 558 (2004).
- [59] S. Shigetomi and S. Mori, Electrical Properties of Bi₂Te₃, *Journal of the Physical Society of Japan* **11**, 915 (1956).
- [60] C. H. Champness and A. L. Kipling, THE HALL AND SEEBECK EFFECTS IN NONSTOICHIOMETRIC BISMUTH TELLURIDE, *Canadian Journal of Physics* **44**, 769 (1966).
- [61] J. P. Heremans, R. J. Cava, and N. Samarth, Tetratellurites as thermoelectrics and topological insulators, *Nature Reviews Materials* **2**, 17049 (2017).
- [62] S. Cai, J. Guo, V. A. Sidorov, Y. Zhou, H. Wang, G. Lin, X. Li, Y. Li, K. Yang, A. Li, Q. Wu, J. Hu, S. K. Kushwaha, R. J. Cava, and L. Sun, Independence of topological surface state and bulk conductance in three-dimensional topological insulators, *npj Quantum Materials* 10.1038/s41535-018-0134-z (2018).
- [63] J. Liang, L. Cheng, J. Zhang, H. Liu, and Z. Zhang, Maximizing the thermoelectric performance of topological insulator Bi₂Te₃ films in the few-quintuple layer regime, *Nanoscale* **8**, 8855 (2016).
- [64] G. S. Nolas, J. Yang, and H. J. Goldsmid, Semiconductors and Thermoelectric Materials, in *Thermal Conductivity* (Springer US, 2006) pp. 123–152.
- [65] See Supplemental Material at [URL will be inserted by publisher] for the temperature dependence of the thermoelectric and thermomagnetic figure of merit, .
- [66] G. Moreau, Sur les phénomènes thermomagnétiques, *Journal de Physique Théorique et Appliquée* **9**, 497 (1900).
- [67] W. Thomson, On a mechanical theory of thermo-electric currents, *Proceedings of the Royal Society of Edinburgh* **3**, 91 (1851).
- [68] K. Behnia, *Fundamentals of Thermoelectricity* (Oxford University Press, 2015).
- [69] A. C. Smith, J. F. Janak, and R. B. Adler, *Electronic conduction in solids*, Tech. Rep. (McGraw-Hill, 1967).
- [70] K. Behnia and H. Aubin, Nernst effect in metals and superconductors: a review of concepts and experiments, *Reports on Progress in Physics* **79**, 046502 (2016).